



Designation: A702 – 89(Reapproved 2006)

Standard Specification for Steel Fence Posts and Assemblies, Hot Wrought¹

This standard is issued under the fixed designation A702; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the Department of Defense.

1. Scope

1.1 This specification covers steel fence posts and assemblies manufactured from hot-wrought sections and intended for use in field and line fencing.

1.2 The posts are available in tee, channel, or U and Y-bar shapes or angle shapes and are furnished painted or galvanized, unless otherwise specified.

1.3 The values stated in inch-pound units are to be regarded as standard. The values given in parentheses are mathematical conversions to SI units that are provided for information only and are not considered standard.

2. Referenced Documents

2.1 ASTM Standards:²

- A29/A29M Specification for Steel Bars, Carbon and Alloy, Hot-Wrought, General Requirements for
- A36/A36M Specification for Carbon Structural Steel
- A123/A123M Specification for Zinc (Hot-Dip Galvanized) Coatings on Iron and Steel Products
- A153/A153M Specification for Zinc Coating (Hot-Dip) on Iron and Steel Hardware
- A499 Specification for Steel Bars and Shapes, Carbon Rolled from “T” Rails
- A641/A641M Specification for Zinc-Coated (Galvanized) Carbon Steel Wire
- A700 Practices for Packaging, Marking, and Loading Methods for Steel Products for Shipment

¹ This specification is under the jurisdiction of ASTM Committee A01 on Steel, Stainless Steel and Related Alloys and is the direct responsibility of Subcommittee A01.15 on Bars. This standard is a revision of Commercial Standard CS 184-51, Steel Fence Posts—Field Line Type, formerly published by the United States Department of Commerce.

Current edition approved March 1, 2006. Published March 2006. Originally approved in 1974. Last previous edition approved in 2000 as A702 – 89 (2000). DOI: 10.1520/A0702-89R06.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

2.2 Federal Standards:

FED-STD-123 Marking for Shipments (Civil Agencies)³

2.3 Military Standards:

MIL-STD-129 Marking for Shipment and Storage³

MIL-STD-163 Steel Mill Products, Preparation for Shipment and Storage³

3. Terminology

3.1 Definitions:

3.1.1 *assemblies*—angel section post components for installation of gates, fence ends or corners, and intermediate bracing.

3.1.2 *line posts*—posts that support the straight-line body of the fence.

4. Ordering Information

4.1 Orders for products under this standard should include the following information:

4.1.1 Quantity (number of pieces) of line posts, end or gate assemblies, corner or intermediate brace assemblies (it is customary to order line posts in multiples of five of the required length and the required number of end or corner assemblies),

4.1.2 Type of section (if a specific section is required) (see 5.2 and Fig. 1),

4.1.3 Length or lengths required (see 6.2),

4.1.4 Finish: galvanized or painted,

4.1.5 ASTM designation and date of issue,

4.1.6 Anchor plates, if required (see 5.4.3), and

4.1.7 Wire fasteners (state weight of zinc coating if other than Class 1) (see 5.6.2 and 5.6.3).

NOTE 1—A typical ordering description is as follows: 500 line posts; 8 ft long; painted; ASTM A702 dated ____; omit anchor plates.

5. Materials and Manufacture

5.1 Material:

³ Available from Standardization Documents Order Desk, Bldg. 4 Section D, 700 Robbins Ave., Philadelphia, PA 19111-5094, Attn: NPODS.

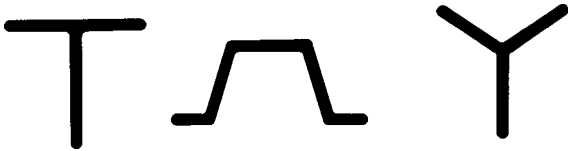


FIG. 1 Typical Cross Sections of Line Post Types

5.1.1 Line posts shall be fabricated from Steels A or B and assemblies from Steels A, B, or C as specified in Table 1.

5.1.2 Except as provided in 6.1.3, the finished line post and assemblies shall conform to the tensile properties specified in Table 1 for the applicable steel.

5.1.3 At the manufacturer’s option, a Brinell or Rockwell B hardness test may be substituted for the tensile requirements in Table 1. In such cases the material shall conform to the Brinell or Rockwell B hardness specified in Table 2.

5.2 Line Post Section:

5.2.1 The posts shall be furnished as T, channel or U, or Y sections as illustrated in Fig. 1. The cross section of T posts shall be approximately 1 3/8 in. (35 mm) wide, 1 3/8 in. deep, and 1/8 in. (3.2 mm) thick. Unless otherwise specified by the purchaser, the line post type is at the manufacturer’s option.

5.2.2 Dimensions may vary slightly in individual design in maintaining the control weight per foot.

5.3 Wire Attachments—Line posts shall have corrugations, knobs, notches, holes, or studs so placed and formed as to engage a substantial number of fence line wires in proper positions.

5.4 Anchor Plates:

5.4.1 Each line post shall be manufactured with an anchor plate, unless otherwise specified. The anchor plate shall be made from carbon steel and shall be swaged or riveted to the post in such a manner as to prevent displacement when the posts are driven.

5.4.2 The placement of the anchor plate shall be nominally 14 in. (350 mm), 16 in. (400 mm), or 18 in. (450 mm) from the bottom of the post to the uppermost portion of the anchor plate.

5.4.3 Anchor plates shall be tapered to facilitate driving, shall have a minimum area of 18 in.² (11600 mm²) and shall weigh 0.67 lb (0.3 kg) ± 5 %.

5.4.4 When specified, line posts may be furnished without anchor plates.

5.4.5 Anchor plates shall be manufactured from Type A or B materials.

5.5 Post Assemblies:

Steel	Steel Description	Brinell Hardness, min	Rockwell B Hardness, min
A	hot-wrought carbon steel, 0.35 % carbon, min	143	79
B	hot-wrought carbon steel or rail steel ^A	156	83
C	structural steel ^B	116	68

^A Hot wrought rail steel in accordance with Specification A499.

^B In accordance with Specification A36/A36M.

5.5.1 Uprights shall consist of angles with a nominal size 2 1/2 by 2 1/2 by 1/4 in. (65 by 65 by 6.4 mm) weighing approximately 4.10 lb/ft (6.1 kg/m) prior to fabrication.

5.5.2 Braces shall consist of angles with a nominal size 2 by 2 by 1/4 in. (50 by 50 by 6.4 mm) weighing approximately 3.19 lb/ft (4.75 kg/m) prior to fabrication, or an alternative angle of equivalent weight.

5.5.3 Uprights and braces shall be furnished with the necessary holes and galvanized hardware for the required assembly.

5.5.4 All assemblies shall be furnished with one upright. End and gate assemblies shall be furnished with one brace, and corner and intermediate braces with two braces.

5.6 Wire Fasteners:

5.6.1 Unless otherwise specified by the purchaser, each line post shall be provided with not less than five suitable fasteners for attaching fence wire to the posts.

5.6.2 The fasteners shall be formed from zinc-coated steel wire not less than 0.120 in. (3.05 mm) diameter zinc coated in accordance with Specification A641/A641M. Class 1 coating shall be furnished unless otherwise specified by purchaser.

5.6.3 When line posts are intended for range type western fencing using three line wires, it is satisfactory to provide only three fasteners for each post.

6. Dimensions, Mass and Permissible Variations

6.1 Nominal Weights and Tolerances:

6.1.1 Nominal Weight—Prior to fabrication by punching, drilling, attaching anchors, or finish coating, the line post sections shall have a nominal weight of 1.33 lb/ft of the length.

6.1.2 The weight of line posts plus anchor plates (if specified), prior to fabrication, drilling, or finish coating shall not

TABLE 1 Materials for Line Posts and Assemblies

Steel	Steel Description	Line Posts		Assemblies	
		Yield Point, min, ksi (MPa)	Tensile Strength, min, ksi (MPa)	Yield Point, min, ksi (MPa)	Tensile Strength, min, ksi (MPa)
A	hot-wrought carbon steel, 0.35 % carbon, min	40 (275)	70 (485)	40 (275)	70 (485)
B	hot-wrought carbon steel, or hot-wrought rail steel ^A	50 (345)	80 (550)	50 (345)	80 (550)
C	structural steel ^B	36 (250)	58 (400)

^A Hot wrought rail steel in accordance with Specification A499.

^B In accordance with Specification A36/A36M.