
**Timber structures — Dowel-type
fasteners —**

**Part 1:
Determination of yield moment**

Structures en bois — Éléments de fixation de type cheville —

Partie 1: Détermination du moment plastique

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 10984-1:2009](https://standards.iteh.ai/catalog/standards/sist/d753825b-9c73-4bf8-9c1e-9ed9edc96806/iso-10984-1-2009)

<https://standards.iteh.ai/catalog/standards/sist/d753825b-9c73-4bf8-9c1e-9ed9edc96806/iso-10984-1-2009>



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 10984-1:2009](#)

<https://standards.iteh.ai/catalog/standards/sist/d753825b-9c73-4bf8-9c1e-9ed9edc96806/iso-10984-1-2009>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2009

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction	v
1 Scope	1
2 Terms and definitions	1
3 Symbols	2
4 Requirements	2
5 Test method	2
6 Test report	7
Annex A (informative) Fastener bending apparatus used for method A	9
Bibliography	12

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 10984-1:2009](https://standards.iteh.ai/catalog/standards/sist/d753825b-9c73-4bf8-9c1e-9ed9edc96806/iso-10984-1-2009)

<https://standards.iteh.ai/catalog/standards/sist/d753825b-9c73-4bf8-9c1e-9ed9edc96806/iso-10984-1-2009>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 10984-1 was prepared by Technical Committee ISO/TC 165, *Timber structures*.

ISO 10984 consists of the following parts, under the general title *Timber structures — Dowel-type fasteners*:

— *Part 1: Determination of yield moment* (standards.iteh.ai)

— *Part 2: Determination of embedding strength* [ISO 10984-1:2009](#)

<https://standards.iteh.ai/catalog/standards/sist/d753825b-9c73-4bf8-9c1e-9ed9edc96806/iso-10984-1-2009>

Introduction

Dowel-type fasteners are those mechanical fasteners that are most widely used for timber structures. Their characteristics, such as yield moment, have a great effect on the mechanical performance of joints made with dowel-type fasteners under loads.

The purpose of this part of ISO 10984 is to define methods to measure the yield moment of a fastener as one of the basic parameters to interpret the behaviour of joints under loads. The requirements are necessary to replicate the same conditions as those for timber structures in the field. This part of ISO 10984 contains two testing methods: method A, based on EN 409, by applying a four-points loading principle, and method B, based on ASTM F1575, by applying a three-points loading principle. The user can choose whichever method is relevant for the test to measure the yield moment of fasteners.

ISO 10984-2 provides the test method to obtain other basic information on the behaviour of mechanical joints under loads.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 10984-1:2009](https://standards.iteh.ai/catalog/standards/sist/d753825b-9c73-4bf8-9c1e-9ed9edc96806/iso-10984-1-2009)

<https://standards.iteh.ai/catalog/standards/sist/d753825b-9c73-4bf8-9c1e-9ed9edc96806/iso-10984-1-2009>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 10984-1:2009

<https://standards.iteh.ai/catalog/standards/sist/d753825b-9c73-4bf8-9c1e-9ed9edc96806/iso-10984-1-2009>

Timber structures — Dowel-type fasteners —

Part 1: Determination of yield moment

1 Scope

This part of ISO 10984 specifies a laboratory method for determining the yield moment of dowel-type fasteners.

2 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

2.1 dowel-type fastener

nail, staple, bolt, screw, dowel or the like with plain or patterned surfaces

2.2 Fastener section dimension

[ISO 10984-1:2009](https://standards.iteh.ai/catalog/standards/sist/d753825b-9c73-4bf8-9c1e-9ed9edc96806/iso-10984-1-2009)

<https://standards.iteh.ai/catalog/standards/sist/d753825b-9c73-4bf8-9c1e-9ed9edc96806/iso-10984-1-2009>

2.2.1 fastener section dimension

⟨plain round or profiled fastener⟩ diameter of the shank without coating

2.2.2 fastener section dimension

⟨square fastener⟩ length of one side of the section

2.2.3 fastener section dimension

⟨oval or rectangular fastener⟩ minimum dimension of the section

2.3 Yield moment

2.3.1 yield moment

⟨method A⟩ the bending moment at the maximum load sustained by a dowel-type fastener under test, or the bending moment at which the fastener has deformed through an angle of 45°, whichever is the lesser

2.3.2 yield moment

⟨method B⟩ the bending moment calculated using the load at the intersection of the load and deformation curve with a line represented by the initial tangent modulus offset by 5 % of the fastener diameter

3 Symbols

d	fastener nominal section dimension as defined in 2.2, expressed in millimetres
F_1, F_3	maximum support loads on the fastener, expressed in newtons
F, F_2, F_4	test loads applied to the fastener, expressed in newtons
F_y	yield load determined from the load and deformation curve, expressed in newtons; see Figure 6
l	length of fastener, expressed in millimeters
l_1, l_3	distances between loading points and the nearest support, expressed in millimetres; see Figure 1
l_2	free length of the fastener, expressed in millimetres; see Figure 1
l_4	length between supports, expressed in millimetres; see Figure 5
l_5	length between the end of fastener and the nearest support, expressed in millimetres; see Figure 5
M_y	yield moment of the fastener, expressed in newton-millimetres
$\alpha, \alpha_1, \alpha_2$	bending angle, expressed in degrees; see Figure 2
ρ_k	characteristic density of the timber, expressed in kilograms per cubic metre
f_t	tensile strength of the fastener, expressed in newtons per square millimetre

STANDARD PREVIEW
(standards.iteh.ai)

[ISO 10984-1:2009](https://standards.iteh.ai/catalog/standards/sist/d753825b-9c73-4bf8-9c1e-9ed9edc96806/iso-10984-1-2009)

4 Requirements

<https://standards.iteh.ai/catalog/standards/sist/d753825b-9c73-4bf8-9c1e-9ed9edc96806/iso-10984-1-2009>

The fasteners shall be, as far as possible, of the quality allowed by the relevant manufacturing specification.

5 Test method

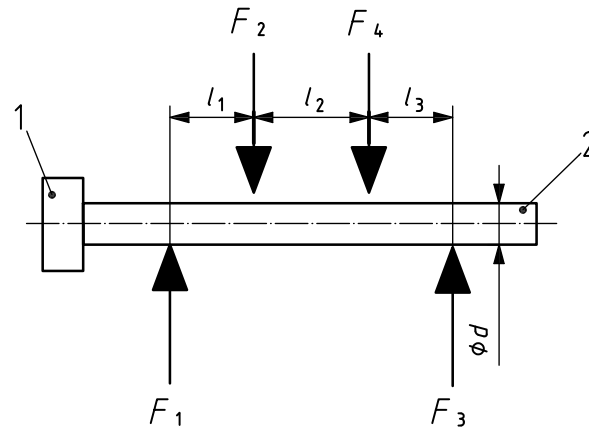
5.1 General

One of the two test methods shall be used: the four-point loading method (method A) or the three-point loading method (method B). The user may choose one of these two methods, whichever is most relevant.

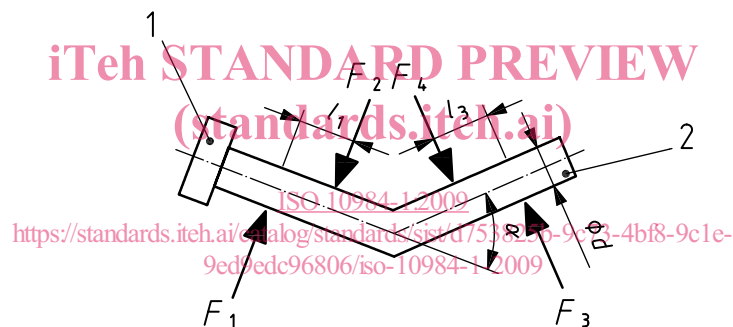
5.2 Method A

5.2.1 Principle

The principle of the test method involves the loading of the fastener under test as shown in Figure 1 in such a manner that the loading points do not move along the fastener and the loads remain normal to the axis of the fastener during the test. The dimensions l_1 and l_3 shall be not less than $2d$. The free length of the fastener, l_2 , shall be between d and $3d$.

**Key**

- 1 fastener head
- 2 dowel-type fastener

Figure 1 — Fastener loading in method A**Key**

- 1 fastener head
- 2 dowel-type fastener

Figure 2 — Fastener deformation in method A**5.2.2 Materials**

Dowel-type fasteners shall be the same nails, staples, bolts, screws, dowels or the like as those used in the actual construction.

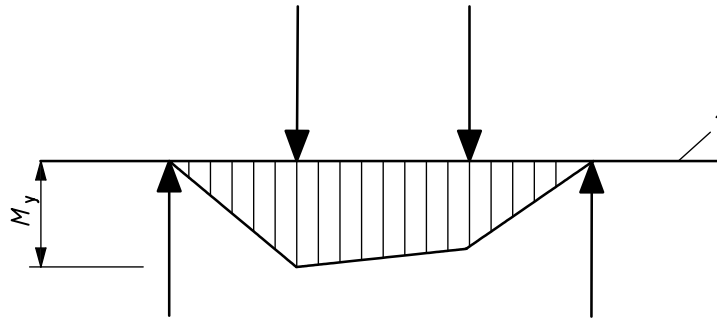
For the fasteners with coatings, the coatings shall be removed before measuring the diameter and carrying out the tests.

5.2.3 Apparatus

5.2.3.1 Testing apparatus, such that the loads F_2 and F_4 (see Figures 1 and 2) do not deviate by more than 5 % from each other.

The bending moment diagram for the resulting yield moment M_y is shown in Figure 3.

NOTE A test apparatus that has been found suitable for this test is shown in Annex A.



Key

1 dowel-type fastener

Figure 3 — Yield moment M_y on the fastener in method A

5.2.4 Preparation of specimen

The fastener shall be tested about its weakest axis.

5.2.5 Loading procedure

The load shall be applied to the fastener as shown in Figure 1, and shall be increased at such a rate that the bending angle defined in 5.2.6 is reached in (10 ± 5) s.

The maximum load shall be determined to an accuracy of 1 %.

Record the loads and the corresponding values of the bending angle.

5.2.6 Bending angle

For nails and staples, the bending angle shall be 45°.

For bolts, screws or dowels used in wood-based products, the bending angle shall be $(110/d)$ degrees.

For bolts, screws or dowels produced from steel material with a tensile strength of at least 1 000 N/mm² used in timber and glued laminated timber with a characteristic density of 360 kg/m³ (based on oven-dry mass and volume), the bending angle is given by Figure 4.

For different tensile strength and/or different characteristic density of timber, the bending angle, α , expressed in degrees, shall be determined as given in Equation (1):

$$\alpha = \alpha_1 \left(\frac{2,78 \rho_k}{f_t} \right)^{0,44} + \alpha_2 \tag{1}$$

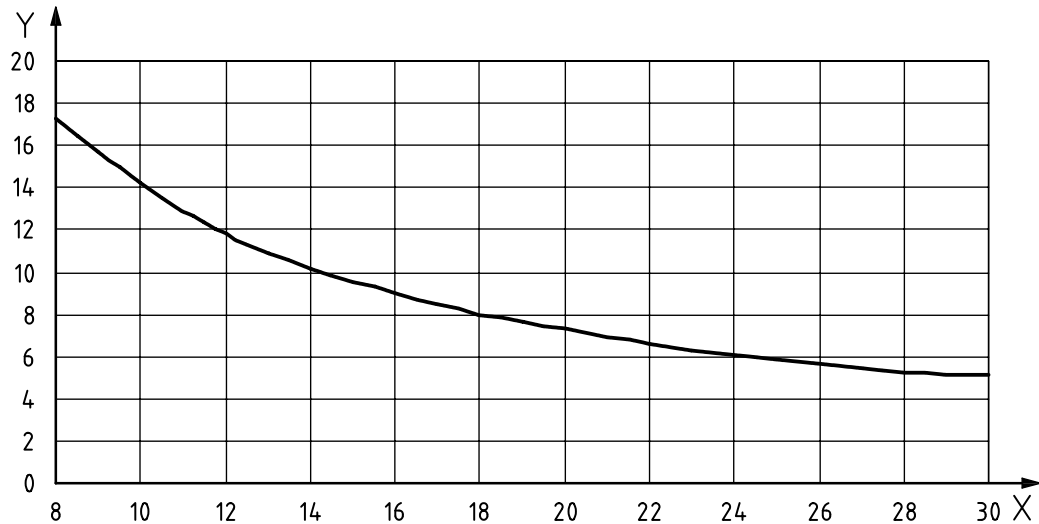
where

α_1 is the bending angle according to Figure 4, expressed in degrees;

α_2 is 10° for nails, staples and screws, and 0° for dowels and bolts;

ρ_k is the characteristic density of the timber, expressed in kilograms per cubic metre;

f_t is the tensile strength of the fastener, expressed in newtons per square millimetre.

**Key**

- X nominal section, d , expressed in millimetres
 Y angle, α , expressed in degrees

Figure 4 — Diagram for bending angle versus fastener diameter used for method A

iTeh STANDARD PREVIEW
 (standards.iteh.ai)

5.2.7 Results

Measure the loads, F_1 and F_3 , at the bending angle, α , determined in accordance with 5.2.6.

The value of the yield moment, M_y , shall be calculated as the greater of the two expressions ($F_1 \times l_1$) and ($F_3 \times l_3$), and shall be determined to an accuracy of 1%.

When the test apparatus used is that shown in Annex A, Equation (A.1) or Equation (A.2) shall be used to determine the yield moment in lieu of Equation (1).

5.3 Method B**5.3.1 Principle**

The principle of the test method B involves the loading of the fastener under test as shown in Figure 5 in such a manner that the lateral bending load is applied at a constant rate during the test. Dimension l_4 shall be at least $11d$ for nails and staples and $4d$ for bolts. Dimension l_5 shall be not less than $2d$ for nails, staples and bolts. If the fastener is too short to meet this requirement, it shall be tested with the largest possible span and the span and testing circumstances shall be described in the test report.