
**Building construction — Jointing
products —**

Part 1:

Determination of extrudability of sealants

Construction immobilière — Produits pour joints —

Partie 1: Détermination de l'extrudabilité des mastics

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 8394-1:2010

<https://standards.iteh.ai/catalog/standards/sist/151e1ee2-dd2a-441d-9349-3a66a1fe31fd/iso-8394-1-2010>



Reference number
ISO 8394-1:2010(E)

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 8394-1:2010

<https://standards.iteh.ai/catalog/standards/sist/151e1ee2-dd2a-441d-9349-3a66a1fe31fd/iso-8394-1-2010>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2010

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 8394-1 was prepared by Technical Committee ISO/TC 59, *Building construction*, Subcommittee SC 8, *Jointing products*.

ISO 8394 consists of the following parts, under the general title *Building construction — Jointing products*

- *Part 1: Determination of extrudability of sealants*
- *Part 2: Determination of extrudability of sealants using standardized apparatus*

This first edition of ISO 8394-1, together with ISO 8394-2, cancels and replaces ISO 8394:1988, which has been technically revised.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 8394-1:2010

<https://standards.iteh.ai/catalog/standards/sist/151e1ee2-dd2a-441d-9349-3a66a1fe31fd/iso-8394-1-2010>

Building construction — Jointing products —

Part 1: Determination of extrudability of sealants

1 Scope

This part of ISO 8394 specifies a method for determining the extrudability of sealants.

The method is for use in testing the extrudability of a sealant. It is not applicable to the classification of sealants.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 6927, *Building construction — Jointing products — Sealants — Vocabulary*

<https://standards.iteh.ai/catalog/standards/sist/151e1ee2-dd2a-441d-9349-3a66a1fe31fd/iso-8394-1-2010>

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 6927 apply.

4 Principle

A sealant is extruded from its package, under defined conditions. The mass of the extruded sealant is determined.

This part of ISO 8394 indicates reference test conditions, such as temperature, pressure, extrusion time, geometry of nozzle. Deviation from these conditions is possible. Deviation modifies the final result; therefore, any deviation shall be described in the test report. The comparison of results is possible, only if all the test conditions are the same.

5 Apparatus

5.1 Enclosure, regulated to (5 ± 2) °C, (23 ± 2) °C, (35 ± 2) °C or a temperature agreed on by the parties concerned.

5.2 Nozzle, as specified in this subclause, shall be used in conjunction with the package. The dimensions and nature of the nozzle shall be determined by the parties concerned.

The nozzle shall be either

- metallic (see Figures 1 and 2 for the dimensions of two different metallic nozzles), or
- plastic. The plastic nozzle shall be cut at internal diameter of between 3 mm and 6 mm. The default internal diameter shall be 6 mm. Acceptable tolerances of the internal diameter shall be $\pm 5\%$.

5.3 Pneumatically operated extrusion gun, supplied with compressed air up to 700 kPa.

5.4 Stopwatch, accurate to 0,1 s.

5.5 Balance, accurate to 0,1 g.

6 General

For each tested sealant, perform three extrusion tests.

For each extrusion test, use one package.

Perform the three measurements under the same conditions (same batch number, temperature, nozzle and diameter, same pressure, etc.).

7 Conditioning

iTeh STANDARD PREVIEW

Condition the three packages containing the tested sealant at the testing temperature in the regulated enclosure (5.1) for a minimum of 12 h, before testing.

The default conditioning temperature is $(23 \pm 2)^\circ\text{C}$. <https://standards.iteh.ai/catalog/standards/sist/151e1ee2-dd2a-441d-9349-3a66a1fe31fd/iso-8394-1-2010>

This conditioning temperature may be at $(5 \pm 2)^\circ\text{C}$, $(23 \pm 2)^\circ\text{C}$ or $(35 \pm 2)^\circ\text{C}$, or a temperature agreed on by the parties concerned.

8 Test procedure

The measurements may be carried out at usual laboratory room temperature. All the following operations shall be carried out within 5 min.

Prepare the packages, removing all elements which can prevent the extrusion of the sealant during testing (i.e. screw, setting, internal membrane between the nozzle and the cartridge).

Attach the nozzle (5.2), at the end of the package. This test of extrudability may be also performed with any other metallic or plastic nozzles, as agreed on by the parties concerned.

Insert the package in the pneumatic gun (5.3).

Extrude sufficient sealant to remove the air from the nozzle.

Set the air pressure of the compressor to (300 ± 10) kPa, or a pressure agreed on by the parties concerned.

Extrude the sealant out of the package for 30 s. Measure this time with the stopwatch (5.4). Do not take into account the quantity of sealant coming out of the nozzle after the end of test time.

The package shall not be empty after testing.

NOTE In the case of a low viscosity sealant, the extrusion time can be lower. In the case of a high viscosity sealant, the extrusion time can be higher.

After the pneumatic extrusion, weigh the quantity of extruded sealant, with the balance (5.5).

9 Expression of results

9.1 Extrusion rate, expressed as mass per minute

The result of each measurement, expressed in grams of extruded sealant per minute, is rounded to the nearest gram, using Equation (1):

$$E_m = \frac{m \times 60}{t} \quad (1)$$

where

E_m is the extrusion rate of the sealant, expressed in grams per minute;

m is the mass of the extruded sealant, expressed in grams;

t is the time of extrusion, expressed in seconds.

Calculate the mean value of the three measurements, rounded to the nearest gram per minute.

9.2 Extrusion rate, expressed as volume per minute

If needed, the result can be expressed in millilitres of extruded sealant per minute, rounded to the nearest millilitre, using Equation (2):

$$E_v = \frac{E_m}{D} \quad (2)$$

where

E_v is the extrusion rate of the sealant, expressed in millilitres per minute;

E_m is the extrusion rate of the sealant, expressed in grams per minute;

D is the density of the sealant, expressed to 2 decimal places, at the test temperature of the sealant.


Calculate the mean value of the three values of E_v , rounded to the nearest millilitre per minute.

10 Test report

The test report shall contain the following information:


- a reference to this part of ISO 8394, i.e. ISO 8394-1:2010;
- the name of the test laboratory and the date of test;
- the name, type (chemical family) and colour of sealant;
- the batch number of the sealant;

- e) the conditioning temperature;
- f) the extrusion pressure;
- g) the extrusion time;
- h) the type of nozzle. If another nozzle is used, the nature (plastic or metallic), the geometry, commercial reference and diameter of the nozzle shall be indicated;
- i) the result of each extrusion rate, in grams per minute, and the mean value;
- j) the result of the extrusion rate, in millilitres per minute, the mean value and the density, if necessary;
- k) any deviation from this part of ISO 8394.

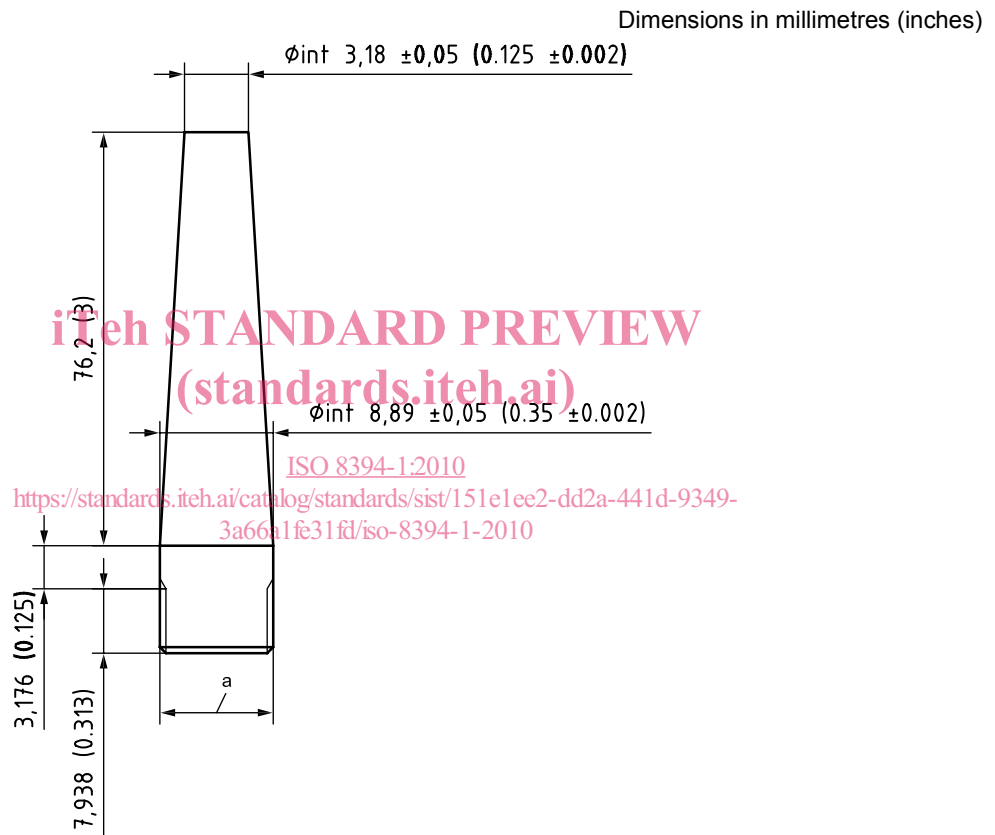

a ¼ in NPT threads.

Figure 1 — First metallic nozzle scheme

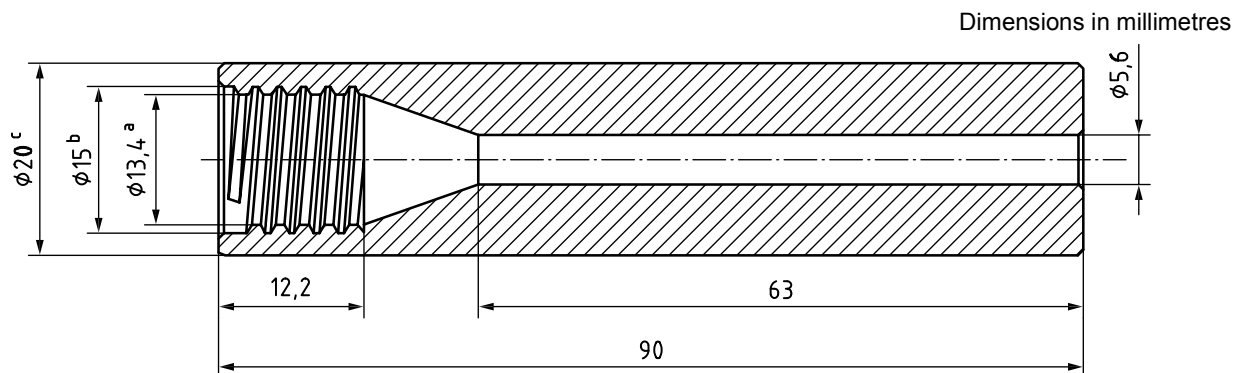

- a Pitch of 2,5 mm.
- b Chamfer of 0,5 mm.
- c 316 Inox.

Figure 2 — Second metallic nozzle scheme

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 8394-1:2010

<https://standards.iteh.ai/catalog/standards/sist/151e1ee2-dd2a-441d-9349-3a66a1fe31fd/iso-8394-1-2010>