



Designation: ~~D6605-00~~ Designation: D 6605 – 06

Standard Practice for Determining the Color Stability of Hydrocarbon Resins After Heating¹

This standard is issued under the fixed designation D 6605; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope*

1.1 This practice covers ~~the~~ determination of the color stability of a hydrocarbon resin by exposure to a specific temperature for a defined time period in a forced-draft oven.

1.2 Color stability is measured by the change in color of the test resin, measured via the yellowness index color scale, in accordance with Practice E 313, or the procedure for Gardner Color, Test Method D 6166.

1.3 The values stated in SI units are to be regarded as standard. The values given in parentheses are for information only.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards:*²

D 6166 Test Method for Color of Naval Stores and Related ~~Products~~, Products (Instrumental Determination of Gardner Color)

D 6440 Terminology Relating to Hydrocarbon Resins

E 313 Practice for Calculating Yellowness and Whiteness Indices from Instrumentally Measured Color ~~Coordinates~~, Coordinates

3. Summary of Practice

3.1 ~~Samples of the hydrocarbon resin to be tested are placed in 250-mL (8-oz) glass jars and placed in a heating block that is in a ventilated oven set at 175°C. The samples are kept in the oven for a given period of 5 h. At the end of this time, the samples are removed and allowed to cool. After cooling, the samples are dissolved in toluene. The color of each aged sample solution is measured and compared to an initial sample solution. This color change is a measure of the stability of the resin.~~ Terminology

3.1 Definitions:

3.1.1 For definitions of terms relating to hydrocarbon resins, see Terminology D 6440.

4. Significance and Use

4.1 ~~This practice is useful for both quality control and research.~~ Summary of Practice

4.1 Specimens of the hydrocarbon resin(s) to be tested are placed in 250-mL (8-oz) glass jars, which are placed in a heating block that is in a ventilated oven set at 175°C. The samples are kept in the oven for an agreed upon period. At the end of this time, the samples are removed and allowed to cool. After cooling, the samples are dissolved in toluene. The color of each aged resin solution is measured and compared to that of a solution of the corresponding unaged resin. This color increase is a measure of the (lack of) stability of the resin.

5. Significance and Use

5.1 This practice is useful for both quality control and research.

6. Apparatus and Materials

6.1

6.1 Forced Draft Oven, with the ventilation set at maximum capacity.

¹ This practice is under the jurisdiction of ASTM Committee D01 on Paint and Related Coatings, Materials, and Applications and is the direct responsibility of Subcommittee D01.38 on Hydrocarbon Resins.

Current edition approved Nov. 10, 2000. Published January 2001.

Current edition approved Nov. 1, 2006. Published November 2006. Originally approved in 2000. Last previous edition approved in 2000 as D 6605 - 00.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards*, Vol 06.03, volume information, refer to the standard's Document Summary page on the ASTM website.

*A Summary of Changes section appears at the end of this standard.

5.2

6.2 *Aluminum Block*, equipped with a control thermocouple (see Fig. 1).

5.3

6.3 *Temperature Indicator*.

5.4

6.4 *Glass Jars*, 250 mL (8 oz), with suitably lined screw cap.

NOTE 1—Tetrafluoroethylene (TFE) lined caps work well.

5.5 *1—TFE-fluorocarbon-lined caps work well.*

6.5 *Balance*, readable to at least 0.1g.

5.6

6.6 *Shaker*: used to facilitate the dissolution of the ~~heat-aged resin~~ resin specimens.

5.7 *6.7 Spectrophotometer or Tristimulus Colorimeter.*

6.

7. Reagents

6.1

Aluminum Block

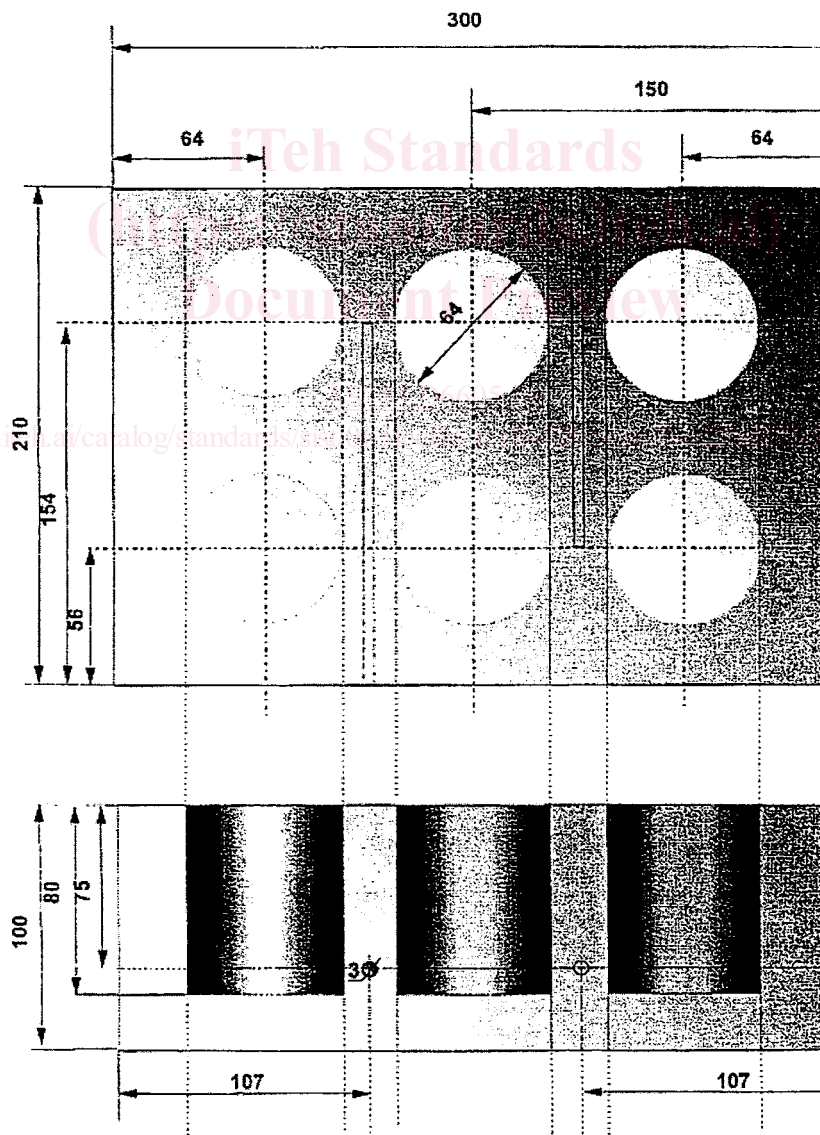


FIG. 1 Measurements in Millimetres