
**Paints and varnishes — Determination of
density —**

**Part 4:
Pressure cup method**

Peintures et vernis — Détermination de la masse volumique —

Partie 4: Méthode du cylindre sous pression

**iTeh STANDARD PREVIEW
(standards.iteh.ai)**

ISO 2811-4:2011

<https://standards.iteh.ai/catalog/standards/sist/cde3b36d-49df-4e36-8777-e461a5b240cb/iso-2811-4-2011>



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 2811-4:2011](https://standards.iteh.ai/catalog/standards/sist/cde3b36d-49df-4e36-8777-e461a5b240cb/iso-2811-4-2011)

<https://standards.iteh.ai/catalog/standards/sist/cde3b36d-49df-4e36-8777-e461a5b240cb/iso-2811-4-2011>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2011

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Temperature	2
6 Apparatus	2
7 Sampling	2
8 Procedure	2
8.1 General	2
8.2 Determination	2
9 Calculation	4
10 Precision	4
10.1 General	4
10.2 Repeatability limit, r	4
10.3 Reproducibility limit, R	4
11 Test report	4
Annex A (normative) Calibration of pressure cup	6
Annex B (informative) Temperature variation	8

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 2811-4 was prepared by Technical Committee ISO/TC 35, *Paints and varnishes*, Subcommittee SC 9, *General test methods for paints and varnishes*.

This second edition cancels and replaces the first edition (ISO 2811-4:1997), which has been technically revised.

The main changes are:

- <https://standards.iteh.ai/catalog/standards/sist/cde3b361-49df-4e36-8777-e461a5b240cb/iso-2811-4-2011>
- ISO 2811-4:2011**
(standards.iteh.ai)
- a) The unit for the density has been changed from grams per millilitre to grams per cubic centimetre, because this is the more common SI unit.
 - b) The determination in duplicate has been changed to a single determination.
 - c) The normative references have been updated.

ISO 2811 consists of the following parts, under the general title *Paints and varnishes — Determination of density*:

- *Part 1: Pycnometer method*
- *Part 2: Immersed body (plummet) method*
- *Part 3: Oscillation method*
- *Part 4: Pressure cup method*

Paints and varnishes — Determination of density —

Part 4: Pressure cup method

1 Scope

This part of ISO 2811 specifies a method for determining the density of paints, varnishes and related products using a pressure cup.

The method is suitable for products which are aerated. Emulsion paints, for example, often trap small air bubbles, and these might still be present when the density is measured.

It is not, however, suitable for textured paints which contain coarse particles.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1513, *Paints and varnishes — Examination and preparation of test samples*

ISO 3696, *Water for analytical laboratory use — Specification and test methods*

ISO 15528, *Paints, varnishes and raw materials for paints and varnishes — Sampling*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

density

ρ

mass divided by the volume of a portion of a material

NOTE This is expressed in grams per cubic centimetre.

4 Principle

The product under test is compressed in a cylindrical pressure cup to reduce any error due to air bubbles which have not been eliminated. The density is calculated from the mass of the product and the volume of the cylinder.

NOTE Air is more soluble at higher pressures, and it is thought that the main mechanism of bubble removal is by dissolving. Any undissolved bubbles are compressed to a fraction of their original size.

5 Temperature

The effect of temperature on density is highly significant with respect to filling properties, and varies with the type of product.

Carry out the test at $(23,0 \pm 0,5)$ °C.

NOTE For some purposes, a different temperature, for example $(20,0 \pm 0,5)$ °C, might be needed.

The test sample and pressure cup shall be conditioned to the specified or agreed temperature, and it shall be ensured that the temperature variation does not exceed 0,5 °C during testing.

6 Apparatus

Ordinary laboratory apparatus and glassware, together with the following.

6.1 Pressure cup, comprising a hollow cylinder closed by a screw-driven piston at its lower end and by a pressure-release cap at the top (see Figure 1). A calibration collar on the screw is set to stop further movement of the piston when the volume contained in the cylinder is 100 cm³. The pressure-release cap is designed to let liquid escape when the pressure in the cylinder rises above $(1,0 \pm 0,1)$ MPa (10 bar). The apparatus is made of a strong, inert material, for example stainless steel, and it is easily dismantled for cleaning.

6.2 Thermometer, accurate to 0,2 °C and graduated at intervals of 0,2 °C or finer.

6.3 Temperature-controlled chamber, capable of maintaining the pressure cup and sample at the specified or agreed temperature (see Clause 5).

6.4 Balance, accurate to 10 mg. [ISO 2811-4:2011
https://standards.itech.ai/catalog/standards/sist/cde3b36d-49df-4e36-8777-e461a5b240cb/iso-2811-4-2011](https://standards.itech.ai/catalog/standards/sist/cde3b36d-49df-4e36-8777-e461a5b240cb/iso-2811-4-2011)

7 Sampling

Take a representative sample of the product under test, as described in ISO 15528. Examine and prepare the sample as described in ISO 1513.

8 Procedure

8.1 General

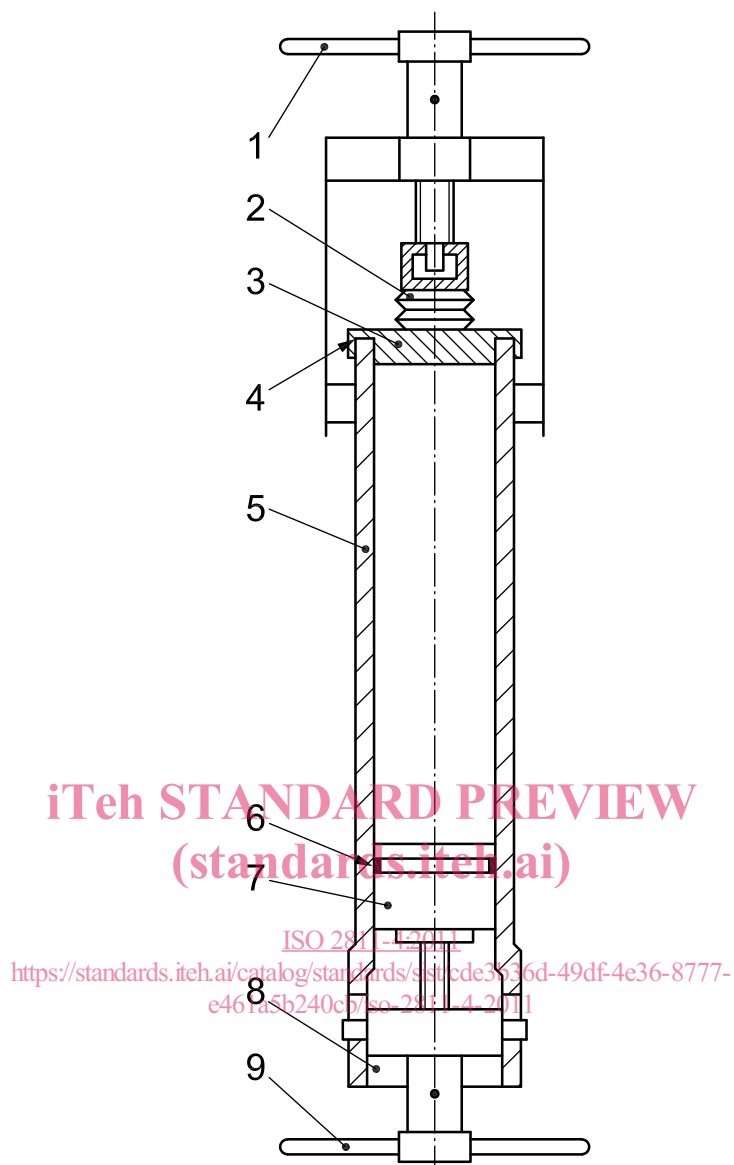
Carry out a single determination on a fresh test sample.

8.2 Determination

Weigh the dismantled apparatus, ensure that it is clean and has a trace of grease on the moving parts. Fit the piston in its lowest position in the cylinder.

Weigh the complete apparatus to the nearest 10 mg (m_1). Bring the apparatus and the test sample to the specified or agreed temperature by placing it next to the balance for at least 30 min.

Pour the test sample into the cylinder until it is almost full, and allow sufficient time for the test sample and the cylinder to come to equilibrium at the test temperature. Confirm that the temperature is correct using the thermometer (6.2). Secure the pressure-release cap in position, in accordance with the manufacturer's instructions.

**Key**

- | | | | |
|---|---|---|-----------------------------|
| 1 | pressure-setting handle | 6 | piston seal |
| 2 | pressure-release device | 7 | piston |
| 3 | end cap | 8 | calibration-collar stop |
| 4 | end seal | 9 | pressure-application handle |
| 5 | cylinder (closed volume 100 cm ³) | | |

Figure 1 — Pressure cup

Compress the test sample by turning the screw. As the pressure reaches about 1 MPa, excess paint is forced out between the cylinder and the cap. Continue turning the screw until the calibration collar stops further movement.

NOTE A rag held around the top of the cylinder reduces the mess. It is essential that some excess paint is forced out, to confirm that full pressure is achieved.

Clean and dry the outside of the filled cup, and weigh it to the nearest 10 mg (m_2).

Unscrew the piston enough to reduce the pressure. Dismantle, empty and clean the apparatus.

For reference tests, and periodically during routine tests, check the calibration of the apparatus, using pure water as the test liquid (see Annex A).

9 Calculation

Calculate the density, ρ , of the product, in grams per cubic centimetre, at the test temperature, t_T , using Equation (1):

$$\rho = \frac{m_2 - m_1}{V_t} \quad (1)$$

where

m_1 is the mass, in grams, of the empty pressure cup;

m_2 is the mass, in grams, of the pressure cup filled with the product at the test temperature, t_T ;

V_t is the volume, in cubic centimetres, of the pressure cup at the test temperature, t_T , determined in accordance with Annex A.

NOTE The result is not corrected for air buoyancy because the uncorrected value is required by most filling-machine control procedures and the correction (0,001 2 g/cm³) is negligible in relation to the precision of the method.

If the test temperature used is not the reference temperature, the density can be calculated using Equation (B.2).

ITeCH STANDARD PREVIEW
(standards.iteh.ai)

10 Precision

ISO 2811-4:2011

<https://standards.iteh.ai/catalog/standards/sist/cde3b36d-49df-4e36-8777-e461a5b240cb/iso-2811-4-2011>

10.1 General

The precision of the method depends on the characteristics of the product under test. For materials which contain no entrapped air, the values in 10.2 and 10.3 are valid.

10.2 Repeatability limit, r

The value below which the absolute difference between two single test results, obtained on identical material by one operator in one laboratory using the same equipment within a short interval of time using the standardized test method, may be expected to lie, with a 95 % probability, is 0,005 g/cm³.

10.3 Reproducibility limit, R

No data are currently available.

11 Test report

The test report shall include at least the following information:

- a) all details necessary to identify the product tested;
- b) a reference to this part of ISO 2811, i.e. ISO 2811-4:2011;
- c) the supplier and serial number or other identification of the pressure cup;
- d) the test temperature;

- e) the result of the density measurement, in grams per cubic centimetre, rounded to the nearest 0,001 g/cm³;
- f) any deviation from the test method specified;
- g) any unusual features (anomalies) observed during the test;
- h) the date of the test.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 2811-4:2011

<https://standards.iteh.ai/catalog/standards/sist/cde3b36d-49df-4e36-8777-e461a5b240cb/iso-2811-4-2011>