
**Plastics — Epoxy resins — Determination
of chlorine content —**

**Part 2:
Easily saponifiable chlorine**

*Plastiques — Résines époxydes — Détermination de la teneur en
chlore —*

iTeh STANDARD PREVIEW
Partie 2: Chlore facilement saponifiable
(standards.iteh.ai)

ISO 21627-2:2009

<https://standards.iteh.ai/catalog/standards/sist/8dc24e4d-a6c5-482e-a6ee-25497d5e5879/iso-21627-2-2009>



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 21627-2:2009

<https://standards.iteh.ai/catalog/standards/sist/8dc24e4d-a6c5-482e-a6ee-25497d5e5879/iso-21627-2-2009>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2009

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction.....	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Reagents	2
6 Apparatus	3
7 Procedure	3
8 Expression of results	5
9 Precision	5
10 Test report.....	5
Bibliography.....	6

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 21627-2:2009](https://standards.iteh.ai/catalog/standards/sist/8dc24e4d-a6c5-482e-a6ee-25497d5e5879/iso-21627-2-2009)

<https://standards.iteh.ai/catalog/standards/sist/8dc24e4d-a6c5-482e-a6ee-25497d5e5879/iso-21627-2-2009>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 21627-2 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 12, *Thermosetting materials*.

This second edition cancels and replaces the first edition (ISO 21627-2:2002), which has been technically revised.

ISO 21627 consists of the following parts, under the general title *Plastics — Epoxy resins — Determination of chlorine content*:

- *Part 1: Inorganic chlorine*
- *Part 2: Easily saponifiable chlorine*
- *Part 3: Total chlorine*

iTeh STANDARD PREVIEW
(standards.iteh.ai)
<https://standards.iteh.ai/catalog/standards/sist/8dc24e4d-a6c5-482e-a6ee-25497d5e5879/iso-21627-2-2009>

Introduction

In producing epoxy resins based on epichlorohydrin, impurities containing chlorine may be formed. These are shown below. Since these impurities could impair the final properties of the cured resins, it is necessary to control their formation. Their chemical activities differ significantly, so different analytical procedures are needed for their analysis.

ISO 21627 specifies methods for the determination of these organic and inorganic chlorides which occur as impurities in epoxy resins derived from epichlorohydrin:



- Part 1: Inorganic chlorine (also called ionic chlorine).
- Part 2: Easily saponifiable chlorine, consisting mainly of chlorine which is present as 1,2-chlorohydrin as the result of incomplete dehydrohalogenation.
- Part 3: Total chlorine, consisting mainly of all saponifiable organic chlorine, e.g. 1,2-chlorohydrin, 1,3-chlorohydrin and 1-chloro-2-glycidylether (chloromethyl derivative) which are the result of incomplete dehydrohalogenation, along with inorganic chlorine present in the test portion of epoxy resin.

Since the purposes of Parts 1 to 3 of ISO 21627 differ, one of these methods should be selected, depending on the impurities to be measured.

For analytical methods for impurities other than those shown below, see ISO 4615.

Typical types of inorganic and organic chlorine impurity are shown below:

Cl⁻ <https://standards.iteh.ai/catalog/standards/sist/8dc24e4d-a6c5-482e-a6ee-25497d5e5879/iso-21627-2-2009> Inorganic chlorine (or ionic chlorine)

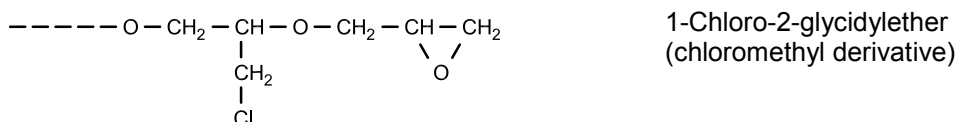

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 21627-2:2009

<https://standards.iteh.ai/catalog/standards/sist/8dc24e4d-a6c5-482e-a6ee-25497d5e5879/iso-21627-2-2009>

Plastics — Epoxy resins — Determination of chlorine content —

Part 2: Easily saponifiable chlorine

SAFETY STATEMENT — Persons using this document should be familiar with normal laboratory practice, if applicable. This document does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to ensure compliance with any regulatory requirements.

1 Scope

This part of ISO 21627 specifies a method for the determination of easily saponifiable chlorine in epoxy resins.

The easily saponifiable chlorine content is the quantity of easily saponifiable chlorine in a given quantity of epoxy resin.

The values obtained are indicative of the concentration of easily saponifiable chlorine in chlorohydrin groups in the resin.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3696:1987, *Water for analytical laboratory use — Specification and test methods*

ISO 21627-1, *Plastics — Epoxy resins — Determination of chlorine content — Part 1: Inorganic chlorine*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

easily saponifiable chlorine

amount of chlorine saponifiable by this test method, consisting mainly of chlorine present as 1,2-chlorohydrin as a result of incomplete dehydrohalogenation

4 Principle

Epoxy resins, except glycidyl esters, are reacted with NaOH solution at room temperature in 2-butoxyethanol.

Glycidyl esters are reacted with NaOH solution at 50 °C in methanol.

The mixture is acidified and the concentration of chloride ions resulting from the saponification is determined by potentiometric titration with standardized silver nitrate solution. A correction is made for the inorganic chlorine content of the sample, determined by the method specified in ISO 21627-1.

5 Reagents

During the analysis, use only reagents of recognized analytical grade and water of grade 3 purity, as defined in ISO 3696:1987, or better.

5.1 Glacial acetic acid.

5.2 2-Butoxyethanol (ethylene glycol monobutyl ether), stored in a brown bottle in the dark.

WARNING — 2-Butoxyethanol is toxic. Avoid inhalation of vapour. Prevent contact with skin and eyes. Work under a fume hood or in a well-ventilated area. The threshold limit value is a volume fraction of 5×10^{-5} .

5.3 2-Butanone (methyl ethyl ketone).

5.4 Methanol.

WARNING — Methanol is toxic. Avoid inhalation of vapour. Prevent contact with skin and eyes. Work under a fume hood or in a well-ventilated area.

5.5 Sodium hydroxide, 120 g/l solution

— in 2-butoxyethanol (for epoxy resins);

— in methanol (for glycidyl esters).

STANDARD PREVIEW
(standards.iteh.ai)
<https://standards.iteh.ai/catalog/standards/sist/8dc24e4d-a6c5-482e-a6ee-2549745-5870/sist/21627-2-2009>

Dissolve 120 g of sodium hydroxide in 75 ml of water plus sufficient 2-butoxyethanol (5.2) or methanol (5.4) to achieve complete dissolution. Cool and make up to 1 l with the same solvent.

5.6 Acetone.

5.7 Silver nitrate solution, 0,01 mol/l.

5.7.1 Preparation

Dissolve 1,7 g of silver nitrate in water and make up to 1 l.

5.7.2 Standardization

Weigh, to the nearest 0,1 mg, 584 mg of sodium chloride, previously dried at 500 °C to 600 °C, and dissolve in 1 l of water.

Pipette 5 ml of this solution into a 200 ml beaker and add 100 ml of acetone (5.6) and 2 ml of glacial acetic acid (5.1). Then titrate potentiometrically with the silver nitrate solution prepared in 5.7.1.

Conduct a blank test in the same way, leaving out the sodium chloride.

5.7.3 Calculation of concentration

Calculate the concentration using the following equation, rounding the result to three significant figures:

$$c_2 = \frac{0,005 \times m}{58,5 \times (V - V_0)}$$

where

- c_2 is the concentration of the silver nitrate solution, expressed in moles per litre (mol/l);
- m is the mass of sodium chloride used, expressed in milligrams (mg);
- 58,5 is the gram equivalent of sodium chloride (g/mol);
- V is the volume of silver nitrate solution used in the titration, expressed in millilitres (ml);
- V_0 is the volume of silver nitrate solution used in the blank, expressed in millilitres (ml).

5.7.4 Storage

Store the silver nitrate solution in a brown bottle in the dark.

6 Apparatus

Usual laboratory apparatus, plus the following:

- 6.1 Potentiometric-titration apparatus**, comprising a suitable potentiometer or autotitrator equipped with a glass-silver/silver chloride electrode system, titration stand and 10 ml microburette.
- 6.2 Analytical balance**, accurate to 0,1 mg.
- 6.3 Beaker**, of capacity 200 ml.
- 6.4 Volumetric flask**, of capacity 1 l.
- 6.5 Pipettes**, of capacities 2 ml, 5 ml and 25 ml.
- 6.6 Graduated glass cylinder**, of capacity 100 ml.
- 6.7 Water bath**, capable of being maintained at 50 °C.
- 6.8 Conical flask**, of capacity 200 ml, with a ground-glass stopper.
- 6.9 Reflux condenser**.
- 6.10 Magnetic stirrer**, with a PTFE (polytetrafluoroethylene) coated stirring bar.

7 Procedure

7.1 Epoxy resins

7.1.1 Weigh, to the nearest 0,1 mg, a test portion containing not more than 1,78 mg of easily saponifiable chlorine into the beaker (6.3). Pipette 25 ml of 2-butoxyethanol (5.2) into the beaker and dissolve the test portion using the magnetic stirrer (6.10) and by heating, if necessary. Cool the solution to room temperature