



SLOVENSKI STANDARD SIST ISO 10505:2011

01-julij-2011

Fotografija - Geometrično povprečje zrnatosti fotografskih filmov - Metode merjenja

Photography - Root mean square granularity of photographic films - Method of measurement

iTeh STANDARD PREVIEW

Photographie - Moyenne quadratique granulaire de films photographiques - Méthode de mesure

[SIST ISO 10505:2011](https://standards.iteh.ai/catalog/standards/sist/c7cc9481-73c0-49ce-b9f9-5c54947eb46f/sist-iso-10505-2011)

Ta slovenski standard je istoveten z: **ISO 10505:2009**

ICS:

37.040.20	Fotografski papir, filmi in fotografske plošče. Filmski zvitki	Photographic paper, films and cartridges
-----------	--	--

SIST ISO 10505:2011

en

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST ISO 10505:2011](#)

<https://standards.iteh.ai/catalog/standards/sist/c7cc9481-73c0-49ce-b9f9-5c54949eb46f/sist-iso-10505-2011>

INTERNATIONAL
STANDARD

ISO
10505

First edition
2009-05-15

**Photography — Root mean square
granularity of photographic films —
Method of measurement**

*Photographie — Moyenne quadratique granulaire de films
photographiques — Méthode de mesure*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST ISO 10505:2011](https://standards.iteh.ai/catalog/standards/sist/c7cc9481-73c0-49ce-b9f9-5c54949eb46f/sist-iso-10505-2011)

<https://standards.iteh.ai/catalog/standards/sist/c7cc9481-73c0-49ce-b9f9-5c54949eb46f/sist-iso-10505-2011>



Reference number
ISO 10505:2009(E)

© ISO 2009

ISO 10505:2009(E)**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[SIST ISO 10505:2011](https://standards.iteh.ai/catalog/standards/sist/c7cc9481-73c0-49ce-b9f9-5c54949eb46f/sist-iso-10505-2011)

<https://standards.iteh.ai/catalog/standards/sist/c7cc9481-73c0-49ce-b9f9-5c54949eb46f/sist-iso-10505-2011>

**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2009

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword.....	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions.....	1
4 Measurement instrument	3
4.1 General.....	3
4.2 Microdensitometer.....	3
4.3 Spectral products	6
4.4 Spatial frequency response.....	7
4.5 Scanning motion.....	7
5 Instrument electronics	8
5.1 Conversion to density	8
5.2 Temporal frequency response of the instrument.....	8
5.3 Instrument noise	8
6 Diffuse rms-granularity	8
6.1 Optical geometry.....	8
6.2 Diffuse conversion factor g.....	9
7 Preparation of specimens	9
7.1 Sampling and storage	9
7.2 Exposure.....	10
7.3 Processing.....	10
7.4 Specimen uniformity	10
7.5 Sampled area.....	10
8 Operation of the measurement instrument.....	10
8.1 Positioning the specimen	10
8.2 Specimen scanning	10
8.3 Control of focus	10
8.4 Rate of scan.....	11
8.5 Density mode	11
9 Method of test	11
9.1 Principle	11
9.2 Statistical background	11
9.3 Construction of the median estimator and the 95 % confidence intervals.....	12
9.4 Instrument noise	13
9.5 Diffuse rms-granularity	14
9.6 Uncertainty of the rms-granularity result.....	14
9.7 Reporting results	14
9.8 Summary of rms-granularity characterization parameters	15
Annex A (informative) Typical viewing magnifications for critical naked-eye viewing	16
Annex B (informative) Limiting the temporal frequency response of the measuring instrument	18
Annex C (informative) The effects of specimen non-uniformity.....	20
Annex D (informative) Derived constants c for subgroup sizes 10, 20, ..., 200	21
Annex E (informative) Determination of sample size for specified precision and subgroup size.....	22
Bibliography	24

ISO 10505:2009(E)**Foreword**

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 10505 was prepared by Technical Committee ISO/TC 42, *Photography*.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST ISO 10505:2011](https://standards.iteh.ai/catalog/standards/sist/c7cc9481-73c0-49ce-b9f9-5c54949eb46f/sist-iso-10505-2011)

<https://standards.iteh.ai/catalog/standards/sist/c7cc9481-73c0-49ce-b9f9-5c54949eb46f/sist-iso-10505-2011>

Introduction

This International Standard specifies procedures for measuring and computing the root mean square granularity (rms-granularity) of photographic films. Its purpose is to provide guidance in making accurate measurements, and also to provide an objective basis for comparing films. This International Standard describes a method for making accurate rms-granularity measurements in the presence of instrument noise and minor sample imperfections.

In principle, the measurement of rms-granularity is straightforward, but its determination with accuracy is not a trivial matter. Experience has shown that the preparation of an imperfection-free sample is virtually impossible in usual practice. Therefore, considerable attention has been devoted to the definition of a method of accurately estimating the rms-granularity of a film in the presence of density fluctuations not caused by the intrinsic grain structure of the film.

Research in rms-granularity (see Reference [10]) has pointed out that the inclusion of several “artefact-induced” data values in a set of several thousand “grain-produced” data values may result in large errors in the rms-granularity estimate. Under these circumstances, the traditional method for estimating rms-granularity produces higher rms-granularity estimates than the new method. It can also be shown that this method produces results that are identical to those produced by the traditional method when using artefact-free data.

In either case, it is important to bear in mind that rms-granularity is a statistical estimate which is necessarily reported with its associated confidence intervals. In addition, the measurement process recognizes and accounts for the presence of instrument noise that can affect the accuracy of the rms-granularity estimate.

[SIST ISO 10505:2011](https://standards.iteh.ai/catalog/standards/sist/c7cc9481-73c0-49ce-b9f9-5c54949eb46f/sist-iso-10505-2011)

<https://standards.iteh.ai/catalog/standards/sist/c7cc9481-73c0-49ce-b9f9-5c54949eb46f/sist-iso-10505-2011>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST ISO 10505:2011](#)

<https://standards.iteh.ai/catalog/standards/sist/c7cc9481-73c0-49ce-b9f9-5c54949eb46f/sist-iso-10505-2011>

Photography — Root mean square granularity of photographic films — Method of measurement

1 Scope

This International Standard describes a method for determining the intrinsic root mean square granularity (rms-granularity) of photographic films. Intrinsic rms-granularity refers to those density fluctuations produced solely by the distribution of developed image forming centres in the photographic emulsion.

Continuous-tone monochrome (silver absorbing species) and colour (dye absorbing species) materials coated on a transmitting support can be measured by the procedures described in this International Standard. This International Standard is intended for imaging systems with viewing magnifications between 5× and 12× (see Annex A).

The following kinds of granularity measurements are not covered by this International Standard, even though they are photographically important:

- reflecting materials (photographic papers);
- materials having emulsion coated on both sides of the support (e.g. some X-ray films);
- the estimation of the noise power spectrum (Wiener spectrum).

<https://standards.iteh.ai/catalog/standards/sist/c7cc9481-73c0-49ce-b9f9-5c54949eb46f/sist-iso-10505-2011>

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 5-2, *Photography — Density measurements — Part 2: Geometric conditions for transmission density*

ISO 5-3, *Photography — Density measurements — Part 3: Spectral conditions*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

transmittance factor

T

ratio of the measured flux transmitted by a specimen to the measured flux when the specimen is removed from the sampling aperture of the measuring device

NOTE $T = \frac{\phi_T}{\phi_J}$

where

ϕ_T is the transmitted flux;

ϕ_J is the aperture flux.

ISO 10505:2009(E)**3.2
transmission density**

D_T
 logarithm to the base 10 of the reciprocal of the transmittance factor, T

NOTE $D_T = \log_{10} 1/T$.

**3.3
microtransmittance factor**

transmittance factor of a small area of a film or plate, measured using a suitable instrument such as a microphotometer

NOTE In general, the microtransmittance factor of a uniformly exposed and developed film sample varies from point-to-point on the surface. The measured microtransmittance factor of a given film or plate can depend on the optical geometry of the instrument in which it is measured.

**3.4
microdensity**

D
 transform of the microtransmittance factor in accordance with the usual relation $D = \log_{10} 1/T$

**3.5
graininess**

sensation produced, in the mind of an observer viewing a photographic image, by random inhomogeneity in what should be structureless areas.

NOTE Graininess is a subjective quantity that is necessarily measured by psychophysical methods and, as such, is outside the scope of this International Standard.

**3.6
root mean square granularity
rms-granularity**

σ_D
 objective characterization of the spatial microdensity fluctuation of a uniformly exposed and developed photographic layer, determined in accordance with this International Standard

NOTE 1 See Reference [3].

NOTE 2 In contrast to graininess, rms-granularity is an objective quantity.

NOTE 3 The spatial fluctuation is observed when the microdensity of the layer is measured at various points over the surface and is the result of the random distribution of the absorbent species in the layer. The fluctuation in the microdensity over an area of a specimen is characterized by its standard deviation, σ_D , and is generally a function of the specimen's macrodensity. This quantity is termed the "rms-granularity" and in all conceivable cases of interest, this population parameter cannot be determined exactly because of finite sample size. The method for estimating σ_D is described in Clause 9.

NOTE 4 The relation between graininess and rms-granularity is as follows: rms-granularity is intended to be an objective correlate of graininess. The methods of measuring film rms-granularity as defined in 3.6 have been found to give values that generally correlate with the magnitude of the graininess sensation produced when images produced by the film are viewed under suitable conditions. The just-noticeable differences in graininess, detectable by observers viewing areas having a visual density of about 1,0, correspond to differences in rms-granularity of 6 % for a uniform field, of 16 % for an average scene and of 30 % for a complex or busy scene^[4]. Because rms-granularity does not account for effects encountered in multiple stage imaging processes, methods for evaluating the graininess of final images have been developed^[11]. These methods are particularly useful for comparing the image graininess of different final print formats when produced from different negative formats and film types.

3.7**specimen**

piece of photographic film or photographic plate on which rms-granularity measurements are made

NOTE The specimen can be specific or constitute a sample from a population whose rms-granularity is being determined.

3.8**diffuse conversion factor** g

factor used to convert small transmission (projection) density differences produced by most microdensitometers to small diffuse density differences, as determined in accordance with 6.2

3.9**spatial frequency passband**

part of the spatial frequency spectrum that passes through the measuring system

NOTE The spatial frequency passband is determined by the cut-off frequencies of the system on the low side and the high side of the spatial frequency. The passband characteristics required for the measuring instrument are specified in 5.2.

4 Measurement instrument**4.1 General**

This clause describes the basic elements of an instrument suitable for the measurement of rms-granularity. The generic instrument described in this clause follows the general principles for a linear, incoherent microdensitometer used in an overfilled, image-scanning mode. Microdensitometers of different designs may be employed, provided they are shown to conform to the physical optics principles required for linearity and incoherent illumination, as described in References [6], [7], [8] and [9].

<https://standards.iteh.ai/catalog/standards/sist/c7cc9481-73c0-49ce-b9f9-5c54949eb46f/sist-iso-10505-2011>

4.2 Microdensitometer**4.2.1 Apparatus**

A typical microdensitometer is shown schematically in Figure 1. Its key elements are as follows:


- light source (1): an incoherent source of suitable spectral power distribution;
- illumination filter (2), which produces spectral transmittance necessary to conform to 4.2.2;
- condenser lens (3): optics that fill the influx aperture uniformly with light;
- influx aperture (4): in the optical system shown in Figure 1, this aperture limits the area of the specimen that is illuminated in order to minimize stray light in the optical system;
- influx optics (5), which images the influx aperture (4) on the specimen at point 6;
- specimen (6): emulsion (7) facing the efflux optics;
- efflux optics (8), which collects the light transmitted by the specimen and focuses it upon the efflux aperture of the instrument;
- efflux (measuring) aperture (9): this aperture, projected back onto the specimen, determines the area of the specimen whose density is being measured; its effective size at the specimen is determined by its physical size divided by the optical magnification from the plane at point 6 to the plane at point 9;

ISO 10505:2009(E)

- collecting lens (10), which collects the light transmitted by the aperture (9) and relays it to the photodetector;

NOTE The collecting lens is omitted in some designs.

- efflux optical filter (11): spectral transmittance determined by density measurement type;
- photodetector (12), which shall have a spectral responsivity consistent with the spectral products required to produce one or more of the density measurement spectral types defined in ISO 5-3.

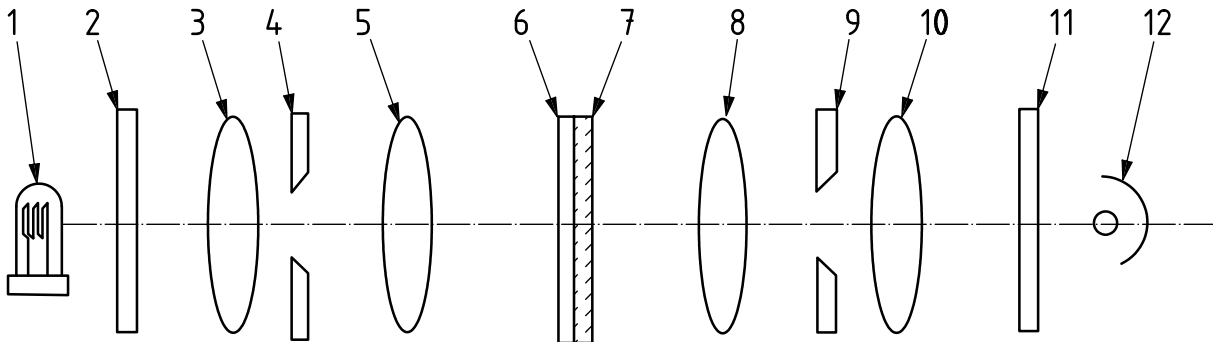

Key

- 1 light source
- 2 illumination filter
- 3 condenser lens
- 4 influx aperture
- 5 influx optics
- 6 specimen
- 7 emulsion
- 8 efflux optics
- 9 efflux (measuring) aperture
- 10 collecting lens
- 11 efflux optical filter
- 12 photodetector

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST ISO 10505:2011](https://standards.iteh.ai/catalog/standards/sist/c7cc9481-73c0-49ce-b9f9-5c54949eb46f/sist-iso-10505-2011)

<https://standards.iteh.ai/catalog/standards/sist/c7cc9481-73c0-49ce-b9f9-5c54949eb46f/sist-iso-10505-2011>

Figure 1 — Schematic representation of a typical rms-granularity measuring microdensitometer

4.2.2 Influx spectrum

The influx spectrum for rms-granularity measurements shall be as specified for transmission densitometry in ISO 5-3.

For transmission density measurements, if either the densitometer manufacturer or the user is not sure of the absence of fluorescence in the sample to be measured, the relative spectral power distribution of the incident flux S_H shall be that of the CIE standard illuminant A (ISO 5-3), modified in the infrared region to protect the sample and optical elements from excessive heat, which is typical for most transmission densitometers.

4.2.3 Influx aperture

The influx aperture shall be circular or square in shape and its image shall be concentric with that of the efflux aperture. When both apertures are referred to the plane of the specimen, the linear size of the influx aperture shall not be less than 1,5 times, nor more than 2 times, the linear size of the efflux aperture.