

---

---

**Textiles — Evaluation of the wrinkle  
recovery of fabrics — Appearance  
method**

*Textiles — Évaluation de la défroissabilité des étoffes — Méthode  
d'évaluation de l'aspect*

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[ISO 9867:2009](https://standards.iteh.ai/catalog/standards/sist/5eb1a4b-871b-43b1-a305-01ce5cb0f1ca/iso-9867-2009)

<https://standards.iteh.ai/catalog/standards/sist/5eb1a4b-871b-43b1-a305-01ce5cb0f1ca/iso-9867-2009>



**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 9867:2009

<https://standards.iteh.ai/catalog/standards/sist/5eb1a4b-871b-43b1-a305-01ce5cb0f1ca/iso-9867-2009>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2009

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

## Contents

Page

Foreword.....	iv
1 Scope .....	1
2 Normative references .....	1
3 Principle .....	1
4 Apparatus .....	1
5 Atmospheres for conditioning and testing .....	4
6 Test specimens .....	4
7 Procedure .....	4
8 Evaluation .....	5
9 Expression of results .....	5
10 Test report .....	6
Annex A (informative) Summary of an international interlaboratory study on wrinkle recovery of fabrics .....	7
Annex B (informative) Digital description of the ISO wrinkle replicas .....	8
Bibliography .....	22

[ISO 9867:2009](https://standards.iteh.ai/catalog/standards/sist/5eb1a4b-871b-43b1-a305-01ce5cb0f1ca/iso-9867-2009)

<https://standards.iteh.ai/catalog/standards/sist/5eb1a4b-871b-43b1-a305-01ce5cb0f1ca/iso-9867-2009>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 9867 was prepared by Technical Committee ISO/TC 38, *Textiles*, Subcommittee SC 2, *Cleansing, finishing and water resistance tests*.

This second edition cancels and replaces the first edition (ISO 9867:1991), which has been technically revised. Annex B (informative) has been added.

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**  
ISO 9867:2009  
<https://standards.iteh.ai/catalog/standards/sist/5eb1a4b-871b-43b1-a305-01ce5cb0f1ca/iso-9867-2009>

# Textiles — Evaluation of the wrinkle recovery of fabrics — Appearance method

## 1 Scope

This International Standard describes a method for evaluating the appearance of textile fabrics after induced wrinkling. It is applicable to fabrics made from any fibre or combination of fibres.

NOTE A digital description of the ISO wrinkle replicas is given in Annex B.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 105-A03, *Textiles — Tests for colour fastness— Part A03: Grey scale for assessing staining*

ISO 139, *Textiles — Standard atmospheres for conditioning and testing*

[ISO 9867:2009](https://standards.iteh.ai/catalog/standards/sist/5eb1a4b-871b-43b1-a305-01ce5cb0f1ca/iso-9867-2009)

<https://standards.iteh.ai/catalog/standards/sist/5eb1a4b-871b-43b1-a305-01ce5cb0f1ca/iso-9867-2009>

## 3 Principle

A test specimen is wrinkled under specified atmospheric conditions in a wrinkling device under a pre-determined load for a prescribed period of time. The specimen is reconditioned in a standard atmosphere and evaluated for appearance by comparison with three-dimensional wrinkle recovery replicas.

## 4 Apparatus

4.1 **Wrinkle tester** <sup>1)</sup> (see Figure 1).

4.2 **Three-dimensional wrinkle recovery replicas** <sup>2)</sup> (see Figure 2).

---

1) For details of the source of supply of wrinkle testers, apply to national standards institutions. The apparatus shown in Figure 1 is for illustrative purposes only. A suitable product is available from AATCC Technical Center, One Davis Drive, P.O. Box 12215, Research Triangle Park, North Carolina 27709-2215, USA; Tel: +1 919-549-8141; Fax: +1 919-549-8933; <http://www.aatcc.org>. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of the product named. Equivalent products may be used if they can be shown to lead to the same results.

2) Wrinkle Recovery Replica is the trade name of a product supplied by the American Association of Textile Chemists and Colorists. These replicas may be obtained from AATCC Technical Center, One Davis Drive, P.O. Box 12215, Research Triangle Park, North Carolina 27709-2215, USA; Tel: +1 919-549-8141; Fax: +1 919-549-8933; <http://www.aatcc.org>. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of the product named. Equivalent products may be used if they can be shown to lead to the same results.

**4.3 Lighting and evaluation area**, in a darkened room, using the overhead lighting arrangement shown in Figure 3 and comprising the items described in 4.3.1 to 4.3.3.

The lamp dimensions should be chosen to extend beyond the overall surface of the test specimen and replicas, when used for the assessment.

**4.3.1 Two cool white (CW) fluorescent lamps**, without a baffle or glass, a minimum of 2 m in length each, placed side by side.

**4.3.2 One white enamel reflector**, without a baffle or glass.

**4.3.3 One thick plywood viewing board**, painted grey to match the No. 2 rating on the grey scale for assessing staining specified in ISO 105-A03.

The evaluation area shall be maintained under the conditions specified in Clause 5 b).

**4.4 Clothes hangers with clips**, to hang test specimens for conditioning and grading.



Figure 1 — Wrinkle tester


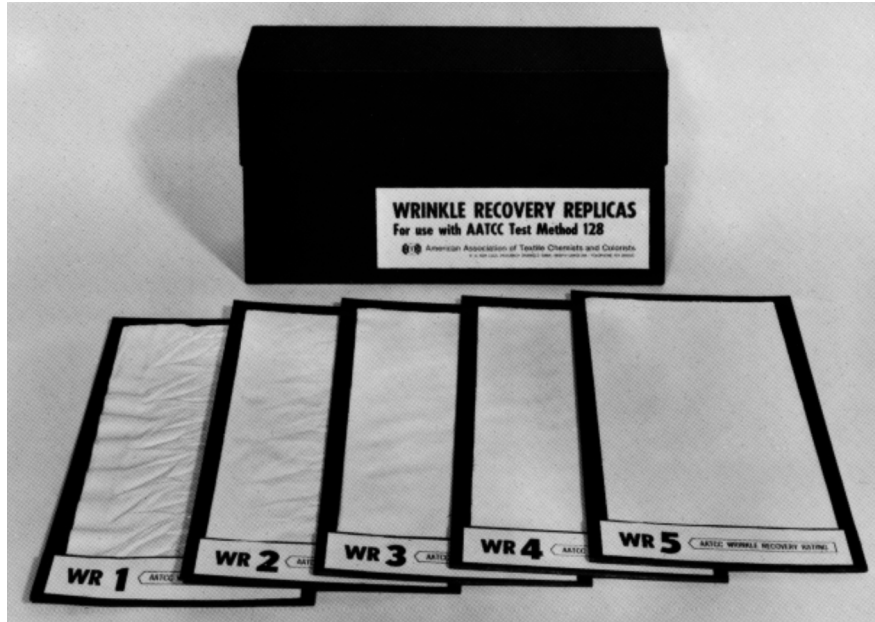


Figure 2 — Wrinkle recovery replicas

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

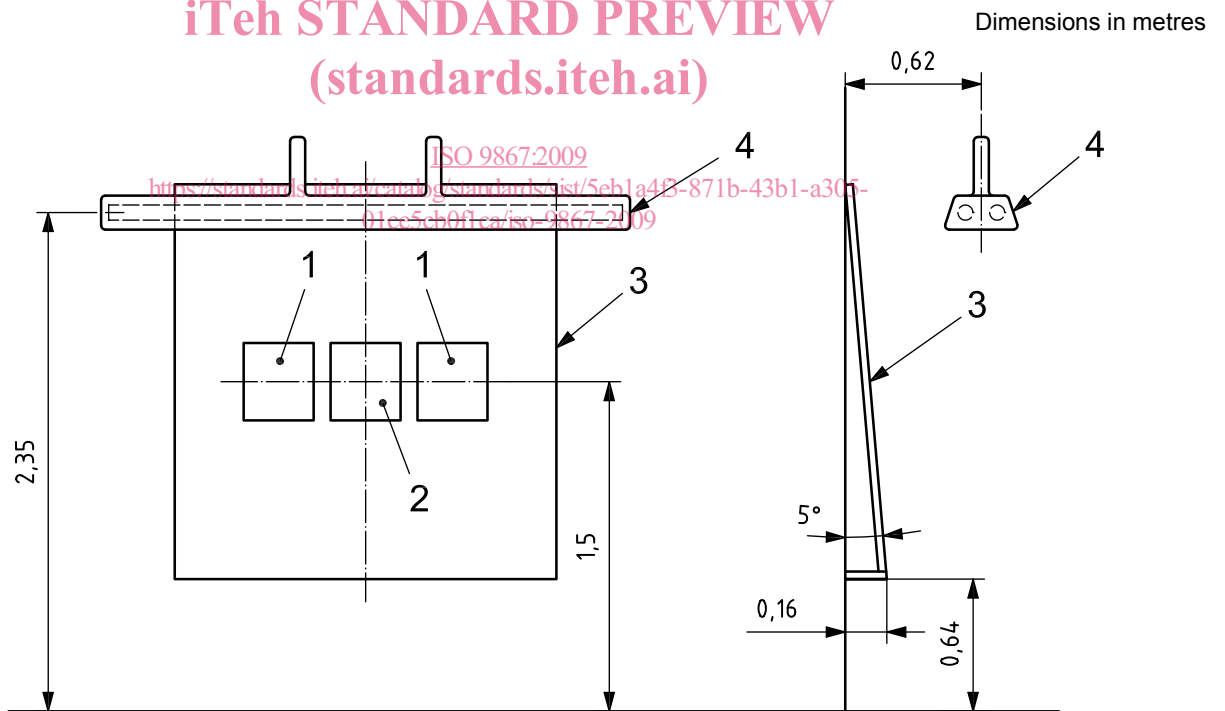

**Key**

- 1 replica
- 2 test specimen
- 3 board for viewing
- 4 example of fluorescent lamp placement

Figure 3 — Lighting equipment for viewing test specimens

## 5 Atmospheres for conditioning and testing

Unless otherwise indicated, the following atmospheres, as specified in ISO 139, shall be used:

- a) for preconditioning, an atmosphere having a relative humidity of 10 % or lower and a temperature of 50 °C or lower;
- b) for conditioning and testing, an atmosphere having a relative humidity of  $(65 \pm 4)$  % and a temperature of  $(20 \pm 2)$  °C or  $(27 \pm 2)$  °C;
- c) for alternative standard atmospheres, see ISO 139.

## 6 Test specimens

### 6.1 Preparation

From the fabric to be tested, cut three specimens, each measuring 150 mm × 280 mm, and each with the long dimension running in the warp direction of a woven fabric or the wale direction of a knitted fabric. Identify each specimen along one edge of the face side.

Cut the specimens from an area of the fabric that is free from wrinkles. If any wrinkles are unavoidably present in the test specimens, press each specimen lightly with a steam iron before conditioning.

### 6.2 Conditioning

Precondition and then condition the test specimens in accordance with ISO 139 in the respective atmospheres specified in Clause 5.

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)  
<https://standards.iteh.ai/catalog/standards/sist/5eb1a4b-871b-43b1-a305-01ce5cb0f1ca/iso-9867-2009>

## 7 Procedure

- 7.1 Raise the top flange of the wrinkle tester (4.1) and hold it in the top position with the locking pin.
- 7.2 Wrap one long edge (i.e. the 280 mm side) of a preconditioned and conditioned test specimen (see 6.2) around the top flange of the wrinkle tester, with the face side of the specimen on the outside, and clamp it in position using the steel spring and clamp provided. Arrange the ends of the specimen so that they are opposite the opening in the spring clamp.
- 7.3 Wrap the opposite long edge of the specimen around the bottom flange and clamp it as described in 7.2.
- 7.4 Adjust the specimen by pulling on its bottom edge so that it lies smooth without sagging between the top and bottom flanges.
- 7.5 Withdraw the locking pin and lower the top flange gently with one hand until it comes to rest.
- 7.6 Immediately place a total mass of 3 500 g on the top flange and record the time.

There may be differences in the weights supplied with different wrinkle testers. If necessary, add additional weights to the top flange to achieve a total mass of 3 500 g on the top flange.

- 7.7 After 20 min, remove the mass, the springs and the clamps. Raise the top flange and gently remove the specimen from the wrinkle tester so as not to distort any induced wrinkles.
- 7.8 With a minimum of handling, place the shorter edge (i.e. the 150 mm side) under the clips on the clothes hanger (4.4) and allow the specimen to hang vertically in the long direction.
- 7.9 After 24 h in the standard atmosphere [see Clause 5 b)], gently remove the hanger with the specimen and transfer it to the evaluation area (4.3).



## 8 Evaluation

**8.1** Three trained observers shall rate each test specimen independently.

Since previous tests have proven that specimens change in appearance during the first few hours, it is important that accurate times be observed and that a minimum time elapse while the three observers are evaluating the specimens. Because of these changing conditions, the duration of recovery before rating for this method has been standardized at 24 h.

**8.2** Mount the test specimen on the viewing board as illustrated in Figure 3, with the warp or wale direction vertical. Place three-dimensional wrinkle recovery replicas (4.2), one on each side of the test specimen, to facilitate comparative rating. Mount replicas 1, 3 or 5 on the left side and 2 or 4 on the right side.

The overhead fluorescent light shall be the only light source for the viewing board, and all other lights in the room shall be turned off.

It has been the experience of many observers that light reflected from the side walls near the viewing board can interfere with the rating results. It is recommended that the side walls be painted black, or that blackout curtains be mounted on either side of the viewing board, to eliminate reflective interference.

**8.3** The observer shall stand directly in front of the specimen, 1,22 m away from the bottom front of the board.

NOTE It has been found that normal variations in the height of the observer above and below the arbitrary 1,50 m eye level have no significant effect on the rating given.

**8.4** Assign the number of the replica which most closely matches the appearance of the test specimen (see Table 1).

NOTE A No. 5 rating is equivalent to the WR-5 replica and represents the smoothest appearance and best retention of the original appearance, while a No. 1 rating is equivalent to the WR-1 replica and represents the poorest appearance and poorest retention of the original appearance.

**8.5** Similarly, the observer independently rates the other two test specimens. The other two observers proceed in the same manner, assigning ratings independently.

**Table 1 — Fabric smoothness ratings**

Rating No.	Fabric appearance
5	An appearance equivalent to the WR-5 replica
4	An appearance equivalent to the WR-4 replica
3	An appearance equivalent to the WR-3 replica
2	An appearance equivalent to the WR-2 replica
1	An appearance equivalent to or worse than the WR-1 replica

## 9 Expression of results

Calculate the average of the nine observations for each sample and express the results to the nearest half-rating.

NOTE Annex A gives a summary of the report of an international interlaboratory study on the wrinkle recovery of fabrics.

## 10 Test report

The test report shall include the following information:

- a) a reference to this International Standard, i.e. ISO 9867:2009;
- b) all details necessary for the identification of the sample tested;
- c) the average of the nine observations made for each sample, to the nearest half-rating;
- d) the conditioning atmosphere used for testing;
- e) details of any deviation from the specified procedure.

## iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 9867:2009](https://standards.iteh.ai/catalog/standards/sist/5eb1a4b-871b-43b1-a305-01ce5cb0f1ca/iso-9867-2009)

<https://standards.iteh.ai/catalog/standards/sist/5eb1a4b-871b-43b1-a305-01ce5cb0f1ca/iso-9867-2009>

## **Annex A** (informative)

### **Summary of an international interlaboratory study on wrinkle recovery of fabrics**

In the spring of 1986, eleven laboratories agreed to participate in an interlaboratory trial to determine the reproducibility of this method. Data was received from nine of the laboratories: in Belgium, South Africa, Sweden, the United Kingdom and five laboratories in the United States.

The within-laboratory variability demonstrated in this study is negligible and, while there is more variability between laboratories, that variability is within statistical control. From the data presented, it can be concluded that this method of test does provide a test procedure which will allow laboratories to compare the wrinkle behaviour of fabrics in a reproducible manner.

NOTE The full study containing all raw data is available from the secretariat of ISO/TC 38/SC 2 (ANSI) upon request.

## **iTeh STANDARD PREVIEW** (standards.iteh.ai)

[ISO 9867:2009](#)

<https://standards.iteh.ai/catalog/standards/sist/5eb1a4b-871b-43b1-a305-01ce5cb0f1ca/iso-9867-2009>