

---

---

**Rubber — Determination of the  
aromaticity of oil in vulcanized rubber  
compounds**

*Caoutchouc — Détermination de l'aromaticité des huiles dans les  
mélanges vulcanisés*

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[ISO 21461:2009](https://standards.iteh.ai/catalog/standards/sist/0579fe69-32fb-47aa-a278-6c23d0e35dda/iso-21461-2009)

[https://standards.iteh.ai/catalog/standards/sist/0579fe69-32fb-47aa-a278-  
6c23d0e35dda/iso-21461-2009](https://standards.iteh.ai/catalog/standards/sist/0579fe69-32fb-47aa-a278-6c23d0e35dda/iso-21461-2009)



**PDF disclaimer**

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 21461:2009

<https://standards.iteh.ai/catalog/standards/sist/0579fe69-32fb-47aa-a278-6c23d0e35dda/iso-21461-2009>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2009

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

## Contents

Page

Foreword.....	iv
<b>1 Scope .....</b>	<b>1</b>
<b>2 Normative references .....</b>	<b>1</b>
<b>3 Terms and definitions.....</b>	<b>1</b>
<b>4 Reagents and materials .....</b>	<b>1</b>
<b>5 Apparatus .....</b>	<b>2</b>
<b>6 Procedure .....</b>	<b>2</b>
<b>7 Calculation.....</b>	<b>4</b>
<b>8 Precision.....</b>	<b>5</b>
<b>9 Test report .....</b>	<b>5</b>
<b>Annex A (informative) <sup>1</sup>H NMR spectra of extracts from compounds containing aromatic oil (Figures A.1 and A.3) and MES oil (Figures A.2 and A.4) .....</b>	<b>6</b>
<b>Annex B (informative) <sup>1</sup>H NMR analysis results for typical rubber compounds (those used for the interlaboratory trial described in Clause 8) .....</b>	<b>8</b>
<b>Annex C (informative) Preparation of clean samples of rubber compounds from tyres .....</b>	<b>9</b>

ISO 21461:2009

<https://standards.iteh.ai/catalog/standards/sist/0579fe69-32fb-47aa-a278-6c23d0e35dda/iso-21461-2009>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 21461 was prepared by Technical Committee ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 3, *Raw materials (including latex) for use in the rubber industry*.

This second edition cancels and replaces the first edition (ISO 21461:2006), to which a new annex (Annex C) has been added describing a procedure for the preparation of clean samples from the various components of a tyre.

ISO 21461 is referenced in European regulation (EC) No. 1907/2006 concerning the Registration, Evaluation, Authorization and Restriction of Chemicals (REACH) as the method used to measure and calculate bay protons.

# Rubber — Determination of the aromaticity of oil in vulcanized rubber compounds

**WARNING** — Persons using this International Standard should be familiar with normal laboratory practice. This standard does not purport to address all the safety problems, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to ensure compliance with any national regulatory conditions.

**IMPORTANT** — The electronic file of this document contains colours which are considered to be useful for the correct understanding of the document. Users should therefore consider printing this document using a colour printer.

## 1 Scope

This International Standard provides a method for the selective determination of polyaromaticity of oil in vulcanized rubber compounds. The method is based on nuclear magnetic resonance (NMR) spectrometry.

iTeh STANDARD PREVIEW

## 2 Normative references (standards.iteh.ai)

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1407, *Rubber — Determination of solvent extract*

## 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

### 3.1

**polycyclic aromatic hydrocarbon**

**PAH**

organic compound consisting of two or more aromatic rings, certain carbon atoms of which are common to two or three rings

## 4 Reagents and materials

All reagents shall be of recognized analytical grade unless otherwise specified.

### 4.1 Extraction solvent

4.1.1 Acetone.

### 4.2 Sample preparation reagents

4.2.1 *n*-Hexane.

4.2.2 Methylene chloride.

4.2.3 Nitrogen, purity > 99,9 %, for protecting the extract from oxidation during drying.

4.2.4  $\text{CDCl}_3$ , 99,9 %, NMR grade.

4.2.5 Hexamethyldisiloxane (HMDS), 99,5 %, NMR grade, or tetramethylsilane (TMS), 99,5 %, NMR grade.

## 5 Apparatus

5.1 Analytical balance, accurate to 0,1 mg.

5.2 Extraction apparatus, as specified in ISO 1407.

5.3 Steam bath.

5.4 Extract purification apparatus, consisting of the items specified in 5.4.1 to 5.4.5:

5.4.1 2 cm<sup>3</sup>, 5 cm<sup>3</sup> and 25 cm<sup>3</sup> or 30 cm<sup>3</sup> syringes, with conical end fittings, compatible with solid-phase extraction (SPE) columns for manual purification operations.

5.4.2 SPE cartridge containing 500 mg of silica gel. <sup>1)</sup>

5.4.3 Laboratory glassware.

5.4.4 (Optional) Solid-phase extraction equipment, connected to a vacuum pump, for simultaneous purification of many extracts.

5.4.5 Disposable needles. <https://standards.iteh.ai/catalog/standards/sist/0579fe69-32fb-47aa-a278-6c23d0e35dda/iso-21461-2009>

5.5 NMR spectrometer, at least 200 MHz, preferably with the following acquisition parameters:

probe:	<sup>1</sup> H;
pulse phase:	30°;
spectral width:	– 2 ppm to + 12 ppm;
number of scans:	256;
relaxation delay:	2 s.

## 6 Procedure

### 6.1 Sample extraction

6.1.1 The laboratory sample shall be of sufficient size to provide at least 0,35 g of extracted oil.

Annex C gives guidance on the preparation of laboratory samples from tyres.

---

1) VARIAN BOND ELUT JR-SI, 500 mg, part number 12162037B, is an example of a suitable product available commercially. This information is given for the convenience of users of this International Standard and does not constitute an endorsement by ISO of this product. Equivalent products may be used.

**6.1.2** Pass the sample between the rolls of a laboratory mill to reduce its thickness to less than 0,7 mm or, alternatively, cut the sample in pieces smaller than 1 mm × 1 mm × 2 mm.

**6.1.3** Wrap the sample in a small filter paper and insert it in the extractor (5.2), or fill the extractor with the small cut pieces. Fill the flask of the extractor with acetone (4.1.1) and extract for 8 h.

**6.1.4** Evaporate the extract to dryness under a stream of nitrogen (4.2.3) to prevent oxidation.

## 6.2 Purification of extract

**6.2.1** Weigh, to the nearest 0,1 mg, 100 mg ± 5 mg of dry extract into a vial and dissolve it in 1 cm<sup>3</sup> of methylene chloride (4.2.2). There may be some insoluble matter.

**6.2.2** Condition the SPE cartridge (5.4.2) by injecting 5 cm<sup>3</sup> of *n*-hexane (4.2.1) onto it using a 5 cm<sup>3</sup> syringe (see 5.4.1).

**6.2.3** When nearly all the *n*-hexane has drained out, transfer quantitatively the methylene chloride solution onto the SPE cartridge and start collecting the eluate in a beaker or glass bottle. Use an additional 0,5 cm<sup>3</sup> of methylene chloride to rinse the vial and ensure complete transfer of the evaporation residue to the cartridge.

**6.2.4** When nearly all the methylene chloride solution has been absorbed onto the SPE cartridge, start eluting the non-polar fraction with 25 cm<sup>3</sup> of hexane. During the elution, maintain a constant solvent flow not exceeding a rate of 5 cm<sup>3</sup>/min.

**6.2.5** Stop collecting the purified fraction when all of the 25 cm<sup>3</sup> of *n*-hexane has been added to the SPE cartridge.

**6.2.6** Evaporate the eluate to dryness under a stream of nitrogen to prevent oxidation.

**6.2.7** Weigh the dry residue to the nearest 0,1 mg and calculate the percentage recovered.

**6.2.8** Repeat the extract purification procedure two more times, taking a fresh portion of extract each time.

**6.2.9** Calculate the average of the three percentage recovery values. If the individual values obtained are within ± 5 % of the average, proceed to 6.3. Otherwise, repeat the sample extraction and extract purification procedure until three values within ± 5 % of the average are obtained.

## 6.3 NMR analysis

### 6.3.1 General

The aromatic character of the oil present in the dry residue obtained in 6.2.7 is determined by means of <sup>1</sup>H NMR spectroscopy.


### 6.3.2 Principle

The molecular structure of non-linear PAHs with three or more fused rings contains a characteristic three-sided concave area, located at the periphery of the molecule. The hydrogen atoms in this area are called bay region hydrogens (see Figure 1).

<sup>1</sup>H NMR spectroscopy can identify and quantify selectively the hydrogen atoms in the bay region, which are characteristic of aromatic oils.

This method describes a procedure for determining the percentage of bay region hydrogens (% H<sub>Bay</sub>) in a sample solution by <sup>1</sup>H NMR, thus giving an indication of the aromatic character of the oil.

The higher the percentage of bay region hydrogens, the higher the aromaticity.

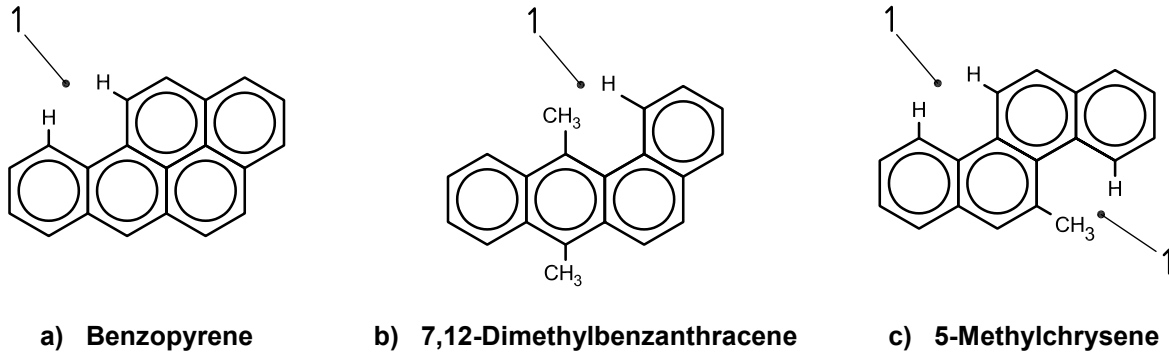

**Key**

1 bay region

**Figure 1**

**6.3.3 NMR measurement**

**6.3.3.1** Dissolve one of the dry residues obtained in 6.2.7 and 6.2.8 in a glass vial in about 1 cm<sup>3</sup> of CDCl<sub>3</sub> (4.2.4). If necessary, enhance dissolution by using a small magnetic stirrer or mechanical shaker; if this is not enough, add more CDCl<sub>3</sub>.

**6.3.3.2** Prepare the NMR tube by adding the sample solution prepared in 6.3.3.1 and a few drops of reference solvent, HMDS or TMS (see 4.2.5).

**6.3.3.3** Acquire the free induction decay (FID) signal and apply a Fourier transform, multiplying by an exponential function (LB = 0,3 Hz) to obtain the spectrum (see the examples in Annex A). Adjust the resonance of the reference (HMDS or TMS) peak to 0,0 ppm.

**6.3.3.4** Integrate the spectrum and record the following areas:

- $I_0$  the aromatic area, from 6,0 ppm to 9,5 ppm, including the CHCl<sub>3</sub> signal (impurity contained in CDCl<sub>3</sub>);
- $I_{\text{CHCl}_3}$  the CHCl<sub>3</sub> signal (located around 7,2 ppm);
- $I_1$  the pure aromatic area (=  $I_0 - I_{\text{CHCl}_3}$ );
- $I_2$  the area of the bay region from 8,3 ppm to 9,5 ppm;
- $I_3$  the area of the aliphatic and ethylenic regions from 0,2 ppm to 5,8 ppm.

**6.3.3.5** Perform NMR measurements on each of the three purified extracts obtained in 6.2.7 and 6.2.8.

**7 Calculation**

For each of the three purified extracts, calculate the percentage of bay region hydrogens (% H<sub>Bay</sub>) to two decimal places using the following equation:

$$\% \text{ H}_{\text{Bay}} = \frac{I_2}{I_1 + I_3} \times 100$$

where the symbols are as defined in 6.3.3.4.



## 8 Precision

An interlaboratory test programme was carried out in which five laboratories participated. The percentage of bay region hydrogens was determined for three different rubber samples. The number of within-laboratory replicates was two, and the time span for repeatability was 7 days. The precision calculations to express repeatability and reproducibility were performed in accordance with ISO/TR 9272, *Rubber and rubber products — Determination of precision for test method standards*. A type 2 interlaboratory precision was determined.

The results are given in Table 1.

**Table 1 — Precision data for % H<sub>Bay</sub> determined by NMR**

Sample	Mean level %	Within-laboratory			Between laboratories		
		$s_r$	$r$	( $r$ )	$s_R$	$R$	( $R$ )
Compound No. 1: 20 phr of distilled aromatic (DAE) oil	0,48	0,045	0,13	26,7	0,047	0,13	27,9
Compound No. 2: 20 phr of treated distilled aromatic (TDAE) oil	0,19	0,036	0,1	55,2	0,045	0,13	69,5
Compound No. 3: 20 phr of mild extract solvent (MES) oil	0,07	0,033	0,09	142	0,046	0,13	197,9
Pooled values		0,038	0,11	74,6	0,046	0,13	98,4
Number of laboratories $p = 5$ , number of materials $q = 3$ , number of replicates $n = 2$							
$s_r$ is the within-laboratory standard deviation; $s_R$ is the between-laboratories standard deviation; $r$ is the repeatability, in measurement units; $(r)$ is the repeatability, in percent (these values represent percent relative, i.e. percent of a percent); $R$ is the reproducibility, in measurement units; $(R)$ is the reproducibility, in percent (these values represent percent relative, i.e. percent of a percent).							

## 9 Test report


The test report shall include the following information:

- a reference to this International Standard (ISO 21461);
- all details necessary for the identification of the rubber sample(s) tested;
- details of the silica gel used in the solid-phase extraction cartridge (5.4.2);
- the three percentage recovery values calculated in 6.2.7 and 6.2.8;
- the average values of  $I_0$ ,  $I_{\text{CHCl}_3}$ ,  $I_1$ ,  $I_2$ ,  $I_3$  and % H<sub>Bay</sub>;
- any unusual features noted during the determination;
- details of any operation not included in this International Standard, as well as details of any aspect regarded as optional, such as the NMR parameters in 5.5 if different from those specified;
- the date of the test.

## Annex A (informative)

### <sup>1</sup>H NMR spectra of extracts from compounds containing aromatic oil (Figures A.1 and A.3) and MES oil (Figures A.2 and A.4)

#### A.1 Complete spectra

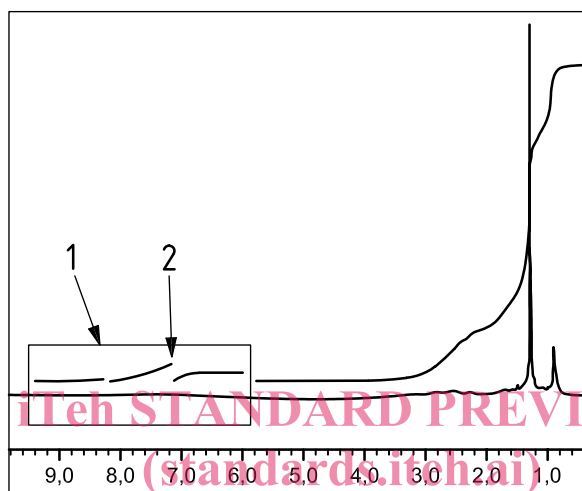


**Key**

- 1 aromatic region
- 2 CHCl<sub>3</sub> impurity

ISO 21461:2009  
<https://standards.iteh.ai/catalog/standards/sist/0579fe69-32fb-47aa-a278-6c23d0e35dda/iso-21461-2009>

**Figure A.1 — <sup>1</sup>H NMR spectrum of an extract from a compound containing aromatic oil**

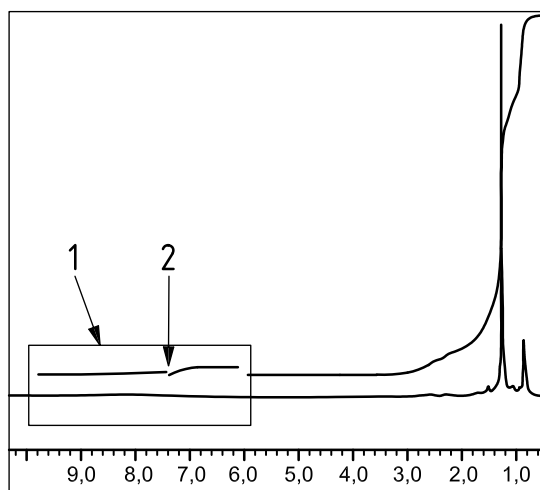


**Key**

- 1 aromatic region
- 2 CHCl<sub>3</sub> impurity

**Figure A.2 — <sup>1</sup>H NMR spectrum of an extract from a compound containing MES oil**


## A.2 Zoom-in on aromatic region with (circled) the specific “bay region”

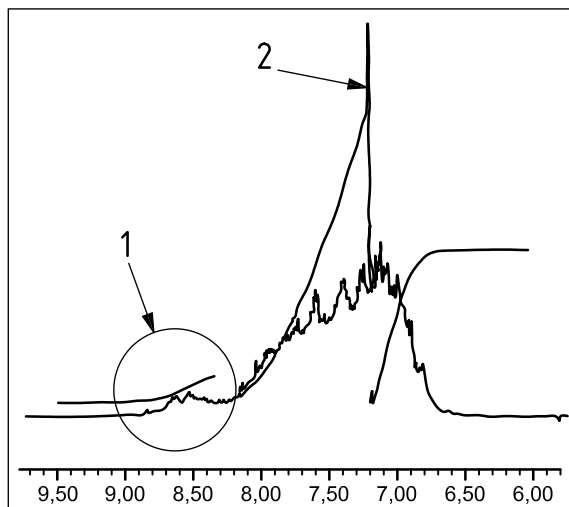**Key**

- 1 bay region (8,3 ppm to 9,5 ppm)
- 2 CHCl<sub>3</sub> impurity

Figure A.3 — Aromatic region of the <sup>1</sup>H NMR spectrum of an extract from a compound containing aromatic oil (% H<sub>Bay</sub> = 0,46)

iTeh STANDARD PREVIEW  
(standards.iteh.ai)

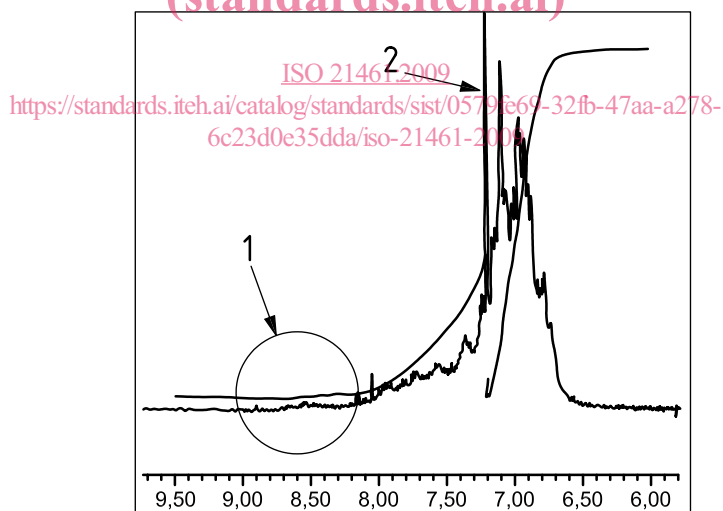**Key**

- 1 bay region (8,3 ppm to 9,5 ppm)
- 2 CHCl<sub>3</sub> impurity

Figure A.4 — Aromatic region of the <sup>1</sup>H NMR spectrum of an extract from a compound containing MES oil (% H<sub>Bay</sub> = 0,04)