

ISO

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION

ISO RECOMMENDATION R 944

iTeh STANDARD PREVIEW
PEARLITIC MALLEABLE CAST IRON
(standards.itih.ai)

ISO/R 944:1969

<https://standards.itih.ai/catalog/standards/sist/e780e751-28f4-48f9-bc1f-b339000c211f/iso-r-944-1969>

1st EDITION
January 1969

COPYRIGHT RESERVED

The copyright of ISO Recommendations and ISO Standards belongs to ISO Member Bodies. Reproduction of these documents, in any country, may be authorized therefore only by the national standards organization of that country, being a member of ISO.

For each individual country the only valid standard is the national standard of that country.

Printed in Switzerland

Also issued in French and Russian. Copies to be obtained through the national standards organizations.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO/R 944:1969

<https://standards.iteh.ai/catalog/standards/sist/e780e751-28f4-48f9-bc1f-b339000c211f/iso-r-944-1969>

BRIEF HISTORY

The ISO Recommendation R 944, *Pearlitic malleable cast iron*, was drawn up by Technical Committee ISO/TC 25, *Cast iron*, the Secretariat of which is held by the British Standards Institution (BSI).

Detailed work on this question by the Technical Committee led, in 1966, to the adoption of a Draft ISO Recommendation.

In February 1967, this Draft ISO Recommendation (No. 1195) was circulated to all the ISO Member Bodies for enquiry. It was approved, subject to a few modifications of an editorial nature, by the following Member Bodies :

Argentina	Greece	South Africa, Rep. of
Belgium	India	Sweden
Brazil	Israel	Switzerland
Canada	Korea, Rep. of	Thailand
Chile	Netherlands	Turkey
Czechoslovakia	New Zealand	U.A.R.
Finland	Norway	United Kingdom
France	Portugal 4:1969	Yugoslavia
Germany	Romania	

Two Member Bodies opposed the approval of the Draft :

Australia
Italy

The Draft ISO Recommendation was then submitted by correspondence to the ISO Council, which decided, in January 1969, to accept it as an ISO RECOMMENDATION.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO/R 944:1969

<https://standards.iteh.ai/catalog/standards/sist/e780e751-28f4-48f9-bc1f-b339000c211f/iso-r-944-1969>

PEARLITIC MALLEABLE CAST IRON

1. SCOPE

This ISO Recommendation refers to the characteristics of pearlitic malleable cast iron and its classification by mechanical properties. Details are also included on testing conditions, dimensions of test bars and sampling.

2. GENERAL

iTeh STANDARD PREVIEW
(standards.iteh.ai)

2.1 Malleable cast iron is a heat-treated iron-carbon alloy, which solidifies in the as-cast condition with a graphite-free structure, i.e. the total carbon content at the moment of solidification is present in the dissolved form and in the combined form as cementite (Fe_3C).

<https://standards.iteh.ai/catalog/standards/sist/e780e751-28f4-48f9-bc1f-b339000e211f/iso-r-944-1969>

2.2 Three groups of malleable cast iron are specified, differentiated by temperature and time cycle of the annealing process, by the annealing atmosphere and by the properties resulting therefrom, as follows :

- whiteheart malleable cast iron (see ISO Recommendation R 942);
- blackheart malleable cast iron (see ISO Recommendation R 943);
- pearlitic malleable cast iron (covered by this ISO Recommendation).

3. CHARACTERISTICS OF PEARLITIC MALLEABLE CAST IRON

The microstructure has a matrix essentially, according to the grade specified, of pearlite or other transformation products of austenite. Tempered carbon is also present. The microstructure should not contain primary or flake graphite.

4. MECHANICAL PROPERTIES

4.1 Tensile strength, proof stress, elongation

The minimum tensile strength, proof stress and elongation of grades A, B, C, D and E should be in accordance with the values included in Table 1.

TABLE 1 – Minimum mechanical properties of pearlitic malleable cast iron

Grade	Diameter of test bar	Tensile strength		0.5 % proof stress **		0.2 % proof stress **		Elongation ($L_0 = 3d$)
	mm	kgf/mm ²	tonf/in ²	kgf/mm ²	tonf/in ²	kgf/mm ²	tonf/in ²	%
A*	15	70	44.4	55	34.9	50	31.7	2
B	15	65	41.3	43	27.3	39	24.8	3
C	15	55	34.9	36	22.9	33	21.0	4
D	15	50	31.7	32	20.3	30	19.0	5
E	15	45	28.6	28	17.8	26	16.5	7

* Oil quenched and subsequently tempered.

** In cases of dispute regarding the proof stress values, the value for the 0.5 % proof stress should be binding.

4.2 Brinell hardness (for information only)

The Brinell hardness values, measured at an agreed point on the casting, should be within the range of values, which are given for information only, in Table 2.

ISO/R 944:1969
<http://standards.iteh.ai/catalog/standards/sist/780-751-38f1-489-bc1f-b339000c211f/iso-r-944-1969>
 TABLE 2 – Brinell hardness of pearlitic malleable cast iron

Grade	Brinell hardness, HB
A	240 to 285
B	210 to 250
C	190 to 240
D	170 to 230
E	150 to 200

5. TESTING CONDITIONS

5.1 Tensile test

For the tensile test (tensile strength, proof stress, elongation), test bars in accordance with section 6 should be used.

5.2 Brinell hardness test

The Brinell hardness test should be carried out in accordance with ISO Recommendation R 184, *Brinell hardness test for grey cast iron*.

6. TEST BAR DIMENSIONS

Test bars used for the tensile test (see Figure and Table 3) should be separately cast and should be unmachined.

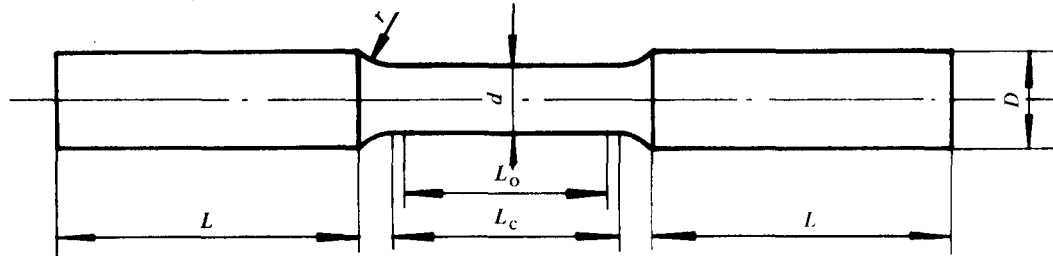


FIGURE – Tensile test bar

TABLE 3 – Dimensions of tensile test bar

Diameter d	Tolerances on diameter d	Nominal sectional area S_o	Shank dimensions *		Gauge length $L_o = 3d$	Minimum parallel length L_c	Radius at shoulder r
			Diameter D	Length L^{**}			
mm	mm	mm ²	mm	mm	mm	mm	mm
15	+0.7 0	176.7	19	60	45	50	8

* If necessary, the shanks may be modified to suit the grips of the testing machine available.

** The minimum length L should fit the full length of the grips of the testing machine available.

<https://standards.iteh.ai/catalog/standards/sist/e780e751-28f4-48d9-bc1f-b339000c211f/iso-r-944-1969>

7. SAMPLING

- 7.1 The minimum number of test bars to be provided should be one set of test bars representing each two hours of pouring, and sufficient test bars should be heat-treated to ensure adequate quality control.
- 7.2 By agreement between the purchaser and the manufacturer, if small batches of castings are being produced, one tensile test bar should be tested from every heat or every cast of metal.
- 7.3 Two further tensile test bars should be available for purposes of retest if necessary.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO/R 944:1969

<https://standards.iteh.ai/catalog/standards/sist/e780e751-28f4-48f9-bc1f-b339000c211f/iso-r-944-1969>

Date of the first printing :
March 1969