# INTERNATIONAL STANDARD

ISO 6363-4

Second edition 2012-07-15

Wrought aluminium and aluminium alloys — Cold-drawn rods/bars, tubes and wires —

Part 4:

Drawn rectangular bars and wires — Tolerances on form and iTeh STdimensions PREVIEW

(standards itch ai) Aluminium et alliages d'aluminium corroyés — Barres, tubes et fils étirés à froid —

https://standards.itel Partie 13: Barres rectangulaires et fils étirés — Tolérances sur forme et dimensions -6363-4-2012



# iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 6363-4:2012 https://standards.iteh.ai/catalog/standards/sist/e157fbef-5dea-4ffb-af05-78b2b71f695a/iso-6363-4-2012



#### **COPYRIGHT PROTECTED DOCUMENT**

© ISO 2012

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org
Published in Switzerland

Cor	<b>ntents</b>	Page
Fore	word	iv
1	Scope	1
2	Normative references	
3	Terms and definitions	
4	Materials	1
5	Tolerances on form and dimensions	2
5.1	Tolerances on width and thickness	2
5.2	Fixed-length tolerances Squareness of cut ends Corner radii	3
5.3	Squareness of cut ends	3
5.4	Corner radii	3
5.5	Form tolerances	4
Biblio	ography	7

# iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 6363-4:2012 https://standards.iteh.ai/catalog/standards/sist/e157fbef-5dea-4ffb-af05-78b2b71f695a/iso-6363-4-2012

#### **Foreword**

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 6363-4 was prepared by Technical Committee ISO/TC 79, *Light metals and their alloys*, Subcommittee SC 6, *Wrought aluminium and aluminium alloys*.

This second edition cancels and replaces the first edition (ISO 6363-4:1991), which has been technically revised.

ISO 6363 consists of the following parts, under the general title *Wrought aluminium and aluminium alloys* — *Cold-drawn rods/bars, tubes and wires*:

- Part 1: Technical conditions for inspection and delivery
- Part 2: Mechanical properties
- Part 3: Drawn round bars and wires Tolerances on diameter) https://standards.iteh.ai/catalog/standards/sist/e157fbef-5dea-4ffb-af05-78b2b71f695a/iso-6363-4-2012

standards.iteh.ai)

- Part 4: Drawn rectangular bars and wires Tolerances on form and dimensions
- Part 5: Drawn square and hexagonal bars and wires Tolerances on form and dimensions
- Part 6: Drawn round tubes Tolerances on form and dimensions

## Wrought aluminium and aluminium alloys — Cold-drawn rods/bars, tubes and wires —

#### Part 4:

## Drawn rectangular bars and wires — Tolerances on form and dimensions

#### 1 Scope

This part of ISO 6363 specifies the tolerances on form and dimensions of wrought aluminium and aluminium alloy drawn rectangular bars and wires with thicknesses ranging from 2 mm up to and including 60 mm and widths up to and including 200 mm.

For wires, this part of ISO 6363 does not apply to electrical, welding and aeronautical purposes.

For drawn bars, 5.1 to 5.4 apply, and only 5.1 applies to drawn wires.

### 2 Normative references STANDARD PREVIEW

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 6363-1, Wrought aluminium and aluminium alloys—Cold-drawn rods/bars, tubes and wires — Part 1: Technical conditions for inspection and delivery 5a/iso-6363-4-2012

#### 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 6363-1 apply.

#### 4 Materials

For the purposes of this part of ISO 6363, wrought aluminium and aluminium alloys are divided into two groups, which correspond to varying difficulty whenever manufacturing the products.

The division into group I and group II of the most commonly used general engineering alloys is specified in Table 1. The division into group I and group II of the most commonly used general engineering alloys is specified in Table 1. Grouping of other alloys is subject to agreement between the purchaser and supplier.

© ISO 2012 – All rights reserved

#### Table 1 — Alloy group

	1050, 1050A, 1070, 1100, 1200, 1350			
	3003, 3102, 3103, 3203			
Group I	5005, 5005A, 5050, 5051, 5051A			
	6005, 6005A, 6005C, 6008, 6012, 6014, 6018, 6056, 6060, 6061, 6063, 6063A, 6065, 6081, 6082, 6101, 6101A, 6101B, 6110A, 6181, 6261, 6262, 6262A, 6351, 6360, 6463			
	2007, 2011, 2011A, 2014, 2014A, 2017, 2017A, 2024, 2030, 2219			
Group II	5019, 5041, 5049, 5052, 5056, 5083, 5086, 5154, 5154A, 5251, 5454, 5754			
	7003, 7005, 7020, 7021, 7022, 7049A, 7050, 7075, 7108, 7108A, 7204			
NOTE The four-digit numbers listed in this table are taken from the Registration of International Alloy Designations and Chemical Composition Limits for Wrought Aluminium Alloys (also known as "Teal sheets") <sup>[1]</sup> .				

#### 5 Tolerances on form and dimensions

#### 5.1 Tolerances on width and thickness

The tolerances on width and thickness shall be in accordance with Tables 2 and 3.

The dimensions shall be measured without influence from the corner radii.

iTeh STANDARD PREVIEW
Table 2 — Tolerances on width and thickness for alloy group I

(standards.iteh.ai)

Dimensions in millimetres

Width <sup>a</sup>		Thickness a tolerances for thickness ranges <sup>a</sup>					
Range	Toler- ances	https://standa $2 \le a \le 6$	rds.iteh.ai/catal <b>6</b> < <i>9</i> 862 <b>19</b> 1	og/standards/sist/e f699a/is8-6308-4	$157 \text{fbef-} 5 \text{dea-} 4 \text{fl} \\ -2 8 \le a \le 3 \text{ 0}$	6 - a = 605 -	<b>40</b> < <i>a</i> ≤ <b>60</b>
<i>b</i> ≤ 10	±0,08	±0,06	±0,08	-	_	_	_
10 < <i>b</i> ≤ 18	±0,10	±0,06	±0,08	±0,10	_	_	_
18 < <i>b</i> ≤ 30	±0,15	±0,06	±0,08	±0,10	±0,15	_	_
30 < <i>b</i> ≤ 50	±0,20	±0,08	±0,10	±0,12	±0,15	±0,20	_
50 < <i>b</i> ≤ 80	±0,25	±0,10	±0,10	±0,12	±0,15	±0,20	±0,25
80 < <i>b</i> ≤ 120	±0,28	-	±0,12	±0,15	±0,20	±0,25	±0,30
120 < <i>b</i> ≤ 160	±0,32	_	_	±0,15	±0,20	±0,30	±0,35
160 < <i>b</i> ≤ 200	±0,35	_	_	±0,20	±0,25	±0,35	±0,40
a If $b/a > 10$ , the permissible tolerances shall be agreed upon.							

Table 3 — Tolerances on width and thickness for alloy group II

Dimensions in millimetres

Width <sup>a</sup>		Thickness a tolerances for thickness ranges <sup>a</sup>					
Range	Toler- ances	<b>2</b> ≤ a ≤ <b>6</b>	<b>6</b> < <i>a</i> ≤ <b>10</b>	<b>10</b> < <i>a</i> ≤ <b>18</b>	<b>18</b> < $a \le 30$	<b>30</b> < <i>a</i> ≤ <b>40</b>	<b>40</b> < <i>a</i> ≤ <b>60</b>
<i>b</i> ≤ 10	±0,12	±0,09	±0,12	_	-	_	_
10 < <i>b</i> ≤ 18	±0,15	±0,09	±0,12	±0,15	_	_	_
18 < <i>b</i> ≤ 30	±0,23	±0,09	±0,12	±0,15	±0,23	_	_
30 < <i>b</i> ≤ 50	±0,30	±0,12	±0,15	±0,18	±0,23	±0,30	_
50 < <i>b</i> ≤ 80	±0,38	±0,15	±0,15	±0,18	±0,23	±0,30	±0,38
80 < <i>b</i> ≤ 120	±0,42	_	±0,18	±0,23	±0,30	±0,38	±0,45
120 < <i>b</i> ≤ 160	±0,48	_	_	±0,23	±0,30	±0,45	±0,53
160 < <i>b</i> ≤ 200	±0,53	_	_	±0,30	±0,38	±0,53	±0,60
a If $b/a > 10$ , the permissible tolerances shall be agreed upon.							

#### 5.2 Fixed-length tolerances

If fixed-length bars are ordered, their maximum permissible length tolerances shall be in accordance with Table 4.

### iTeh STable 4 D Fixed-length tolerances W

(standards.iteh.ai)

Dimensions in millimetres

Width		Tolerances on fixed lengths			
b	<i>L</i> ≤ <b>250</b>	1 1 1 1 1 1 1 1	$\frac{12010}{1000}$ 00 < $L \le 2000$	2 000 < L ≤ 5 000	5 000 < L
<i>b</i> ≤ 30	Hups//standa +1 0	78b2l <b>o</b> 71f695a/iso-		+5 0	
30 < <i>b</i> ≤ 50	+2	+3	+4	+6	Ву
50 < <i>b</i> ≤ 120	+2,5 0	+4	+5 0	+7 0	agreement
120 < <i>b</i> ≤ 200	+3	+5 0	+6	+8	

#### 5.3 Squareness of cut ends

Squareness of cut ends shall be within half of the fixed length tolerance range (Table 4) for both fixed and random lengths. For example, for a fixed-length tolerance of  $^{+2}_{\phantom{0}0}$  mm, the squareness of cut ends shall be within 1 mm.

#### 5.4 Corner radii

The corners of the bars shall be slightly rounded, but the corner radii shall not exceed the values specified in Table 5.

Table 5 — Maximum corner radii

Dimensions in millimetres

Thickness	Maximum corner radii		
а	Alloy group I	Alloy group II	
<i>a</i> ≤ 10	0,4	0,6	
10 < <i>a</i> ≤ 40	0,8	1,0	
40 < <i>a</i> ≤ 60	1,5	2,0	

#### 5.5 Form tolerances

#### 5.5.1 General

The maximum form tolerances specified in 5.5.2 to 5.5.4 apply to all tempers, except temper O.

Form tolerances are measured by placing the bar on a horizontal plate under its own weight as shown in Figures 1 to 3.


#### 5.5.2 Flatness tolerances

The maximum allowable flatness tolerances, e, shall be in accordance with Table 6. The deviation from flatness,  $e_i$ , shall be measured in accordance with Figure 1.

Table 6 — Flatness tolerances (Standards.iten.ai)

Dimensions in millimetres

Width <u>ISO 6363-4:2012</u>	Flatness tolerance
https://standar@ls.iteh.ai/catalog/standards/sist/e1	57fbef-5dea-4ffl <b>%</b> -af05-
$b \le 30 78b2b71f695a/iso-6363-4-2$	0,2
30 < <i>b</i> ≤ 50	0,3
50 < <i>b</i> ≤ 80	0,4
80 < <i>b</i> ≤ 120	0,6
120 < <i>b</i> ≤ 200	0,9



#### Key


- 1 base plate
- 2 thickness
- b width
- ei deviation from flatness

Figure 1 — Measurement of deviation from flatness

#### 5.5.3 Straightness tolerances

The maximum allowable straightness tolerance, h, for the total length, l, shall be 2 mm per 1 000 mm of length (see Figure 2). In addition,  $h_2$  shall not exceed 0,6 mm for each section of 300 mm length ( $l_2$ ).

Dimensions in millimetres

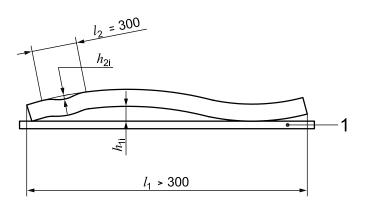

#### Key

1 base plate

Figure 2 — Measurement of deviation from straightness

### 5.5.4 Twist tolerance iTeh STANDARD PREVIEW

The maximum allowable twist tolerances shall be in accordance with Table 7.

The twist,  $v_i$ , shall be measured as shown in Figure 3.

ISO 6363-4:2012

For rectangular bars with width less than 10 mm, the twist tolerances shall be agreed between the supplier and purchaser. 78b2b71f695a/iso-6363-4-2012

Table 7 — Twist tolerances

Dimensions in millimetres

Width b	Twist tolerances				
	Per 1 000 mm of	otal length			
	length	<i>L</i> ≤ <b>5 000</b>	<b>5 000</b> < <i>L</i>		
10 ≤ <i>b</i> ≤ 30	1,5	3	Ву		
30 < <i>b</i> ≤ 50	2	5	agreement		
50 < <i>b</i> ≤ 120	3	7			
120 < <i>b</i> ≤ 200	4	10			