
**Textiles — Oil repellency — Hydrocarbon
resistance test**

Textiles — Oléofugation — Essai de résistance aux hydrocarbures

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[ISO 14419:2010](https://standards.iteh.ai/catalog/standards/sist/a70371f3-1fe7-4a76-bb99-b674e00fd70b/iso-14419-2010)

[https://standards.iteh.ai/catalog/standards/sist/a70371f3-1fe7-4a76-bb99-
b674e00fd70b/iso-14419-2010](https://standards.iteh.ai/catalog/standards/sist/a70371f3-1fe7-4a76-bb99-b674e00fd70b/iso-14419-2010)



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 14419:2010

<https://standards.iteh.ai/catalog/standards/sist/a70371f3-1fe7-4a76-bb99-b674e00fd70b/iso-14419-2010>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2010

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle.....	2
5 Safety precautions	2
6 Reagents.....	2
7 Apparatus	3
8 Test specimens.....	3
9 Procedure	3
10 Evaluation.....	4
11 Evaluation of results	4
12 Test report	5
Annex A (informative) Precision and bias statement	6
Bibliography	7

<https://standards.iteh.ai/catalog/standards/sist/a70371f3-1fe7-4a76-bb99-b674e00fd70b/iso-14419-2010>
 iTeh STANDARD PREVIEW
 (standards.iteh.ai)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 14419 was prepared by Technical Committee ISO/TC 38, *Textiles*, Subcommittee SC 2, *Cleansing, finishing and water resistance tests*.

This second edition cancels and replaces the first edition (ISO 14419:1998), of which it constitutes a minor revision. It also incorporates Technical Corrigendum ISO 14419:1998/Cor 1:2004.

ISO 14419:2010

<https://standards.iteh.ai/catalog/standards/sist/a70371f3-1fe7-4a76-bb99-b674e00fd70b/iso-14419-2010>

Textiles — Oil repellency — Hydrocarbon resistance test

1 Scope

This International Standard is applicable to the evaluation of a substrate's resistance to absorption of a selected series of liquid hydrocarbons of different surface tensions.

This International Standard is intended to provide a guide to oil stain resistance. It can provide a rough index of oil stain resistance as, generally, the higher the oil repellency grade, the better resistance to staining by oily materials, especially liquid oil substances. This is particularly true when comparing various finishes for a given substrate. This International Standard can also be utilized in determining if washing and/or drycleaning treatments have any adverse effect on the oil repellency characteristics of a substrate.

NOTE 1 Washing and drycleaning treatment procedures are described in ISO 6330 or ISO 3175 (all parts), respectively.

This International Standard is not intended to give an absolute measure of the resistance of the substrate to staining by all oily materials. Other factors, such as composition and viscosity of the oily substances, substrate construction, fibre type, dyes and other finishing agents, also influence stain resistance. This International Standard is not intended to estimate the resistance to penetration of the substrate by oil-based chemicals.

NOTE 2 For the evaluation of the resistance to penetration of the substrate by oil-based chemicals, see ISO 6530.

2 Normative references

ISO 14419:2010

<https://standards.iteh.ai/catalog/standards/sist/a70371f3-1fe7-4a76-bb99-b674e00fd70b/iso-14419-2010>

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 139, *Textiles — Standard atmospheres for conditioning and testing*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

grade

symbol for any step of a multistep standard reference scale for a quality characteristic

NOTE The grade is assigned to test specimens exhibiting a degree of the quality comparable to that step of the standard reference scale.

3.2

oil repellency

characteristic of a fabric whereby it resists absorption of oily liquids

4 Principle

Drops of standard test liquids, consisting of a selected series of hydrocarbons with different surface tensions, are placed on the substrate surface and then observed for absorption, wicking and contact angle. The oil repellency grade is the highest numbered test liquid which is not absorbed by the substrate surface.

5 Safety precautions

SAFETY PRECAUTIONS — These safety precautions are for information purposes only. The precautions are ancillary to the testing procedures and are not intended to be all inclusive. It is the user's responsibility to use safe and proper techniques in handling materials in this International Standard. Manufacturers should be consulted for specific detail such as material safety data sheets and other manufacturer's recommendations.

5.1 Good laboratory practices should be followed. Wear safety glasses and impervious gloves when handling test liquids in all laboratory areas.

5.2 Some of the hydrocarbons specified in this International Standard are flammable. Keep away from heat, sparks and open flame. Use with adequate ventilation. Avoid prolonged breathing of vapour or contact with skin. Do not take internally.

6 Reagents

All reagents shall be of a suitable analytical grade. Ensure the standard test liquids are used and stored at a temperature of (20 ± 2) °C. All reagents and standard test liquids have a maximum shelf life of three years.

6.1 Test liquids, prepared and numbered according to Table 1.

The purity of test liquids affects surface tension of the liquid. Use only analytical grades of test liquids.

6.2 White mineral oil, USP white mineral oil 340-355 SSU at 37,8 °C with Saybolt colour +30.

Table 1 — Standard test liquids

Composition	Oil test liquid number	Density	Surface tension
		kg/l	N/m at 25 °C
None (fails with white mineral oil)	0	—	—
White mineral oil	1	0,84 – 0,87	0,031 5
65:35 white mineral oil: <i>n</i> -hexadecane by volume	2	0,82	0,029 6
<i>n</i> -hexadecane	3	0,77	0,027 3
<i>n</i> -tetradecane	4	0,76	0,026 4
<i>n</i> -dodecane	5	0,75	0,024 7
<i>n</i> -decane	6	0,73	0,023 5
<i>n</i> -octane	7	0,70	0,021 4
<i>n</i> -heptane	8	0,69	0,019 8

7 Apparatus

7.1 Dropping bottles, each marked with the appropriate oil test liquid number, to which, for convenience, it is desirable to transfer the test liquids from stock solutions. A typical system found useful consists of 60 ml dropping bottles with ground-in pipettes and neoprene bulbs. Prior to use, the bulbs should be soaked in heptane for several hours and then rinsed in fresh heptane to remove soluble substances. It has been found helpful to place the test liquids in sequential order on a wooden platform on the grading table.

7.2 White textile blotting paper, of approximately $(0,71 \pm 0,1)$ mm in thickness, weight of $(370 \pm 5 \%)$ g/m² and an absorbent capacity of $(220 \pm 30) \%$.¹⁾

7.3 Laboratory gloves of general purpose are sufficient.

8 Test specimens

Three test specimens of approximately 20 cm × 20 cm are needed. Test specimen size should be chosen to represent all physical and colour characteristics of the fabric and allow ample room for testing. Condition the test specimens for a minimum of 4 h at $(20 \pm 2) ^\circ\text{C}$ and $(65 \pm 4) \%$ RH prior to testing. See ISO 139.

9 Procedure

9.1 Place the first test specimen flat on the white textile blotting paper (7.2) on a smooth, horizontal surface with the face side on top. Testing should be conducted in standard atmosphere for testing in accordance with ISO 139. Testing should be completed within 30 min, if test specimens are removed from a conditioning chamber.

9.1.1 When evaluating open-weave or "thin" substrates, place the test specimen on at least two layers of the substrate; otherwise, the test liquid can wet the underlying surface, not the actual test substrate, and thereby cause confusion in the reading of the results.

9.1.2 Equipment, benches and gloves should be free of silicone. Use of silicone-containing products could adversely affect oil repellency grades.

9.2 Wearing clean laboratory gloves (7.3), brush the pile of napped or pile substrates using the hand, in the direction giving the greatest lay of the surface prior to placing the drops of the test liquid. (The direction giving the lowest pile.)

9.3 Beginning with the lowest-numbered test liquid (oil test liquid No. 1), carefully place small drops (approximately 5 mm in diameter or 0,05 ml volume) on the test specimen in a minimum of five locations representing all physical and colour characteristics of the fabric. The drops should be approximately 4,0 cm apart. The dropper tip should be held at a height of approximately 0,6 cm from the substrate surface while placing drops. Do not touch the substrate with the dropper tip. Observe the drops for (30 ± 2) s from approximately a 45° angle. Assess each drop in accordance with Figure 1. Immediately examine the reverse of the fabric for any wetting.

1) White Textile Blotting Paper is the trade name of a product supplied by the American Association of Textile Chemists and Colorists (AATCC), P.O. Box 12215, Research Triangle Park, NC 27709-2215. This information is given for the convenience of users of this International Standard and does not constitute an endorsement by ISO of the product named. Equivalent products may be used if they can be shown to lead to the same results.

9.4 If no penetration or wetting of the substrate at the liquid–substrate interface and also no wicking around the drops occur, place drops of the next high-numbered test liquid at an adjacent site on the substrate so as not to interfere with the previous test and again observe for (30 ± 2) s. Assess each drop in accordance with Figure 1. Immediately examine the reverse of the fabric for any wetting.

9.5 Continue this procedure until one of the test liquids shows obvious wetting or wicking of the substrate under or around the drop within (30 ± 2) s. A maximum of six tests (oil test liquids) may be performed on one test specimen.

9.6 Repeat the procedure with the second sample. A third sample may be required (see Clause 11).

10 Evaluation


10.1 The oil repellency grade of a substrate is the numerical value of the highest-numbered test liquid which will not wet the substrate within a period of (30 ± 2) s. A grade of zero (0) is assigned when the substrate fails the white mineral oil liquid test. Wetting of the substrate is normally evidenced by a darkening (greying/shadowing) of the substrate at the liquid–substrate interface or wicking and/or loss of contact angle of the drop. On black or dark substrates, wetting can be detected by loss of “sparkle” within the drop.

10.2 Different types of wetting may be encountered depending on the finish, fibre, construction, etc.; and the determination of the end point can be difficult on certain substrates. Many substrates show complete resistance to wetting by a given test liquid [as indicated by a clear drop with a high contact angle (see Figure 1, Example A)], followed by immediate penetration by the next higher-numbered test liquid. In these instances, the end point and oil repellency grade are obvious. However, some substrates show progressive wetting under several test liquids as evidenced by a partial darkening of the substrate at the liquid–substrate interface (see Figure 1, Examples B, C and D). For such substrates the point of failure is considered to be that test liquid which exhibits complete darkening of the interface or any wicking within (30 ± 2) s.

10.3 A failure occurs when three (or more) of the five drops applied from a given test liquid show complete wetting (see Figure 1, Example D) or wicking with loss of contact angle (see Figure 1, Example C). A pass occurs if three (or more) of the five drops applied show a clear, well-rounded appearance with high contact angle (see Figure 1, Example A). The grade is expressed as the value of the pass oil test liquid immediately prior to the fail oil test liquid. A borderline pass occurs if three (or more) of the five drops applied show the rounded drop with partial darkening of the test specimen (see Figure 1, Example B). The grade is expressed to the nearest 0,5 value determined by subtracting one-half from the number of the borderline pass test liquid.

11 Evaluation of results

The oil repellency grade should be measured on two separate specimens. If the two grades agree, report the value. When the two grades are not in agreement, a third determination should be made. Report the grade of the third determination if that value is the same as either of the first two determinations. When the third determination is different from either of the first two, report the median value. For example, if the first two grades are 3,0 and 4,0 and the third determination is a 4,5 value, report the median value of 4,0. Report the oil repellency grade. This grade variation can be an indication of non-uniform fabric or contamination problems.

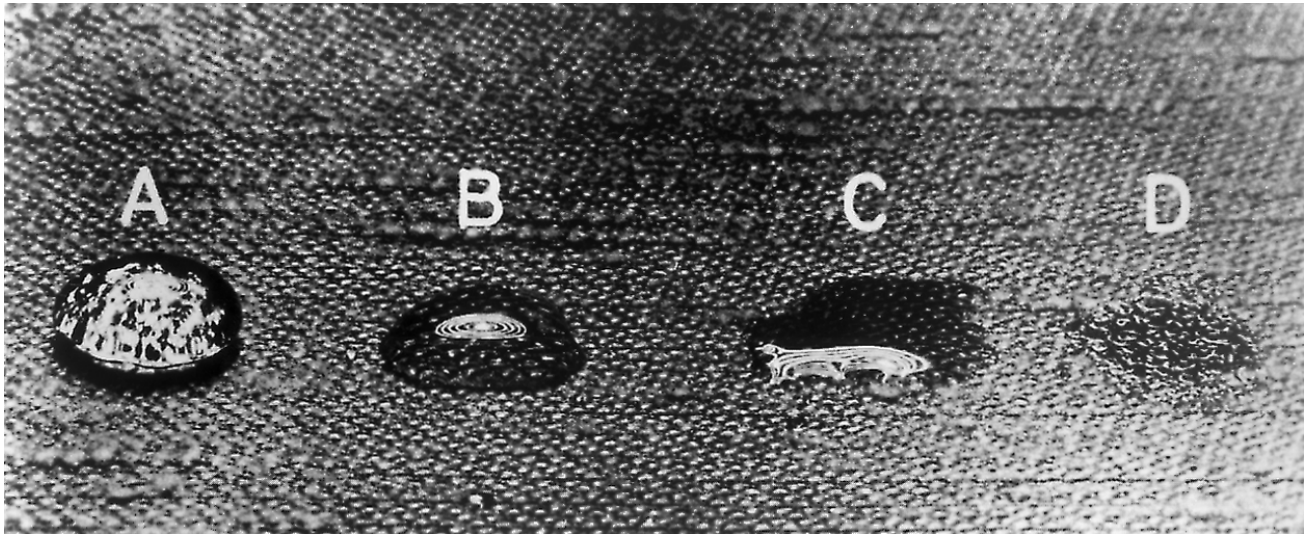

Key

- A passes; clear, well-rounded drop
- B borderline pass; rounding drop with partial darkening
- C fails; wicking apparent and/or complete wetting
- D fails; complete wetting

Figure 1 — Example of assigned grades

iTeh STANDARD PREVIEW

(standards.iteh.ai)

[Source: American Association of Textile Chemists and Colorists (AATCC)]

ISO 14419:2010

<https://standards.iteh.ai/catalog/standards/sist/a70371f3-1fe7-4a76-bb99-b674e00fd70b/iso-14419-2010>

12 Test report

The test report shall include the following information:

- a) reference to this International Standard, i.e. ISO 14419:2010;
- b) all information necessary to complete identification of the sample tested;
- c) number of specimens tested;
- d) conditioning and testing atmosphere used;
- e) any deviation from the procedure specified;
- f) test results;
- g) oil repellency grade.