
Paints and varnishes — Determination of film hardness by pencil test

*Peintures et vernis — Détermination de la dureté du feuil par l'essai de
dureté crayon*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 15184:2012

[https://standards.iteh.ai/catalog/standards/sist/8d535431-ef17-4a52-ae4b-
8c6f1261a391/iso-15184-2012](https://standards.iteh.ai/catalog/standards/sist/8d535431-ef17-4a52-ae4b-8c6f1261a391/iso-15184-2012)



Reference number
ISO 15184:2012(E)

© ISO 2012

iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 15184:2012

<https://standards.iteh.ai/catalog/standards/sist/8d535431-ef17-4a52-ae4b-8c6f1261a391/iso-15184-2012>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2012

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Apparatus	2
6 Sampling	3
7 Test panels	3
7.1 Substrate	3
7.2 Shape and dimensions	3
7.3 Preparation and coating	3
7.4 Drying and conditioning	4
7.5 Thickness of coating	4
8 Procedure	4
9 Types of defect	5
10 Precision	5
11 Test report	5
Annex A (informative) Applicability of the pencil hardness test	6
Bibliography	7

ISO 15184:2012
<https://standards.iteh.ai/catalog/standards/sist/8d535431-ef17-4a52-ae4b-8c6f1261a391/iso-15184-2012>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 15184 was prepared by Technical Committee ISO/TC 35, *Paints and varnishes*, Subcommittee SC 9, *General test methods for paints and varnishes*.

This second edition cancels and replaces the first edition (ISO 15184:1998), which has been technically revised. The main changes are:

- a) the incorrect instruction in 9.5 in the previous edition (now 8.5) to push the test panel has been corrected to an instruction to push the pencil;
- b) the requirement in 9.5 in the previous edition (now 8.5) that the pencil move at 0,5 mm/s to 1 mm/s has been replaced by a requirement that the speed simply be uniform;
- c) the use of propelling/mechanical pencils is now permitted;
- d) the supplementary test conditions (formerly Annex A) have been incorporated in the test report;
- e) a new Annex A giving information on the applicability of the method has been added.

Paints and varnishes — Determination of film hardness by pencil test

IMPORTANT — The electronic file of this document contains colours which are considered to be useful for the correct understanding of the document. Users should therefore consider printing this document using a colour printer.

1 Scope

This International Standard specifies a method for determining the film hardness by pushing pencils of known hardness over the film.

The test can be performed on a single coating of a paint, varnish or related product, or on the upper layer of a multi-coat system.

This rapid test has not been found to be useful in comparing the pencil hardness of different coatings. It is more useful in providing relative ratings for a series of coated panels exhibiting significant differences in pencil hardness.

The method is applicable only to smooth surfaces.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1513, *Paints and varnishes — Examination and preparation of test samples*

ISO 1514, *Paints and varnishes — Standard panels for testing*

ISO 2808, *Paints and varnishes — Determination of film thickness*

ISO 15528, *Paints, varnishes and raw materials for paints and varnishes — Sampling*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

pencil hardness

resistance of the surface of a paint film to marking, or the formation of some other defect, as a result of the action of a pencil, with a lead of specified dimensions, shape and hardness, which is pushed across the surface

4 Principle

A pencil lead with a defined geometry is pushed over the paint surface at an angle of 45°, exerting a force of 7,5 N on the surface. The hardness of the pencil lead is increased in steps until the surface of the coating is marked by visible defects. The test result is the highest hardness at which no marking occurs.

5 Apparatus

5.1 Test instrument, consisting of a metal block fitted with two wheels, one on each side, as shown in Figure 1. The wheels shall be made in such a way that they do not scratch the paint surface during testing. In the middle of the metal block, there is a cylindrical hole, inclined at an angle of $(45 \pm 1)^\circ$, for the pencil.

With the help of a clamp, pencils can be fixed in the instrument so that they are always in the same position.

Mounted on the top of the instrument is a level which is used to ensure that the test is carried out with the instrument horizontal.

The instrument shall be designed so that, with the instrument in the horizontal position, the tip of the pencil exerts a force of $(7,5 \pm 0,1)$ N on the paint surface.

Other types of test instrument may also be used, provided they give similar relative rating results.

5.2 Set of wooden drawing pencils, of the following hardnesses (see note):

9B - 8B - 7B - 6B - 5B - 4B - 3B - 2B - B - HB - F - H - 2H - 3H - 4H - 5H - 6H - 7H - 8H - 9H

Softer

Harder

B - black

HB - hard black

F - firm

H - hard

iteh STANDARD PREVIEW
(standards.iteh.ai)

Pencils made by various manufacturers may be used by agreement between the interested parties, provided they give similar relative rating results.

[ISO 15184:2012](https://standards.iteh.ai/catalog/standards/sist/8d535431-ef17-4a52-ac4b-100000000000/iso-15184-2012)

<https://standards.iteh.ai/catalog/standards/sist/8d535431-ef17-4a52-ac4b-100000000000/iso-15184-2012>

NOTE Some examples of pencil makes and manufacturers which have been found suitable are as follows¹⁾:

- Cleos Fine Art 160, manufactured by Cretacolor;
- Graphic, manufactured by Derwent;
- Turquoise T-2375, manufactured by Sanford;
- KOH-I-NOOR 1500, manufactured by Hardtmuth AG;
- Uni, manufactured by Mitsubishi Pencil Co.;
- Chunghwa, manufactured by China First Pencil Co., Ltd.

For comparative testing, it is recommended that pencils from the same manufacturer be used. Variations might be found between manufacturers and between batches from the same manufacturer.

Pencil leads in mechanical holders (propelling/mechanical pencils) may be used provided they give the same results as wooden pencils.

5.3 Special mechanical sharpener, which will remove the wood only, leaving the cylindrical pencil lead intact (see Figure 2).

5.4 Abrasive paper, grit No. 400.

5.5 Soft cloth or swab of cotton wool, to clean the panel after the test, using a solvent to which the coating is inert.

¹⁾ This information is given for the convenience of users of this International Standard and does not constitute an endorsement by ISO of these products.

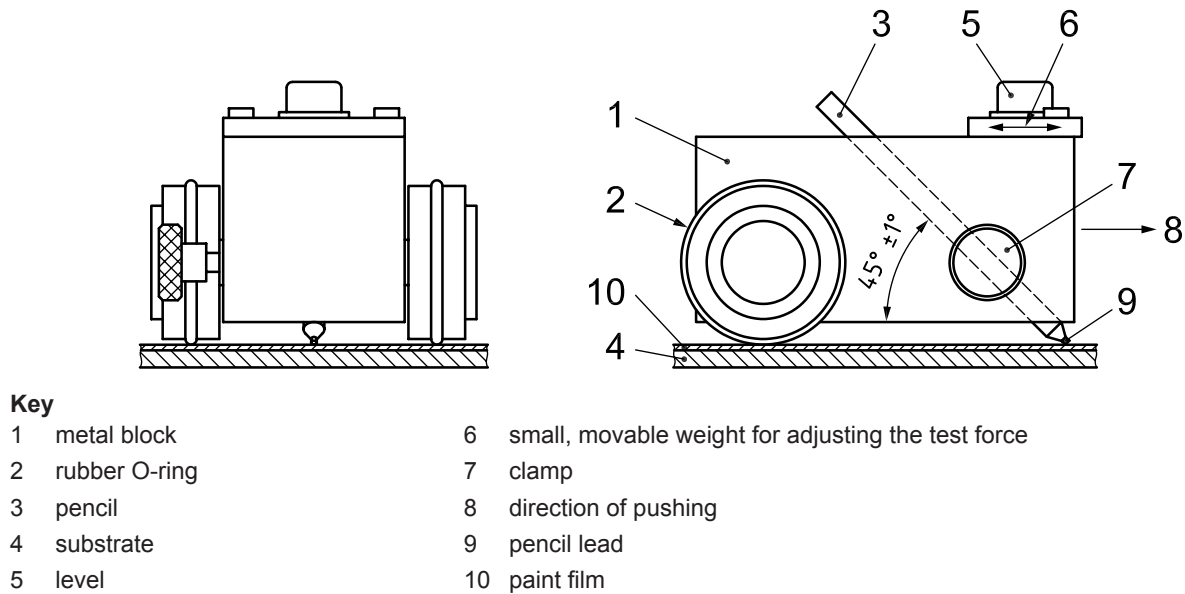


Figure 1 — Schematic diagram of test instrument

Dimensions in millimetres



6 Sampling

Take a representative sample of the product to be tested (or of each product in the case of a multi-coat system), as described in ISO 15528.

Examine and prepare each sample for testing, as described in ISO 1513.

7 Test panels

7.1 Substrate

Unless otherwise agreed, select the substrate from one of those described in ISO 1514, using, where possible, the same type of material as will be used in practice. The substrate panels shall be plane and free from distortion.

7.2 Shape and dimensions

The shape and dimensions of the test panels shall be such that, during the test, the panel will stay in the horizontal position.

7.3 Preparation and coating

Unless otherwise agreed, prepare each test panel in accordance with ISO 1514 and then coat it by the specified method with the product or system under test.

7.4 Drying and conditioning

Dry (or stove) and age, if applicable, each coated test panel for the specified time under the specified conditions. Before testing, condition the coated panels at $(23 \pm 2)^\circ\text{C}$ and a relative humidity of $(50 \pm 5)\%$, unless otherwise agreed, for a minimum period of 16 h.

7.5 Thickness of coating

The thickness of the coating shall be as specified or as agreed between the interested parties. Determine the thickness of the coating by one of the procedures specified in ISO 2808.

8 Procedure

8.1 Carry out the test at a temperature of $(23 \pm 2)^\circ\text{C}$ and a relative humidity of $(50 \pm 5)\%$, unless otherwise agreed.

8.2 Remove approximately 5 mm to 6 mm of wood from the point of each pencil using the special mechanical sharpener (5.3), being careful to leave an undisturbed, unmarked, smooth cylinder of pencil lead.

8.3 Flatten the tip of the lead by holding the pencil in a vertical position and moving the pencil back and forth over abrasive paper (5.4), maintaining an angle of 90° . Continue until a flat, smooth, circular cross-section is obtained, free from chips or nicks in the edges.

Repeat this procedure each time a pencil is used.

8.4 Place the coated panel on a level, firm, horizontal surface.

Insert a pencil in the test instrument (5.1) and clamp it in position so that the instrument is horizontal, with the tip of the pencil resting on the surface of the paint film (see Figure 1).

8.5 Immediately after the tip of the pencil has come to rest on the coating, push the pencil in the direction away from the operator at a uniform speed.

8.6 Unless otherwise agreed, inspect the coating after 30 s, using normal corrected vision, for marking of the kind defined in Clause 9.

The damage can be assessed more easily after cleaning all fragments of pencil lead from the paint surface, using a soft cloth or swab of cotton wool (5.5) and an inert solvent. If this is done, take care that the solvent does not affect the hardness of the coating in the test area.

By agreement, a magnifying lens (magnification $\times 6$ to $\times 10$) may be used to assess the damage. If a magnifying lens is used, this shall be reported in the test report.

If no marking has occurred, repeat the test (8.3 to 8.6) without overlap of the test areas, moving up the hardness scale until marking occurs over a distance of at least 3 mm.

If marking has occurred, repeat the test (8.3 to 8.6) down the hardness scale until marking no longer occurs.

Determine which of the defects of the kinds defined in Clause 9 has been produced.

The hardness of the hardest pencil which does not mark the coating is the so-called pencil hardness.

By agreement, the test may also be carried out to determine the minimum pencil hardness which does not cause a cohesive fracture (the so-called "gouge" hardness as defined in ASTM D3363). If the test is done this way, this shall be reported in the test report.

8.7 Carry out the test in duplicate. If the two results differ by more than one unit of pencil hardness, discard them and repeat the test.

9 Types of defect

Marking by pencil leads covers a range of defects in the surface of the paint film.

These defects are defined as follows:

- a) Plastic deformation: a permanent indentation in the paint surface without cohesive fracture.
- b) Cohesive fracture: the presence of a visible scratch or rupture in the surface of the paint film, material having been removed from the paint film.
- c) Combinations of the above.

These defects can occur simultaneously.

10 Precision

No precision data are available.

NOTE The applicability of the method is discussed in Annex A.

11 Test report

The test report shall contain at least the following information:

- a) all details necessary to identify the product tested;
- b) a reference to this International Standard (ISO 15184);
- c) details of the preparation of the test panels, including
 - 1) the material and surface preparation of the substrate (see 7.1 and 7.2);
 - 2) the method of application of the test coating to the substrate, including the duration and conditions of drying between coats in the case of a multi-coat system (see 7.3),
 - 3) the duration and conditions of drying (or stoving) of the coating, and the conditions of ageing, if applicable, before testing (see 7.4),
 - 4) the thickness, in micrometres, of the dry coating and the method of measurement used from ISO 2808 (see 7.5), and whether it is a single coating or a multi-coat system;
- d) the temperature and relative humidity of the test, if different from those specified in 8.1;
- e) the make and manufacturer of the pencils used;
- f) the result of the test, including, if agreed between the interested parties, a description of the kinds of defect defined in Clause 9 which actually occurred;
- g) the magnification of the magnifying lens, if used;
- h) any deviation from the test method specified;
- i) any unusual features (anomalies) observed during the test;
- j) the date of the test.