



DRAFT INTERNATIONAL STANDARD ISO/DIS 2285

ISO/TC 45/SC 2

Secretariat: JISC

Voting begins on
2012-04-04

Voting terminates on
2012-09-04

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION • МЕЖДУНАРОДНАЯ ОРГАНИЗАЦИЯ ПО СТАНДАРТИЗАЦИИ • ORGANISATION INTERNATIONALE DE NORMALISATION

Rubber, vulcanized or thermoplastic — Determination of tension set under constant elongation, and of tension set, elongation and creep under constant tensile load

Caoutchouc vulcanisé ou thermoplastique — Détermination de la déformation rémanente sous allongement constant et de la déformation rémanente, de l'allongement et du fluage sous charge constante de traction

[Revision of sixth edition (ISO 2285:2007)]

ICS 83.060

iTeh STANDARD PREVIEW
(standards.iteh.ai)
Full standard:
<https://standards.iteh.ai/catalog/standards/sist/3600a1eb-2481-4032-9bd9-4b3d113bd5303/iso-2285-2013>

To expedite distribution, this document is circulated as received from the committee secretariat. ISO Central Secretariat work of editing and text composition will be undertaken at publication stage.

Pour accélérer la distribution, le présent document est distribué tel qu'il est parvenu du secrétariat du comité. Le travail de rédaction et de composition de texte sera effectué au Secrétariat central de l'ISO au stade de publication.

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

iTeh STANDARD PREVIEW
(standards.iteh.ai)
Full standard:
<https://standards.iteh.ai/catalog/standards/sist/3600a1eb-2481-4032-9bd9-4b3d113bd5303/iso-2285-2013>

Copyright notice

This ISO document is a Draft International Standard and is copyright-protected by ISO. Except as permitted under the applicable laws of the user's country, neither this ISO draft nor any extract from it may be reproduced, stored in a retrieval system or transmitted in any form or by any means, electronic, photocopying, recording or otherwise, without prior written permission being secured.

Requests for permission to reproduce should be addressed to either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Reproduction may be subject to royalty payments or a licensing agreement.

Violators may be prosecuted.

Contents

Page

1	Scope	%
2	Normative references	%
3	Terms and definitions	&
4	Apparatus	4
5	Test pieces.....	(
6	Procedure	*
7	Expression of results	"
8	Test report	1\$
	Annex A (normative) Calibration Schedule.....	1&

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Full standard:
<https://standards.iteh.ai/catalog/standards/sist/3600a1eb-2481-4032-9bd9-4b3d13bd5303/iso-2285-2013>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 2285 was prepared by Technical Committee ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 2, *Testing and analysis*.

This seventh edition cancels and replaces the sixth edition (ISO 2285:2007), which has been aligned with ISO 815-1 and completed with a new Annex A with a calibration schedule.

PREVIEW
iTech STANDARD (standard@itech.ai)
Full standard: <https://standards.itech.ai/catalog/standards/sist/2285-2011>
2481-4032-9bd9-4b3d113bd5303/iso-2285-2011

Rubber, vulcanized or thermoplastic — Determination of tension set under constant elongation, and of tension set, elongation and creep under constant tensile load

WARNING — Persons using this International Standard should be familiar with normal laboratory practice. This standard does not purport to address all of the safety problems, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to ensure compliance with any national regulatory conditions.

WARNING — Certain procedures specified in this International Standard may involve the use or generation of substances, or the generation of waste, that could constitute a local environmental hazard. Reference should be made to appropriate documentation on safe handling and disposal after use.

1 Scope

This International Standard specifies a number of methods of determining the dimensional changes in test pieces of vulcanized or thermoplastic rubber during and after tensile loading for relatively short periods under constant elongation or constant loading.

The constant-elongation test is intended to measure the ability of rubbers to retain their elastic properties after extension, at a standard laboratory temperature, to a specified strain which is maintained for a specified time at the same or at a specified higher temperature and then released at the test temperature or at the standard laboratory temperature.

The constant-load test specifies a method for the determination of elongation, creep and tension set of rubbers subjected to a constant load at standard laboratory temperature.

The test methods are intended to measure the elastic properties of rubber in the hardness range 20 IRHD to 94 IRHD.

The creep measurement is not recommended for product design or the evaluation of low-creep materials. For these, reference should be made to ISO 8013. No agreement between the results of this test or those of ISO 8013 should be inferred.

NOTE The constant-load test is primarily intended for the measurement of state of cure and the quality control of thin-walled products. An increase in the state of cure or degree of crosslinking is usually reflected in a decrease in set, creep or elongation.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 188, *Rubber, vulcanized or thermoplastic — Accelerated ageing and heat resistance tests*

ISO 8013, *Rubber, vulcanized — Determination of creep in compression or shear*

ISO 23529, *Rubber — General procedures for preparing and conditioning test pieces for physical test methods*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply (see also the definitions of creep functions given in ISO 8013).

3.1

tension set at constant load

elongation remaining in a test piece in the unloaded condition after it has been subjected to a constant load during a specified time, expressed as a percentage of the original length in the unloaded condition

3.2

tension set at constant elongation

elongation remaining in a test piece in the relaxed condition after it has been subjected to a constant elongation during a specified time, expressed as a percentage of the elongation

3.3

creep

increase in elongation of a test piece at constant load during a specified time, expressed as a percentage of the elongation at the beginning of that time

4 Apparatus

4.1 Constant-elongation measurements

4.1.1 Straining device, consisting of a metal rod or other suitable guide fitted with pairs of holders, one fixed and one moveable, for the ends of the test piece. The holders shall be in the form of self-tightening clamps for strip test pieces, in the form of jaws to hold tab (enlarged) ends, and in the form of flat pulleys of about 5 mm width and 10 mm diameter for ring test pieces.

If so desired, a means of operating the moving holder other than by hand can be provided, for example a threaded rod, provided that the tolerances on extension speed are met (see 6.1.2). Suitable stops or graduations can also be provided to avoid over-extension in the initial straining of the test piece.

The straining device shall be so designed that, when used at high temperatures in an oven, it can be placed with the reference length of the test piece perpendicular to the direction of the air flow. It shall also be of minimum mass in order to avoid excessive lag in the attainment of temperature equilibrium after its introduction into the oven.

A multiple-unit straining device can be used, provided that the foregoing requirements are met.

4.1.2 Oven, conforming to the requirements of ISO 188 (if the test is to be carried at a temperature above the standard laboratory temperature). For short heating times, controlled air flow is not necessary.


4.1.3 Length-measuring device, capable of measuring the reference length to the nearest 0,1 mm.

For strip test pieces, a bench marker shall be provided to mark the length used as the reference length.

For ring test pieces, the reference length can be the inner diameter of the ring, in which case a graduated cone allowing measurements to be made to the nearest 0,1 mm shall be used. Alternatively, if measurements are to be made on a straight reference length, a rigid channel, 3,5 mm deep and 20 mm wide for large ring test pieces and 1,75 mm deep and 10 mm wide for small ring test pieces, shall be provided for straightening portions of such test pieces during marking and measuring of the reference length.

4.2 Constant-load measurements

4.2.1 Straining device, comprising clamps and weights, or equivalent, for loading the test pieces (see Figure 1).

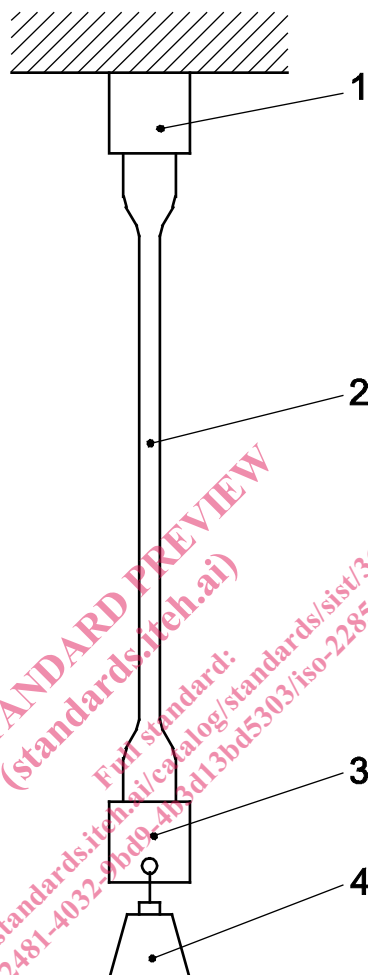

Key

- 1 fixed clamp
- 2 test piece
- 3 clamp for holding weight
- 4 weight

Figure 1 — Straining device

4.2.2 Thickness- and width-measuring device, comprising a gauge for measuring the thickness and, where appropriate, the width of the test piece in accordance with ISO 23529, method A.

The width of die-cut test pieces shall be taken as the distance between the cutting edges of the die in the narrow part, in which case a device capable of measuring the width to the nearest 0,05 mm in accordance with ISO 23529 shall be provided.

4.2.3 Length-measuring device, capable of measuring the reference length to the nearest 0,1 mm.

5 Test pieces

5.1 Preparation

Test pieces shall be prepared in accordance with ISO 23529. They shall be cut from flat sheet 2 mm ± 0,2 mm thick (except large ring test pieces, which shall be cut from sheet 4 mm ± 0,2 mm thick) prepared by moulding or slitting and buffing in accordance with ISO 23529.

Strip test pieces and strip test pieces with enlarged ends shall be cut using a sharp die with a cutter as specified in ISO 23529.

Ring test pieces shall be cut from sheet by means of a pair of concentric circular dies or rotating cutters. The separation of the two cutting edges shall not differ from the average value by more than 0,05 mm.

5.2 Test pieces for testing under constant elongation


5.2.1 Strip test pieces

Strip test pieces shall be between 2 mm and 10 mm wide. A width of 6 mm is preferred.

The length of any given strip depends on the selected reference length and the type of straining device.

5.2.2 Strip test pieces with enlarged ends

Test pieces with enlarged ends shall be as shown in Figure 2, with a narrow section of length between 25 mm and 50 mm which shall be used as the reference length.

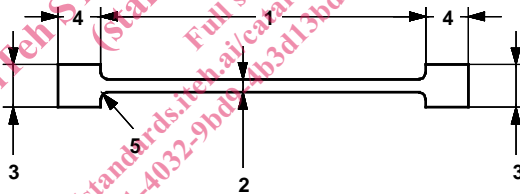

Key

- 1 length of narrow section 25 mm – 50 mm
- 2 width of narrow section 2 mm ± 0,2 mm
- 3 width of ends ≈ 6,5 mm
- 4 length of ends ≈ 6,5 mm
- 5 transition radius inside ≈ 1 mm

Thickness 2 mm ± 0,2 mm

Figure 2 — Test piece with enlarged ends

5.2.3 Ring test pieces

Ring test pieces shall be of one of the following sizes:

Large ring test piece:


- thickness: 4 mm ± 0,2 mm
- outer diameter: 52,6 mm ± 0,2 mm
- inner diameter: 44,6 mm ± 0,2 mm

Small ring test piece:

thickness:	2 mm ± 0,2 mm
outer diameter:	33,5 mm ± 0,2 mm
inner diameter:	29,5 mm ± 0,2 mm

5.3 Test pieces for testing under constant load

Test pieces shall have the shape and dimensions shown in Figure 3.

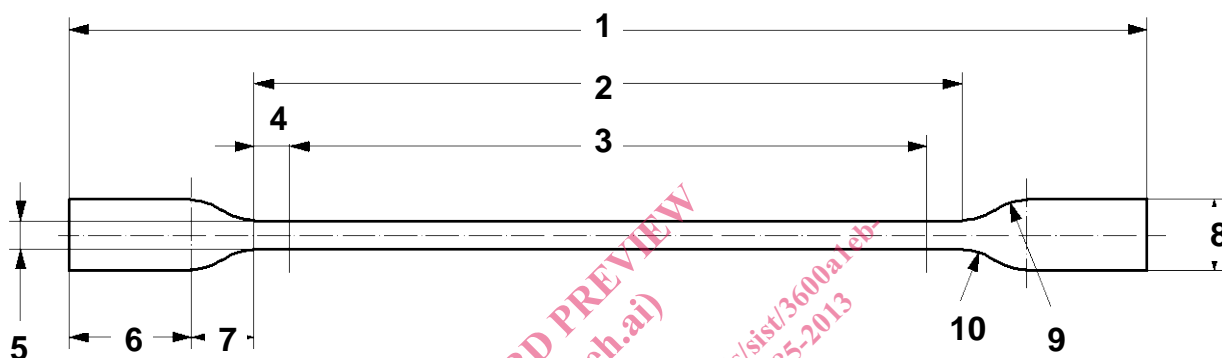

Key

- 1 overall length ≈ 152 mm
- 2 length of narrow section ≈ 100 mm
- 3 test length 90 mm ± 0,5 mm
- 4 distance between shoulder and test length ≈ 5 mm
- 5 width of narrow section 2 mm ± 0,2 mm
- 6 length of ends ≈ 16 mm
- 7 length of shoulder ≈ 10 mm
- 8 width of ends ≈ 10 mm
- 9 transition radius outside ≈ 7,5 mm
- 10 transition radius inside ≈ 7,5 mm

Thickness 2 mm ± 0,2 mm

Figure 3 — Test piece for constant loading

5.4 Marking

5.4.1 General

Reference marks shall be marked on the test pieces, using a suitable bench marker and an ink which does not affect the material and withstands the temperature of test.