



SLOVENSKI STANDARD
SIST EN 754-7:2016

01-september-2016

Nadomešča:
SIST EN 754-7:2008

**Aluminij in aluminijeve zlitine - Hladno vlečene palice/drogovi in cevi - 7. del:
Nevarjene (narejene iz celega) cevi, tolerance mer in oblike**

Aluminium and aluminium alloys - Cold drawn rod/bar and tube - Part 7: Seamless tubes, tolerances on dimensions and form

Aluminium und Aluminiumlegierungen - Gezogene Stangen und Rohre - Teil 7: Nahtlose Rohre, Grenzabmaße und Formtoleranzen

Aluminium et alliages d'aluminium - Barres et tubes étirés - Partie 7 : Tubes filés sur aiguille, tolérances sur dimensions et forme

Ta slovenski standard je istoveten z: EN 754-7:2016

ICS:

77.150.10 Aluminijski izdelki Aluminium products

SIST EN 754-7:2016 **en,fr,de**

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 754-7:2016](#)

<https://standards.iteh.ai/catalog/standards/sist/9d87ac25-1e9b-4afd-b0b0-2c37d1d90c96/sist-en-754-7-2016>

EUROPEAN STANDARD

EN 754-7

NORME EUROPÉENNE

EUROPÄISCHE NORM

June 2016

ICS 77.150.10

Supersedes EN 754-7:2008

English Version

Aluminium and aluminium alloys - Cold drawn rod/bar and tube - Part 7: Seamless tubes, tolerances on dimensions and form

Aluminium et alliages d'aluminium - Barres et tubes
étirés - Partie 7 : Tubes filés sur aiguille, tolérances sur
dimensions et forme

Aluminium und Aluminiumlegierungen - Gezogene
Stangen und Rohre - Teil 7: Nahtlose Rohre,
Grenzabmaße und Formtoleranzen

This European Standard was approved by CEN on 11 April 2016.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

iTeh STANDARD PREVIEW

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

| Contents | Page |
|---|-------------|
| European foreword..... | 3 |
| 1 Scope | 4 |
| 2 Normative references | 5 |
| 3 Tolerances on dimensions | 5 |
| 3.1 General..... | 5 |
| 3.2 Diameter - Round tube..... | 5 |
| 3.3 Width, depth or width across flats - squares, rectangles, hexagons, octagons..... | 6 |
| 3.4 Wall thickness variation (eccentricity)..... | 7 |
| 3.5 Length..... | 8 |
| 3.6 Squareness of cut ends..... | 9 |
| 4 Tolerances on form | 9 |
| 4.1 General..... | 9 |
| 4.2 Straightness..... | 9 |
| 4.3 Convexity-Concavity..... | 10 |
| 4.4 Twist..... | 11 |
| 4.5 Angularity..... | 12 |
| 4.6 Corner and fillet radii..... | 13 |
| 4.7 Depth of dents for round tube..... | 13 |
| Annex A (informative) Wall thickness variation (eccentricity) | 14 |
| A.1 General..... | 14 |
| A.2 Specifying round tube sizes and tolerances..... | 14 |
| Bibliography | 16 |

iTeh STANDARD PREVIEW

(standards.iteh.ai)

SIST EN 754-7:2016

[https://standards.iteh.ai/catalog/standards/sist/9d87ac25-1e9b-4afd-b0b0-](https://standards.iteh.ai/catalog/standards/sist/9d87ac25-1e9b-4afd-b0b0-2c37d1d90c96/sist-en-754-7-2016)[2c37d1d90c96/sist-en-754-7-2016](https://standards.iteh.ai/catalog/standards/sist/9d87ac25-1e9b-4afd-b0b0-2c37d1d90c96/sist-en-754-7-2016)

European foreword

This document (EN 754-7:2016) has been prepared by Technical Committee CEN/TC 132 “Aluminium and aluminium alloys”, the secretariat of which is held by AFNOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by December 2016, and conflicting national standards shall be withdrawn at the latest by December 2016.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 754-7:2008.

The following technical modifications have been introduced during the revision:

- correction of Subclause 3.2, Diameter - Round tube.

EN 754 comprises the following parts under the general title *Aluminium and aluminium alloys — Cold drawn rod/bar and tube*:

- *Part 1: Technical conditions for inspection and delivery;*
- *Part 2: Mechanical properties;*
- *Part 3: Round bars, tolerances on dimensions and form;*
- *Part 4: Square bars, tolerances on dimensions and form;*
- *Part 5: Rectangular bars, tolerances on dimensions and form;*
- *Part 6: Hexagonal bars, tolerances on dimensions and form;*
- *Part 7: Seamless tubes, tolerances on dimensions and form;*
- *Part 8: Porthole tubes, tolerances on dimensions and form.*

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

1 Scope

This European Standard specifies the tolerances on dimensions and form for aluminium and aluminium alloys cold drawn seamless tubes with an outside diameter (OD) from 3 mm to 350 mm (round tube, see Figure 1) or with a cross section contained within a circumscribing circle (CD) from 8 mm to 300 mm (other than round tube, see Figure 2) supplied in straight lengths.

This European Standard only applies to tube produced by the seamless die/mandrel method of extrusion (and then cold drawn to the final dimensions required).

The temper designations used in this part are according to EN 515.

This document applies to cold drawn, seamless tube for general engineering applications.

This document does not apply to:

- cold drawn tube produced by the porthole/bridge method (EN 754-8),
- tubes delivered in coils (EN 13958),
- coiled tubes cut to length (EN 13958).

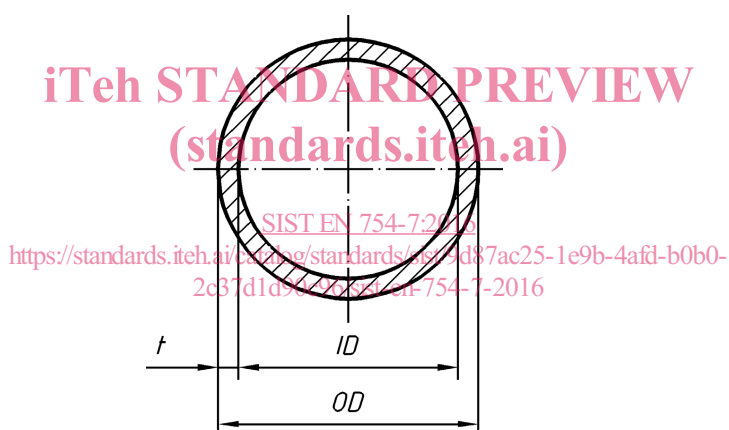


Figure 1 — Round tube

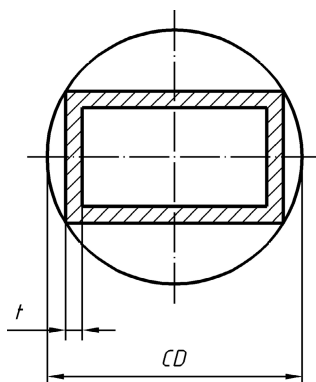


Figure 2 — Circumscribing circle for other than round tube

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 754-1:2016, *Aluminium and aluminium alloys — Cold drawn rod/bar and tube — Part 1: Technical conditions for inspection and delivery*

3 Tolerances on dimensions

3.1 General

When outside diameter (*OD*), inside diameter (*ID*), and wall thickness (*t*) (or their equivalent dimensions in other than round tube), are all specified, standard tolerances shall apply to any two of these dimensions, but not to all three. As a result, the purchaser shall only state two nominal dimensions on any given order.

3.2 Diameter - Round tube

Mean diameter is defined as the average of two diameter measurements taken at right angles to each other at any position along the length.

The maximum allowable deviation of diameter at any point from the specified diameter is the maximum difference measured at any point along the length of the tube, i.e. it is inclusive of any ovality in the cross section.

The tolerances on diameter are specified in Table 1.

As detailed in EN 754-1:2016, Clause 4, if the original order does not make clear the nature of the diameter tolerances required, the supplier shall interpret them as inclusive of any ovality (i.e. maximum allowable deviation at any point from the specified diameter in Table 1). However, the diameter tolerances may be expressed as both mean and inclusive of ovality if this is specifically requested by the purchaser.

Table 1 — Tolerances on diameter for round tube

Dimensions in millimetres

| Diameter (OD or ID) | | Tolerance on diameter | | | |
|------------------------|------------------------|---|--|-----------------------------------|---------------------------------|
| | | Maximum allowable deviation of mean diameter from specified diameter ^e | Maximum allowable deviation of diameter at any point from specified diameter ^a | | |
| Over | Up to and including | | Non-annealed and non heat treated tube ^b | Heat treated tube ^c | Tempers O, H111 and Tx511 |
| ≥ 3 | 8 | ±0,04 ^d | ±0,08 ^d | ±0,12 ^d | ±0,25 ^d |
| 8 | 18 | ±0,05 | ±0,09 | ±0,15 | ±0,30 |
| 18 | 30 | ±0,06 | ±0,10 | ±0,20 | ±0,40 |
| 30 | 50 | ±0,07 | ±0,12 | ±0,25 | ±0,50 |
| 50 | 80 | ±0,09 | ±0,15 | ±0,36 | ±0,70 |
| 80 | 120 | ±0,14 | ±0,20 | ±0,60 | ±1,2 |
| 120 | 200 | ±0,25 | ±0,40 | ±1,2 | ±2,4 |
| 200 | 350 | ±0,38 | ±0,60 | ±1,7 | ±3,4 |

^a Not applicable to tubes having a wall thickness less than 2,5 % of the specified outside diameter. The tolerance for tubes with wall thickness less than 2,5 % of the specified outside diameter shall be determined by multiplying the applicable tolerance as follows:

- wall thickness over 2,0 % up to and including 2,5 % of outside diameter: 1,5 × tolerance;
- wall thickness over 1,5 % up to and including 2,0 % of outside diameter: 2,0 × tolerance;
- wall thickness over 1,0 % up to and including 1,5 % of outside diameter: 3,0 × tolerance;
- wall thickness over 0,5 % up to and including 1,0 % of outside diameter: 4,0 × tolerance.

^b Applies to all alloys in H1x, H2x, H3x tempers, and to alloy EN AW-6063 in the T832 temper.

^c Applies to all alloys in T3, T4, T6, T66, T73, T8, T9 and Tx511 tempers.

^d This tolerance applies for outside diameter only, i.e. tube in this size range can only be specified as "Outside Diameter x Wall Thickness".

^e Shall not apply to Tx510 or Tx511 tempers.

3.3 Width, depth or width across flats - squares, rectangles, hexagons, octagons

The tolerances on width, depth or width across flats are specified in Table 2.

Table 2 — Tolerances on width, depth or width across flats

Dimensions in millimetres

| Width, depth or width across flats | | Maximum allowable deviation of width, depth or width across flats at any point from the specified value ^a | | |
|------------------------------------|---------------------|--|--------------------------------|----------------------------|
| Over | Up to and including | Non-annealed and non heat treated tube ^b | Heat treated tube ^c | Annealed tube ^d |
| ≥ 8 | 18 | ±0,20 | ±0,30 | ±0,60 |
| 18 | 30 | ±0,25 | ±0,40 | ±0,80 |
| 30 | 50 | ±0,35 | ±0,50 | ±1,0 |
| 50 | 80 | ±0,50 | ±0,70 | ±1,4 |
| 80 | 120 | ±0,70 | ±1,0 | ±2,0 |
| 120 | 200 | ±1,0 | ±1,5 | ±3,0 |

^a Not applicable to tubes having a wall thickness less than 2,5 % of the specified outside width, depth or width across flats. The tolerance for tubes with wall thickness less than 2,5 % of the specified width, depth or width across flats shall be determined by multiplying the applicable tolerance as follows:
— wall thickness over 2,0 % up to and including 2,5 % of outside parameter: 1,5 × tolerance;
— wall thickness over 1,5 % up to and including 2,0 % of outside parameter: 2,0 × tolerance;
— wall thickness over 1,0 % up to and including 1,5 % of outside parameter: 3,0 × tolerance;
— wall thickness over 0,5 % up to and including 1,0 % of outside parameter: 4,0 × tolerance.

^b Applies to all alloys in F, H1x, H2x, H3x tempers.

^c Applies to all alloys in T3, T4, T6, T66, T73, T8, T9 and Tx511 tempers.

^d Applies to all alloys in O, H111 and Tx510 tempers.

SIST EN 754-7:2016

3.4 Wall thickness variation (eccentricity)

The tolerances on wall thickness variation (eccentricity) are specified in Table 3.