



SLOVENSKI STANDARD
kSIST-TP FprCEN/TR 17469:2020
01-januar-2020

Železniške naprave - Metoda načrtovanja osi

Railway applications - Axle design method

Bahnanwendungen - Konstruktionsverfahren von Radsatzwellen

Applications ferroviaires - Méthode de conception des essieux

Ta slovenski standard je istoveten z: FprCEN/TR 17469

SAMPLE

ICS:

45.040	Materiali in deli za železniško tehniko	Materials and components for railway engineering
--------	--	---

kSIST-TP FprCEN/TR 17469:2020 **en,fr,de**

SAMPLE

TECHNICAL REPORT
RAPPORT TECHNIQUE
TECHNISCHER BERICHT

FINAL DRAFT
FprCEN/TR 17469

October 2019

ICS

English Version

Railway applications - Axle design method

Applications ferroviaires - Méthode de conception des
essieux

Bahnanwendungen - Konstruktionsverfahren von
Radsatzwellen

This draft Technical Report is submitted to CEN members for Vote. It has been drawn up by the Technical Committee CEN/TC 256.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.

Recipients of this draft are invited to submit, with their comments, notification of any relevant patent rights of which they are aware and to provide supporting documentation.

Warning : This document is not a Technical Report. It is distributed for review and comments. It is subject to change without notice and shall not be referred to as a Technical Report.

SAMPLE



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

Contents

European foreword.....	4
Introduction	5
1 Scope.....	9
2 Normative references.....	9
3 Terms, definitions, symbols and abbreviations.....	9
3.1 Terms and definitions	9
3.2 Symbols and abbreviations	9
4 Loads.....	11
4.1 Reliability analysis based on the Stress Strength Interference Analysis method	11
4.2 Fatigue load analysis method	13
4.2.1 General.....	13
4.2.2 Load signals processing and Fatigue-Equivalent-Load	13
4.2.3 Method to generate the distribution of in-service load severities.....	19
4.3 Fatigue reliability assessment of a railway passenger coach axle	22
4.3.1 Load measurements.....	22
4.3.2 Load spectra classification and generation and distribution of load severity.....	26
4.3.3 Estimation of the probability of a crack initiation.....	30
5 Modelling.....	32
5.1 General.....	32
5.2 Stress concentration factors	32
5.3 Length of the transition	35
5.4 Numerical modelling of axles	37
5.4.1 Development of numerical models and validation.....	37
5.4.2 Analysis of mounted components.....	40
5.4.3 Modelling recommendations.....	41
5.5 Axle calculation method	42
6 Fatigue limits	43
6.1 Testing method principals.....	43
6.1.1 F1 tests.....	43
6.1.2 F4 tests	44
6.1.3 Fatigue limit estimation.....	44
6.2 Test plan	45
6.3 Axle body fatigue limit results.....	49
6.3.1 F1 standard surface – transitions and groves (EA4T axles)	49
6.3.2 F1 Blasted surface – transitions (EA4T axles)	50
6.3.3 F1 Standard surface – transitions (EA1N axles).....	51
6.3.4 F1 Corroded surfaces – transitions of unpainted axles	52
6.4 Axle press-fit seat fatigue limits (F4).....	53
6.4.1 Diameter ratio = 1,12 (EA4T axles)	53
6.4.2 Diameter ratio = 1,08 (EA4T)	54
7 Safety factors.....	55
7.1 Aims and problem statement.....	55

7.2	Probabilistic fatigue assessment	57
7.2.1	Failure probability under constant amplitude stress	57
7.2.2	Fatigue damage under VA loading.....	58
7.2.3	Bignonnet method.....	59
7.3	Input data for probabilistic fatigue assessment of railway axles.....	60
7.3.1	Definitions of reference S-N diagrams	60
7.3.2	Miner Index at failure.....	62
7.3.3	Target reliability and failure rate for railway axles	63
7.4	Probabilistic fatigue damage calculations for railway axles	64
7.4.1	Format for the calculations.....	64
7.4.2	Montecarlo simulations.....	65
7.4.3	Stress spectra	65
7.5	Results	66
7.5.1	General	66
7.5.2	Safety factor and reliability under constant amplitude stress.....	67
7.5.3	Safety factor for damage calculations	68
8	Conclusions of Euraxles Project	69
9	Recommendations of CEN TC256/SC2/WG11	73
	Annex A (informative) Application example of the axle calculation method	74
A.1	General	74
A.2	General descriptions	74
A.3	Load distribution	75
A.4	Results according to EN 13103-1	76
A.5	Design of EURAXLES method	77
A.6	Comparison of results	79
	Bibliography	80

FprCEN/TR 17469:2019 (E)

European foreword

This document (FprCEN/TR 17469:2019) has been prepared by Technical Committee CEN/TC 256 “Railway applications”, the secretariat of which is held by DIN.

This document is currently submitted to the Vote on TR.

SAMPLE

Introduction

The first railway accident due to the fatigue failure of an axle occurred on 1842, May 8th, in France, near Meudon, on the Versailles-Paris line.

In those days, the fatigue phenomenon was unknown. This failure initiated numerous studies including German Engineer August WOHLER works on wheelset failures at the end of XIXth century.

In the middle of XXth century, M. KAMMERER, an engineer working for French railways, established the bases for the calculation of wheelset axles.

At international level, the report ORE B136 RP11 « Calculation of fret wagon and passenger coaches' wheelset axles » was edited in April 1979, using in particular the French approach.

This document allowed editing on 1994, July 1st of UIC leaflet 515-3 « Railway rolling stock – Bogie – Running gears – Axle calculation method».

The first edition of the European Standards about design of axles occurs on April 2001 (EN 13103 for non-powered axles for powered axles).

The ongoing European standardization has allowed the merging of EN 13103 in only one standard (EN 13103-1 Railway applications – Wheelsets and bogies – Part 1: Design method for axles with external journals) and the creation of a new Technical Specification about internal journal (prTS13103-2 Railway applications – Wheelsets and bogies – Part 2: Design method for axles with internal journals).

All these documents, including M. KAMMERER's work up to EN 13103-1 and prTS 13103-2, use the beam theory calculation method. The stresses taken into account are then the nominal stresses. The fatigue limit is determined from full scale tests in which nominal stresses are taken into account. Concentration factors are defined from tests to consider the local geometry and to increase the nominal stress locally. The method is quite simple, with no need of sophisticated calculations or dedicated software.

On another hand, in the middle of XXth century, the need in mechanics to have a tool to calculate complicated parts lead to the development of the finite element method.

Along with the theoretical study of this method, the use of new mathematical objects and the growth of calculation capacities of computers, the finite element method raised to a large and common use in design.

The stresses then calculated are local stresses, and not anymore nominal stresses, and the fatigue limit to be applied with this methodology are based on local stresses.

In the Euraxles project, the objective was to propose the use of a new assessment method based on load measurements, finite element method, experimental fatigue limit and new safety concept for the design of axles in particular for axle designs requiring more complex geometries. This design procedure is different from today's proven methods given by the EN standards *and not in a status to substitute them. Nevertheless, it was considered interesting to gather the Euraxles project results inside this Technical Report. The content should be considered as partial and only for informative uses at this stage. For example, the reliability of the input data, the variability of parameters, boundary conditions and the confidence in the partial results should be assessed at full extent.*

Where relevant, CEN TC256/SC2/WG11 comments and responses to preliminary enquiry inside the community were inserted for additional use for the reader, as Observations of CEN/TC 256/SC 2/WG 11. Besides, a general recommendation of use has been drafted by WG11 members in chapter 9.

This new method is described in this Technical Report in order to allow the possibility for wheelset designers to apply it and to collect return of experience for further improvement.

Work Program summary

FprCEN/TR 17469:2019 (E)

Clause 3 deals with the definition of a new fatigue design method which enables to assess the in-service reliability of axles with regards to fatigue failure. The proposed approach, based on the “Stress Strength Interference Analysis” (SSIA) and the “Fatigue-Equivalent-Load” (FEL) methods, aims at estimating the probability of axles’ fatigue failure by characterizing the variability of in-service loads and the scatter of the axles fatigue strength.

First of all, the main lines of the SSIA method are recalled. This method aims at evaluating the in-service reliability of components for their design or their homologation. In the second part, the fatigue load analysis method that is proposed for railway axles is described. It starts with a post-processing of an axle load measurement: from a time signal of forces applied to both wheels fitted on the axle, fatigue cycles of bending moment applied to the axle are identified and transformed into a cyclic equivalent load, Meq , which is a measurement of the severity of the initial variable load. Then, virtual but realistic load spectra are generated, thanks to a classification operation followed by a random draw of elementary load data that considers the operation and maintenance conditions of the axle. All the spectra are then analysed with the FEL method in order to build the distribution of in-service load severities. This distribution gives a picture of the stress to which the axles are submitted. In the third and last part, the methods are applied to real data of SNCF. Sensitivity analyses are performed in order to quantify the effect on Meq of variations of parameters and to verify the convergence and robustness of the process. Finally, results obtained for a passenger coach are given. The comparison between the distribution of load severities and the normative load, defined as according to standards EN 13103-1, shows that, for the studied axle, the normative load is very conservative. Finally, using the axles fatigue limits identified on full-scale tests, a Stress Strength Interference Analysis is performed to calculate the probability of failure of the axle.

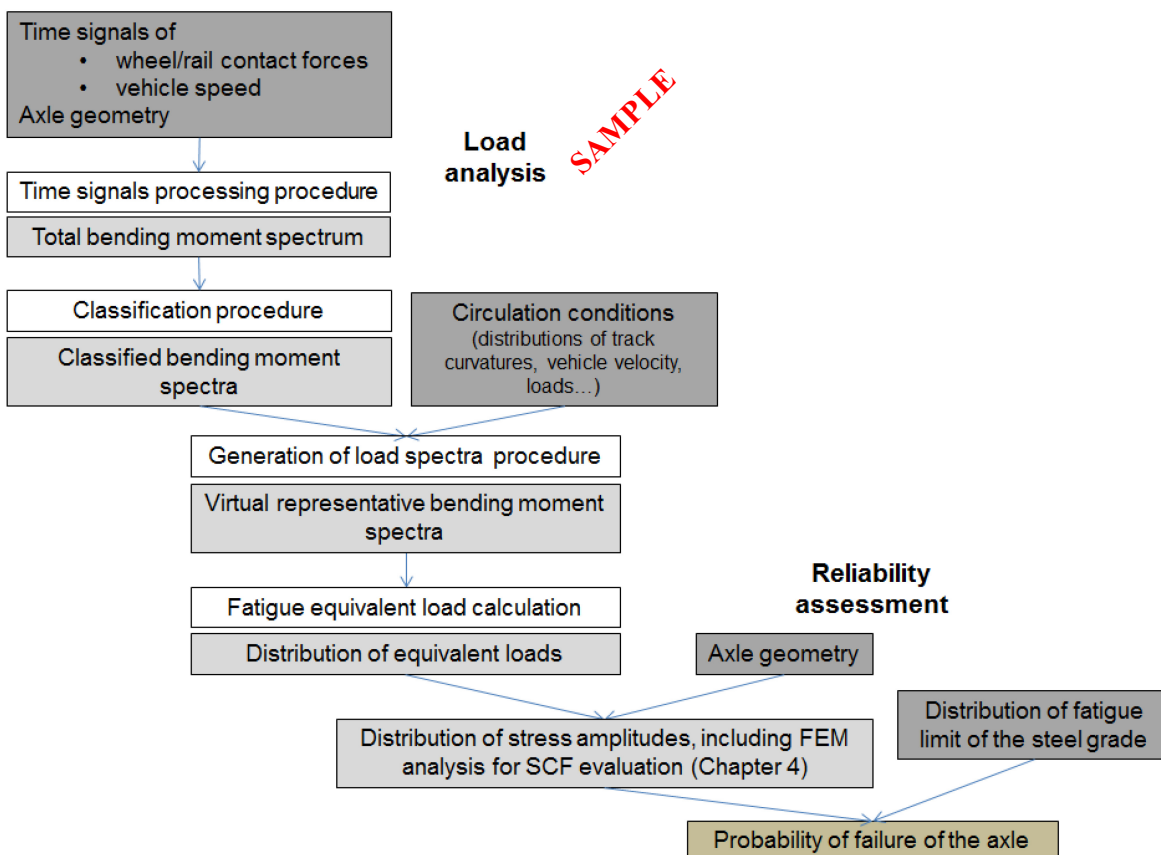


Figure 1 — Flowchart for load analysis and reliability assessment

Clause 4 concerns the mechanical modelling of an axle and defines a procedure to obtain local stresses from the applied loads.

The characteristics of the finite element models to be applied to railway axles are analysed in terms of element definition, convergence analysis, boundary conditions. A parametric analysis was performed to assess the applicability of the models. The numerical models generated were validated through the comparison with experimental results coming from full scale fatigue tests. Finally, a methodology to design axles using modelling tools as a complement to current European norms is proposed looking for a compromise between the computational effort and the results obtained.

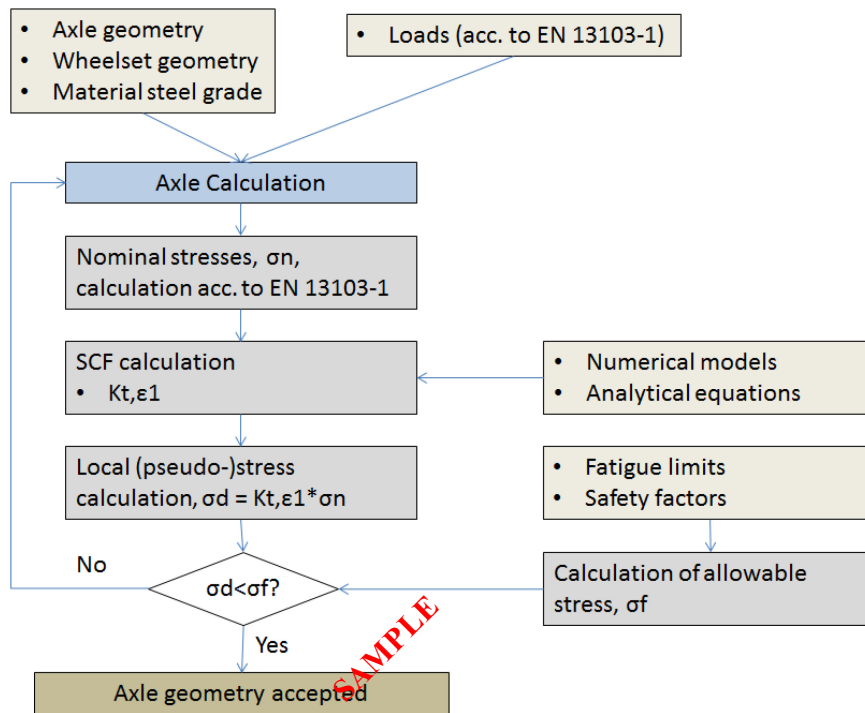


Figure 2 — Flowchart for modelling

The main scope of Clause 5 is to provide the fatigue limits for standard steel grades considering also the effect of surface conditions that may be different from the normal newly machined axles, like surface corrosion that can appear during the service or surface blasting as a method to improve paint adhesion.

The areas of the axles considered were the free body transitions or groves and the wheel seats where at high bending rates relative micro slips take place generating the so called fretting fatigue phenomena.

The paper provides in the conclusions a comparison with the fatigue limits that are today included in the European Standards.

Another aspect that is treated in this work is the stress concentration effect that takes place along the transitions where the body fatigue limit is verified. These parameters were measured by strain gauges during each test and used inside the Euraxle project to validate their estimation through FE model calculation.

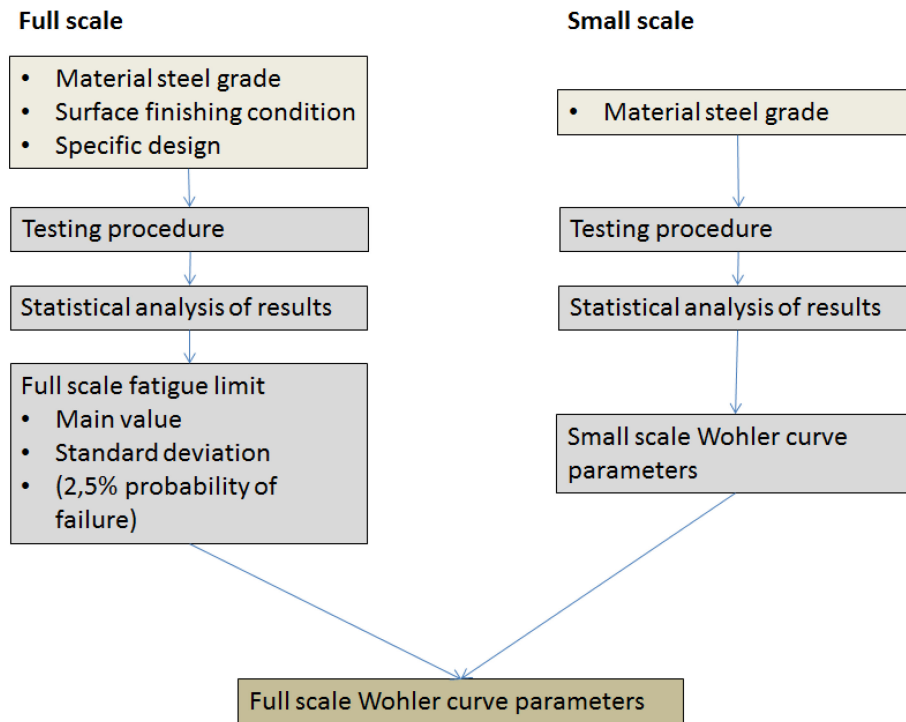


Figure 3 — Full-scale and small-scale fatigue tests

SAMPLE

1 Scope

This document presents the stage of knowledge resulting from the Euraxles project about the design of the axle, and further steps to be taken.

It is the support:

- to define the loads to be taken into account;
- to describe the stress calculation method using finite elements and the validation processes associated;
- to specify the maximum permissible stresses to be assumed in calculations and the safety factors to be used.

This technical report is applicable for:

- wheelset Axles defined in EN 13261 as “pure wheelset”;
- other axle designs such as those encountered in particular rolling stocks e.g. with independent wheels, variable gauges, urban rail...

This document has not for aim to replace EN 13103-1 and prTS 13103-2 but to present a complementary method to the existing ones.

2 Normative references

There are no normative references in this document.

3 Terms, definitions, symbols and abbreviations

3.1 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

3.2 Symbols and abbreviations

FEL	fatigue equivalent load method
SSIA	Stress Strength Interference Analysis
KMR	Consequent Miner Rule
FEM	Finite Element Method

Nomenclature is given in Table 1.

Table 1 — Nomenclature

$Y_1(t), Y_2(t)$	lateral force applied to both wheels
$Q_1(t), Q_2(t)$	vertical force applied to both wheels
P1, P2	Vertical loads applied on the journals
C_{min}	Minimum transition length
F	Fatigue load
F_{eq}	Fatigue equivalent load
F_n	Severe representative load that can be defined for test and simulation validation
x, y, z	Longitudinal, axial, vertical direction of wheelset reference axis
$M_x(y)$	Bending moment applied to the y-section of the axle in the x direction (train circulation direction)
M_x	Bending moment applied to the most critical section of the axle in the x direction
$M_{x,eq}$	Equivalent bending moment applied to the most critical section of the axle in the x direction
$M_{x,EN}$	Normative bending moment
MR	Resultant bending moment
P	Probability
P_f	Probability of failure
P_n	Probability of having a more severe load than F_n
E	Young modulus
K	Stress correction factor
K_t	Stress concentration factor
K_f	Fatigue stress concentration factor
$K_{t,s}$	Stress concentration factor based on strain measurements
D	Total fatigue damage
d_i	Partial damage generated by the ith class of a load spectrum
n_i	Occurrence of the ith class of a load spectrum
N_i	Number of cycles for a crack initiation for the ith class of a load spectrum
CV_X	Coefficient of variation for the X variable
m	Slope of the S-N diagram when using a one single slope curve
k	Slope of the S-N diagram for $S > S_D$
k'	Slope of the S-N diagram for $S < S_D$
N_D	number of cycle for the knee of the S-N diagram
S	Stress load
S_D	stress amplitude for the knee of the S-N diagram
K_{ref}	total mileage of an axle

σ_f	Allowable fatigue stress
σ_d	Calculated dynamic stress
σ_{VM}	Von Mises stress
σ_h	Hydrostatic stress
τ	Shear stress
σ_1	Principal stress
ε_1	Principal strain
σ_n	Nominal stress
D/d	Diameter ratio (diameter of wheel seat divided diameter of nearby body)
D_N	Outer diameter of hub
d	Diameter of the axle shaft
r_{max}	Maximum value of the radius of the transition r
F1	Full scale axle body fatigue limit
F4	Full scale axle seat fatigue limit

4 Loads

4.1 Reliability analysis based on the Stress Strength Interference Analysis method

Fatigue is known to be a damage phenomenon which is very dispersive. The sources of variability are linked to the material properties that depend on its composition but also on the manufacturing process, the geometry of the structure, loads, usages, environment, etc. To ensure safety, margins applied to the specified loads and the prescribed fatigue limits, associated to a stress calculation method were defined in standards EN 13103-1 [21] for the design and validation of railway axles. They were established in the past decades, based on experience of railway experts and experimental and modelling works. Today, they enable to guaranty a high level of safety for the European railway sector, as feedback from operation shows. But, to gain competitiveness, it can be very useful to measure the available margins in order to ensure that when a new design or a new technology is introduced, the level of safety is maintained.

For that reason, it would be beneficial to switch little by little from conservative approaches towards reliability approaches. Maximalist approaches ensure safe designs by defining safety factors that make the load specifications more severe and underestimate the allowable fatigue limits. The consequence is that optimized solutions can't be found. Moreover, when a significant change occurs in the system, it is difficult to evaluate its impact on reliability. In reliable approaches, the aim is to have a "just necessary" design associated to a target probability of failure. For safety critical components, the probability of failure during the lifetime generally vary from 10^{-5} to 10^{-8} . In the example given in [4] on an automotive engine part, the target probability is 10^{-6} . For railway safety applications, if one considers that the number of accidents due to mechanical failures is rather small, a target between 10^{-6} and 10^{-7} sounds reasonable.

Observations of CEN/TC 256/SC 2/WG 11: The target value quoted (10^{-6} to 10^{-7}) is a failure rate per axle during its whole life. It is approximately in line with the 10^{-9} failure rate per operational hour defined in the CSM (EU regulation 402/2013) for technical systems for which a functional failure with immediate disastrous consequences is assumed.