



~~Designation: D70-03~~ Designation: D 70 – 08

Standard Test Method for Density of Semi-Solid Bituminous Materials (Pycnometer Method)¹

This standard is issued under the fixed designation D 70; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the Department of Defense.

1. Scope

1.1 This test method covers the determination of the ~~specific gravity~~ relative density and density of semi-solid bituminous materials, asphalt cements, and soft tar pitches by use of a pycnometer.

NOTE 1—An alternate method for determining the density of semi-solid and solid bituminous materials is Test Method D 3289. For materials which are too fluid for use of this test method, use Test Method D 3142.

~~1.2 This standard does not purport to address the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.~~

1.2 The values stated in SI units are to be regarded as the standard. The values given in parentheses are for information only.

~~1.3 This standard does not purport to address the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.~~

2. Referenced Documents

2.1 ASTM Standards:

~~C 670 Practice for Preparing Precision and Bias Statements for Test Methods for Construction Materials²~~

~~C 670 Practice for Preparing Precision and Bias Statements for Test Methods for Construction Materials~~

~~D 140 Practice for Sampling Bituminous Materials~~

~~D 3142 Test Method for Density of Liquid Asphalts (Hydrometer Method)³~~ Test Method for Specific Gravity, API Gravity, or Density of Cutback Asphalts by Hydrometer Method

~~D 3289 Test Method for Density of Semi-Solid and Solid Bituminous Materials (Nickel Crucible Method)~~

~~D 4311 Practice for Determining Asphalt Volume Correction to a Base Temperature~~

~~E 1 Specification for ASTM Thermometers~~ Specification for ASTM Liquid-in-Glass Thermometers

2.2 Other:

CRC Handbook of Chemistry and Physics

3. Terminology

3.1 Definitions of Terms Specific to This Standard:

3.1.1 *density*—the mass per unit volume of a material.

3.1.2 *relative density*—the ratio of the mass of a given volume of a material to the mass of the same volume of water at the same temperature (see Note 2).

NOTE 2—Relative density is also described as specific gravity.

4. Summary of Test Method

4.1 The sample is placed in a calibrated pycnometer. The pycnometer and sample are weighed, then the remaining volume is filled with water. The filled pycnometer is brought to the test temperature, and weighed. The density of the sample is calculated

¹ This test method is under the jurisdiction of ASTM Committee D04 on Road and Paving Materials and is the direct responsibility of Subcommittee D04.47 on Miscellaneous Asphalt Tests.

Current edition approved Jan. 10, 2003-1, 2008. Published May 2003-January 2008. Originally approved in 1920. Last previous edition approved in 1997-2003 as ~~D70-97~~ D 70 – 03.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards*, Vol 04.02, volume information, refer to the standard's Document Summary page on the ASTM website.

from its mass and the mass of water displaced by the sample in the filled pycnometer.

5. Significance and Use

5.1 Values of density are used for converting volumes to units of mass, and for correcting measured volumes from the temperature of measurement to a standard temperature using Practice D 4311.

6. Apparatus

6.1 *Pycnometer*, glass, consisting of a cylindrical or conical vessel carefully ground to receive an accurately fitting glass stopper 22 to 26 mm in diameter. The stopper shall be provided with a hole 1.0 to 2.0 mm in diameter, centrally located in reference to the vertical axis. The top surface of the stopper shall be smooth-substantially plane and substantially plane, have no chips, and the lower surface shall be concave to allow all air to escape through the bore. The height of the concave section shall be 4.0 to 18.0 mm at the center. The stoppered pycnometer shall have a capacity of 24 to 30 mL and shall weigh not more than 40 g. Suitable pycnometers are illustrated in Fig. 1.

6.2 *Water Bath*, constant-temperature, capable of maintaining the temperature within 0.1°C (0.2°F) of the test temperature.

6.3 *Thermometers*, calibrated liquid in glass, total immersion type, of suitable range with graduations at least every 0.1°C and a maximum scale error of 0.1°C as prescribed in Specification E1. Thermometer commonly used is ASTM 63°C. Older ASTM 63F thermometers may be used until supplies are exhausted. Any other thermometer device of equal accuracy may be used. Thermometric device, calibrated liquid in glass, total immersion type, of suitable range with graduations at least every 0.1°C (0.2°F) and a maximum scale error of 0.1°C (0.2°F) as prescribed in Specification E 1. Thermometer commonly used is ASTM 63°C (63F). Any other thermometric device of equal accuracy may be used.

6.4 *Balance*, capable of making the required measurements to an accuracy of at least 0.001g.

6.5 *Beaker*, 600 mL or larger Griffin low-form beaker.

7. Materials

7.1 *Water*—Freshly boiled and cooled distilled or deionized water.

8. Hazards

8.1 **Warning:** Mercury has been designated by the United States Environmental Protection Agency (EPA) and many state agencies as a hazardous material that can cause central nervous system, kidney and liver damage. Mercury, or its vapor, may be hazardous to health and corrosive to materials. Caution should be taken when handling mercury and mercury containing products. See the applicable product Material Safety Data Sheet (MSDS) for details and EPA’s website—www.epa.gov/mercury/faq.htm—for additional information. Users should be aware that selling mercury, mercury containing products, or both, into your state may be prohibited by state law.

9. Sampling

9.1 Take 9.1 Take samples in accordance with Practice D 140. The sample shall be free of foreign substances.

9.2 Thoroughly mix the sample before removing a representative portion for testing.

9. Preparation of Apparatus

9.1 Partially fill a 600-mL Griffin low-form beaker with freshly boiled and cooled distilled or deionized water to a level that will allow the top of the pycnometer to be immersed to a depth of not less than 40 mm.

9.2 Partially immerse the beaker in the water bath to a depth sufficient to allow the bottom of the beaker to be immersed to a depth of not less than 100 mm, while the top of the beaker is above the water level of the bath. Clamp the beaker in place.

9.3 Maintain the temperature of the water bath within 0.1°C of the test temperature.

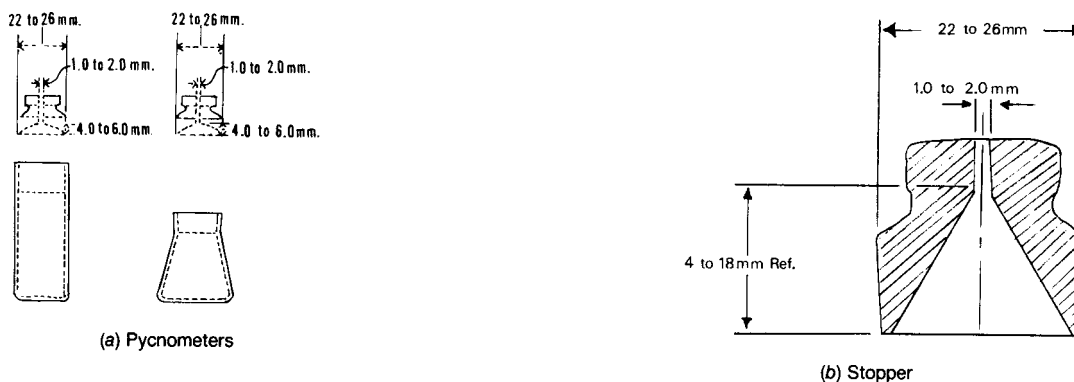


FIG. 1 Suitable Pycnometers and Stopper