

ISO/TC 61/SC 13

Secretariat: JISC

Voting begins on:
2014-05-20

Voting terminates on:
2014-07-20

Reinforcement materials — Tubular braided sleeves — Basis for a specification

Produits de renfort — Gaines tressées — Base de spécification

ITeH STANDARD PREVIEW
(standards.iteh.ai)
Full standard:
<https://standards.iteh.ai/catalog/standards/sist/1e972a1f-b2ed-4995-bbc1-b77fad69e3d7/iso-10122-2014>

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.



Reference number
ISO/FDIS 10122:2014(E)

iTeh STANDARD PREVIEW
(standards.iteh.ai)
Full standard:
<https://standards.iteh.ai/catalog/standards/sist/1e9724af-b2ed-4995-bbc1-b77fad69e3d7/iso-10122-2014>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2014

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Description and designation	2
4.1 Technical description of tubular braided sleeves	2
4.2 Designation	2
5 Characteristics	3
5.1 General	3
5.2 Characteristics to be specified	3
5.3 Defects	4
6 Sampling and conditioning of specimens	4
6.1 Sampling	4
6.2 Conditioning of specimens	4
7 Test methods	5
7.1 Thickness	5
7.2 Diameter, braid angle, and mass per metre length	5
8 Packaging and ordering	7
8.1 Packaging	7
8.2 Ordering data	7
9 Storage	7

iTeh STANDARD PREVIEW
 (standards.iteh.ai)
 Full standard:
<https://standards.iteh.ai/catalog/standards/sist/1e9724af-b2ed-4995-bbc1-b77fad69e3d7/iso-10122-2014>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: Foreword - Supplementary information

The committee responsible for this document is ISO/TC 61, *Plastics*, Subcommittee SC 13, *Composites and reinforcement fibres*.

This second edition cancels and replaces the first edition (ISO 10122:1995), which has been technically revised.

Reinforcement materials — Tubular braided sleeves — Basis for a specification

1 Scope

This International Standard provides a basis for specifications applicable to tubular braided sleeves used as reinforcements in plastics. It deals with tubular sleeves braided from all types of yarn or roving.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 291, *Plastics — Standard atmospheres for conditioning and testing*

ISO 1887, *Textile glass — Determination of combustible-matter content*

ISO 1889, *Reinforcement yarns — Determination of linear density*

ISO 2797, *Textile glass — Rovings — Basis for a specification*

ISO 3598, *Textile glass — Yarns — Basis for a specification*

ISO 4603, *Textile glass — Woven fabrics — Determination of thickness*

ISO 8516, *Textile glass — Textured yarns — Basis for a specification*

ISO 10548, *Carbon fibre — Determination of size content*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

tubular braided sleeve

sleeve made by interlacing (braiding or plaiting) four or more yarns or rovings in such a way that they cross one another and are laid together in a helical formation

3.2

braiding

method of interlacing yarns or rovings

3.3

construction

structure of a sleeve, depending closely upon the type of machine used and the number of yarns or rovings per carrier

3.4

carrier

braiding-machine part on which the yarns or rovings are wound

3.5

braid angle

angle between the longitudinal axis of a braid and the direction of the yarns or rovings

4 Description and designation

4.1 Technical description of tubular braided sleeves

The complete description of a tubular braided sleeve requires definition of the following points:

- a) designation of the braid yarn(s);
- b) construction of the sleeve;
- c) braid angle at a specific diameter;
- d) type of treatment;
- e) mass per metre length of the sleeve.

As the full description is unwieldy, the manufacturers of tubular braided sleeves normally give a code number to their products to simplify ordering and stocking. The full description of the braided sleeve shall, however, be given in the manufacturer's catalogue against its code number.

Thus, this International Standard is not meant for use in the designation of tubular braided sleeves, but is intended to be used as an aid in the preparation of standardized descriptions in the braided-sleeve catalogues and to ensure the consistency of braided sleeve identification.

4.2 Designation

The designation shall be made up of the following three groups of code-letters/numbers:

- a) the first group (maximum of four characters) indicates the type or types of material used in the braiding;

The following code letters shall be used to designate different types of material:

- G = Glass
- C = Carbon
- A = Aramid
- E = Ceramic
- P = Polyethylene

If two or more types of material are combined in a hybrid braiding, two or more code letters shall be used.


EXAMPLES

- CG = Carbon/glass
- CAE = Carbon/aramid/ceramic
- CGEA = Carbon/glass/ceramic/aramid

If several fibre types are used, they shall be given in order of the cross-sectional area (i.e. the mass per unit length divided by the density) of the fibre concerned, starting with the fibre having the greatest cross-sectional area.

- b) the second group (three digits) indicates the sleeve diameter, in millimetres, at a fibre angle of 45°;
- c) the third group (three digits) indicates the mass, in grams per metre of sleeve, at a diameter which corresponds to a fibre angle of 45°.

EXAMPLE

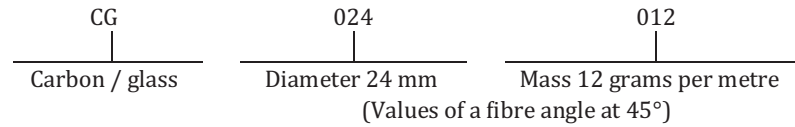

5 Characteristics

5.1 General

The sleeve shall be of uniform structure.

5.2 Characteristics to be specified

For relevant methods of measurement, see [Clause 7](#).

5.2.1 Construction characteristics

5.2.1.1 The type of braiding yarn or roving shall be in accordance with ISO 2797, ISO 3598, and/or ISO 8516.

5.2.1.2 The construction of the sleeve shall be specified by the following:

- a) type(s) of yarn used on each carrier;
- b) linear density, in tex or decitex of the braid yarns in accordance with ISO 1889 or ISO 10120;
- c) number of carriers;
- d) type of braid;
 - 1) standard or regular braid (each carrier passes alternately under and over, or inside and outside two other carriers);
 - 2) two-by-two or paired braid (the carriers run in pairs, each pair passing alternately under and over every other pair revolving in the opposite direction);
- e) braid angle at a specific diameter;
- f) mass per metre length of the sleeve at that diameter.

5.2.1.3 A roll or spool of sleeve shall be assumed to be in one piece, unless otherwise stated.

5.2.1.4 The nominal thickness shall be subject to agreement between supplier and buyer. It shall be given in millimetres.

5.2.2 Treatment

Specify the treatment from the following:

5.2.2.1 Type of treatment

- a) textile size;
- b) plastic size;
- c) desized;

- d) coupling finish;
- e) any other treatment.

5.2.2.2 Amount of size and finish

The amount of size and finish shall be expressed as a nominal percentage by mass in accordance with ISO 1887 or ISO 10548.

5.3 Defects

For the defects listed below, the specification shall define the level of defects which can be considered acceptable and, when applicable, the method of visual examination to be used.

5.3.1 Braiding defects

- 5.3.1.1 Ends out: a gap caused by a missing braiding yarn.
- 5.3.1.2 Tight end: a braiding yarn braided under excessive tension.
- 5.3.1.3 Stack end: a braiding yarn braided under insufficient tension.
- 5.3.1.4 Angle deviation at a specified diameter.

5.3.2 Other defects

- 5.3.2.1 Dirt: self-descriptive.
- 5.3.2.2 Folds: self-descriptive.
- 5.3.2.3 Grease: self-descriptive.
- 5.3.2.4 Faulty splices: self-descriptive.

6 Sampling and conditioning of specimens

6.1 Sampling

Samples shall be taken from the elementary unit for each delivery of a given type of tubular braided sleeve (roll or spool). The whole length of each roll selected shall be examined for defects.

The number of test specimens taken from each sample shall be as specified for each test method.

NOTE The elementary unit is the smallest normally commercially available entity of a given product as the following:

- package (single yarn, folded or cabled yarn, roving, etc.);
- roll (mat, woven fabric, veil, etc.);
- smallest physical entity in a bulk product (e.g. chopped fibres, milled fibres).

6.2 Conditioning of specimens

Specimens shall be kept for at least 6 h in one of the atmospheres specified in ISO 291 [generally 23 °C ± 2 °C (50 ± 10) % relative humidity] unless a different conditioning atmosphere is specified.

7 Test methods

7.1 Thickness

The method specified in ISO 4603 can be used to measure the thickness of the flattened tubular braid.

7.2 Diameter, braid angle, and mass per metre length

The procedure described enables a tubular braided sleeve to be characterized in terms of its diameter, braid angle, and mass per metre length, the values obtained being used to generate a designation code.

7.2.1 Apparatus

7.2.1.1 Circular tube or shaft with a diameter which gives a fibre angle between 20° and 70° relative to the axis of the tube.

It is advisable to use a tube or shaft with a length between 500 mm and 1 000 mm. The walls of the tube shall not deviate from parallel by more than 5 %.

7.2.1.2 Vernier callipers reading to 0,1 mm and accurate to 0,5 mm, for measuring the diameter of the tube.

7.2.1.3 Rule reading to 0,5 mm, to measure the length of the tube and the length of a yarn or roving taken from the specimen.

7.2.1.4 Balance reading to 0,01 g and accurate to 0,05 g, to determine the mass of the specimen.

7.2.1.5 Pair of scissors or knife, suitable for cutting the specimen.

7.2.2 Conditioning

See [6.2](#).

7.2.3 Procedure

Measure the diameter and length in millimetres of the tube or shaft.

Pull the sleeve over the tube or shaft without leaving any slack and cut off a specimen with the same length as the tube.

Determine the mass in grams of the specimen.

Take a yarn or roving from the specimen and measure its length, in millimetres.

Calculate the braid angle (see [7.2.5.1](#)).

Calculate the diameter at a braid angle of 45° (see [7.2.5.2](#)).

Calculate the mass per metre length at a braid angle of 45° (see [7.2.5.3](#)).

7.2.4 Designation code

Generate the designation code as specified in [4.2](#).