

---

---

**Centrifugally cast steel and alloy  
products —**

**Part 1:  
General testing and tolerances**

*Produits en acier et alliages moulés par centrifugation —*

*Partie 1: Conditions générales d'essais et tolérances*

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 13583-1:2015

<https://standards.iteh.ai/catalog/standards/sist/34db345f-d978-4aae-bdda-df528e9bdf75/iso-13583-1-2015>



**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 13583-1:2015

<https://standards.iteh.ai/catalog/standards/sist/34db345f-d978-4aae-bdda-df528e9bdf75/iso-13583-1-2015>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2015, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Ch. de Blandonnet 8 • CP 401  
CH-1214 Vernier, Geneva, Switzerland  
Tel. +41 22 749 01 11  
Fax +41 22 749 09 47  
copyright@iso.org  
www.iso.org

# Contents

	Page
Foreword .....	iv
<b>1 Scope .....</b>	<b>1</b>
<b>2 Normative references .....</b>	<b>1</b>
<b>3 Terms and definitions .....</b>	<b>1</b>
<b>4 Materials .....</b>	<b>3</b>
<b>5 Supply .....</b>	<b>3</b>
<b>6 Mechanical tests .....</b>	<b>3</b>
<b>7 Surface finish requirements .....</b>	<b>4</b>
<b>8 Minimum sound wall (MSW) thickness and soundness .....</b>	<b>4</b>
<b>9 Dimensional and shape tolerances .....</b>	<b>4</b>
9.1 General .....	4
9.2 Length .....	4
9.3 Straightness .....	4
9.4 Outside and inside diameters .....	5
<b>10 Inspection procedures and standards of acceptance .....</b>	<b>6</b>
<b>11 Production welding .....</b>	<b>6</b>
<b>12 Supplementary requirements .....</b>	<b>6</b>
12.1 General .....	6
12.2 Pressure test .....	7
12.3 Elevated temperature test .....	7
12.4 Acid etch ring test .....	7
12.5 Magnetic particle test .....	7
12.6 Ferrite determination .....	7
12.7 Corrosion testing .....	7
12.8 Eddy current testing .....	7
12.9 Radiography .....	7
12.10 Ultrasonic testing .....	7

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](http://www.iso.org/Foreword%20Supplementary%20information)

The committee responsible for this document is ISO/TC 17, *Steel*, Subcommittee SC 11, *Steel castings*.

This second edition cancels and replaces the first edition (ISO 13583-1:2000), which has been technically revised with the following changes:

- in [Clause 2](#), the normative references were replaced with superseding International Standards;
- the former 8.2 having been deleted, the original subclause 8.3 was renumbered [8.2](#);
- [10.1.1](#) was revised;
- [10.1.2](#) was revised.

ISO 13583 consists of the following parts, under the general title *Centrifugally cast steel and alloy products*:

- *Part 1: General testing and tolerances*
- *Part 2: Materials*

# Centrifugally cast steel and alloy products —

## Part 1: General testing and tolerances

### 1 Scope

This part of ISO 13583 specifies the requirements for horizontal and vertical centrifugally cast steel and alloy products to be used in the following applications:

- a) heat resisting;
- b) corrosion resisting;
- c) general engineering.

### 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3651-1, *Determination of resistance to intergranular corrosion of stainless steels — Part 1: Austenitic and ferritic-austenitic (duplex) stainless steels — Corrosion test in nitric acid medium by measurement of loss in mass (Huey test)*

ISO 3651-2, *Determination of resistance to intergranular corrosion of stainless steels — Part 2: Ferritic, austenitic and ferritic-austenitic (duplex) stainless steels — Corrosion test in media containing sulfuric acid*

ISO 4986, *Steel castings — Magnetic particle inspection*

ISO 4987, *Steel castings — Liquid penetrant inspection*

ISO 4990, *Steel castings — General technical delivery requirements*

ISO 4992-1, *Steel castings — Ultrasonic examination — Part 1: Steel castings for general purposes*

ISO 4992-2, *Steel castings — Ultrasonic examination — Part 2: Steel castings for highly stressed components*

ISO 4993, *Steel castings — Radiographic inspection*

ISO 6892-1, *Metallic materials — Tensile testing — Part 1: Method of test at room temperature*

ISO 6892-2, *Metallic materials — Tensile testing — Part 2: Method of test at elevated temperature*

ISO 13520, *Determination of ferrite content in austenitic stainless steel castings*


### 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

### 3.1 minimum sound wall thickness MSW

thickness which remains when all the porosity and roughness associated with the internal and external cast surfaces have been removed by machining

Note 1 to entry: See [Figures 1](#) and [2](#).

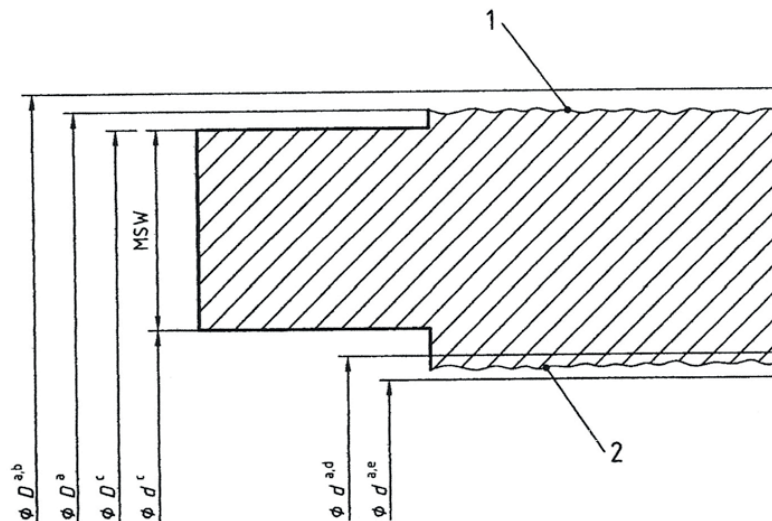

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)


#### Key

- 1 outside roughness
- 2 inside porosity
- $D$  outside diameter
- $d$  inside diameter
- a As-cast.
- b + tolerance.
- c Machined.
- d + porosity.
- e – tolerance.

[ISO 13583-1:2015](#)

<https://standards.iteh.ai/catalog/standards/sist/34db345f-d978-4aae-bdda-df528e9bdf75/iso-13583-1-2015>

**Figure 1 — Horizontal centrifugally cast tube**

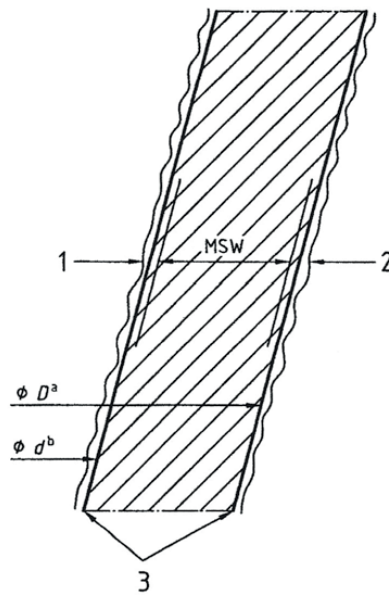

#### Key

- 1 inside porosity
- 2 outside roughness
- 3 unmachined surfaces with MSW and additions resulting from tolerances on diameters
- a Machined + tolerance.
- b Machined – tolerance.

ISO 13583-1:2015  
<https://standards.iteh.ai/catalog/standards/sist/34db345f-d978-4aae-bdda-4f28e9baf5/iso-13583-1-2015>  
**Figure 2—Vertical centrifugally cast tube**

## 4 Materials

Materials shall be specified by the purchaser.

## 5 Supply

The product shall comply with the requirements of ISO 4990.

## 6 Mechanical tests

**6.1** Test pieces for mechanical tests shall be taken either from the centrifugally cast product or from separately cast samples from the same melt as the casting and heat treated under the same conditions as the casting they represent. The tensile test shall be carried out in accordance with ISO 6892-1.

Separately cast samples are acceptable only if agreed between purchaser and manufacturer.

**6.2** Upon agreement, the tensile test at room temperature may be substituted by an elevated temperature tensile test, a stress to rupture test or a creep test, (see [12.3](#)). The elevated temperature tensile test shall be carried out in accordance with ISO 6892-2.

## 7 Surface finish requirements

The surface finish shall be agreed between purchaser and manufacturer.

## 8 Minimum sound wall (MSW) thickness and soundness

**8.1** The purchaser may specify an MSW which may be measured in accordance with either [8.1.1](#) or [8.1.2](#), the method and criteria to be agreed between the purchaser and manufacturer at the time of the enquiry and order.

**NOTE** In the case of cast products supplied with an as-cast internal surface and having a specified MSW thickness, in order to compensate for unsoundness which can be associated with the cast internal surface, it is necessary to add an internal unsoundness allowance. The allowance that will be necessary in any specific cast will vary according to the total as-cast thickness of the cast product and the soundness requirements. In addition, an allowance can be required to accommodate any minor imperfections associated with the as-cast external surface.

**8.1.1** A length of the cast product (100 mm minimum length) machined on the inside and outside diameter surfaces to produce a product having at least the specified MSW and dimensions in accordance with the customer's drawing.

**8.1.2** The machined profile end (weld preparation) of the product.

**8.2** The MSW thickness shall be measured at 90° intervals. All measurements shall be within the MSW tolerance.

## 9 Dimensional and shape tolerances

<https://standards.iteh.ai/catalog/standards/sist/34db345f-d978-4aae-bdda-df528e9bdf75/iso-13583-1-2015>

### 9.1 General

The purchaser shall state clearly on the order the tolerances to be achieved, otherwise the following tolerances shall be used.

### 9.2 Length

The minimum length of the tube shall be agreed upon between the purchaser and manufacturer. In the case where two or more tubes are welded together, if the minimum length is not stated in the enquiry or order it shall be not less than 1,3 m.

The tolerance on length shall be governed by the diameter of the product as shown in [Table 1](#).

**Table 1 — Tolerance on length**

Diameter mm	Tolerance mm
≤ 150	+4 0
> 150	+5 0

### 9.3 Straightness

The deviation from straightness on the full length of tube shall be agreed upon between the purchaser and manufacturer. If no agreement is made, the deviation from straightness shall be at the discretion of the manufacturer.



The cast product may be mechanically straightened at room temperature.

All straightening shall be carried out prior to surface inspection.

## 9.4 Outside and inside diameters

**9.4.1** The tolerance on the outside diameter of the as-cast product shall be in accordance with [Table 2](#).

**Table 2 — Tolerance on outside diameter,  $D$**

Diameter of product mm	Tolerance mm
$\leq 150$	$\begin{smallmatrix} +2 \\ 0 \end{smallmatrix}$
$> 150$ but $\leq 300$	$\begin{smallmatrix} +2,5 \\ 0 \end{smallmatrix}$
$> 300$ but $\leq 500$	$\begin{smallmatrix} +4 \\ 0 \end{smallmatrix}$
$> 500$ but $\leq 750$	$\begin{smallmatrix} +5 \\ 0 \end{smallmatrix}$
$> 750$ but $\leq 1\,000$	$\begin{smallmatrix} +6 \\ 0 \end{smallmatrix}$
$> 1\,000$	$\begin{smallmatrix} +8 \\ 0 \end{smallmatrix}$

**9.4.2** The tolerances on the machined surfaces shall be stated on the enquiry and order. If tolerances are not given, the following tolerances shall be used:

- tolerance on outside diameter  $\begin{smallmatrix} +1,5 \text{ mm} \\ 0 \text{ mm} \end{smallmatrix}$
- tolerance on inside diameter  $\begin{smallmatrix} 0 \text{ mm} \\ -1,5 \text{ mm} \end{smallmatrix}$

**9.4.3** The tolerance on inside diameter,  $d$ , of the as-cast product shall be dependent upon the wall thickness of the product as shown in [Table 3](#). For products with an inside diameter greater than 900 mm and a wall thickness greater than 100 mm, the tolerance shall be by agreement between purchaser and manufacturer.