



Designation: ~~D1084-97~~ (Reapproved 2005) Designation: D 1084 – 08

Standard Test Methods for Viscosity of Adhesives¹

This standard is issued under the fixed designation D 1084; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the Department of Defense. These test methods replace Method 4021 or Federal Test Method Standard No. 175a.

1. Scope

1.1 These test methods cover the determination of the viscosity of free-flowing adhesives.

1.1.1 The limitation of this test method to self-leveling adhesives eliminates thixotropic and plastic materials whose viscosity is a function of the rate of stirring and previous history of the adhesive.

~~1.2~~

~~1.2 The values stated in SI units are to be regarded as the standard. The values in parentheses are for information only.~~

~~1.3 This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.~~

~~1.3 The values stated in SI units are to be regarded as the standard. The values in parentheses are for information only.~~

2. Referenced Documents

2.1 *ASTM Standards:*²

D 88 Test Method for Saybolt Viscosity

D 115 Test Methods for Testing Solvents/Solvent Containing Varnishes Used for Electrical Insulation

D 562 Test Method for Consistency of Paints Measuring Krebs Unit (KU) Viscosity Using a Stormer-Type Viscometer

D 907 Terminology of Adhesives

D 1200 Test Method for Viscosity by Ford Viscosity Cup

D 1545 Test Method for Viscosity of Transparent Liquids by Bubble Time Method

D 1601 Test Method for Dilute Solution Viscosity of Ethylene Polymers

D 2556 Test Method for Apparent Viscosity of Adhesives Having Shear-Rate-Dependent Flow Properties

2.2 *ISO Document:*³

ISO 2555 Plastics — Resins in the Liquid State or as Emulsions or Dispersions — Determination of Apparent Viscosity by the Brookfield Test Method

3. Terminology

3.1 *Definitions*—Many terms in these test methods are defined in Terminology D 907.

3.1.1 *viscosity, n—of a liquid*, the resistance to flow expressed as the ratio of the applied stress to the resulting rate of shearing strain (see Newtonian behavior and thixotropy). (Compare consistency.)

3.2 *Definitions of Terms Specific to This Standard:*

3.2.1 *viscosity, n*—the ratio of shear stress to shear rate. The viscosity of a liquid is a measure of the internal friction of the liquid in motion. The unit of dynamic viscosity is the poise, which is expressed as dyne-seconds per square centimetre. For a Newtonian liquid, the viscosity is constant at all shear rates. For a non-Newtonian liquid, viscosity will vary depending on shear rate.

4. Significance and Use

4.1 Several test methods are noted for viscosity determination of Newtonian and near Newtonian flow characteristics. (For

¹ These test methods are under the jurisdiction of ASTM Committee D14 on Adhesives and are the direct responsibility of Subcommittee D14.10 on Working Properties

Current edition approved April/Feb. 1, 2005-2008. Published April-2005/February 2008. Originally approved in 1950. Last previous edition approved in 1997/2005 as D 1084 – 97 (2005).

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ Manufactured by the Brookfield Engineering Laboratories, Stoughton, MA.

³ Available from American National Standards Institute (ANSI), 25 W. 43rd St., 4th Floor, New York, NY 10036, <http://www.ansi.org>.

adhesives not fitting into this category, Test Method D 2556 should be considered.) Four test methods are covered as follows:

4.1.1 *Method A* is applicable only to adhesives that will deliver 50 mL in a steady uninterrupted stream from one of the cups described in Section 5.

4.1.2 *Method B* is intended for measuring the viscosity of adhesives covering a range from 0.05 Pa · s to 200 Pa · s (50 to 200 000 cP) and is limited to materials that have or approach Newtonian flow characteristics.

4.1.3 *Method C* is intended primarily as a control method for determining the viscosity of adhesives that have or approach Newtonian flow characteristics.

4.1.4 *Method D* is intended primarily as a control method for determining the viscosity of materials that have an equivalent viscosity no greater than approximately 3000 cP and is limited to materials that have or approach Newtonian flow characteristics.

TEST METHOD A

5. Apparatus

5.1 The apparatus (Fig. 1) consists of a set of four viscosity cups so designed as to deliver 50 mL of the sample in from 30 to 100 s at a temperature of 23 ± 0.5°C (73.4 ± 0.9°F).

5.1.1 Four consistency cups constitute a set as follows:


	Diameter of Orifice, in.
First Cup	0.07 ± 0.0001
Second cup	0.10 ± 0.0001
Third cup	0.15 ± 0.0001
Fourth cup	0.25 ± 0.0001

5.1.2 Cups made of brass or bronze. Orifice disks made of 18 % Chromium, 8 % Nickel stainless steel. The diameter of the Orifice pressed in the cup shall be stamped on the cup

5.1.3 Fractional dimensions subject to permissible variations of ±0.01 in., unless otherwise specified.

6. Procedure

6.1 Bring the sample to be tested and the viscosity cup to a temperature of 23 ± 0.5°C (73.4 ± 0.9°F) (preferably in a constant-temperature room). Then mount the consistency cup in the clamp provided for the purpose and place the receiving cylinder in position. With the outlet of the cup closed by means of the finger, pour the sample into the cup until it is filled to overflowing. Strike off the excess with a straightedge, and then remove the finger from over the outlet and allow the sample to flow

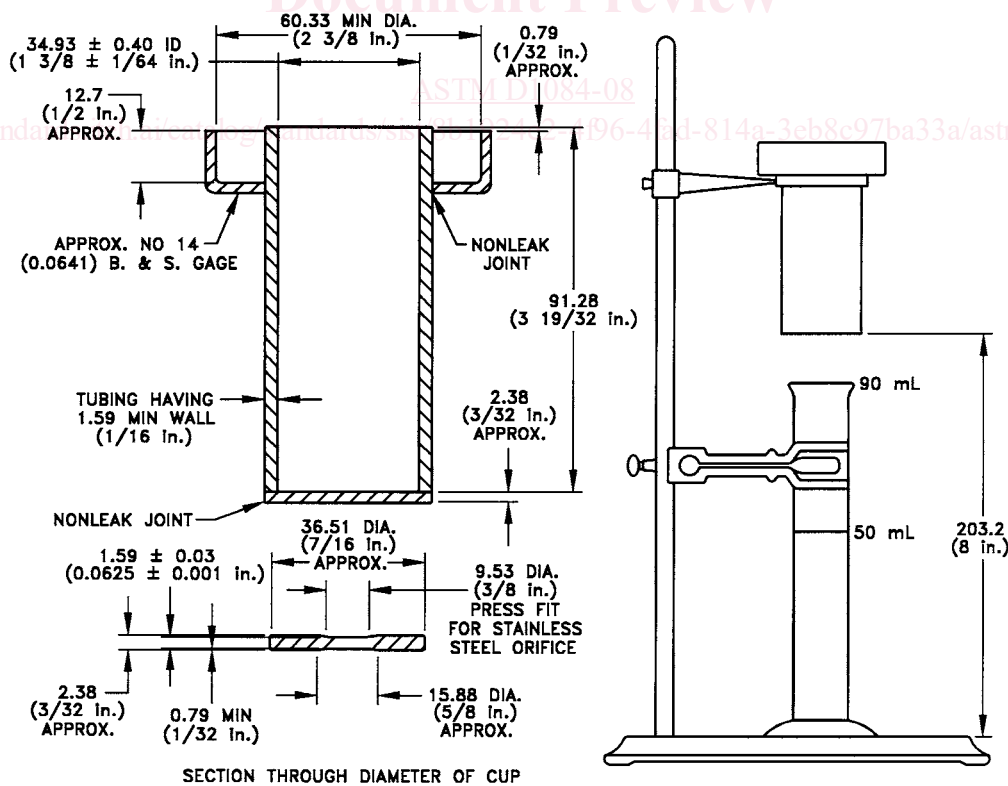

All dimensions are in mm
FIG. 1 Consistency Cups and Apparatus Assembly (Test Method A)

into the receiving cylinder. Determine the number of seconds from the time the finger is removed from the orifice until the top of the meniscus reaches to 50-mL mark on the cylinder by a stop watch and record as the viscosity of the material.

7. Report

7.1 Report the following:

- 7.1.1 Complete identification of the adhesive tested, including type, source, manufacturer's code numbers, form, date of test, date of manufacture, etc.,
- 7.1.2 Conditioning procedure used for samples prior to testing,
- 7.1.3 Number of tests made, and
- 7.1.4 Average consistency in seconds and the number of the viscosity cup used.

TEST METHOD B

8. Apparatus

~~8.1~~*Viscometer*—The apparatus consists of a Brookfield synchroelectric viscosimeter, or an equivalent instrument. A series of spindles with various sized disks is provided with each instrument covering a standard range of viscosities. Scored, warped, or otherwise damaged spindles are not to be used. The calibration sleeve will be used when the values are to be reported in actual centipoise. This spindle guard ensures uniform edge effects. By mutual agreement, the instrument may be used without the calibration sleeve, but the values obtained must be reported in apparent centipoises. Use a standard container and take care to center the spindle in the container. A complete description of the container must be include in the report.

~~8.2~~*Thermometer*—A precision thermometer with graduations not greater than 0.2°C (0.36°F) divisions.

9. Calibration

~~9.1~~When used for referee purposes, calibrate the instrument by measuring the viscosity of a standard oil, using the same spindle and speed of rotation employed to measure the sample. If the viscosity of the oil as read by the instrument differs by more than 2% and less than 20% from the certified viscosity of the oil, calculate the viscosity of the unknown by means of the appropriate correction factor. Investigate a difference of more than 20%, and determine a calibration curve using at least two standard oils with viscosities on either side of the sample for the instrument.

10. Procedure

~~10.1~~*Conditioning*—Bring the sample of the adhesive and the instrument to a temperature of $23 \pm 0.5^\circ\text{C}$ (73.4°F) (preferably in a constant-temperature room), and maintain the sample uniformly at this standard temperature throughout the test. Protect adhesives containing volatile solvents from evaporation during conditioning. If special conditioning methods are necessary, such as the use of a circulating water bath, report in 11.1.5.

~~10.2~~*Adjustment*—Select a spindle suitable to the viscosity range of the material and firmly fit it into the shaft extension which comes down through the center of the dial casing.

~~10.3~~*Determination*—Insert the spindle perpendicularly into the material to be tested until immersed to the depth indicated by the groove cut into the shaft. Press down the clutch lever and start the motor by snapping the toggle switch. Then release the lever and allow rotation to continue until the pointer has reached the position where it is stationary in relation to the rotating dial. Again press down the clutch lever and snap the switch off. If the pointer is not in view when the dial has come to rest, the motor should be started again and allowed to run until the pointer reaches the vision plate, keeping the clutch lever depressed. Take the reading at the pointer. A check reading can also be made by restarting the motor before releasing the clutch. If the pointer makes a complete turn of the dial, this indicates that the viscosity is too great for the capacity of the spindle used. A slower speed of rotation or a spindle with a greater range should be used. If the pointer moves less than 20% of the way around the dial, this indicates that the viscosity is too low for accurate measurement with the spindle or rate of rotation used. A faster speed of rotation or a spindle with a lower range should be used. Make a minimum of three readings. Some instruments have two concentric scales, and great care should be taken to read the pointer on the correct scale as specified by the manufacturer for the spindle used.

11. Report

11.1 Report the following:

- 11.1.1 Complete identification of the adhesive tested, including type, source, manufacturer's code numbers, form, date of test, date of manufacture, etc.;
- 11.1.2 Name and model number of the instrument used;
- 11.1.3 Number of the spindle used, and specify use of spindle guard;
- 11.1.4 Speed used;
- 11.1.5 Conditioning procedure employed, including details of the container and time elapsed between various operations used in the preparation of the adhesive mix;
- 11.1.6 Temperature of the sample at the conclusion of the test;
- 11.1.7 Number of tests made, and