

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[oSIST prEN ISO 20876:2016](https://standards.iteh.ai/catalog/standards/sist/c5ba4720-df9e-49cf-acbe-c77ee9c713f1/osist-pren-iso-20876-2016)

<https://standards.iteh.ai/catalog/standards/sist/c5ba4720-df9e-49cf-acbe-c77ee9c713f1/osist-pren-iso-20876-2016>

DRAFT INTERNATIONAL STANDARD

ISO/DIS 20876

ISO/TC 216

Secretariat: AENOR

Voting begins on:
2016-01-28Voting terminates on:
2016-04-28

Footwear — Test methods for insoles — Resistance to stitch tear

Chaussures — Méthodes d'essai applicables aux premières de montage — Résistance au déchirement des points de couture

ICS: 61.060

iTeh STANDARD PREVIEW (standards.iteh.ai)

oSIST prEN ISO 20876:2016

<https://standards.iteh.ai/catalog/standards/sist/c5ba4720-df9e-49cf-acbe-c77ee9c713f1/osist-pren-iso-20876-2016>

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

ISO/CEN PARALLEL PROCESSING

This draft has been developed within the European Committee for Standardization (CEN), and processed under the **CEN lead** mode of collaboration as defined in the Vienna Agreement.

This draft is hereby submitted to the ISO member bodies and to the CEN member bodies for a parallel five month enquiry.

Should this draft be accepted, a final draft, established on the basis of comments received, will be submitted to a parallel two-month approval vote in ISO and formal vote in CEN.

To expedite distribution, this document is circulated as received from the committee secretariat. ISO Central Secretariat work of editing and text composition will be undertaken at publication stage.



Reference number
ISO/DIS 20876:2015(E)

© ISO 2015

iTeh STANDARD PREVIEW (standards.iteh.ai)

[oSIST prEN ISO 20876:2016
https://standards.iteh.ai/catalog/standards/sist/c5ba4720-df9e-49cf-acbe-
c77ee9c713f1/osist-pren-iso-20876-2016](https://standards.iteh.ai/catalog/standards/sist/c5ba4720-df9e-49cf-acbe-c77ee9c713f1/osist-pren-iso-20876-2016)



COPYRIGHT PROTECTED DOCUMENT

© ISO 2015, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 20876 was prepared by Technical Committee ISO/TC 216, *Footwear*, Subcommittee SC , and by Technical Committee CEN/TC 309, *Footwear* in collaboration.

This second/third/... edition cancels and replaces the first/second/... edition (), [clause(s) / subclause(s) / table(s) / figure(s) / annex(es)] of which [has / have] been technically revised.

<https://standards.iteh.ai/catalog/standards/sist/c5ba4720-df9e-49cf-acbe-c77ee9c713f1/osist-pren-iso-20876-2016>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[oSIST prEN ISO 20876:2016](https://standards.iteh.ai/catalog/standards/sist/c5ba4720-df9e-49cf-acbe-c77ee9c713f1/osist-pren-iso-20876-2016)

<https://standards.iteh.ai/catalog/standards/sist/c5ba4720-df9e-49cf-acbe-c77ee9c713f1/osist-pren-iso-20876-2016>

Footwear — Test methods for insoles — Resistance to stitch tear

1 Scope

This international standard describes a method for evaluating the ability of an insole, irrespective of the material, to hold stitches, or to take clenched metal fastenings. The method has become accepted as a general quality criterion for insole materials even where attachment is by means of adhesives.

2 Normative references

The following normative documents contain provisions which, through reference in this text, constitute provisions of this International Standard. For dated references, subsequent amendments to, or revisions of, any of these publications do not apply. However, parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the normative documents indicated below. For undated references, the latest edition of the normative document referred to applies. Members of ISO and IEC maintain registers of currently valid International Standards.

ISO 7500-1 Metallic materials. Tensile testing. Part 2: Verification of the force measuring system of the tensile testing machines.

ISO 18454 Footwear. Standard atmospheres for conditioning and testing of footwear and components for footwear.

ISO 17709 Footwear. Sampling location of components for footwear.

3 Terms and definitions

For the purposes of this International Standard, the following definition applies:

3.1

resistance to stitch tear

force required to pull a loop of wire of specified dimensions through a test specimen of insole material

4 Apparatus and material

The following apparatus and material shall be used:

4.1 Drill, fitted with a twist drill bit, with diameter of 1,60 mm ± 0,01 mm.

4.2 Drilling jig, to ensure accurate spacing of 8,0 mm ± 0,2 mm between the centres of each pair of holes (see figure 1) in the test piece.

4.3 Steel wire, 150 mm in length, with a diameter of 0,90 mm ± 0,01 mm (20 SWG). This is formed over a 7 mm diameter mandrel into a loop with parallel arms of equal length by applying a force of 1,5 kN to 2 kN to each end of the wire so that the shape of the loop conforms to that of the mandrel.

ISO/WD 20876

NOTE Loops which have become mis-shapen by use can be reused, provided that the irregularities are removed, over the forming mandrel.

4.4 Tensile testing machine, the tensile testing machine shall comply with the requirement of ISO 7500-1, to an accuracy corresponding to class 2, with a constant rate of transverse of 100 mm/min \pm 20 mm/min. Autographic recording of force or a maximum force pointer is recommended.

4.5 Attachment to the tensile testing machine, consisting of the following two parts:

4.5.1 Upper jaw, consisting of a rigid supporting plate for the test piece, with a rectangular aperture 12,0 mm \pm 0,5 mm by 6,0 mm \pm 0,5 mm and a means of attachment to the force-measuring system so that the line of action of the force passes through the centre of the aperture and is perpendicular to the plate.

4.5.2 Lower jaw, containing a means of attaching the steel wire loop to the drive system so that the two arms of the loop are held parallel by two guide holes 8 mm apart and equidistant from the line of action of the force applied during the test.

The attachment is designed to ensure that in the test the loop is drawn through the centre of the aperture in the rigid supporting plate for the test piece, with the plane of the loop parallel to the longer side of the aperture.

4.6 Dial micrometer gauge, standing on a firm base and loaded with a dead weight such that the presser foot applies a pressure of 49 kPa \pm 5 kPa¹⁾. The gauge has a presser foot which is flat, circular and 10,0 mm in diameter.

The gauge has scale divisions of 0,01 mm.

iTech STANDARD PREVIEW
(standards.iteh.ai)

5 Sampling and conditioning

From the footwear insole, cut insole or from the component as supplied, cut two rectangular test pieces approximately 75 mm x 25 mm, one test piece perpendicular to the other. Mark both test pieces to show their orientation.

If the test pieces are taken from the shoe or from the cut component, sampling shall be done in accordance with ISO17709.

Condition the test pieces, in accordance with ISO 18454, for a minimum of 24 h.

6 Test methods

6.1 Measure the thickness (in millimetres) of each test piece at three points equally spaced along the centreline parallel to the 75 mm side, using the dial micrometer gauge (see 4.6).

6.2 Using the drill fitted with a 1,6 mm twist drill bit (see 4.1), drill each test piece from the face side with three pairs of holes along the centreline and parallel to the 75 mm side. Use the drilling jig (see 4.2) to ensure that the holes of each pair are accurately spaced 8,0 mm \pm 0,2 mm apart. Drill one pair of holes in the centre and the other two pairs midway between the centre pair and the ends of the test specimen as shown in figure 1.

6.3 Thread the wire loop (see 4.3) through a pair of holes in one test piece from the face side.

Keeping the arms of the loop parallel, pass them through the aperture in the test piece supporting plate (see 4.5.1), and through the guide holes (8 mm apart) in the lower jaw attachment (see 4.5.2). Clamp the ends firmly in position.

Operate the tensile testing machine (see 4.5) until the insole material fails.

1) 1 Pa = 1 N/m²

Note the maximum force (in newtons) exerted. If the mass of the stitch-tear attachment contributes to the recorded force, correct this value to obtain the net force exerted on the test piece.

6.4 Repeat the method on the remaining two pairs of holes in the test piece. Carry out this procedure similarly on the second test piece.

7 Expression of results

7.1 For each test piece calculate the mean of the three maximum forces noted. Report these two values as the stitch-tear resistances for the principal directions, in newtons to the nearest 0,1 N.

The results will be the average of the three values.

7.2 For each test piece calculate the mean value of three thickness measurements.

8 Test report

The test report shall include the following information:

- a) stitch-tear resistance, for each principal direction, expressed in accordance with 7.1;
- b) thickness of each test piece, expressed in accordance with 7.2;
- c) full description of shoe samples tested including commercial styles codes, colours, nature, etc.;
- d) description of sampling procedure, where relevant;
- e) reference to this standard test method;
- f) details of any deviation from the standard test method;
- g) date of testing;
- h) any deviation from this test method.
- i) standard atmospheric conditions observed during the test

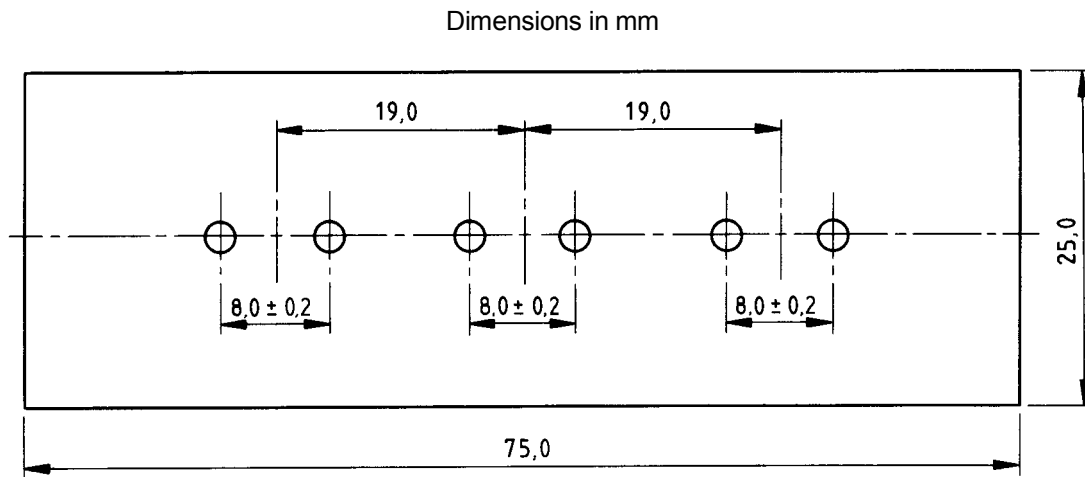


Figure 1 — Test piece

iTeh STANDARD PREVIEW
(standards.iteh.ai)

<https://standards.iteh.ai/catalog/standards/sist/c5ba4720-df9e-49cf-acbe-c77ee9c713f1/osist-pren-iso-20876-2016>