



**SLOVENSKI STANDARD**  
**SIST EN 16974:2017**

**01-marec-2017**

---

**Naprave za kontinuirni transport - Trakovi tračnih transporterjev - Kotalni upor  
trakov tračnih transporterjev v odvisnosti od širine pasu - Zahteve, preskušanje**

Conveyor belts - Indentation rolling resistance of conveyor belts related to belt width -  
Requirements, testing

Fördergurte - Gurtbreitenbezogener Eindrückrollwiderstand von Fördergurten -  
Anforderungen, Prüfung

Courroies transporteuses - Résistance au roulement par suite d'enfoncement des  
courroies transporteuses en fonction de la largeur de courroie - Exigences, essais

<https://standards.iteh.ai/catalog/standards/sist/785845cb-b53a-44aa-a08a->

[e11744b58006/sist-en-16974-2017](https://standards.iteh.ai/catalog/standards/sist/785845cb-b53a-44aa-a08a-e11744b58006/sist-en-16974-2017)

**Ta slovenski standard je istoveten z: EN 16974:2016**

---

**ICS:**

53.040.20      Deli za transporterje      Components for conveyors

**SIST EN 16974:2017**

**en,fr,de**

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

SIST EN 16974:2017

<https://standards.iteh.ai/catalog/standards/sist/785845cb-b53a-44aa-a08a-e11744b58006/sist-en-16974-2017>

EUROPEAN STANDARD

EN 16974

NORME EUROPÉENNE

EUROPÄISCHE NORM

September 2016

ICS 53.040.20

English Version

## Conveyor belts - Indentation rolling resistance related to belt width - Requirements, testing

Courroies transporteuses - Résistance au roulement  
par suite d'enfoncement relative à la largeur de  
courroie - Exigences, essais

Fördergurte - Gurtbreitenbezogener  
Eindrückrollwiderstand - Anforderungen, Prüfung

This European Standard was approved by CEN on 13 July 2016.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

**CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels**

<b>Contents</b>		Page
<b>European foreword</b> .....		<b>3</b>
<b>1</b>	<b>Scope</b> .....	<b>4</b>
<b>2</b>	<b>Normative references</b> .....	<b>4</b>
<b>3</b>	<b>General information</b> .....	<b>4</b>
<b>4</b>	<b>Symbols and units</b> .....	<b>5</b>
<b>5</b>	<b>Test rig</b> .....	<b>6</b>
<b>6</b>	<b>Preparation of test samples</b> .....	<b>7</b>
<b>7</b>	<b>Procedure</b> .....	<b>7</b>
<b>8</b>	<b>Calculation and expression of results</b> .....	<b>8</b>
<b>9</b>	<b>Test report</b> .....	<b>8</b>
<b>Annex A (informative) Conversion of the measured width related indentation rolling resistance to a 3-part idler station</b> .....		<b>10</b>
<b>Bibliography</b> .....		<b>12</b>

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)

SIST EN 16974:2017

<https://standards.iteh.ai/catalog/standards/sist/785845cb-b53a-44aa-a08a-e11744b58006/sist-en-16974-2017>

## European foreword

This document (EN 16974:2016) has been prepared by Technical Committee CEN/TC 188 “Conveyor belts”, the secretariat of which is held by SNV.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by March 2017, and conflicting national standards shall be withdrawn at the latest by March 2017.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

According to the CEN-CENELEC Internal Regulations, the national standards organisations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

## iTeh STANDARD PREVIEW (standards.iteh.ai)

[SIST EN 16974:2017](https://standards.iteh.ai/catalog/standards/sist/785845cb-b53a-44aa-a08a-e11744b58006/sist-en-16974-2017)

<https://standards.iteh.ai/catalog/standards/sist/785845cb-b53a-44aa-a08a-e11744b58006/sist-en-16974-2017>

**EN 16974:2016 (E)****1 Scope**

This European Standard defines a method for the determination of the width related indentation rolling resistance of conveyor belts. The goal is that the method easily and quickly delivers values which are reproducible and relevant for the practical use. The test results enable a comparing evaluation and the design of belt conveyors with steelcord and fabric conveyor belts.

This European Standard is not suitable or valid for light conveyor belts described in EN ISO 21183-1.

**2 Normative references**

Not applicable.

**3 General information**

The indentation rolling resistance is caused by the energy loss connected to the deformation of the conveyor belt due to its contact with the idler. Apart from the technological properties of the conveyor belt the magnitude of the indentation rolling resistance depends on the following factors:

- design of the conveyor belt, especially the pulley side cover plate thickness;
- vertical load;
- idler diameter;
- ambient temperature;
- belt speed.

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[SIST EN 16974:2017](https://standards.iteh.ai/catalog/standards/sist/785845cb-b53a-446a-a08e-e11744b58006/sist-en-16974-2017)

The width related indentation rolling resistance is measured in a test rig with an idler which exerts an evenly distributed vertical force on the belt. An indentation rolling resistance to be used for the design of belt conveyors for an idler station with more than one idler can only be calculated considering the vertical forces and their distribution between belt and idler (refer to Annex A).

## 4 Symbols and units

Table 1 shows the symbols and units used in this standard.

**Table 1 — Symbols and units**

Symbol	Meaning	Unit
$B$	Belt width	mm
$D_{R,M}$	Diameter of measuring idler	mm
$D_{R,G}$	Diameter of the opposing idler	mm
$D_{Tr}$	Pulley diameter	mm
$F_E$	Indentation rolling resistance acting on one idler	N
$F_{E,ges}$	Total indentation rolling resistance acting on an idler station with three idlers	N
$F'_E$	Indentation rolling resistance related to belt width	N/mm
$F_{M,h}$	Horizontal force acting on the measuring idler turning clockwise ( $F_{M,h,r}$ ) or anti-clockwise ( $F_{M,h,l}$ )	N
$F_{M,v}$	The vertical force on the measuring idler corresponding to the load	N
$F'_{M,v}$	Vertical force related to the belt width	N/mm
$F_n$	Normal force acting on an idler	N
$F_R$	Idler rolling resistance	N
$L$	Distance axis-to-axis	mm
$T_U$	Ambient temperature	°C
$b_K$	Width of the rubber edge of the belt	mm
$c_a$	Factor in the approximation equation for the width related indentation rolling resistance	-
$c_b$	Exponent in the approximation equation for the width related indentation rolling resistance	-
$b_R$	Length of the contact line between belt and idler shell	mm
$d$	Steelcord diameter	mm
$q$	Length related load acting on the idler	N/mm
$n_s$	Number of steelcords	-
$s_1$	Cover plate thickness, carrying side	mm
$s_2$	Cover plate thickness, pulley side	mm
$t$	Cord pitch	mm
$v$	Belt speed	m/s
$z$	Coordinate of length	mm

Table 2 described the used indices in this standard.

**Table 2 — Indices**

Index	Meaning
m	Middle idler
s	Side idler


## 5 Test rig

The testing apparatus is a test rig with a rotating belt sample, constructed with a drive pulley and a tensioning pulley. Both pulleys have a minimum diameter of 800 mm (Figure 1). The distance axis-to-axis has a minimum value of 3 500 mm. For high strength conveyor belts and large splice lengths differing pulley diameters and distances axis-to-axis shall be agreed upon with the operator of the test rig. The belt speed is adjustable and is constantly monitored with appropriate sensors. The complete test rig is placed in an isolated climate chamber, so that the ambient temperature can be adjusted with suitable heating and cooling devices. In the top run there is a special measuring arrangement with which an idler can be pressed down on to the belt with a defined force. As counter support an idler is installed. This idler has a minimum diameter  $D_{R,G}$  of 400 mm and the diameter shall be larger than the diameter of the measuring idler by a minimum factor of 1,5.

$$D_{R,G} \geq 1,5 \times D_{R,M} \quad (1)$$

The diameters  $D_{R,G}$  and  $D_{R,M}$  shall be chosen corresponding to the parameters of the belt conveyor and to be agreed upon with the operator of the test rig.

The test rig shall be constructed in a way that it is possible to install the test belt as an endless belt. Figure 1 shows a schematic picture of the test rig.

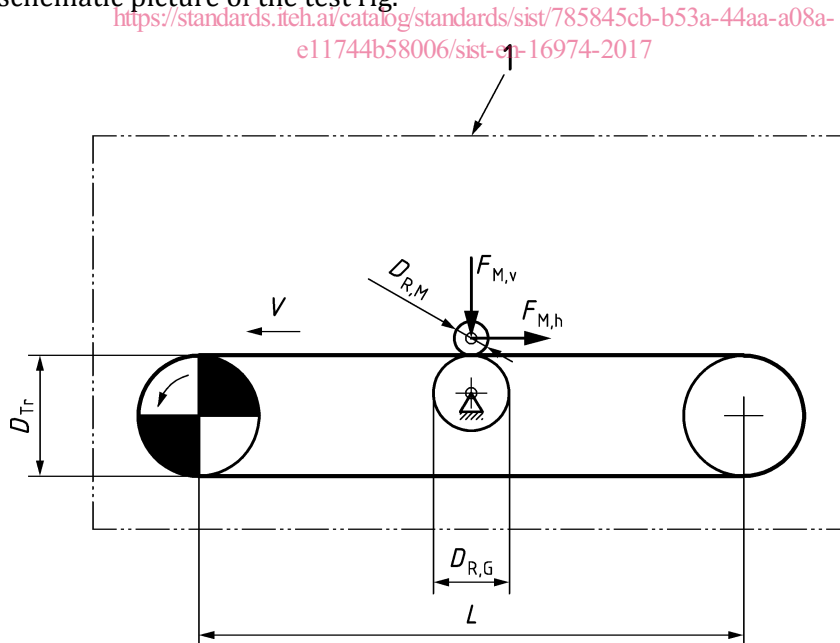

### Key

1 temperature isolating chamber

**Figure 1 — Schematic picture of the test rig**



For the measurement of the indentation rolling resistance idlers with varying diameters and shell lengths are used. These are installed in an adjustable frame. The shell length of the idler shall be at least 10 % longer than the width of the test belt. The frame shall be in a statically simply fixed position. It shall be avoided that the position is over-determined and that resulting forces are created. These could distort the measurement results. All suspension points shall be equipped with suitable force sensors in order to determine all suspending forces unambiguously. The perpendicular alignment of the measuring idler to the belt can be checked with the help of a force sensor which records the forces that act in axial direction upon the idler, if the alignment is not correct.

In order to determine the width related indentation rolling resistance the forces are measured which act upon the left and the right side of the idler – and therefore upon the frame – with suitable force sensors. To calculate the indentation rolling resistance from these values, the part of the horizontal force cause by the idler rolling resistance shall be known and shall be subtracted from the measured horizontal force  $F_{M,h}$ . The idler rolling resistance can either be measured simultaneously with suitable sensors, or it can be measured separately. In this case the test parameters of the measurement of indentation rolling resistance need to be taken into consideration.

## 6 Preparation of test samples

The endless length of the test belts depends on the distance axis-to-axis of the test rig  $L$  and the pulley diameter  $D_{Tr}$  and deviations from the values stated in clause 5 shall be agreed with the operator of the test rig. The width of the test belt shall be a minimum of 350 mm. For steel cord belts the width of the rubber belt edge shall be chosen as follows:

$$b_k = \frac{1}{2} \times (t - d) \quad (2)$$

In fabric belts rubber edges shall be avoided, so that the belt width is equal to the width of the tension carrier.

The test belts shall be joined with a splice of minimized length, which can differ from the standard splice layout. The horizontal force measured in the splice area can differ from the force measured in the belt. Therefore it is not taken into consideration for the calculation of the indentation rolling resistance.

## 7 Procedure

The cover plate to be measured shall be in contact with the measuring idler.

Prior to each measurement the test rig shall be operated in constant test conditions long enough, so that the idler running resistance and the measured horizontal forces reach a steady-state. The complete test rig shall be brought to the desired temperature over a sufficiently long time, so that in the complete cross section of the test belt the temperature equals the surrounding temperature in the climate chamber of the test rig.

In order to cancel the influence of zero drift errors when measuring the horizontal forces acting on the measuring idler, the belt running direction shall be alternated several times during the measurement. The value of the difference between the measured horizontal force of the belt running to the left  $F_{M,h,l}$  and the belt running to the right  $F_{M,h,r}$  is taken into account for the calculation of the indentation rolling resistance.

The measurements shall be performed with a test idler of which the diameter  $D_{R,M}$  equals the diameter of the idlers in the conveyor. The vertical forces used in the measurements shall be chosen according to the normal forces between belt and idler station in the real life conveyor.

The different temperatures  $T_U$  set in the climate chamber of the test rig shall be chosen corresponding to the temperatures to be expected at the real life conveyor.