



SLOVENSKI STANDARD

SIST EN 3475-605:2018

01-marec-2018

Nadomešča:

SIST EN 3475-605:2010

Aeronavtika - Električni kabli za uporabo v zračnih plovilih - Preskusne metode - 605. del: Mokri preskus kratkega stika

Aerospace series - Cables, electrical, aircraft use - Test methods - Part 605: Wet short circuit test

Luft- und Raumfahrt - Elektrische Leitungen für Luftfahrtverwendung - Prüfverfahren - Teil 605: Verhalten nach Kurzschluss, feucht

Série aérospatiale - Câbles électriques à usage aéronautique - Méthodes d'essais - Partie 605 : Essai de court-circuit humide

Ta slovenski standard je istoveten z: EN 3475-605:2018

ICS:

29.060.20	Kabli	Cables
49.060	Letalska in vesoljska električna oprema in sistemi	Aerospace electric equipment and systems

SIST EN 3475-605:2018

en,fr,de

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 3475-605:2018

<https://standards.iteh.ai/catalog/standards/sist/186c4ac6-b13f-442f-8e3a-8643e59618bd/sist-en-3475-605-2018>

EUROPEAN STANDARD

EN 3475-605

NORME EUROPÉENNE

EUROPÄISCHE NORM

January 2018

ICS 49.060

Supersedes EN 3475-605:2010

English Version

Aerospace series - Cables, electrical, aircraft use - Test methods - Part 605: Wet short circuit test

Série aérospatiale - Câbles électriques à usage
aéronautique - Méthodes d'essais - Partie 605 : Essai
de court-circuit humide

Luft- und Raumfahrt - Elektrische Leitungen für
Luftfahrtverwendung - Prüfverfahren - Teil 605:
Verhalten nach Kurzschluss, feucht

This European Standard was approved by CEN on 28 August 2017.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents	Page
European foreword.....	3
1 Scope.....	4
2 Normative references.....	4
3 Specimen requirements.....	4
4 Preparation of specimen	4
5 Apparatus.....	6
6 Method	8
7 Requirements	9

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 3475-605:2018](https://standards.iteh.ai/catalog/standards/sist/186c4ac6-b13f-442f-8e3a-8643e59618bd/sist-en-3475-605-2018)

<https://standards.iteh.ai/catalog/standards/sist/186c4ac6-b13f-442f-8e3a-8643e59618bd/sist-en-3475-605-2018>

European foreword

This document (EN 3475-605:2018) has been prepared by the Aerospace and Defence Industries Association of Europe - Standardization (ASD-STAN).

After enquiries and votes carried out in accordance with the rules of this Association, this Standard has received the approval of the National Associations and the Official Services of the member countries of ASD, prior to its presentation to CEN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by July 2018 and conflicting national standards shall be withdrawn at the latest by July 2018.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 3475-605:2010.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 3475-605:2018](https://standards.iteh.ai/catalog/standards/sist/186c4ac6-b13f-442f-8e3a-8643e59618bd/sist-en-3475-605-2018)

<https://standards.iteh.ai/catalog/standards/sist/186c4ac6-b13f-442f-8e3a-8643e59618bd/sist-en-3475-605-2018>

EN 3475-605:2018 (E)**1 Scope**

This European Standard specifies a method for appraising the behaviour of cable insulation subjected to an electric arc initiated and maintained by a contaminating fluid.

This European Standard shall be used together with EN 3475-100.

The primary aim of this test is:

- to produce, in a controlled fashion, continuous failure effects which are representative of those which may occur in service when a typical cable bundle is damaged and subjected to aqueous fluid contamination such that electrical arcing occurs between cables;
- to examine the aptitude of the insulation to track to propagate electric arc to the electrical origin.

Originally defined for 115 Vac network, this test also proposes conditions for 230 Vac network. Unless otherwise specified in product standard, only 115 Vac conditions shall be satisfied.

Six (6) levels of prospective fault current have been specified for concerned cable sizes (see Clause 7). It is generally agreed that larger sizes need not be assessed since the short-circuit phenomenon becomes dominant at low line impedances.

Unless otherwise specified in the technical/product standard sizes 002, 006 and 020 cable shall be assessed.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 2350, *Aerospace series — Circuit breakers — Technical specification*
[https://standards.iteh.ai/catalog/standards/sist/186c4ac6-b13f-442f-8e3a-](https://standards.iteh.ai/catalog/standards/sist/186c4ac6-b13f-442f-8e3a-8643e59618bd/sist-en-3475-605-2018)

EN 3197, *Aerospace series — Design and installation of aircraft electrical and optical interconnection systems*

EN 3475-100, *Aerospace series — Cables, electrical, aircraft use — Test methods — Part 100: General*

A-A-52083, *Tape, lacing and tying, glass* ¹⁾

3 Specimen requirements

Cables to be tested shall be of traceable origin and shall have passed the high voltage dielectric test defined in the product standard.


4 Preparation of specimen

4.1 Cut seven (7) separate lengths of approximately 0,5 m consecutively from one (1) length of cable, and strip one of the ends of insulation to permit electrical connection. Clean each length of cable with a clean cloth moistened with propan-2-ol (isopropyl alcohol) fluid.

¹⁾ Published by: Department of Defense Industrial Supply Center, ATTN: DISC-BBEE, 700 Robbins Avenue, Philadelphia, PA 19111-5096 - USA.

4.2 Lay up the seven (7) cables as follows:

- a) Form the cables in a six (6) around one (1) configuration as shown in Figure 1.
- b) Ensure that all cables are straight and geometrically parallel, and restrained by lacing tapes such that they are in continuous contact at least within the test zone.
- c) Position the lacing tapes at 50 mm spacing toward the end of the specimen as shown in Figure 2. The first lacing tapes shall be at no more than 5 mm behind the dripping point. The tie material shall be PTFE glass lacing tape conforming to A-A-52083 type IV, finish D, size 3.
- d) Number the cables as shown in Figure 1 such that the cables in direct contact with the drops are numbers A1 and B1 and the centre is N. Cables C1, A2, B2 and C2 are grouped around N.

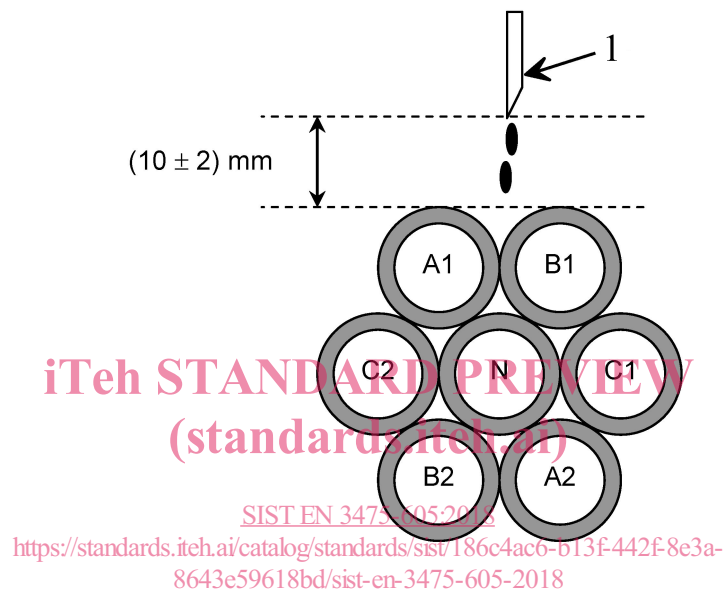

Key

1 Drop needle


A1-A2 : Phase A

B1-B2 : Phase B

C1-C2 : Phase C

N : Neutral cable connected to earth

Figure 1 — Specimen configuration

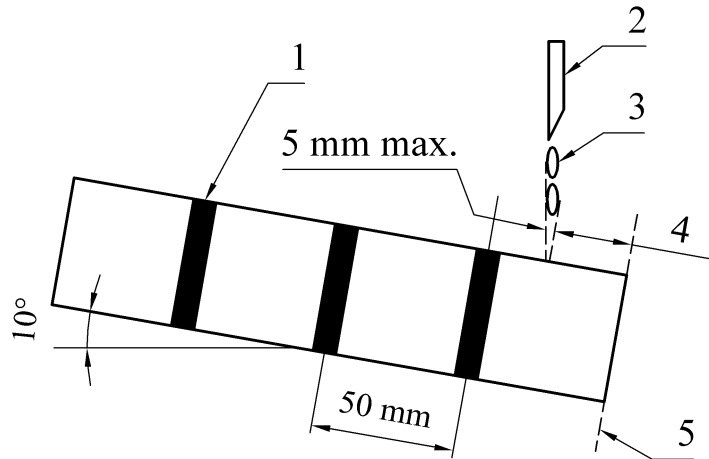

Key

- 1 Lancing tape
- 2 Drop needle
- 3 Drops
- 4 10 mm to 20 mm
- 5 Ends of the 7 cables in the same plane

Figure 2 — Test configuration

iTeh STANDARD PREVIEW
(standards.iteh.ai)

5 Apparatus

5.1 Electrical equipment

Connect the seven (7) cables of the test sample within a circuit as shown in Figure 3. This circuit shall have the following requirements:

- a) The provision of adjustable levels of prospective fault currents for the six (6) A, B and C cables.
- b) A three phase 115/200 V 400 Hz (115 Vac network) or 230/400 V 400 Hz (230 Vac network) star (Y) connected supply shall be derived from a dedicated rotary machine capable of sustaining the maximum prospective fault current given in Table 1 (115 Vac network) or Table 2 (230 Vac network) for at least sufficient time for circuit protection to operate. In any case the generator shall have a sufficient rating to provide these prospective fault currents.
- c) 115 Vac or 230 Vac circuit breakers (D2) shall be single pole units rated at the values specified in Table 3. They shall have trip characteristics in accordance with EN 2350 or as required in the product specification.


NOTE 1 Reference of circuit breakers used shall be recorded.

NOTE 2 In particular case, others ratings of thermal breaker protection could be employed in accordance with aircraft manufacturer rules.

- d) The electrical power source shall be appropriately protected and it shall be established that no combination of test circuit events would activate this protection.
- e) The ballast R_b resistors shall be non-inductive and of appropriate power rating. Care shall be taken to position all laboratory wiring such that inductive effects are reduced to a practical minimum. Supply cables shall be as short as possible.

The ballast resistor R_b is in order to prevent over voltage ($115 \Omega - 115 \text{ W}$ per phase for 115 Vac network or $230 \Omega - 230 \text{ W}$ per phase for 230 Vac network) during the arc extinction phases (opening of an inductive circuit).

- f) A rheostat, R_f , limiting maximum short-circuit current per phase by simulating a line length.
- g) Appropriate instrumentation, recording and switching control shall be installed in accordance with good laboratory practice.

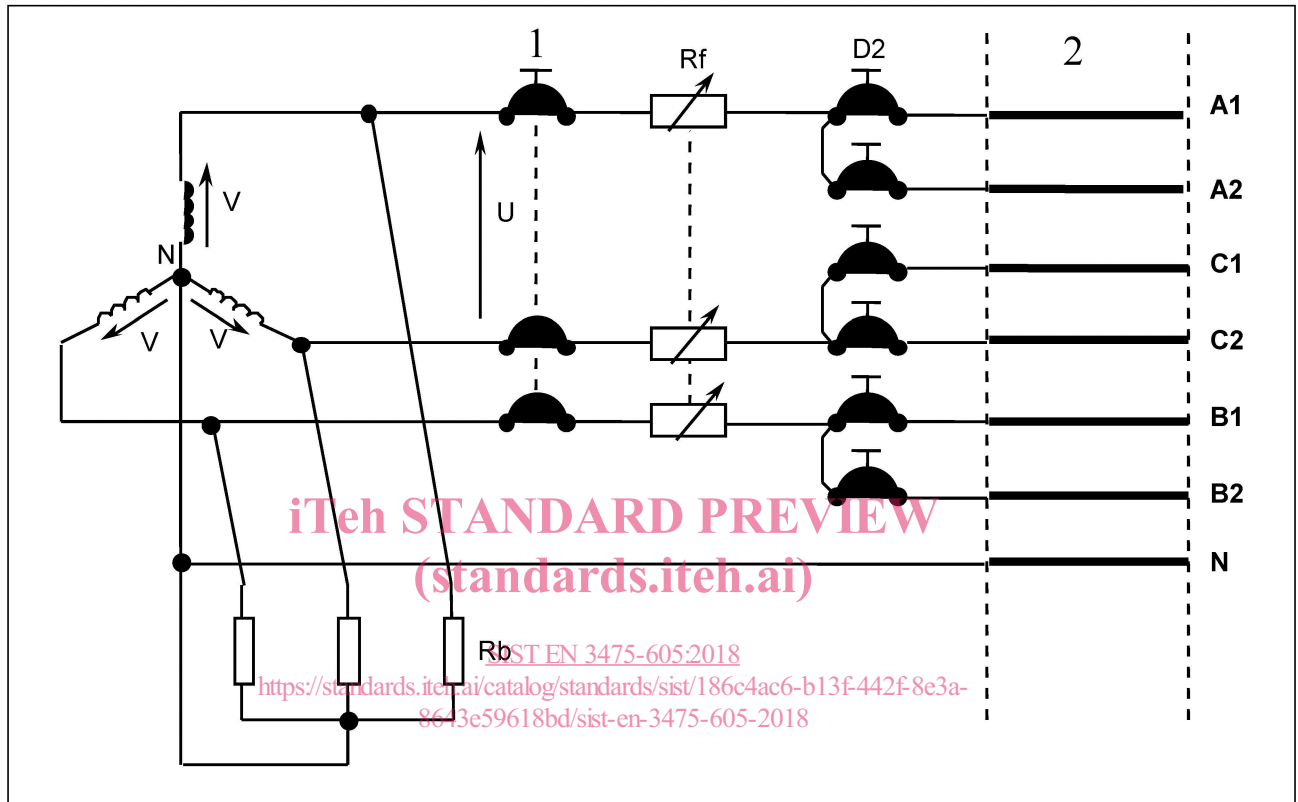

Key

- 1 Supply protection
- 2 Test bundle

Figure 3 — Test schematic circuit

5.2 Test equipment

Construct an apparatus as shown diagrammatically in Figure 2, which includes the following minimum provisions:

- a) Electrical terminations to provide a ready means of connecting test specimens into the circuit as shown in Figure 3.
- b) A transparent enclosure to protect personnel from ejected molten metal and short wavelength ultra violet light.
- c) An electrolyte delivery system which provides a constant rate of $(100 \pm 10) \text{ mg/min}$ and dispenses drops from an 18 gauge needle, cut of square at the outlet.