



# SLOVENSKI STANDARD

## SIST EN 12814-4:2018

01-junij-2018

Nadomešča:  
SIST EN 12814-4:2002

---

### Preskus zvarjenih spojev plastomernih polizdelkov - 4. del: Preskus luščenja

Testing of welded joints of thermoplastics semi-finished products - Part 4: Peel test

Prüfen von Schweißverbindungen aus thermoplastischen Kunststoffen - Teil 4:  
Schälversuch

Essai des assemblages soudés sur produits semi-finis en thermoplastiques - Partie 4 :  
Essai de pelage

iTeh STANDARD PREVIEW

(standards.iteh.ai)

SIST EN 12814-4:2018

<https://standards.iteh.ai/catalog/standards/sist/31a9edee-b088-48c4-8198-42d3/sist-en-12814-4>

Ta slovenski standard je istoveten z: **EN 12814-4:2018**

---

#### **ICS:**

25.160.40      Varjeni spoji in vari      Welded joints and welds

**SIST EN 12814-4:2018**

**en,fr,de**

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

SIST EN 12814-4:2018

<https://standards.iteh.ai/catalog/standards/sist/31a9edee-b088-48c4-8198-4855201c42d3/sist-en-12814-4-2018>

EUROPEAN STANDARD  
NORME EUROPÉENNE  
EUROPÄISCHE NORM

**EN 12814-4**

April 2018

ICS 25.160.40

Supersedes EN 12814-4:2001

English Version

## Testing of welded joints of thermoplastics semi-finished products - Part 4: Peel test

Essai des assemblages soudés sur produits semi-finis  
en thermoplastiques - Partie 4 : Essai de pelage

Prüfen von Schweißverbindungen aus  
thermoplastischen Kunststoffen - Teil 4: Schälversuch

This European Standard was approved by CEN on 10 December 2017.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.

<https://standards.iteh.ai/catalog/standards/sist/31a9edee-b088-48c4-8198-4855201c42d3/sist-en-12814-4-2018>



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

**CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels**

| <b>Contents</b>                         | <b>Page</b> |
|---|-------------|
| European foreword .....                 | 3           |
| <b>1 Scope</b> .....                    | <b>4</b>    |
| <b>2 Normative references</b> .....     | <b>4</b>    |
| <b>3 Terms and definitions</b> .....    | <b>4</b>    |
| <b>4 Symbols and designations</b> ..... | <b>4</b>    |
| <b>5 T-peel test</b> .....              | <b>5</b>    |
| <b>6 Decohesion test</b> .....          | <b>8</b>    |
| <b>7 Crush test</b> .....               | <b>12</b>   |
| <b>8 Test report</b> .....              | <b>14</b>   |
| <b>Bibliography</b> .....               | <b>16</b>   |

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[SIST EN 12814-4:2018](https://standards.iteh.ai/catalog/standards/sist/31a9edee-b088-48c4-8198-4855201c42d3/sist-en-12814-4-2018)

<https://standards.iteh.ai/catalog/standards/sist/31a9edee-b088-48c4-8198-4855201c42d3/sist-en-12814-4-2018>

## European foreword

This document (EN 12814-4:2018) has been prepared by Technical Committee CEN/TC 249 “Plastics”, the secretariat of which is held by NBN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by October 2018, and conflicting national standards shall be withdrawn at the latest by October 2018.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 12814-4:2001.

In comparison with the previous edition, the following technical modifications have been made:

- the procedures in the Clauses “T-peel test”, “Decohesion test”, “Crush test” have been detailed with specifications and consequently with the reference figures.

EN 12814, *Testing of welded joints of thermoplastics semi-finished products*, is composed with the following parts:

- iTeh STANDARD PREVIEW**  
(standards.iteh.ai)
- *Part 1: Bend test;*
  - *Part 2: Tensile test;*
  - *Part 3: Tensile creep test;*
  - *Part 4: Peel test;*
  - *Part 5: Macroscopic examination;*
  - *Part 6: Low temperature tensile test;*
  - *Part 7: Tensile test with waisted test specimens;*
  - *Part 8: Requirements.*
- [SIST EN 12814-4:2018  
https://standards.iteh.ai/catalog/standards/sist/31a9edee-b088-48c4-8198-4855201c42d3/sist-en-12814-4-2018](https://standards.iteh.ai/catalog/standards/sist/31a9edee-b088-48c4-8198-4855201c42d3/sist-en-12814-4-2018)

According to the CEN-CENELEC Internal Regulations, the national standards organisations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

**EN 12814-4:2018 (E)****1 Scope**

This document specifies the dimensions, the method of sampling and the preparation of the test specimens, and also the conditions for performing the peel test perpendicular to the weld in order to determine the peel resistance and the failure behaviour.

A peel test can be used in conjunction with other tests (e.g. tensile creep, macroscopic examination...) to assess the performance of welded assemblies, made from thermoplastics materials.

Peel tests are applicable to overlap welded assemblies made from thermoplastics materials.

The T-peel test as defined in Clause 5 will be used only for assessing welded sheet assemblies. This test is not applicable to welded test pieces containing sheets of different nominal thickness.

The decohesion test as defined in Clause 6 will be used only for assessing electrofusion joints with nominal thickness of pipe/fitting greater than 10 mm.

For socket fusion and for electrofusion socket joints with nominal outside diameter less than or equal to 90 mm, a crush test will be used, as defined in Clause 7.

The crush test can also be used for electrofusion joints with outside diameters greater than 90 mm.

The crush test for electrofusion saddle joints will be performed in accordance with ISO 13955 [1].

NOTE A decohesion test is also defined in ISO 13954 [2].

The tests defined in this standard are not intended to be used for assessment and/or qualification of thermoplastic fittings that already have their own requirements, e.g. polyethylene fittings according to EN 1555-3 [3] and EN 12201-3 [4].

IT-IT STANDARD PREVIEW  
(standards.iteh.ai)

**2 Normative references**

SIST EN 12814-4:2018

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 5893, *Rubber and plastics test equipment — Tensile, flexural and compression types (constant rate of traverse) — Specification*

**3 Terms and definitions**

For the purposes of this document, the following term and definition apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

**3.1****peel resistance****P<sub>1</sub>**

arithmetic mean of the force values divided by the width of the test specimen (only relevant for T-peel test)

**4 Symbols and designations**

For the purposes of this document, the symbols and designations given in Table 1 apply.

**Table 1 — Test specimen designations**

| Symbols and abbreviations   | Designations                                     | Units |
|---|--|-------|
| $a_n$   | Nominal thickness of test piece                  | mm    |
| $b$   | Width of the test specimen                       | mm    |
| $c$   | Maximum width of the air channel (if applicable) | mm    |
| $C_c$   | Percentage of brittle failure                    | %     |
| $d_2$   | Maximum brittle-fracture length measure          | mm    |
| $d_n$   | Nominal outside diameter of pipe                 | mm    |
| $F_w$   | Maximum force measured during the test           | N     |
| $L_c$   | Clamped length of test specimen ligament         | mm    |
| $L_d$   | Length of fracture in the fusion plane           | mm    |
| $L_i$   | Free length of test specimen                     | mm    |
| $L_w^a$   | Maximum width of the weld of the test specimen   | mm    |
| $P_l$   | Peel resistance                                  | N/mm  |
| $y$   | Fusion zone length of electrofusion socket       | mm    |
| <sup>a</sup> For welds containing an air channel, $L_w$ shall be taken as the width of the whole weld minus the width of the channel ( $c$ ). |  |       |

## 5 T-peel test

### 5.1 Principle of the test

The test consists of peeling a test specimen at a constant rate of displacement until it fractures, peels or yields.

### 5.2 Test specimens

#### 5.2.1 Dimensions of test specimens

The test specimen is shown in Figure 1 and the dimensions are given in Table 2.

## EN 12814-4:2018 (E)

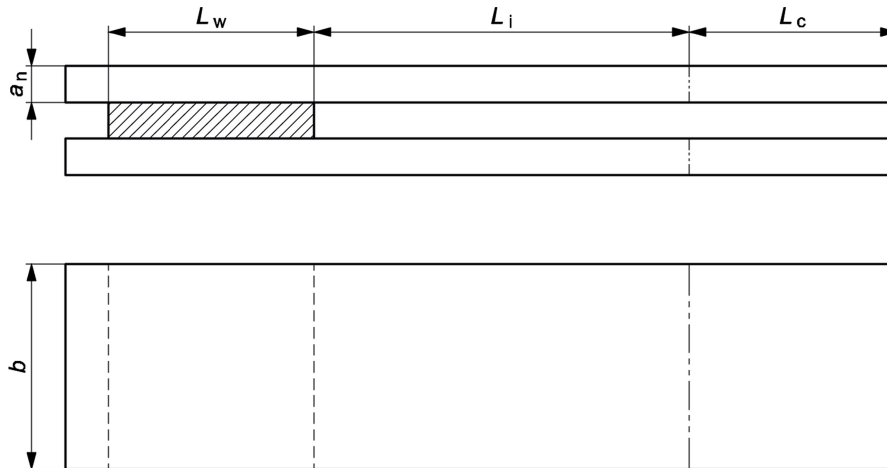


Figure 1 — T-peel test specimen

The value of  $L_c$  shall be greater than, or equal to,  $b$ .

Table 2 — Dimensions of test specimen

Dimensions in millimetres

| $a_n$              | $b^a$          | $L_i$                |
|--------------------|----------------|----------------------|
| $a_n \leq 1,5$     | 15             | $\geq 15$            |
| $1,5 < a_n \leq 3$ | 15             | $\geq 10 \times a_n$ |
| $3 < a_n \leq 5$   | 25             | $\geq 10 \times a_n$ |
| $a_n > 5$          | $5 \times a_n$ | $\geq 10 \times a_n$ |

<sup>a</sup> For reinforced materials,  $b$  shall be 50 mm.

The tolerance for  $b$  shall be  $\pm 0,5$  mm.

### 5.2.2 Preparation of test specimens

The time between the end of the welding operations and the start of machining operations, shall be at least 8 h.

The welded test specimens shall be cut perpendicular to the welded joint.

The test specimens shall be cut with parallel sides as shown in Figure 1.

During cutting, heating of the test specimen should be avoided.

Cutting of the test specimen shall not produce notches.

After cutting, a visual examination of the weld should be carried out and any imperfections, as defined in EN 14728 [5], recorded.

Each test specimen shall be marked so that its original position in the test piece can be identified.

### 5.2.3 Number of test specimens

At least 5 specimens shall be tested for each welded test piece unless otherwise specified in the relevant application standard.



### 5.2.4 Conditioning of test specimens

No heat treatment or mechanical straightening operations shall be carried out on the test specimen. After machining, the test specimens shall be conditioned at least 2 h at the testing temperature.

### 5.3 Apparatus

The test equipment shall conform to the requirements given in ISO 5893.

The crosshead displacement shall be continuous, uniform and in accordance with Table 3.

After setting, the rate shall not vary during the course of any test or series of tests by more than  $\pm 5\%$  of the mean rate and shall remain within the limits imposed in Table 3.

The force shall be measured and recorded with an accuracy of  $\pm 2\%$ .

The test equipment shall be provided with a suitable self-aligning grip to hold the specimen.

### 5.4 Test procedure

The two unwelded ends of the test specimen shall be bent in opposite directions until each end is perpendicular to the weld, to form a T-shaped specimen (see Figure 2) for clamping in the jaws of the test equipment. Inserting the test specimen into the test equipment shall not cause cracking at the weld. If it does, the test is invalid.

Unless otherwise specified, the test shall be carried out at a room temperature of  $(23 \pm 2)^\circ\text{C}$ .

The test speeds for some relevant thermoplastic materials are listed in Table 3.

**Table 3 — T-peel test speeds for some thermoplastics**

| Material         | Speed<br>mm/min |
|------------------|-----------------|
| PVC              | $10 \pm 2$      |
| PVDF, PP-H, PP-B | $20 \pm 2,5$    |
| PE, PP-R         | $50 \pm 5$      |

For other materials, the test speed shall be agreed between the contracting parties.