



SLOVENSKI STANDARD

SIST EN ISO 9969:1997

01-februar-1997

Cevi iz plastomernih materialov - Določevanje obodne togosti

Thermoplastics pipes - Determination of ring stiffness (ISO 9969:1994)

Thermoplastische Rohre - Bestimmung der Ringsteifigkeit (ISO 9969:1994)

Tubes en matières thermoplastiques - Détermination de la rigidité annulaire (ISO 9969:1994)

(standards.iteh.ai)

Ta slovenski standard je istoveten z: EN ISO 9969:1995

<https://standards.iteh.ai/catalog/standards/sist/4e71eaf5-2b1e-4934-9999-f5e8c3c80acc/sist-en-iso-9969-1997>

ICS:

23.040.20 Cevi iz polimernih materialov Plastics pipes

SIST EN ISO 9969:1997

en

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 9969:1997

<https://standards.iteh.ai/catalog/standards/sist/4e71eaf5-2b1e-4934-9999-f5e8c3c80aec/sist-en-iso-9969-1997>

EUROPEAN STANDARD

EN ISO 9969

NORME EUROPÉENNE

EUROPÄISCHE NORM

February 1995

ICS 23.040.20

Descriptors: plastic products, thermoplastic resins, plastic tubes, tests, stiffness tests, circular letter

English version

Thermoplastics pipes - Determination of ring stiffness (ISO 9969:1994)

Tubes en matières thermoplastiques -
Détermination de la rigidité annulaire
(ISO 9969:1994)

Thermoplastische Rohre - Bestimmung der
Ringsteifigkeit (ISO 9969:1994)

This European Standard was approved by CEN on 1994-11-21. CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

The European Standards exist in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

<https://standards.iteh.ai/catalog/standards/sist/4e71ea5-2b1e-4934-9999-15e8c3c80aec/sist-en-iso-9969-1997>

CEN

European Committee for Standardization
Comité Européen de Normalisation
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart,36 B-1050 Brussels

© 1995

All rights of reproduction and communication in any form and by any means reserved in all countries to CEN and its members.

Ref. No. EN ISO 9969:1995 E

Foreword

This European Standard was taken over by the Technical Committee CEN/TC 155 "Plastics piping and ducting systems" from the work of ISO/TC 138 "Plastics pipes, fittings and valves for the transport of fluids" of the International Standards Organization (ISO).

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by August 1995, and conflicting national standards shall be withdrawn at the latest by August 1995.

According to the CEN/CENELEC Internal Regulations, the following countries are bound to implement this European Standard: Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland, United Kingdom.

Endorsement notice

The text of the International Standard ISO 9969:1994 was approved by CEN as a European Standard without any modification.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN ISO 9969:1997](https://standards.iteh.ai/catalog/standards/sist/4e71eaf5-2b1e-4934-9999-f5e8c3c80aacc/sist-en-iso-9969-1997)

<https://standards.iteh.ai/catalog/standards/sist/4e71eaf5-2b1e-4934-9999-f5e8c3c80aacc/sist-en-iso-9969-1997>

INTERNATIONAL
STANDARD

ISO
9969

First edition
1994-03-01

**Thermoplastics pipes — Determination of
ring stiffness**

iTeh STANDARD PREVIEW
(standards.iteh.ai)

*Tubes en matières thermoplastiques — Détermination de la rigidité
annulaire*

[SIST EN ISO 9969:1997](https://standards.iteh.ai/catalog/standards/sist/4e71eaf5-2b1e-4934-9999-f5e8c3c80acc/sist-en-iso-9969-1997)

[https://standards.iteh.ai/catalog/standards/sist/4e71eaf5-2b1e-4934-9999-
f5e8c3c80acc/sist-en-iso-9969-1997](https://standards.iteh.ai/catalog/standards/sist/4e71eaf5-2b1e-4934-9999-f5e8c3c80acc/sist-en-iso-9969-1997)



Reference number
ISO 9969:1994(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 9969 was prepared by Technical Committee ISO/TC 138, *Plastics pipes, fittings and valves for the transport of fluids*, Sub-Committee SC 1, *Plastics pipes and fittings for soil, waste and drainage (including land drainage)*.

<https://standards.iteh.ai/catalog/standards/sist/4e71ea5-2b1e-4934-9999-f5e8c3c80acc/sist-en-iso-9969-1997>

© ISO 1994

All rights reserved. No part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

Thermoplastics pipes — Determination of ring stiffness

1 Scope

This International Standard specifies a method of determining the ring stiffness of thermoplastics pipes having a circular cross-section.

2 Symbols

The following symbols are used in this International Standard:

		Units
d_n	nominal diameter of pipe	mm
d_i	internal diameter of pipe test piece	m
F	loading force	kN
L	length of test piece	m
S	ring stiffness	kN/m ²
y	vertical deflection	m

3 Principle

The ring stiffness is determined by measuring the force and the deflection while deflecting the pipe at a constant rate.

A length of pipe supported horizontally is compressed vertically between two parallel flat plates moved at a constant speed which is dependent upon the diameter of the pipe.

A plot of force versus deflection is generated. The ring stiffness is calculated as a function of the force necessary to produce a deflection of 0,03 d_i diametrically across the pipe.

4 Apparatus

4.1 Compressive-testing machine, capable of a constant rate of crosshead movement adjustable as appropriate to the nominal diameter of the pipe in conformance with table 1, with sufficient force and

travel to produce the specified deflection (see clause 7) via a pair of parallel plates (4.2).

Table 1 — Deflection speeds

Nominal diameter d_n of pipe mm	Deflection speed mm/min
$d_n \leq 100$	$2 \pm 0,4$
$100 < d_n \leq 200$	5 ± 1
$200 < d_n \leq 400$	10 ± 2
$400 < d_n \leq 1\,000$	20 ± 2
$d_n > 1\,000$	50 ± 5

4.2 Two steel plates, through which the compressive force can be applied to the test piece. The plates shall be flat, smooth and clean and shall not deform during the test to an extent that would affect the results.

The length of each plate shall be at least equal to the length of the test piece. The width of each plate shall be not less than the maximum width of the surface in contact with the test piece while under load plus 25 mm.

4.3 Measuring devices, capable of determining

- the length of the test piece to within 1 mm (see 5.2);
- the inside diameter of the test piece to within 0,5 %;
- the change in inside diameter of the test piece in the direction of loading with an accuracy of 0,1 mm, or 1 % of the deflection, whichever is the greater.

An example of a device for measuring the inside diameter of corrugated pipes is shown in figure 1.

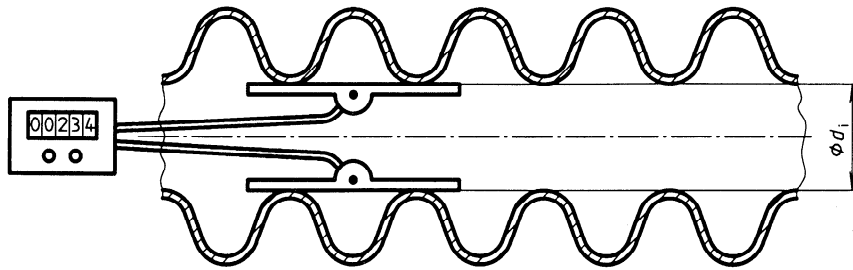


Figure 1 — Example of a device for measuring the inside diameter of a corrugated pipe

4.4 Force-measuring device, capable of determining to within 2 % the force necessary to produce a 1 % to 4 % deflection of the test piece diametrically across the test piece.

Each of the three to six length measurements shall be made to within 1 mm.

For each individual test piece, the smallest of the three to six length measurements shall not be less than 0,9 times the largest measurement.

5 Test pieces

5.2.2 For pipes that have nominal diameters less than or equal to 1 500 mm, the average length of each test piece shall be $300 \text{ mm} \pm 10 \text{ mm}$.

5.1 Marking and number of test pieces

The pipe for which the ring stiffness is to be determined shall be marked on the outside along its full length with a line along one generatrix. Three test pieces, **a**, **b** and **c**, respectively, shall be taken from this marked pipe such that the ends of the test pieces are perpendicular to the pipe axis and their lengths conform to 5.2.

5.2.3 For pipes that have nominal diameters greater than 1 500 mm, the average length, in millimetres, of each test piece shall be at least $0,2d_n$.

5.2 Length of test pieces

5.2.1 The length of each test piece shall be determined by calculating the arithmetic mean of three to six length measurements equally spaced around the perimeter of the pipe as given in table 2. The length of each test piece shall conform to 5.2.2, 5.2.3, 5.2.4 or 5.2.5, as applicable.

5.2.4 Structured-wall pipes with perpendicular ribs or corrugations or other regular structures shall be cut such that each test piece contains the minimum whole number of ribs, corrugations or other structures necessary to satisfy the requirement on length given in 5.2.2 or 5.2.3, as applicable (see figure 2).


The cuts shall be made at the mid-point between the ribs, corrugations or other structures.

5.2.5 For helically wound pipes (see figure 3), the length of each test piece shall be such that it contains the minimum whole number of helical windings necessary to satisfy the requirement on length given in 5.2.2 or 5.2.3, as applicable.

For pipes with helical stiffeners in the form of ribs, corrugations, etc., the length of each test piece shall be such that it comprises a whole number of stiffeners, with a minimum of three, and shall conform to 5.2.2 or 5.2.3, as applicable.

Table 2 — Number of length measurements

Nominal diameter d_n of the pipe mm	Number of length measurements
$d_n \leq 200$	3
$200 < d_n < 500$	4
$d_n \geq 500$	6

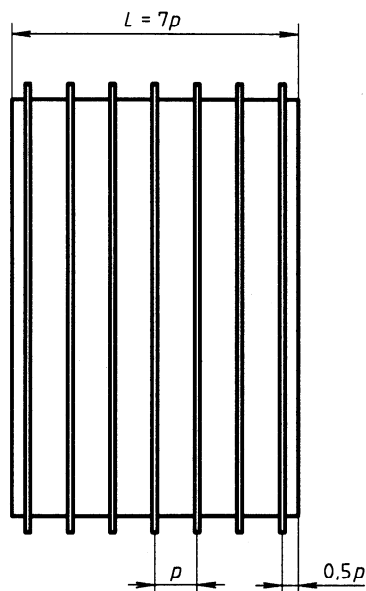

e.g. $p = 45$ mm

Figure 2 — Test piece cut out of a perpendicularly ribbed pipe

5.3 Inside diameter of test pieces

Determine the inside diameters d_{ia} , d_{ib} and d_{ic} of the respective test pieces **a**, **b** and **c** (see 5.1) as the arithmetic mean of four measurements obtained at 45° intervals on one cross-section at mid-length, each measurement being made to within 0,5 %.

Record the calculated mean inside diameter d_{ia} , d_{ib} and d_{ic} for each test piece **a**, **b** and **c**, respectively.

Calculate the average value d_i of these three values using the following equation:

$$d_i = \frac{d_{ia} + d_{ib} + d_{ic}}{3}$$

5.4 Age of test pieces

At the start of the test, the age of the test pieces shall be at least 24 h.

For type testing, and in cases of dispute, the age of the test pieces shall be 21 days \pm 2 days.

6 Conditioning

Condition the test pieces in air at the test temperature (see 7.1) for at least 24 h immediately prior to testing.

7 Procedure

7.1 Unless otherwise specified in the referring standard, carry out the test procedure at $23\text{ °C} \pm 2\text{ °C}$ or, in countries where 27 °C is used as the standard laboratory temperature, at $27\text{ °C} \pm 2\text{ °C}$.

In cases of dispute, $23\text{ °C} \pm 2\text{ °C}$ shall be used.


NOTE 1 It is probable that the test temperature has an influence on the ring stiffness.

7.2 If it can be determined in which position the test piece has the lowest ring stiffness, place the first test piece **a** in this position in the compressive-testing machine.

Otherwise, place the first test piece in such a way that the marking line is in contact with the upper plate.

Rotate the two others **b** and **c** by 120° and 240° , respectively, in relation to the first test piece when placing them in the testing machine.

7.3 For each test piece, attach the deflection gauge and check the angular position of the test piece with respect to the upper plate.

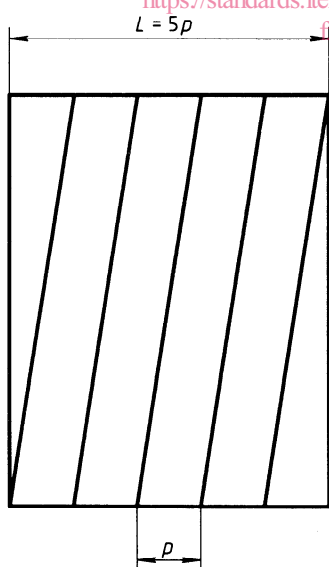

e.g. $p = 65$ mm

Figure 3 — Test piece cut out of a helically wound pipe