

---

---

**Textiles — Tensile properties of  
fabrics —**

**Part 1:  
Determination of maximum force and  
elongation at maximum force using  
the strip method**

*Textiles — Propriétés des étoffes en traction —*

*Partie 1: Détermination de la force maximale et de l'allongement à la  
force maximale par la méthode sur bande*

ISO 13934-1:2013

<https://standards.iteh.ai/catalog/standards/iso/ab11781a-7deb-4b19-be60-0710cddaf83a/iso-13934-1-2013>



iTeh Standards  
(<https://standards.iteh.ai>)  
Document Preview

ISO 13934-1:2013

<https://standards.iteh.ai/catalog/standards/iso/ab11781a-7deb-4b19-be60-0710cddaf83a/iso-13934-1-2013>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2013

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

Page

<b>Foreword</b> .....	<b>iv</b>
<b>Introduction</b> .....	<b>v</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>1</b>
<b>4 Principle</b> .....	<b>3</b>
<b>5 Sampling</b> .....	<b>4</b>
<b>6 Apparatus</b> .....	<b>4</b>
6.1 CRE machine.....	4
<b>7 Atmosphere for conditioning and testing</b> .....	<b>5</b>
<b>8 Preparation of test specimen</b> .....	<b>5</b>
8.1 General.....	5
8.2 Dimensions.....	5
8.3 Preparation of test specimens.....	5
8.4 Wet test specimens.....	6
<b>9 Procedure</b> .....	<b>6</b>
9.1 Gauge length.....	6
9.2 Rate of extension or elongation.....	6
9.3 Mounting of test specimens.....	6
9.4 Operation.....	7
9.5 Tests on wet test specimens.....	8
<b>10 Calculation and expression of results</b> .....	<b>8</b>
<b>11 Test report</b> .....	<b>8</b>
<b>Annex A (informative) Suggested procedure for sampling</b> .....	<b>10</b>
<b>Annex B (informative) Locations of test specimens cut from a laboratory sample</b> .....	<b>11</b>
<b>Bibliography</b> .....	<b>12</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

The first edition of this International Standard ISO 13934-1 was prepared by the European Committee for Standardization (CEN) in collaboration with ISO Technical Committee TC 38, Textiles, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

ISO 13934-1 was prepared by Technical Committee ISO/TC 38, *Textiles*, Subcommittee SC 24, *Conditioning atmospheres and physical tests for textile fabrics*.

This second edition cancels and replaces the first edition (ISO 13934-1:1999), of which it constitutes a minor revision.

ISO 13934 consists of the following parts, under the general title *Textiles — Tensile properties of fabrics*:

- Part 1: *Determination of maximum force and elongation at maximum force using the strip method*
- Part 2: *Determination of maximum force using the grab method*

## Introduction

This part of ISO 13934 has been prepared in the context of several test methods for determination of certain mechanical properties of textiles using mainly tensile testing machines, e.g. tensile properties, seam tensile properties, tear properties, seam slippage. The procedure for these standards agrees where appropriate. The results obtained by one of the methods should not be compared with those obtained by the other methods.

**iTeh Standards**  
**(<https://standards.iteh.ai>)**  
**Document Preview**

[ISO 13934-1:2013](https://standards.iteh.ai/catalog/standards/iso/ab11781a-7deb-4b19-be60-0710cddaf83a/iso-13934-1-2013)

<https://standards.iteh.ai/catalog/standards/iso/ab11781a-7deb-4b19-be60-0710cddaf83a/iso-13934-1-2013>



# Textiles — Tensile properties of fabrics —

## Part 1:

# Determination of maximum force and elongation at maximum force using the strip method

## 1 Scope

This part of ISO 13934 specifies a procedure to determine the maximum force and elongation at maximum force of textile fabrics using a strip method.

NOTE ISO 13934-2 describes the method known as the grab method. For informative references, see Bibliography.

The method is mainly applicable to woven textile fabrics, including fabrics which exhibit stretch characteristics imparted by the presence of an elastomeric fibre, mechanical, or chemical treatment. It can be applicable to fabrics produced by other techniques. It is not normally applicable to geotextiles, nonwovens, coated fabrics, textile-glass woven fabrics, and fabrics made from carbon fibres or polyolefin tape yarns (see Bibliography).

The method specifies the determination of the maximum force and elongation at maximum force of test specimens in equilibrium with the standard atmosphere for testing, and of test specimens in the wet state.

The method is restricted to the use of constant rate of extension (CRE) testing machines.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 139, *Textiles — Standard atmospheres for conditioning and testing*

ISO 3696, *Water for analytical laboratory use — Specification and test methods*

ISO 7500-1, *Metallic materials — Verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Verification and calibration of the force-measuring system*

ISO 10012, *Measurement management systems — Requirements for measurement processes and measuring equipment*

## 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

### 3.1

#### **constant-rate-of-extension (CRE) testing machine**

tensile-testing machine provided with one clamp which is stationary and another clamp which moves with a constant speed throughout the test, the entire testing system being virtually free from deflection

### 3.2

#### **strip test**

tensile test in which the full width of the test specimen is gripped in the jaws of the testing machine

### 3.3

#### **gauge length**

distance between the two effective clamping points of a testing device

Note 1 to entry: The effective clamping points (or lines) of jaws can be checked by clamping a test specimen under defined pretension with carbon copy paper to produce a gripping pattern on the test specimen and/or the jaw faces.

### 3.4

#### **initial length**

length of a test specimen under specified pretension between the two effective clamping points at the beginning of certain tests

Note 1 to entry: See also 3.3.

### 3.5

#### **pretension**

force applied to a test specimen at the beginning of certain tests

Note 1 to entry: Pretension is used to determine the initial length of the test specimen (see also 3.4 and 3.7).

### 3.6

#### **extension**

increase in length of a test specimen produced by a force

Note 1 to entry: Extension is expressed in units of length.

### 3.7

#### **elongation**

ratio of the extension of a test specimen to its initial length

Note 1 to entry: Elongation is expressed as a percentage.


### 3.8

#### **elongation at maximum force**

elongation of a test specimen produced by the maximum force<sup>13</sup>

Note 1 to entry: See [Figure 1](https://standards.iteh.ai/catalog/standards/iso/ab11781a-7deb-4b19-be60-0710cddaf83a/iso-13934-1-2013).

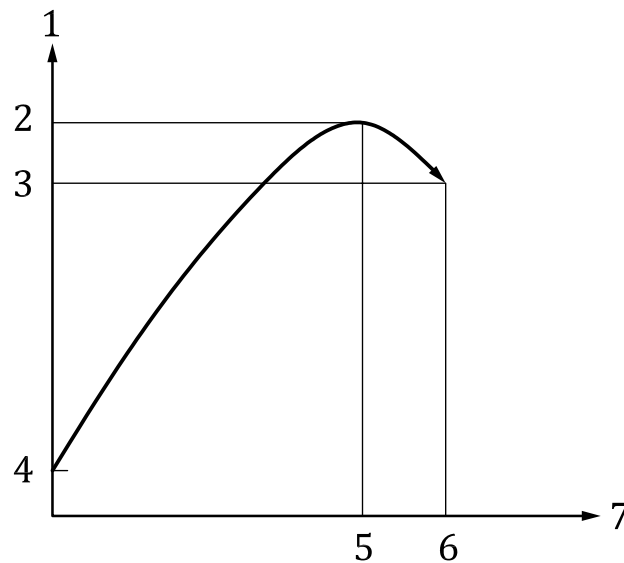

**Key**

- 1 force
- 2 maximum force
- 3 force at rupture
- 4 pretension
- 5 elongation at max. force
- 6 elongation at rupture
- 7 elongation

**Figure 1 — Example of force-elongation curve**

**3.9****elongation at rupture**

elongation of a test specimen corresponding to the force at rupture

Note 1 to entry: See [Figure 1](#).

**3.10****force at rupture**

force recorded at the point of rupture of a test specimen during a tensile test

Note 1 to entry: See [Figure 1](#).

**3.11****maximum force**

maximum force recorded when a test specimen is taken to rupture during a tensile test under the specified conditions

Note 1 to entry: See [Figure 1](#).

**4 Principle**

A fabric test specimen of specified dimensions is extended at a constant rate until it ruptures. The maximum force and the elongation at maximum force and, if required, the force at rupture and the elongation at rupture are recorded.

## 5 Sampling

Select samples either in accordance with the procedure laid down in the material specification for the fabric, or as agreed between the interested parties.

In the absence of an appropriate material specification, the example of a suitable sampling procedure given in [Annex A](#) may be used.

An example of a suitable pattern for cutting test specimens from the laboratory sample is given in [Annex B](#). Avoid test specimens from folded or creased areas, selvages, and areas not representative of the fabric.

## 6 Apparatus

### 6.1 CRE machine

Metrological confirmation system of the tensile-testing machine shall be in accordance with ISO 10012.

The constant-rate-of-extension (CRE) machine shall have the general characteristics given in [6.1.1](#) to [6.1.6](#).

**6.1.1** The tensile-testing machine shall be provided with means for indicating or recording both the force applied to the test specimen in stretching it to rupture and the corresponding extension of the test specimen. Under conditions of use, the accuracy of the apparatus shall be class 1 of ISO 7500-1. The error of the indicated or recorded maximum force at any point in the range in which the machine is used shall not exceed  $\pm 1\%$ , and the error of the indicated or recorded jaw separation shall not exceed  $\pm 1$  mm.

**6.1.2** If a class 2 tensile-testing machine according to ISO 7500-1 is to be used, this shall be stated in the test report.

**6.1.3** If recording of force and elongation is obtained by means of data acquisition boards and software, the frequency of data collection shall be at least eight per second.

**6.1.4** The machine shall be capable of constant rates of extension of 20 mm/min and 100 mm/min, with an accuracy of  $\pm 10\%$ .

**6.1.5** The machine shall be capable of setting the gauge length to 100 mm and 200 mm, to within  $\pm 1$  mm.

**6.1.6** The clamping device of the machine shall be positioned with the centre of the two jaws in the line of applied force, the front edges shall be at right angles to the line of applied force, and their clamping faces shall be in the same plane.

The jaws shall be capable of holding the test specimen without allowing it to slip and designed so that they do not cut or otherwise weaken the test specimen.

The faces of the jaws shall be smooth and flat, except that when, even with packing, the test specimen cannot be held satisfactorily with flat-faced jaws, engraved or corrugated jaws can be used to prevent slippage. Other auxiliary materials for use with either smooth or corrugated jaws to improve specimen gripping include paper, leather, plastics, or rubber.

**NOTE 1** It is recommended that serrated metal faced jaws are used when testing fabrics with stretch properties. Different jaw face surfaces may lead to different elongation results.

**NOTE 2** If jaw breaks or slippage cannot be prevented with flat jaws, capstan jaws have often been found suitable. Extension measurement can be carried out by means of an extensometer which follows the movement of two reference points on the test specimen.

The jaws preferably should have a width of at least 60 mm but shall not be less than the width of the test specimen.