



# DRAFT INTERNATIONAL STANDARD ISO/DIS 22649

ISO/TC 216

Secretariat: AENOR

Voting begins on  
2013-01-17

Voting terminates on  
2013-06-17

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION • МЕЖДУНАРОДНАЯ ОРГАНИЗАЦИЯ ПО СТАНДАРТИЗАЦИИ • ORGANISATION INTERNATIONALE DE NORMALISATION

## Footwear — Test methods for insoles and insocks — Water absorption and desorption

*Chaussures — Méthodes d'essai applicables aux premières de montage et aux premières de propreté — Absorption et désorption d'eau*

[Revision of first edition (ISO 22649:2003)]

ICS 61.060

### ISO/CEN PARALLEL PROCESSING

This draft has been developed within the European Committee for Standardization (CEN), and processed under the **CEN-lead** mode of collaboration as defined in the Vienna Agreement.

This draft is hereby submitted to the ISO member bodies and to the CEN member bodies for a parallel five-month enquiry.

Should this draft be accepted, a final draft, established on the basis of comments received, will be submitted to a parallel two-month approval vote in ISO and formal vote in CEN.

**To expedite distribution, this document is circulated as received from the committee secretariat. ISO Central Secretariat work of editing and text composition will be undertaken at publication stage.**

**Pour accélérer la distribution, le présent document est distribué tel qu'il est parvenu du secrétariat du comité. Le travail de rédaction et de composition de texte sera effectué au Secrétariat central de l'ISO au stade de publication.**

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)  
Full standard:  
<https://standards.iteh.ai/catalog/standards/sist/7c374406-12f3-4bd8-99d7-978dbd1730e0/iso-22649-2016>

### Copyright notice

This ISO document is a Draft International Standard and is copyright-protected by ISO. Except as permitted under the applicable laws of the user's country, neither this ISO draft nor any extract from it may be reproduced, stored in a retrieval system or transmitted in any form or by any means, electronic, photocopying, recording or otherwise, without prior written permission being secured.

Requests for permission to reproduce should be addressed to either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Reproduction may be subject to royalty payments or a licensing agreement.

Violators may be prosecuted.

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 22649 was prepared by Technical Committee ISO/TC 216, *Footwear*, Subcommittee SC , and by Technical Committee CEN/TC 309, *Footwear* in collaboration.

This second/third/... edition cancels and replaces the first/second/... edition (EN 12746:2000, ISO 22649:2003), [clause(s) / subclause(s) / table(s) / figure(s) / annex(es)] of which [has / have] been technically revised.

# DRAFT 2013

**iTeh STANDARD PREVIEW**  
(standards.iTech.ai)

Full standard:  
<https://standards.iTech.ai/catalog/standards/siv/7c374406-12f3-4bd8-99d7-978dbd1730e0/iso-22649-2016>

# Footwear — Test methods for insoles and insocks — Water absorption and desorption

## 1 Scope

This document specifies two test methods for determining the water absorption and desorption of insoles and insocks, irrespective of the material.

These methods are:

- Method A: Determination of the static water absorption and desorption of insoles and insocks.
- Method B: Determination of the dynamic water absorption and desorption of insoles.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 18454, *Footwear — Standard atmospheres for conditioning and testing of footwear and components for footwear*

ISO 17709, *Footwear — Sampling location, preparation and duration of conditioning of samples and test pieces*

## 3 Definitions

For the purposes of this document, the following definitions apply.

### 3.1

#### **water absorption**

the gain in mass per area unit of the test piece due to water absorption during one or more specified periods of time

### 3.2

#### **water desorption**

the percentage loss in mass of the test piece, expressed in terms of the mass of water absorbed

### 3.3

#### **surface**

surface is the visible site of the material during the use at the shoe

## 4 Apparatus and material

The following apparatus and material shall be used:

### 4.1 Method A

**4.1.1 Laboratory balance** with an accuracy of 0,01 g.

**4.1.2 Square knife**, to cut a test piece of  $(50 \pm 1)$  mm  $\times$   $(50 \pm 1)$  mm. The inner surface of the knife shall be angled outward from the cutting edge at approximately  $5^\circ$  to the vertical so that when the test piece is cut the knife passes through it without damage to the test piece edge.

**4.1.3 Filter paper**

**4.1.4 Distilled water**

**4.1.5 Beaker or recipient** with flat bottom and suitable dimensions.

**4.1.6 Vernier calipers**, capable of measuring to an accuracy of 0,2 mm.

### 4.2 Method B

**4.2.1 Apparatus** (as indicated in figure 1) composed of:

**4.2.1.1 Brass roller (A)**, of diameter  $(120 \pm 1)$  mm and width  $(50 \pm 1)$  mm, which is placed over the test piece (B).

**4.2.1.2 Platform (C)** is covered, with a roughened upper surface and with sufficient perforations to allow the surface to be kept wet by a flow of water through the platform. The upper surface of the platform (C) is covered, by a strip of cotton gauze.

**4.2.1.3 Clamp (D)**, to hold one short side of the test piece (B) in a horizontal position on the platform (C).

**4.2.1.4 Clamp (E)**, to attach the other short side of the test piece to the roller with the attached side being parallel to the axis of the roller.

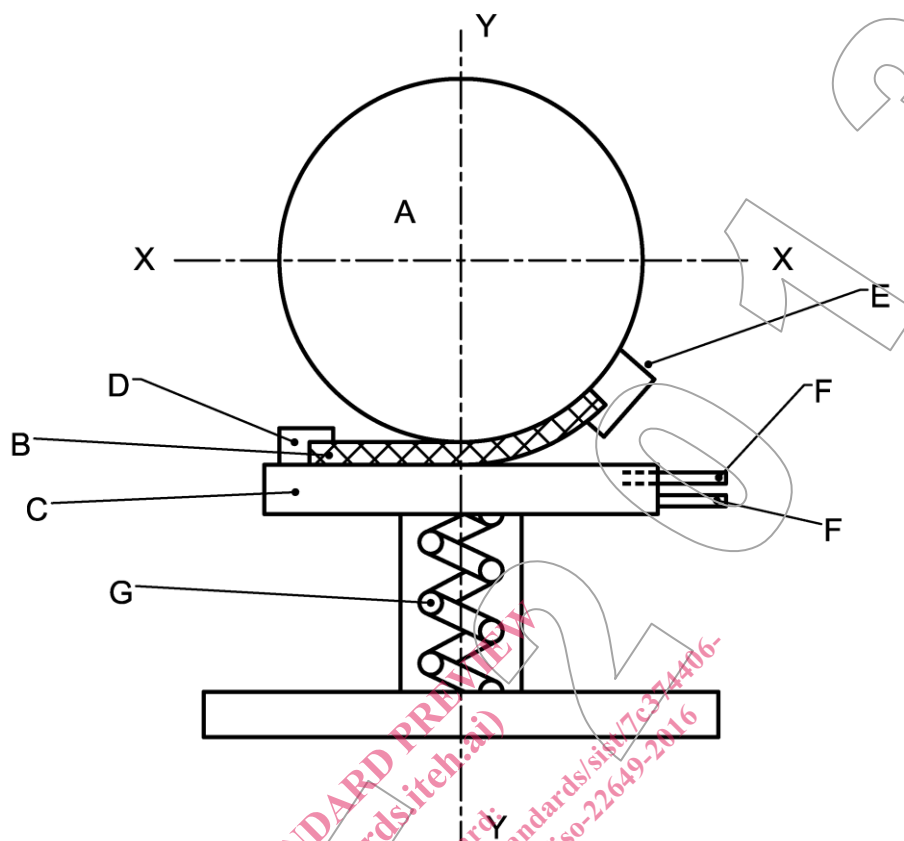
The clamp is held by a weak spring to maintain the sample under slight tension.

**4.2.1.5 Water supply (F)**, through the platform (C) and a means of draining away excess water.

**4.2.1.6 Means** of moving the axis of the roller, with a *to-and-fro* motion along the X-X axis, with an amplitude of  $(50 \pm 2)$  mm about a point directly over the mid point of the test piece and frequency of  $(20 \pm 1)$  cycles per minute.

The movement of the axis causes the roller to move backwards and forwards along the test piece, raising one end and bending it to conform to the shape of the roller.

**4.2.1.7 Means** of pressing the platform, test piece and roller together with a force of  $(80 \pm 5)$  N.

**Key**

- |                 |                 |             |          |
|-----------------|-----------------|-------------|----------|
| a) Brass roller | b) Test piece   | c) Platform | d) Clamp |
| e) Clamp        | f) Water supply |             |          |

**Figure 1 — Device for measuring water absorption and desorption**

**4.2.2 Press knife** to cut test pieces of dimensions  $(110 \pm 1) \text{ mm} \times (40 \pm 1) \text{ mm}$ .

**4.2.3 Balance**, reading to 0,001 g.

**4.2.4 Clock**, reading to 1 s.

**4.2.5 Silicone greas**

## 5 Sampling and conditioning

### 5.1 Method A

Using the square knife described in 4.1.2, cut a test piece of dimensions  $(50 \pm 1) \text{ mm} \times (50 \pm 1) \text{ mm}$  from the shoe insole or insock, cut insole or insock, or from the components as supplied. If the test pieces are taken from the shoe or from the cut components, sampling shall be done in accordance with ISO 17709.

Condition the test pieces according to ISO 18454, for a minimum of 24 h.

Minimum two test pieces are necessary.

## 5.2 Method B

**5.2.1** In the case of footwear, the test pieces should be taken from the forepart of the insole, in the longitudinal sense. For sheet materials, the test pieces shall be taken in the two principal directions, one at 90° to the other.

**5.2.2** Test specimens are strips of  $(110 \pm 1)$  mm  $\times$   $(40 \pm 1)$  mm and shall be placed in a conditioned atmosphere as specified in ISO 18454 for 48 h prior to the test.

**5.2.3** Apply a little silicone grease over the edges of the test piece in order to prevent the ingress of water through the sides.

## 6 Test method

### 6.1 Method A

#### 6.1.1 Determination of the water absorption

Measure (see 4.1.6) the length and the width of the test piece in millimetres to the nearest 0,2 mm. Calculate the area A in square metres.

Weigh the test piece (see 4.1.1) to the nearest 0,01 g, and record its mass,  $M_0$ .

Place the test piece in distilled water conditioned according to ISO 18454 for 6 h. Then remove it, dry off any remaining drops of water using filter paper and reweigh it, recording its mass,  $M_F$ .

The temperature of the test shall be  $(20 \pm 2)$  °C.

#### 6.1.2 Determination of the water desorption

On completion of the test specified in 6.1.1, condition the test piece for 16 h according to ISO 18454 and then reweigh it (see 4.1.1), recording its mass,  $M_R$ .

### 6.2 Method B

#### 6.2.1 Principle

A test piece is positioned on a wet base plate and is submitted to repeat flexing under a given pressure (in the same manner as the insole of a shoe during walking).

#### 6.2.2 Determination of the water absorption

**6.2.2.1** Weigh the piece to the nearest 0,001 g ( $M_0$ ).

**6.2.2.2** Place the cotton gauze on the platform (C).

**6.2.2.3** Apply the test piece in the apparatus with the surface which would be in contact with the foot, in contact with platform (C) covered with the cotton gauze. Attach the narrow ends to the platform and roller, apply a force of  $(80 \pm 5)$  N.

**6.2.2.4** Open the valve for the arrival of water and adjust a flow of water of 7,5 ml/min over the platform.

**6.2.2.5** Switch on the machine and note the time.



- 6.2.2.6** After a suitable period (15 min) stop the water supply 1 min before stopping the machine.
- 6.2.2.7** Remove the test piece and weigh it to the nearest 0,001 g.
- 6.2.2.8** Replace the test piece in the apparatus, open the water valve and continue the test.
- 6.2.2.9** If the test piece is removed before the 8 h period, keep it in a plastic bag long enough to accomplish the night drying time (16 h) established in 6.2.3.

### 6.2.3 Determination of the water desorption

Recondition the test piece in a standard controlled environment specified in ISO 18454 for a period of 16 h, then reweigh the test piece to the nearest 0,001 g ( $M_R$ ).

## 7 Expression of results

### 7.1 Method A

#### 7.1.1 Water absorption

Calculate the water absorption,  $W_A$ , expressed in grams per square metre using the equation (1):

$$W_A = \frac{M_F - M_O}{A} \quad (1)$$

where

$M_O$  is the initial mass of the test piece, i.e. in its dry condition, in grams;

$M_F$  is the final mass of the test piece, i.e. in its wet condition, in grams;

$A$  is the area of the test piece, in square metres.

Express the water absorption to the nearest 1 g/m<sup>2</sup>.

The result will be the average of the two results.

#### 7.1.2 Water desorption

Calculate the water desorption,  $W_D$ , as a percentage of mass using the equation (2):

$$W_D = \frac{M_F - M_R}{M_F - M_O} \times 100 \quad (2)$$

where

$M_O$  is the initial mass of the test piece, in grams;

$M_F$  is the final mass of the test piece, in grams;

$M_R$  is the mass of the reconditioned test piece, in grams.

Report the water desorption to the nearest 1 %.