

Second edition  
2015-03-15

---

---

---

**Resistance welding — Procedure for  
spot welding of uncoated and coated  
low carbon steels**

*Soudage par résistance — Mode opératoire pour le soudage par  
points des aciers à bas carbone revêtus et non revêtus*

**iTeh Standards**  
**(<https://standards.iteh.ai>)**  
**Document Preview**

[ISO 14373:2015](#)

<https://standards.iteh.ai/catalog/standards/iso/257f4af7-5373-45d5-8c17-c2bc4d9e8af3/iso-14373-2015>



Reference number  
ISO 14373:2015(E)

© ISO 2015

# iTeh Standards

## (<https://standards.iteh.ai>)

### Document Preview

[ISO 14373:2015](#)

<https://standards.iteh.ai/catalog/standards/iso/257f4af7-5373-45d5-8c17-c2bc4d9e8af/iso-14373-2015>



#### COPYRIGHT PROTECTED DOCUMENT

© ISO 2015

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

## Contents

Page

<b>Foreword</b>	iv
<b>Introduction</b>	v
<b>1 Scope</b>	1
<b>2 Normative references</b>	1
<b>3 Terms and definitions</b>	2
<b>4 Symbols and abbreviated terms</b>	2
<b>5 Materials</b>	3
5.1 Form	3
5.2 Steel grades	3
<b>6 Surface conditions</b>	3
<b>7 Edge conditions, form of component, and weld spacing</b>	3
<b>8 Electrodes</b>	3
8.1 Materials	3
8.2 Dimensions	3
8.3 Cooling of electrodes	5
<b>9 Weld assessment</b>	6
9.1 General	6
9.2 Weldability tests	6
9.3 Production tests	6
9.4 Frequency of testing	6
<b>10 Weld quality requirements</b>	7
10.1 Weld diameter	7
10.2 Weld penetration and indentation	7
10.3 Failure description of welds	7
10.4 Tensile shear strength	7
10.5 Weld appearance	8
10.5.1 Surface condition	8
10.5.2 Distortion	8
<b>11 Multi-weld arrays</b>	9
<b>Annex A (informative) Recommendations for spot welding equipment</b>	11
<b>Annex B (informative) Typical spot welding conditions</b>	12
<b>Annex C (informative) Partial list of steel types applicable to this International Standard</b>	14
<b>Bibliography</b>	15

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

ISO 14373 was prepared by IIW, *International Institute of Welding*, Commission III. Requests for official interpretations of any aspect of this International Standard should be directed to the ISO Central Secretariat, who will forward them to the IIW Secretariat for an official response.

This second edition cancels and replaces the first edition (ISO 14373:2006), which has been technically revised to align it with ISO 17677-1. [ISO 14373:2015](#)

<https://standards.iteh.ai/catalog/standards/iso/257f4af7-5373-45d5-8c17-c2bc4d9e8af/iso-14373-2015>

## Introduction

This International Standard no longer includes figures showing failure types and modes for tensile shear and cross tension testing in accordance with ISO 14329.

iTeh Standards  
(<https://standards.iteh.ai>)  
Document Preview

[ISO 14373:2015](#)

<https://standards.iteh.ai/catalog/standards/iso/257f4af7-5373-45d5-8c17-c2bc4d9e8af/iso-14373-2015>



# Resistance welding — Procedure for spot welding of uncoated and coated low carbon steels

## 1 Scope

This International Standard specifies requirements for resistance spot welding in the fabrication of assemblies of uncoated and metallic coated low carbon steel, comprising two or three sheets of metal, where the maximum single sheet thickness of components to be welded is within the range 0,4 mm to 3 mm, for the following materials:

- uncoated steels;
- hot-dip zinc or iron-zinc alloy (galvannealed) coated steel;
- electrolytic zinc, zinc-iron, or zinc-nickel coated steel;
- aluminium coated steel;
- zinc-aluminium coated steel.

This International Standard is applicable to welding of sheets of the same or dissimilar thickness, where the thickness ratio is less than or equal to 3:1. It applies to the welding of three thicknesses, where the total thickness is less than or equal to 9 mm.

Welding with the following types of equipment is within the scope of this International Standard:

- a) pedestal welding equipment;
- b) gun welders;
- c) automatic welding equipment where the components are fed by robots or automatic feeding equipment;
- d) multi welders;
- e) robotic welders.

Information on appropriate welding equipment is given in [Annex A](#), and information on spot welding conditions is given in [Annex B](#). This information is provided for guidance only.

Depending on the service conditions of the fabrication, the type of welding equipment, the characteristics of the secondary circuit, the electrode material, and the shape, it is possible that certain modifications are necessary. In such cases, further information can be obtained from the relevant application standard, where one exists.

The welding of organic coated or primer coated steels is not within the scope of this International Standard.

## 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 5182, *Resistance welding — Materials for electrodes and ancillary equipment*

ISO 10447, *Resistance welding — Peel and chisel testing of resistance spot and projection welds*

ISO 14270, *Resistance welding — Specimen dimensions and procedure for mechanized peel testing resistance spot, seam and embossed projection welds*

ISO 15609-5, *Specification and qualification of welding procedures for metallic materials — Welding procedure specification — Part 5: Resistance welding*

ISO 15614-12, *Specification and qualification of welding procedures for metallic materials — Welding procedure test — Part 12: Spot, seam and projection welding*

ISO 17677-1, *Resistance welding — Vocabulary — Part 1: Spot, projection and seam welding*

ISO 18278-1, *Resistance welding — Weldability — Part 1: Assessment of weldability for resistance spot, seam and projection welding of metallic materials*

ISO 18272-2, *Resistance welding — Weldability — Part 2: Alternative procedures for the assessment of sheet steels for spot welding*

### 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 17677-1 and the following apply.

#### 3.1

##### **cross-tension test**

test to determine the load-carrying capability of a spot welded joint subjected to cross tension loading

#### 3.2

##### **tensile shear test**

test to determine the load-carrying capability of a spot welded joint subjected to shear tension loading

#### 3.3

##### **weld nugget**

lenticular zone in a resistance weld, where metal from both (all) sheets has melted and resolidified

#### 3.4

<https://standards.iteh.ai/catalog/standards/iso/257f4af7-5373-45d5-8c17-c2bc4d9e8af/iso-14373-2015>

##### **weld pitch**

centre-to-centre distance between adjacent spot welds

#### 3.5

##### **edge distance**

distance from the edge of the component to the centre of a weld

### 4 Symbols and abbreviated terms

See [Table 1](#).

**Table 1 — Symbols and definitions**

Symbol	Term	Dimension
$d_w$	weld diameter (see ISO 17677-1)	mm
$d_c$	corona bond diameter	mm
$d_e$	electrode tip diameter	mm
$d_n$	nugget diameter	mm
$t$	sheet thickness	mm
$P_s$	tensile shear strength of a weld (TSS)	kN
$R_m$	ultimate tensile strength of steel being welded	MPa

## 5 Materials

### 5.1 Form

The steel shall be flat rolled, in coil or cut to length, and shall be free from harmful imperfections.

### 5.2 Steel grades

A partial list of steel grades to which this International Standard is applicable is given in [Annex C](#).

## 6 Surface conditions

Prior to welding, all surfaces of components to be spot-welded shall be free from grease, scale, rust, paint, dirt, or excessive pitting. Uncoated hot rolled steel shall be in the pickled condition. Coated steels can be supplied with a chromate or phosphate passivation treatment. Phosphated mild steel may be used in certain applications. These materials can be spot welded, although adjustment may be required to the welding parameters outlined in [Annex B](#). Generally speaking, only thin phosphate pretreatment of steel is acceptable prior to spot welding.

**NOTE** Certain surface treatments, such as the application of paint primers, rust preventatives, and oils, can be applied before welding, provided that the coating is uniform in thickness and it has been shown that consistent welds conforming to this International Standard can be obtained. Excessive use of surface pretreatment reduces the length of electrode life.

## 7 Edge conditions, form of component, and weld spacing

The components to be welded shall be free from any burrs or other defects which may interfere with interface contact in some way, or which may necessitate excessive force in fitting the parts together.

The shape of the component should be such that there is satisfactory interfacial contact in the area where the welds are to be made. The edge distance should not be less than  $1,25 d_w$  (see [Figure 1](#)), where  $d_w$  is the weld diameter as defined in [8.2](#). The use of edge distances less than the recommended values influences weld quality adversely. In such cases, the nominal weld size specified may be less than that given in [8.2](#), and therefore due allowance is needed for a lower weld strength (see [10.4](#)).

The distance between adjacent spot welds (see [Figure 1](#)) should not be less than  $16 t$ , and preferably greater. Tolerances for the distance between the centres of two adjacent spot welds should not exceed  $\pm 10\%$ , provided that it does not fall below the minimum value.

## 8 Electrodes

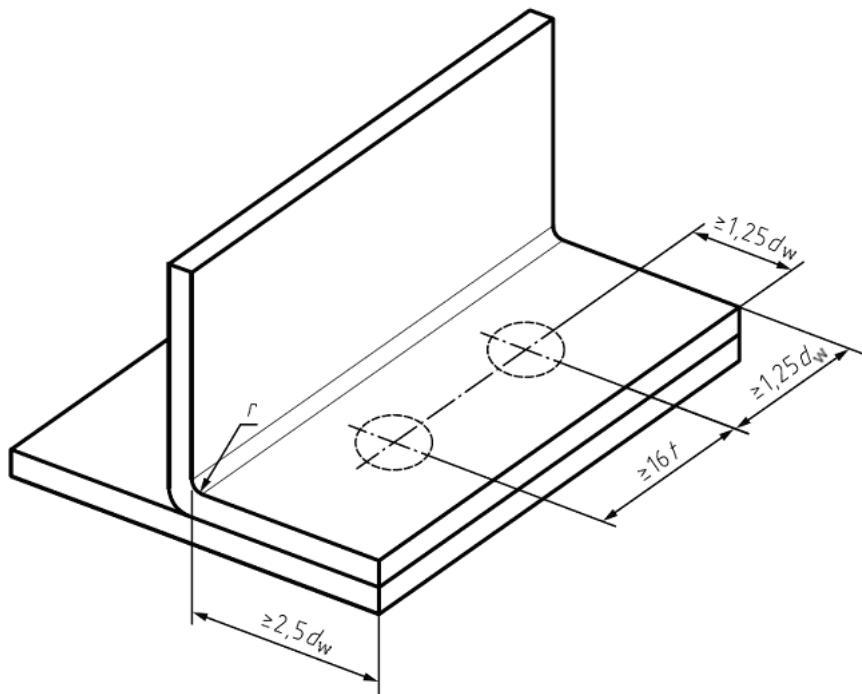
### 8.1 Materials

The electrode materials shall be a copper alloy and should possess high thermal and electrical conductivity. They should comply with, and be used in accordance with, ISO 5182.

### 8.2 Dimensions

The welding electrodes should be of sufficient cross sectional area and strength to carry the welding current and electrode force without overheating, excessive deformation, or excessive deflection.

The electrode dimensions should conform to ISO 5184 for straight electrodes, ISO 5830 for male electrode caps, and ISO 5821 for female electrode caps, as applicable.

**Key** $d_w$  weld diameter $t$  sheet thickness $r$  corner radius

**iTeh Standards**  
**(<https://standards.iteh.ai>)**  
**Document Preview**

NOTE Corner radius  $r$  is recommended to be between one and three times of sheet thickness  $t$ .

**Figure 1 — Recommended edge conditions and weld pitch**

<https://standards.iteh.ai/catalog/standards/iso/257f4af7-5373-45d5-8c17-c2bc4d9e8af/iso-14373-2015>

When welding two sheets of thickness of maximum 3 mm using truncated cone type electrodes, the electrode tip diameter should be chosen from standard sizes according to Formula (1).

$$de = 5\sqrt{t} \quad (1)$$

where

$de$  is the initial tip diameter, in mm;

$t$  is the thickness of the sheet in contact with the electrode, in mm.

When using truncated cone electrodes, the initial (or set-up) weld diameter should be equal to the diameter of the electrode tip; i.e.

$$d_w = de = 5\sqrt{t} \quad (2)$$

where

$d_w$  is the weld diameter, in mm.

**CAUTION — The use of a smaller weld size than that given by Formula (2) may result in lower tensile shear strength (TSS). This needs to be taken into account in all design calculations (see Table 2).**