INTERNATIONAL STANDARD

Second edition 2015-03-01

Resistance welding — Destructive testing of welds — Specimen dimensions and procedure for impact tensile shear test and crosstension testing of resistance spot and embossed projection welds

iTeh STANDARD PREVIEW Soudage par résistance — Essais destructifs des soudures — (S Dimensions des éprouvettes et mode opératoire pour les essais de cisaillement par choc et les essais de traction par choc sur éprouvettes en croix des soudures par résistance par points et par bossage

https://standards.iteh.ai/catalog/standards/sist/c6900df8-b277-4326-b374-8eb5e8585350/iso-14323-2015





Reference number ISO 14323:2015(E)

iTeh STANDARD PREVIEW (standards.iteh.ai)

<u>ISO 14323:2015</u> https://standards.iteh.ai/catalog/standards/sist/c6900df8-b277-4326-b374-8eb5e8585350/iso-14323-2015



COPYRIGHT PROTECTED DOCUMENT

© ISO 2015

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office Case postale 56 • CH-1211 Geneva 20 Tel. + 41 22 749 01 11 Fax + 41 22 749 09 47 E-mail copyright@iso.org Web www.iso.org

Published in Switzerland

Page

Contents

Forev	vord	iv
Intro	duction	v
1	Scope	1
2	Normative references	1
3	Terms and definitions	1
4	Test specimen	1
5	Test equipment and testing procedure5.1General5.2Modified pendulum machine5.3Drop-weight machine	2 2 3 5
6	Test records	10
7	Test report	10
Anne	x A (informative) Determination of failure energy	12
Biblio	ography	15

iTeh STANDARD PREVIEW (standards.iteh.ai)

<u>ISO 14323:2015</u> https://standards.iteh.ai/catalog/standards/sist/c6900df8-b277-4326-b374-8eb5e8585350/iso-14323-2015

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: Foreword - Supplementary information

The committee responsible for this document is ISO/IIW, *International Institute of Welding*, Commission III.

<u>ISO 14323:2015</u>

This second edition cancels and replaces the first edition (180 (14323:2006), 3 which has been technically revised.

Requests for official interpretations of any aspect of this International Standard should be directed to the ISO Central Secretariat, who will forward them to the IIW Secretariat for an official response.

Introduction

This edition of ISO 14323 no longer includes figures showing failure types and modes for tensile shear and cross tension testing in accordance with ISO 14329:2003.

ISO 14323 was revised to align it with ISO 17677-1.

iTeh STANDARD PREVIEW (standards.iteh.ai)

<u>ISO 14323:2015</u> https://standards.iteh.ai/catalog/standards/sist/c6900df8-b277-4326-b374-8eb5e8585350/iso-14323-2015

iTeh STANDARD PREVIEW (standards.iteh.ai)

<u>ISO 14323:2015</u> https://standards.iteh.ai/catalog/standards/sist/c6900df8-b277-4326-b374-8eb5e8585350/iso-14323-2015

Resistance welding — **Destructive testing of welds** — Specimen dimensions and procedure for impact tensile shear test and cross-tension testing of resistance spot and embossed projection welds

1 Scope

This International Standard specifies specimen dimensions and testing procedures for impact tensile shear and cross-tension testing of resistance spot and embossed projection welds in overlapping sheets, in any metallic material of thickness 0,5 mm to 4 mm.

Normative references 2

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 14272, Specimen dimensions and procedure for cross tension testing resistance spot and embossed TTeh STANDARD PREVIEW projection welds

ISO 17677-1, Resistance welding - Stocabulary - Part 1: Spot projection and seam welding

3

Terms and definitions 150 14323.2012 https://standards.iteh.ai/catalog/standards/sist/c6900df8-b277-4326-b374-

For the purposes of this document, the terms and definitions given in ISO 17677-1 and the following apply.

3.1

impact cross-tension failure energy

failure energy obtained from the impact cross-tension testing

3.2

impact cross-tension strength

maximum impact force obtained in the impact cross-tension testing

3.3

impact tensile shear failure energy

failure energy obtained from the impact tensile shear testing

3.4

impact tensile shear strength

maximum impact force obtained in the impact tensile shear testing

4 Test specimen

The dimensions and form of the impact tensile shear test specimen are shown in Figure 1 and Table 1.


The positional accuracy of the weld on the test specimen shall be ± 1 mm or less in every direction.

The dimensions and form of the impact cross-tension specimen are shown in Figure 2 (see ISO 14272).

An example of a jig for welding the impact cross-tension specimen is shown in Figure 3. Two punched strips are placed at right angles to each other, held in the jig, and welded together.

Thickness	Overlap	Specimen width ^a	Specimen length	Free length between clamps	Length of individual test coupons
t	а	b	ls	l_{f}	l _t
mm	mm	mm	mm	mm	mm
$0,5 \leq t \leq 1,5$	35	45	175	95	105
$1,5 < t \le 3$	45	60	230	105	138
$3 < t \le 4$	60	90	260	120	160

Table 1 — Dimensions of impact tensile shear test specimens

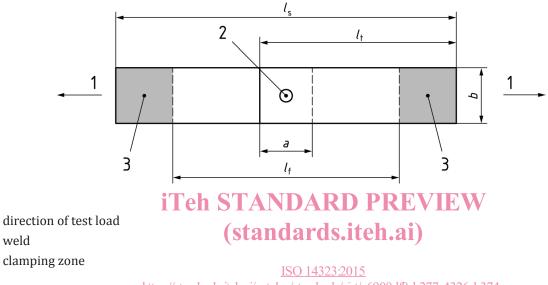

https://standards.iteh.ai/catalog/standards/sist/c6900df8-b277-4326-b374-Figure 1 — Impact tensile shear test specimen

Test equipment and testing procedure 5

5.1 General

Kev 1

2

3

weld

Testing can be accomplished with an appropriate impact-testing machine. If needed, the load can be obtained using hydraulic test equipment.

The pendulum-type machine is generally used for a sheet thickness range of 0,5 mm to 3 mm, and the drop-weight machine for a sheet thickness range of 1 mm to 4 mm.

The minimum number of specimens tested shall be five.

ISO 14323:2015(E)

Dimensions in millimetres

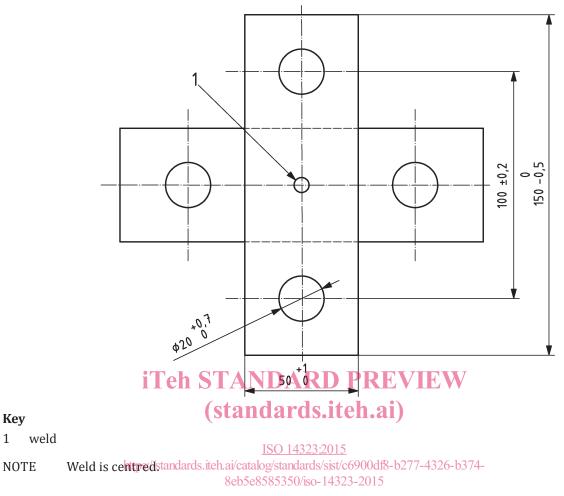



Figure 2 — Impact cross-tension test specimen

5.2 Modified pendulum machine

The test specimen is fixed between the clamping device and the crosshead as shown in Figure 4 and Figure 5. A U-shaped hammer shall be used for testing and is attached to the pendulum.

At the bottom of the pendulum swing, the hammer strikes the crosshead. The energy to failure is indicated by the extent of the upward swing of the pendulum. The velocity of the pendulum at the time of impact is 5,5 m/s. To measure impact force, strain gauges attached to the clamping device or an appropriate load cell shall be used (see Figure 4 and Figure 5). The failure energy is determined as a function of time (see Annex A).

Dimensions in millimetres

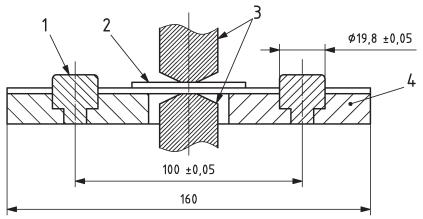

Key

- 1 location pins
- 2 specimen
- 3 welding electrodes
- 4 insulating materials

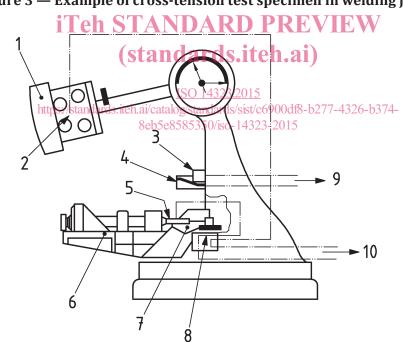



Figure 3 — Example of cross-tension test specimen in welding jig

Кеу

- 1 hammer
- 2 strain gauge/load cell
- 3 lamp
- 4 photodiode
- 5 strain gauge

- 6 clamping device
- 7 test specimen
- 8 cross head
- 9 power supply
- 10 amplifier

Figure 4 — Pendulum machine with U-shaped hammer, equipped for testing spot-welded impact tensile shear specimens

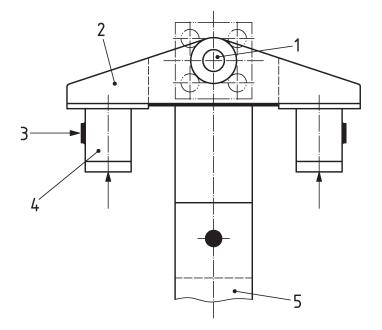

Key

- 1 pivot (maximum rotation 2°)
- 2 cross head (introduce load into test piece)
- 3 strain gauge **iTeh STANDARD PREVIEW**
- 4 impact part of the hammer
- 5 fixed part of the specimen

Figure 5 — Impact tensile shear test specimen and details of crosshead

8eb5e8585350/iso-14323-2015

(standards.iteh.ai)

5.3 Drop-weight machine

The drop-weight machine has a variable mass that can be dropped onto the specimen from different heights. There are two types of equipment as shown in <u>Figure 6</u> and <u>Figure 7</u>. <u>Figure 6</u> is known as a double striking type and <u>Figure 7</u> is known as a single striking type.

The impact tensile shear test specimen and the impact cross-tension test specimen are held in clamps as shown in Figures 8 and Figure 9. The drop-weight machine shall be equipped with instrumentation to monitor displacement or velocity before and after impact, as well as force variation during impact. The difference in velocity can be used to calculate the total energy absorbed by the sample. To ensure complete fracture of the welded specimens, the impact energy shall be greater than 10 times the failure energy. The velocity of the drop-weight striker at the time of impact shall be in the range 5 m/s to 15 m/s.

The force variation during failure shall be monitored by load cells mounted beneath the four corners of the anvil, as shown in <u>Figure 8</u> and <u>Figure 9</u>. Alternatively, a load cell can be mounted in the specimen clamp device to provide the force signal. Examples of results using a drop-weight machine are shown in <u>Figure 10</u>.

To avoid excessive attenuation of the force/time signal through the electronic filtering system, the time to fracture of the specimen shall be at least 1,5 times, and ideally greater than 10 times, the response time of the filter. The optimum filtering system depends on the equipment and should be determined.

The results can be analysed by the method given in <u>Annex A</u>.