

SLOVENSKI STANDARD
oSIST prEN ISO 527-3:2018
01-oktober-2018

Polimerni materiali - Določanje nateznih lastnosti - 3. del: Preskusni pogoji za filme in plošče (ISO/FDIS 527-3:2018)

Plastics - Determination of tensile properties - Part 3: Test conditions for films and sheets (ISO/FDIS 527-3:2018)

Kunststoffe - Bestimmung der Zugeigenschaften - Teil 3: Prüfbedingungen für Folien und Tafeln (ISO/FDIS 527-3:2018)

Plastiques - Détermination des propriétés en traction - Partie 3: Conditions d'essai pour films et feuilles (ISO/FDIS 527-3:2018)

Ta slovenski standard je istoveten z: prEN ISO 527-3

ICS:

83.140.10 Filmi in folije

Films and sheets

oSIST prEN ISO 527-3:2018

en,fr,de

FINAL
DRAFT

INTERNATIONAL
STANDARD

ISO/FDIS
527-3

ISO/TC 61/SC 11

Secretariat: JISC

Voting begins on:
2018-07-19

Voting terminates on:
2018-10-11

Plastics — Determination of tensile properties —

Part 3: Test conditions for films and sheets

Plastiques — Détermination des propriétés en traction —

Partie 3: Conditions d'essai pour films et feuilles

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 527-3:2019

<https://standards.iteh.ai/catalog/standards/sist/d6c88656-25ee-4cee-9b54-b303901847ea/sist-en-iso-527-3-2019>

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

ISO/CEN PARALLEL PROCESSING



Reference number
ISO/FDIS 527-3:2018(E)

© ISO 2018

iTeh STANDARD PREVIEW (standards.iteh.ai)

SIST EN ISO 527-3:2019

<https://standards.iteh.ai/catalog/standards/sist/d6c88656-25ee-4cee-9b54-b303901847ea/sist-en-iso-527-3-2019>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2018

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Apparatus	1
6 Test specimens	2
6.1 Shape and dimensions	2
6.2 Preparation of specimens	4
6.3 Gauge marks	4
6.4 Checking the specimens	4
6.5 Anisotropy	5
7 Number of specimens	5
8 Conditioning	5
9 Procedure	5
10 Calculation and expression of results	5
11 Precision	5
12 Test report	5
Bibliography	6

SIST EN ISO 527-3:2019

<https://standards.iteh.ai/catalog/standards/sist/d6c88656-25ee-4cee-9b54-b303901847ea/sist-en-iso-527-3-2019>

ISO/FDIS 527-3:2018(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 11, *Products*.

SIST EN ISO 527-3:2019

This second edition cancels and replaces the first edition (ISO 527-3:1995), of which it constitutes a minor revision. It also incorporates the Technical Corrigenda ISO 527-3:1995/Cor.1:1998 and ISO 527-3:1995/Cor.2:2001. The changes compared to the previous edition are as follows:

- references to ISO 527-1 have been updated to the latest edition;
- Clauses 3 and 4 have been interchanged;
- the document has been editorially revised.

A list of all parts in the ISO 527-3 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Plastics — Determination of tensile properties —

Part 3:

Test conditions for films and sheets

1 Scope

This document specifies the conditions for determining the tensile properties of plastic films or sheets less than 1 mm thick, based upon the general principles given in ISO 527-1.

NOTE 1 For sheets greater than 1 mm thick, the user is referred to ISO 527-2.

See ISO 527-1:2012, 1.2.

This document is not normally suitable for determining the tensile properties of

- a) cellular materials, and
- b) plastics reinforced by textile fibres.

See ISO 527-1:2012, 1.5.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 527-1:2012, *Plastics — Determination of tensile properties — Part 7: General principles*

ISO 4591, *Plastics — Film and sheeting — Determination of average thickness of a sample, and average thickness and yield of a roll, by gravimetric techniques (gravimetric thickness)*

ISO 4593, *Plastics — Film and sheeting — Determination of thickness by mechanical scanning*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 527-1 apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

4 Principle

See ISO 527-1:2012, 4.1.

5 Apparatus

See ISO 527-1:2012, Clause 5, subject to the following additional requirements.

ISO/FDIS 527-3:2018(E)

According to ISO 527-1:2012, 5.1.2, the tensile-testing machine shall be capable of maintaining the speeds of testing as specified in ISO 527-1:2012, Table 1. It is normal for films and sheets to be tested at a speed of 5 mm/min, 50 mm/min, 100 mm/min, 200 mm/min, 300 mm/min or 500 mm/min. The information contained in ISO 527-1:2013, 9.6, also applies.

According to ISO 527-1:2012, 5.1.5, when testing thin sheets or film material, the specimen shall not carry the weight of the extensometer.

According to ISO 527-1:2012, 5.2, devices complying with the requirements in ISO 4593 shall be used for measuring the thickness, except in the case of very thin film (less than 0,01 mm thick) or embossed film. In those cases, the thickness shall be determined by the method specified in ISO 4591. When ISO 4591 is used, the average thickness of the film sample shall be taken as the thickness of the test specimen.

6 Test specimens

6.1 Shape and dimensions

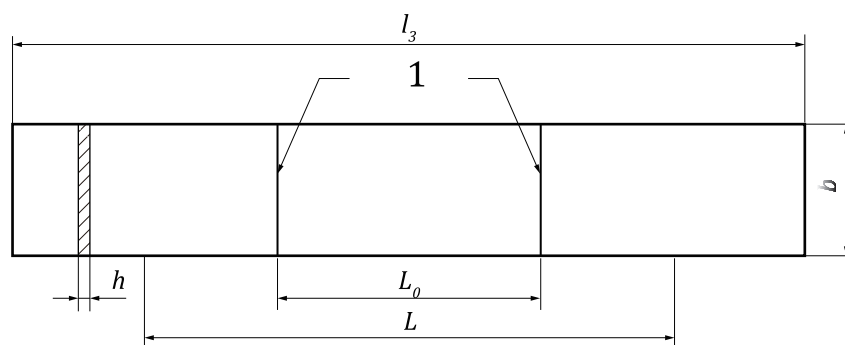
6.1.1 The preferred form of test specimen for the determination of tensile properties by this method is a strip that is 10 mm to 25 mm wide and not less than 150 mm long (specimen type 2 — see [Figure 1](#)), having two parallel gauge marks, 50 mm apart, on the central portion of the specimen.

Some film materials have a very high elongation at break which may result in them being outside the stretching capacity of the testing machine. In such cases, it is permissible to reduce the initial distance between the grips to 50 mm.

6.1.2 When required by the specification for the material under test or for routine quality-control tests, dumb-bell specimen types 5, 1B and 4 of the shape and dimensions shown in [Figures 2, 3 and 4](#) may be used. These specimens are convenient to produce and permit rapid quality-control testing.

Specimen type 5 (see [Figure 2](#)) is recommended for film and sheet with a very high strain at break. Specimen type 4 is recommended for other types of flexible thermoplastic sheet.

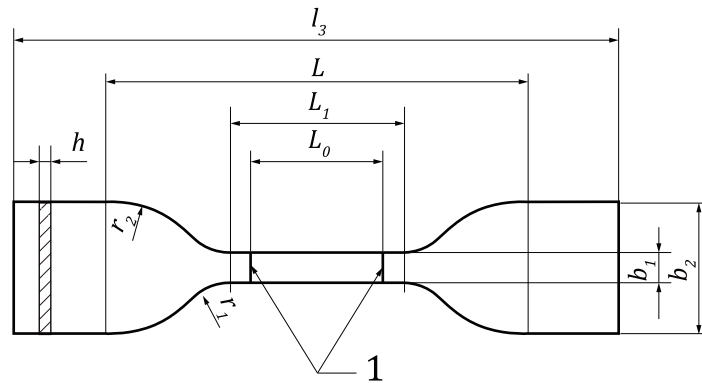
Specimen type 1B (see [Figure 3](#)) is recommended for rigid sheets.



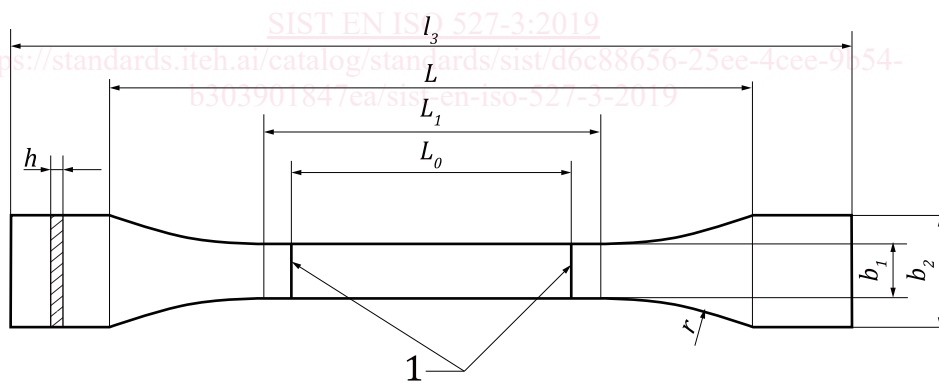
Key

- 1 gauge marks
- b width: 10 mm to 25 mm
- h thickness: ≤ 1 mm
- L_0 gauge length: 50 mm \pm 0,5 mm
- L initial distance between grips: 100 mm \pm 5 mm
- l_3 overall length: ≥ 150 mm

Figure 1 — Specimen type 2

**Key**

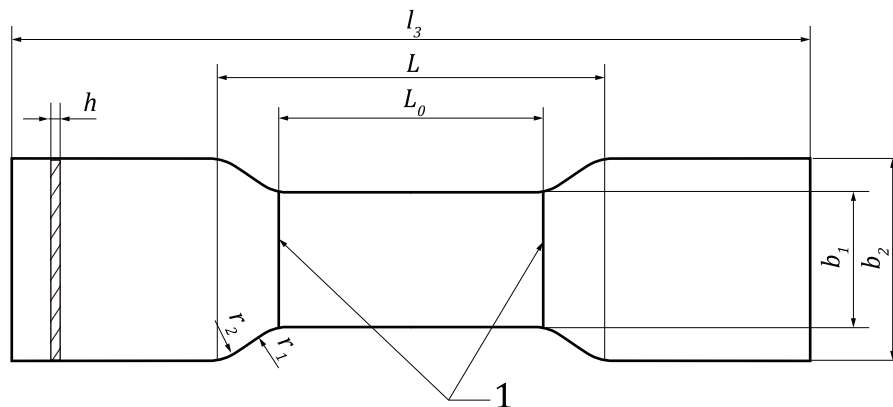
- 1 gauge marks
- b_1 width of narrow parallel-sided portion: $6 \text{ mm} \pm 0,4 \text{ mm}$
- b_2 width at ends: $25 \text{ mm} \pm 1 \text{ mm}$
- h thickness: $\leq 1 \text{ mm}$
- L_0 gauge length: $25 \text{ mm} \pm 0,25 \text{ mm}$
- l_1 length of narrow parallel-sided portion: $33 \text{ mm} \pm 2 \text{ mm}$
- L initial distance between grips: $80 \text{ mm} \pm 5 \text{ mm}$
- l_3 overall length: $\geq 115 \text{ mm}$
- r_1 small radius: $14 \text{ mm} \pm 1 \text{ mm}$
- r_2 large radius: $25 \text{ mm} \pm 2 \text{ mm}$

Figure 2 — Specimen type 5**Key**

- 1 gauge marks
- b_1 width of narrow parallel-sided portion: $10 \text{ mm} \pm 0,2 \text{ mm}$
- b_2 width at ends: $20 \text{ mm} \pm 0,5 \text{ mm}$
- h thickness: $\leq 1 \text{ mm}$
- L_0 gauge length: $50 \text{ mm} \pm 0,5 \text{ mm}$
- l_1 length of narrow parallel-sided portion: $60 \text{ mm} \pm 0,5 \text{ mm}$
- L initial distance between grips: $115 \text{ mm} \pm 5 \text{ mm}$
- l_3 overall length: $\geq 150 \text{ mm}$
- r radius: $\geq 60 \text{ mm}$ (recommended radius: $60,0 \text{ mm} \pm 0,5 \text{ mm}$)

Figure 3 — Specimen type 1B

ISO/FDIS 527-3:2018(E)

**Key**

- 1 gauge marks
- b_1 width of narrow parallel-sided portion: 25,4 mm \pm 0,1 mm
- b_2 width at ends: 38 mm
- h thickness: \leq 1 mm
- L_0 gauge length: 50 mm \pm 0,5 mm
- L initial distance between grips: 98 mm
- l_3 overall length: \geq 152 mm
- r_1 small radius: 22 mm
- r_2 large radius: 25,4 mm

Figure 4 — Specimen type 4

6.2 Preparation of specimens

6.2.1 The test specimens described in 6.1.1 shall be cut or punched so that the edges are smooth and free from notches; examination with a low-power magnifier is recommended to check the absence of notches. Razor blades, suitable paper cutters, scalpels or other devices capable of cutting the specimens to the proper width and producing straight, clean, parallel edges with no visible imperfections shall be used. Punch dies shall be kept sharp by regular honing, and a suitable backing material shall be used with punch dies to ensure a clean-cut edge.

6.2.2 The test specimens described in 6.1.2 shall be obtained by the use of punch dies, using suitable backing material to ensure a clean-cut edge. Dies shall be kept sharp by regular honing, and the edges of the specimen shall be examined with a low-power magnifier to ensure the absence of notches. Discard any specimen with obvious imperfections on the cut edges.

6.3 Gauge marks

See ISO 527-1:2012, 6.3.

The marking device used to produce the gauge marks shall have two parallel edges which are ground smooth and true, 0,05 mm to 0,10 mm wide at the edge and bevelled at an angle of not more than 15°. An ink stamp may also be used to apply ink to the area of the gauge marks, before or after producing them with the marking device, using an ink of a suitable contrasting colour that has no deleterious effect on the film being tested.

6.4 Checking the specimens

Discard any test specimen with obvious imperfections on the cut edges.