## INTERNATIONAL STANDARD

ISO 9649

Second edition 2016-05-15

### **Metallic materials — Wire — Reverse** torsion test

Matériaux métalliques — Fils — Essai de torsion alternée

### iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 9649:2016 https://standards.iteh.ai/catalog/standards/sist/b2105e02-f6f0-4b0c-9884-275890e69d6e/iso-9649-2016



## iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 9649:2016 https://standards.iteh.ai/catalog/standards/sist/b2105e02-f6f0-4b0c-9884-275890e69d6e/iso-9649-2016



#### COPYRIGHT PROTECTED DOCUMENT

#### 

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office Ch. de Blandonnet 8 • CP 401 CH-1214 Vernier, Geneva, Switzerland Tel. +41 22 749 01 11 Fax +41 22 749 09 47 copyright@iso.org www.iso.org

Con	tents	Page
Forew	vord	iv
1	Scope	1
2	Symbols and designations	1
3	Principle	1
4	Testing equipment	2
5	Test piece	2
6	Test conditions	3
7	Procedure	3
8	Test report	3
Riblio	ngranhy	4

## iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 9649:2016 https://standards.iteh.ai/catalog/standards/sist/b2105e02-f6f0-4b0c-9884-275890e69d6e/iso-9649-2016

#### **Foreword**

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see <a href="www.iso.org/directives">www.iso.org/directives</a>).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see <a href="https://www.iso.org/patents">www.iso.org/patents</a>).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: Foreword - Supplementary information

The committee responsible for this document is ISO/TC 164, *Mechanical testing of metals*, Subcommittee SC 2, *Ductility testing*.

ISO 9649:2016

This second edition cancels and replaces the first/edition (ISO29649:1990)) which has been technically revised. 275890e69d6e/iso-9649-2016


### Metallic materials — Wire — Reverse torsion test

#### 1 Scope

This International Standard specifies a method for determining the ability of metallic wire of diameter dimension from 0,3 mm to 10,0 mm inclusive to undergo plastic deformation during reverse torsion. This test is used to detect surface defects, as well as to assess ductility.

#### 2 Symbols and designations

The symbols and designations used in the reverse torsion test of wires are shown in <u>Figure 1</u> and specified in <u>Table 1</u>.

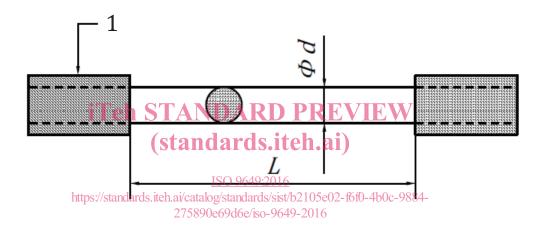

#### Key

1 grip

Figure 1 — Reverse torsion test of wires

<b>Table</b>	1.	— Symbo	alc	and	de	sion	ations
Iabic	1		JIJ	anu	u	-3121	lativiis

Symbol	Designation	Unit
d	Diameter of a round wire	mm
L	Free length between grips	mm
$N_1$	Number of turns in one direction	_
$N_2$	Number of turns in the opposite direction	_

#### 3 Principle

A test piece of wire is twisted a specified number of turns through 360° around its own axis in one direction, and then a specified number of turns through 360° in the opposite direction.

#### 4 Testing equipment

**4.1** The grips shall have a minimum hardness of 55HRC to provide rigidity and/or resistance to abrasion. The grip shall be arranged in the testing machine in such a way that, during testing, they remain on the same axis and do not apply any bending force to the piece.

One of the grips shall be capable of being rotated around the axis of the test piece in two opposite directions while the other shall not be subject to any angular deflection, except for such deflection as may be necessary to measure the torque.

The distance between the grips shall be capable of adjustment for different test piece lengths.

**4.2** The machine shall be constructed so that a change in length between the grips, caused by deformation of the test piece during the test, is not prevented.

The machine shall be constructed so that an appropriate tensile stress (see 7.1) may be applied to the test piece.

- **4.3** The testing speed shall be able to be adjusted, and the number of turns shall be recorded.
- **4.4** A protective shield shall be provided to protect the operator from flying fragments in cases when the wire breaks into more than two pieces.

#### 5 Test piece

### iTeh STANDARD PREVIEW

(standards.iteh.ai)
The length of wire to be used as the test piece shall be as straight as possible.

If straightening is necessary, it shall be done by using suitable methods.

During straightening, the surface of the wire shall not be damaged and the test piece shall not be subject to any twisting.

Wire with a localized sharp curvature or kink shall not be used in the test.

**5.2** Unless otherwise specified in the relevant standard, the nominal free length between the grips (L) of the test piece shall be as given in Table 2.

When testing for surface defects, a fixed free length between grips may be used. This length shall be as specified in the relevant standard and shall be stated in the test report.

Table 2 — Dependence of free length between the grips on nominal diameter of the wire

Nominal diameter	Free length between grips			
d	L			
mm	mm (nominal)			
$0.3 \le d < 1.0$	200 <i>d</i>			
$1.0 \le d < 5.0$	100 <i>d</i> a			
$5,0 \le d \le 10,0$	50 <i>d</i> b			
a 50 <i>d</i> may be used by special agreement.				
b $30d$ may be used by special agreement.				

#### 6 Test conditions

In general, the test is carried out at an ambient temperature between 10 °C and 35 °C. Tests carried out under controlled conditions, where required, shall be made at a temperature of  $(23 \pm 5)$  °C.

#### 7 Procedure

- **7.1** Place the test piece in the testing machine in such a way that its longitudinal axis coincides with the axis of the grips and so that it remains straight during the test. Unless otherwise specified, this may be ensured by applying to the test piece a constant tensile stress not exceeding 2 % of the nominal tensile strength of the wire.
- **7.2** After placing the test piece in the testing machine, rotate one grip at a speed not exceeding 1 turn per second (or not exceeding 0,5 turns per second when the diameter d is 5 mm or greater) through the number of turns,  $N_1$ , in one direction and then the other number of turns,  $N_2$ , in the opposite direction. In general,  $N_1$  and  $N_2$  are specified in the relevant standard. One turn comprises 360°.

After the test, the free length of wire between the grips shall be examined by eyes unless otherwise specified in the relevant standard.

**7.3** If the number of turns,  $N_2$ , meets the requirement of the relevant standard, the test piece is considered as having passed the test. If the number of turns,  $N_2$ , reached does not meet the requirement of the relevant standard and the failure is within a distance of 2d from the grip, the test shall be considered invalid and shall be repeated.

NOTE There is an example for this test in 180 8458-3 teh.ai)

8 Test report https://standards.iteh.ai/catalog/standards/sist/b2105e02-f6f0-4b0c-9884-

The test report shall include the following information:

- a) a reference to this International Standard, i.e. ISO 9649;
- b) all details necessary for the identification of the test piece (type of the material, heat number, etc.);
- c) the diameter *d* of the test piece;
- d) all details regarding the test piece preparation (method of straightening, etc.);
- e) the test conditions (the free length between the grips, the tensile stress applied, test speed, etc.);
- f) the number of turns  $(N_1, N_2)$ .

### **Bibliography**

[1] ISO 8458-3, Steel wire for mechanical springs — Part 3: Oil-hardened and tempered wire

## iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 9649:2016 https://standards.iteh.ai/catalog/standards/sist/b2105e02-f6f0-4b0c-9884-275890e69d6e/iso-9649-2016

# iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 9649:2016

 $https://standards.iteh.ai/catalog/standards/sist/b2105e02-f6f0-4b0c-9884-\\275890e69d6e/iso-9649-2016$