



SLOVENSKI STANDARD
oSIST prEN ISO 7590:2017
01-november-2017

Naprave in sistemi za kontinuirni transport - Trakovi tračnih transporterjev z jeklenim vložkom - Metode za določevanje celotne debeline in debeline zaščitne obloge (ISO/DIS 7590:2017)

Steel cord conveyor belts - Methods for the determination of total thickness and cover thickness (ISO/DIS 7590:2017)

Stahlseil-Fördergurte - Messung der Gesamtdicke und der Deckplattendicke (ISO/DIS 7590:2017)

Courroies transporteuses à câbles d'acier - Méthodes de détermination de l'épaisseur totale et de l'épaisseur des revêtements (ISO/DIS 7590:2017)

Ta slovenski standard je istoveten z: prEN ISO 7590

ICS:

53.040.20 Deli za transporterje Components for conveyors

oSIST prEN ISO 7590:2017 **en,fr,de**

DRAFT INTERNATIONAL STANDARD

ISO/DIS 7590

ISO/TC 41/SC 3

Secretariat: JISC

Voting begins on:
2017-09-07Voting terminates on:
2017-11-30

Steel cord conveyor belts — Methods for the determination of total thickness and cover thickness

Courroies transporteuses à câbles d'acier — Méthodes de détermination de l'épaisseur totale et de l'épaisseur des revêtements

ICS: 53.040.20

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 7590:2018

<https://standards.iteh.ai/catalog/standards/sist/f7ebffd3-019d-428d-bd4e-d8cf59e0cca8/sist-en-iso-7590-2018>

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

This document is circulated as received from the committee secretariat.

ISO/CEN PARALLEL PROCESSING



Reference number
ISO/DIS 7590:2017(E)

© ISO 2017

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 7590:2018

<https://standards.iteh.ai/catalog/standards/sist/f7ebffd3-019d-428d-bd4c-d8cf59e0cca8/sist-en-iso-7590-2018>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2017, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Apparatus	2
6 Procedure	2
6.1 General.....	2
6.2 Measurement points.....	2
6.3 Test pieces and test specimens.....	2
6.3.1 General.....	2
6.3.2 Test pieces and test specimens for method A1.....	3
6.3.3 Test specimens for method A2.....	3
6.3.4 Test specimens for method B.....	3
6.4 Measurement of thickness.....	3
6.4.1 Method A1.....	3
6.4.2 Method A2.....	4
6.4.3 Method B.....	5
7 Test report	5
Bibliography	7

iTech STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 7590:2018

<https://standards.iteh.ai/catalog/standards/sist/f7ebffd3-019d-428d-bd4c-d8cf59e0cca8/sist-en-iso-7590-2018>

ISO/DIS 7590:2017(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html.

The committee responsible for this document is Technical Committee ISO/TC41, *Pulleys and belts (including veebelts)*, Subcommittee SC 3, *Conveyor belts*.

This sixth edition cancels and replaces the fifth edition (ISO 7590:2009), which has been technically revised. <https://standards.iteh.ai/catalog/standards/sist/f7ebffd3-019d-428d-bd4e-d8cf59e0cca8/sist-en-iso-7590-2018>

The main changes compared to the previous edition are as follows:

- The [Figure 4](#) was corrected.

Steel cord conveyor belts — Methods for the determination of total thickness and cover thickness

1 Scope

This International Standard specifies three methods for the measurement of total belt thickness and the thickness of covers of steel cord conveyor belts.

Methods A1 and A2 (micrometer methods) can be used for all steel cord conveyor belts for the measurement of both total belt thickness and cover thickness.

Method B (optical method) is recommended for the measurement of cover thickness only. It is not suitable if there is a textile or metal weft, nor if the ends of the steel cords become twisted when cut.

2 Normative references

There are no normative references in this document.

3 Terms and definitions

For the purposes of this International standard, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

— ISO Online browsing platform: available at <http://www.iso.org/obp>

— IEC Electropedia: available at <http://www.electropedia.org/>

3.1

breaker

Transverse reinforcement in the conveyor belt, typically of a textile material, inserted both above and below or either above or below the layer of longitudinal cords at a distance of at least 1 mm and considered to be part of the cover. Used to protect the longitudinal cords from impact or trapped material damage

3.2

weft

Transverse component of a protective reinforcement of either steel or textile cords, typically inserted both above and below, or either above or below, the layer of longitudinal cords at a distance of less than 1 mm and considered to be part of the belt core

4 Principle

The total thickness is measured using a micrometer at a number of specified points depending on belt width.

The cover thicknesses are measured either:

- a) by removing the covers, taking further measurements at the same specified points and calculating each of the cover thicknesses by subtraction; or
- b) by direct measurement using an optical measuring instrument.

ISO/DIS 7590:2017(E)

5 Apparatus

5.1 Dial gauge micrometer for methods A1 and A2

The instrument shall be graduated every 0,1 mm with flat feet and a circular foot 10 mm in diameter that exerts a pressure of (22 ± 5) kPa on the test specimen.

5.2 Optical measuring instrument for method B

The instrument shall comprise a hand-held magnifying glass with a scale divided in 0,1 mm steps. The magnification shall be at least 8 times.

6 Procedure

6.1 General

If the adhesion strength between cover and core layer is being measured in accordance with ISO 8094, the same test pieces may be used for the determination of cover thickness described in method A1.

If the position of the steel cord is being measured in accordance with EN 13827, the same test piece may be used for the determination of cover thickness described in method A2.

If the use of methods A1 and A2 is impractical, the visible belt end or the end of a laboratory sample of the belt may be used for the determination of cover thickness described in method B.

6.2 Measurement points

If the belt width is less than or equal to 1 000 mm, measure the thickness at three points spaced equidistantly over the belt width (see [Figure 1](#)).

If the belt width is greater than 1 000 mm, measure the thickness at five points spaced equidistantly over the belt width (see [Figure 1](#)).

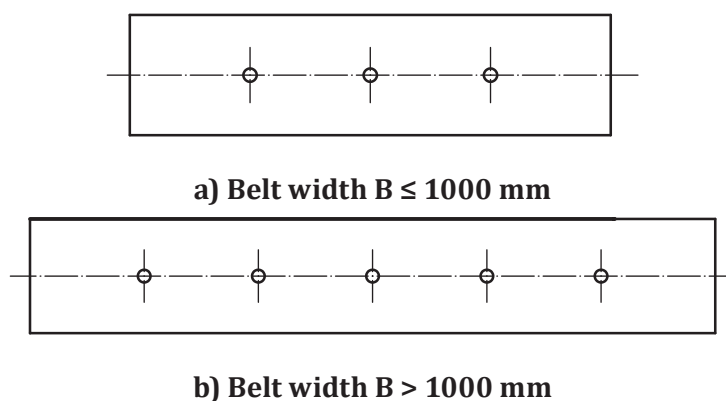


Figure 1 — Location of measurement points


6.3 Test pieces and test specimens

6.3.1 General

Cut a rectangular test piece across the full belt width, at 90° to the belt edge, having dimensions as specified in [6.3.2](#) to [6.3.4](#), as appropriate.

6.3.2 Test pieces and test specimens for method A1

The test piece shall be approximately 150 mm long. Cut three or five, as appropriate, test specimens from the test piece at the measurement points specified in 6.2. Each test specimen shall be two cord pitches wide, i.e. having a width equal to the width that comprises two cords (see Figure 2), and shall have a length of approximately 150 mm.

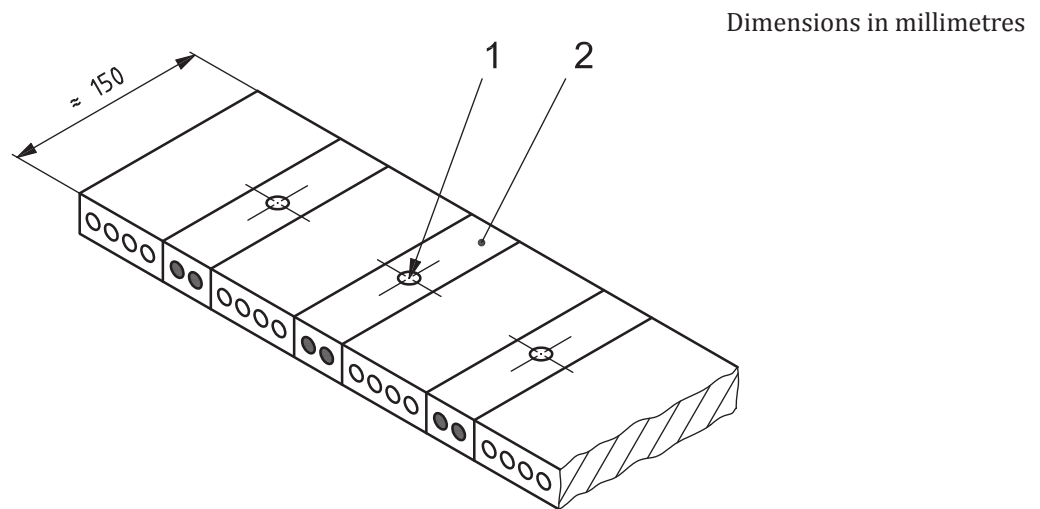

Key

- 1 measurement point
- 2 test specimen

Figure 2 — Test specimens taken at the measurement points and cut from a full width belt sample

6.3.3 Test specimens for method A2

The test specimen shall be not less than 50 mm long with a width equal to the total width of the belt. Mark on the test specimen the measurement points specified in 6.2.

6.3.4 Test specimens for method B

The test shall be carried out either on the end of the conveyor belt *in situ*, or on a test specimen not less than 50 mm long. In either case, the cut edge shall be at 90° to the surface of the belt and the cords shall be visible and free from contamination, the cord ends being cleaned, if necessary. Mark on the test specimen the measurement points specified in 6.2.

6.4 Measurement of thickness

6.4.1 Method A1

6.4.1.1 Measurement of total thickness

Measure the total thickness, s_1 , of the test specimen at each of the measurement points specified in 6.2.


6.4.1.2 Measurement of top cover thickness

Remove the top cover down to the two cords (see Figure 3). Measure the dimension s_7 at the measurement points shown in Figure 1. Take measurements directly above the cord, ensuring that the micrometer foot is in contact with either the surface of the cord (see Figure 3a) or the surface of the weft (see Figure 3b).

ISO/DIS 7590:2017(E)

Calculate the thickness of the top cover, s_2 , at each measurement point using the following equation.

$$s_2 = s_1 - s_7 \quad (1)$$

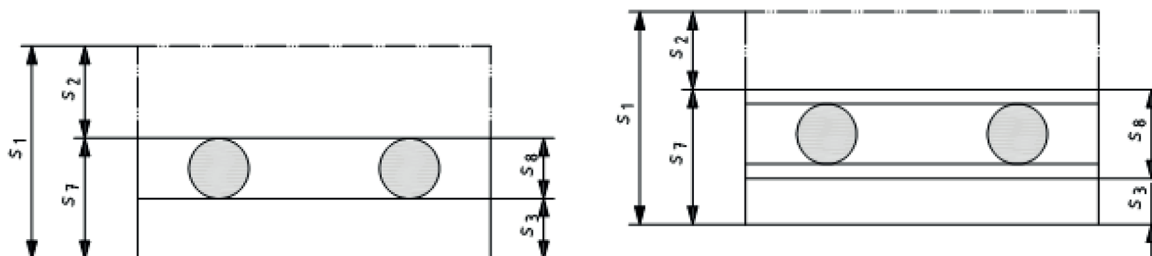

a) Cross-section of a test specimen without weft, with or without breaker

b) Cross-section of a test specimen with weft

Figure 3 — Test specimens for Method A1

6.4.1.3 Measurement of bottom cover thickness

After carrying out the procedure described in 6.4.1.2, remove the bottom cover. Measure the dimension s_8 as described in 6.4.1.2, ensuring that the measurement points are located over the cords.

Calculate the thickness of the bottom cover, s_3 , at each measurement point using the following equation.

$$s_3 = s_7 - s_8 \quad (2)$$

6.4.1.4 Calculation and expression of results

Calculate the arithmetic mean of three or five thicknesses, as appropriate, for s_1 , s_2 and s_3 , as determined in 6.4.1.1, 6.4.1.2 and 6.4.1.3. Express the results in millimetres.

6.4.2 Method A2

6.4.2.1 Measurement of total thickness

Measure the total thickness, s_1 , of the test specimen at each of the measurement points specified in 6.2.

6.4.2.2 Measurement of top cover thickness

Remove a section of the top cover 20 mm in length over the entire width of the test specimen (see Figure 4). Measure the thickness, s_7 , at the same points as in 6.4.2.1. Take measurements directly above the cord, ensuring that the micrometer foot is in contact with either the surface of the cord (see Figure 4a) or the surface of the weft (see Figure 4b).

Calculate the thickness of the top cover, s_2 , at each measurement point, using Formula (1).

6.4.2.3 Measurement of bottom cover thickness

After carrying out the procedure described in 6.4.2.2, remove the bottom cover. Measure the dimension s_8 as described in 6.4.2.2, ensuring that the measurement points are located over the cords.

Calculate the thickness of the bottom cover, s_3 , at each measurement point, using Formula (2).