



Designation: ~~D5895-01~~<sup>ε1</sup> Designation: **D 5895 – 03 (Reapproved 2008)**

## Standard Test Methods for ~~Measuring Times of Evaluating~~ Drying or Curing During Film Formation of Organic Coatings Using Mechanical Recorders<sup>1</sup>

This standard is issued under the fixed designation D 5895; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

~~<sup>1</sup>Note—Research Report was added editorially June 2001.~~

### 1. Scope

~~1.1 These test methods describe the determination of several stages and the rate of dry-film formation of organic coatings using straight line and circular mechanical drying-time recording devices.~~

~~1.2 The values stated in SI are to be regarded as the standard. The values given in parentheses are provided for information only.~~

~~1.3~~

~~1.1 These test methods describe the determination of several stages and the rate of dry-film formation of organic coatings using straight line and circular mechanical drying-time recording devices. The use of mechanical recorders is valuable in comparing the drying behavior of coatings of the same generic type, allowing that one coating may form a gel or resist tearing at a faster rate than another.~~

~~1.2 Drying time measured using the mechanical recorders may differ from those found using conventional methods, such as Test Method D 1640 or ISO 1517.~~

~~1.3 The values stated in SI are to be regarded as the standard. The values given in parentheses are provided for information only.~~

~~1.4 This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.~~

### 2. Referenced Documents

2.1 *ASTM Standards:*<sup>2</sup>

D 823 Practices for Producing Films of Uniform Thickness of Paint, Varnish, and Related Products on Test Panels

D 1005 Test Method Method for Measurement of Dry-Film Thickness of Organic Coatings Using Micrometers

~~D 3924 Specification for Standard Environment for Conditioning and Testing Paint, Varnish, Lacquers, and Related Materials<sup>2</sup>~~

~~1640 Test Methods for Drying, Curing, or Film Formation of Organic Coatings at Room Temperature~~

~~D 3924 Specification for Environment for Conditioning and Testing Paint, Varnish, Lacquer, and Related Materials~~

~~D 3925 Practice for Sampling Liquid Paints and Related Pigmented Coatings<sup>2</sup> Practice for Sampling Liquid Paints and Related Pigmented Coatings~~

~~2.2 ISO Standard:~~

~~ISO 1517 Drying Time Using Ballotini<sup>3</sup>~~

### 3. Terminology

3.1 *Descriptions of Terms Specific to This Standard:*

~~3.1.1 dry-hard time, n—The—the dry-hard condition is reached using mechanical recorders when the drying and curing, or both, reactions have proceeded sufficiently that the film is not displaced nor is any noticeable mark left by pinching the panels between the thumb on the film and forefinger with a relatively strong force.~~

~~3.1.1.1 Discussion—In these test methods, the dry-hard time is reached where the stylus stops tearing or cutting has risen out~~

<sup>1</sup> These test methods are under the jurisdiction of ASTM Committee D01 on Paint and Related Coatings, Materials, and Applications; and are the direct responsibility of Subcommittee D01.23 on Physical Properties of Applied Paint Films.

Current edition approved Feb. 10, 2001; June 1, 2008. Published April 2001. Originally published as D 5895-96 June 2008. Originally approved in 1996. Last previous edition D 5895-96 approved in 2003 as D 5895-03.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For Annual Book of ASTM Standards, Vol 06.01, volume information, refer to the standard's Document Summary page on the ASTM website.

<sup>3</sup> Supporting data are available from ASTM Headquarters. Request RR: D01-1119.

<sup>3</sup> Available from American National Standards Institute (ANSI), 25 W. 43rd St., 4th Floor, New York, NY 10036, <http://www.ansi.org>.

of the film, but leaves film and rides on the surface, leaving only a visible trace on mark without disrupting the body of the film (see Fig. 1 and Fig. 2).

3.1.2 *dry-through time, n*—The—the dry-through condition is reached when the film has solidified so completely that a large, twisting force can be applied without distorting the film.

3.1.2.1 *Discussion*—In these test methods, the dry-through time is reached when the stylus no longer left any visible trackmark on the film (see Fig. 1 and Fig. 2).


3.1.3 *set-to-touch time, n*—The set-to-touch condition is reached when the film has solidified sufficiently, by solvent evaporation or chemical reaction, or both, that it not longer flows nor sticks to a finger that lightly touches it.

3.1.3.1 *Discussion*—In these test methods, the set-to-touch time is reached where a pear-shaped depression appears in the film when the film stops flowing over the path of the recorder's stylus and leaves a track in the film revealing the glass substrate (see Fig. 1 and Fig. 2).

3.1.4 *tack-free time, n*—The—the tack-free condition is reached using mechanical recorders when the film surface has dried or cured (see set-to-touch time) so that the film does not adhere to very light objects placed on it.

3.1.4.1 *Discussion*—In these test methods, the tack-free time is reached where the continuous track in the film ceases and the stylus starts to tear the film or leave a discontinuous cutting of ragged/sharp-edged groove as it first begins to climb over the film (see Fig. 1 and Fig. 2).

NOTE 1—The above descriptions are typical for coatings that do not skin over during curing. Any coating which exhibits skinning, such as two pack epoxies or polyurethane coatings, will show a very different track where the stylus tears the surface of the film, leaving diamond or kite-shaped patterns.

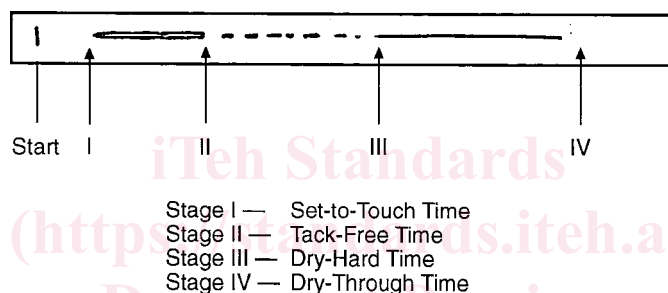

NOTE 1—The above figure represents a typical track of Dry a coating that does not skin over during St curing. Any coating which exhibit skinning, such as two pack e-epoxies or polyurethane coating Ts, will show a ve-Rry different track where the stylus tears the surface of the film, leaving diamond or kite-shaped patterns.

FIG. 1 Stages of Drying Using Straight Line Drying Time Recorders

#### 4. Summary of Test Methods

4.1 In Test Method A (Straight Line Recorder), the coating is applied to glass strips approximately 300 by 25 mm (12 by 1 in.). The drying time recorder is immediately placed on the wet film and the stylus lowered onto the wet coating. The stylus moves across the glass strip at a selected constant speed.

4.2 In Test Method B (Circular Recorder), the coating is applied to glass plates approximately 6 in. by 6 in. (150 by 150 mm). The drying time recorder is immediately placed on the wet film and a stylus is moved in a 360° arc at a selected constant speed.

#### 5. Significance and Use

5.1 The drying times of a coating are significant in determining when a freshly painted room, floor or stair may be put back in use or a coated article handled or packaged. Slow drying may result in dirt pick-up or, on an exterior surface, moisture may cause a nonuniform appearance.

5.2 These test methods are used to determine the various stages of drying or curing in the dry-film formation of organic coatings using mechanical devices for the purpose of comparing types of coatings or ingredient changes, or both. To evaluate the stages of drying in a quantitative manner, use of instrumentation under environmental controlled conditions is strongly recommended. These devices also offer a method of determining drying characteristics of coatings that can not be ascertained within the standard 8-h work day.

5.3 When evaluating drying characteristics of baking systems, the circular drying time devices offer a method to determine quantitatively drying times of coatings at room temperature and elevated conditions. Maximum temperatures would be limited by considerations such as the affect of temperature on the motor lubrication or structural components of the device.

5.4 The straight line drying time devices offer a method to determine quantitatively drying times of coatings tested simultaneously using one recorder.