



SLOVENSKI STANDARD SIST EN 60205:2017

01-junij-2017

Nadomešča:

SIST EN 60205:2006

SIST EN 60205:2006/A1:2009

Izračun efektivnih parametrov magnetnih sestavnih delov

Calculation of the effective parameters of magnetic piece parts

Berechnung der effektiven Kernparameter magnetischer Formteile

Calcul des paramètres effectifs des pièces ferromagnétiques

Ta slovenski standard je istoveten z: **EN 60205:2017**

ICS:

29.100.10 Magnetne komponente Magnetic components

SIST EN 60205:2017 en

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN 60205:2017

<https://standards.iteh.ai/catalog/standards/sist/04d92163-a13f-4f96-bd9b-d6b1c3776486/sist-en-60205-2017>

EUROPEAN STANDARD

EN 60205

NORME EUROPÉENNE

EUROPÄISCHE NORM

March 2017

ICS 29.100.10

Supersedes EN 60205:2006

English Version

Calculation of the effective parameters of magnetic piece parts (IEC 60205:2016)

Calcul des paramètres effectifs des pièces
ferromagnétiques
(IEC 60205:2016)

Berechnung der effektiven Kernparameter magnetischer
Formteile
(IEC 60205:2016)

This European Standard was approved by CENELEC on 2016-12-23. CENELEC members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CENELEC member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CENELEC member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CENELEC members are the national electrotechnical committees of Austria, Belgium, Bulgaria, Croatia, Cyprus, the Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, the Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.



European Committee for Electrotechnical Standardization
Comité Européen de Normalisation Electrotechnique
Europäisches Komitee für Elektrotechnische Normung

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

EN 60205:2017**European foreword**

The text of document 51/1149/FDIS, future edition 4 of IEC 60205, prepared by IEC/TC 51 "Magnetic components, ferrite and magnetic powder materials" was submitted to the IEC-CENELEC parallel vote and approved by CENELEC as EN 60205:2017.

The following dates are fixed:

- latest date by which the document has to be implemented at national level by publication of an identical national standard or by endorsement (dop) 2017-09-23
- latest date by which the national standards conflicting with the document have to be withdrawn (dow) 2019-12-23

This document supersedes EN 60205:2006.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CENELEC [and/or CEN] shall not be held responsible for identifying any or all such patent rights.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Endorsement notice

[SIST EN 60205:2017](https://standards.iteh.ai/catalog/standards/sist/04d92163-a13f-4f96-bd9b-d6b1c3776486/sist-en-60205-2017)

[https://standards.iteh.ai/catalog/standards/sist/04d92163-a13f-4f96-bd9b-](https://standards.iteh.ai/catalog/standards/sist/04d92163-a13f-4f96-bd9b-d6b1c3776486/sist-en-60205-2017)

[d6b1c3776486/sist-en-60205-2017](https://standards.iteh.ai/catalog/standards/sist/04d92163-a13f-4f96-bd9b-d6b1c3776486/sist-en-60205-2017)

The text of the International Standard IEC 60205:2016 was approved by CENELEC as a European Standard without any modification.

In the official version, for Bibliography, the following note has to be added for the standard indicated :

IEC 62317-13

NOTE

Harmonized as EN 62317-13.



INTERNATIONAL STANDARD

Calculation of the effective parameters of magnetic piece parts
(standards.iteh.ai)

[SIST EN 60205:2017](https://standards.iteh.ai/catalog/standards/sist/04d92163-a13f-4f96-bd9b-d6b1c3776486/sist-en-60205-2017)

<https://standards.iteh.ai/catalog/standards/sist/04d92163-a13f-4f96-bd9b-d6b1c3776486/sist-en-60205-2017>

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

ICS 29.100.10

ISBN 978-2-8322-3775-5

Warning! Make sure that you obtained this publication from an authorized distributor.

CONTENTS

FOREWORD.....	4
INTRODUCTION.....	6
1 Scope.....	7
2 Normative references.....	7
3 Terms and definitions.....	7
4 Basic rules applicable to this standard.....	7
5 Formulae for the various types of cores.....	8
5.1 Ring cores.....	8
5.1.1 Ring cores in general.....	8
5.1.2 For ring cores of rectangular cross-section with sharp corners.....	9
5.1.3 For ring cores of rectangular cross-section with an appreciable average rounding radius r_0	9
5.1.4 For ring cores of rectangular cross-section with appreciable chamfer c_0	9
5.1.5 For ring cores of trapezoidal cross-section with sharp corners.....	9
5.1.6 For ring cores of trapezoidal cross-section with an appreciable average rounding radius r_0	9
5.1.7 For ring cores of cross-section with circular arc frontal sides.....	9
5.2 Pair of U-cores of rectangular section.....	10
5.3 Pair of U-cores of rounded section.....	10
5.4 Pair of E-cores of rectangular section.....	11
5.5 Pair of ETD/EER-cores.....	12
5.6 Pair of pot-cores.....	14
5.7 Pair of RM-cores.....	16
5.8 Pair of EP-cores.....	20
5.9 Pair of PM-cores.....	21
5.10 Pair of EL-cores.....	23
5.11 Pair of ER-cores (low profile).....	25
5.12 Pair of PQ-cores.....	28
5.13 Pair of EFD-cores.....	31
5.14 Pair of E planar-cores.....	33
5.15 Pair of EC-cores.....	34
Bibliography.....	37
Figure 1 – Ring cores.....	8
Figure 2 – Pair of U-cores of the rectangular section.....	10
Figure 3 – Pair of U-cores of rounded section.....	11
Figure 4 – Pair of E-cores of rectangular section.....	12
Figure 5 – Pair of ETD/EER-cores.....	13
Figure 6 – Pair of pot-cores.....	14
Figure 7 – Pair of RM-cores.....	18
Figure 8 – Pair of EP-cores.....	20
Figure 9 – Pair of PM-cores.....	22
Figure 10 – Pair of EL-cores.....	23

Figure 11 – PLT(plate)-cores.....	24
Figure 12 – Pair of ER-cores (low profile)	26
Figure 13 – PLT(plate)-cores.....	26
Figure 14 – Pair of PQ-cores	28
Figure 15 – PQ-cores	29
Figure 16 – PLT(plate)-cores.....	29
Figure 17 – Pair of EFD-cores	31
Figure 18 – Pair of E planar-cores	33
Figure 19 – PLT(plate)-cores.....	33
Figure 20 – Pair of EC-cores	35

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 60205:2017](https://standards.iteh.ai/catalog/standards/sist/04d92163-a13f-4f96-bd9b-d6b1c3776486/sist-en-60205-2017)

<https://standards.iteh.ai/catalog/standards/sist/04d92163-a13f-4f96-bd9b-d6b1c3776486/sist-en-60205-2017>

INTERNATIONAL ELECTROTECHNICAL COMMISSION

**CALCULATION OF THE EFFECTIVE PARAMETERS
OF MAGNETIC PIECE PARTS**

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

International Standard IEC 60205 has been prepared by IEC technical committee 51: Magnetic components, ferrite and and magnetic powder materials.

This fourth edition cancels and replaces the third edition published in 2006 and Amendment 1:2009. This edition constitutes a technical revision.

This edition includes the following significant technical changes with respect to the previous edition:

- a) addition, in 5.1, of the drawing of a core of rectangular cross-section with chamfer;
- b) addition, in 5.1.3, of the equation of a core of rectangular cross-section with chamfer;
- c) equations in 5.1.4, 5.6, 5.7, 5.8, 5.9, 5.11, 5.12, 5.14 are amended or replaced;
- d) drawings RM6-S and RM6-R in 5.7 are amended;
- e) addition of EC-cores, see 5.15.

The text of this standard is based on the following documents:

FDIS	Report on voting
51/1149/FDIS	51/1156/RVD

Full information on the voting for the approval of this International Standard can be found in the report on voting indicated in the above table.

This document has been drafted in accordance with the ISO/IEC Directives, Part 2.

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under "<http://webstore.iec.ch>" in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

A bilingual version of this publication may be issued at a later date.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[SIST EN 60205:2017](https://standards.iteh.ai/catalog/standards/sist/04d92163-a13f-4f96-bd9b-d6b1c3776486/sist-en-60205-2017)

<https://standards.iteh.ai/catalog/standards/sist/04d92163-a13f-4f96-bd9b-d6b1c3776486/sist-en-60205-2017>

INTRODUCTION

The purpose of this revision is to provide formulae by which everybody can reach the same effective parameter values. Firstly, it is necessary to have a sufficient number of significant figures when figures are rounded off in the process of calculation. Additionally, some of the calculation formulae have been changed to get closer to the actual shape.

In this revision, the basic idea of calculation has not been changed. Recently, analysis of the magnetic field in the core has been considerably improved, so that, based on these ideas, development of new approaches and formulae can be expected.

Furthermore, the new “EC-cores” have been added.

The parameters in the existing IEC standards will be revised with the outcome from the formulae of this document.

iTeh STANDARD PREVIEW **(standards.iteh.ai)**

[SIST EN 60205:2017](https://standards.iteh.ai/catalog/standards/sist/04d92163-a13f-4f96-bd9b-d6b1c3776486/sist-en-60205-2017)

<https://standards.iteh.ai/catalog/standards/sist/04d92163-a13f-4f96-bd9b-d6b1c3776486/sist-en-60205-2017>

CALCULATION OF THE EFFECTIVE PARAMETERS OF MAGNETIC PIECE PARTS

1 Scope

This document specifies uniform rules for the calculation of the effective parameters of closed circuits of ferromagnetic material.

2 Normative references

There are no normative references in this document.

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

4 Basic rules applicable to this standard

4.1 All results shall be expressed in units based on millimetres, shall be accurate to three significant figures, but to derive I_e , A_e , and V_e the values of C_1 and C_2 shall be calculated to five significant figures. All angles are in radians.

NOTE The purpose of specifying this degree of accuracy is only to ensure that parameters calculated at different establishments are identical and it is not intended to imply that the parameters are capable of being determined to this accuracy.

4.2 A_{\min} is the nominal value of the smallest cross-section. A_g is the geometrical cross-section of a ring core with rectangular shape. All the dimensions used to calculate A_{\min} shall be the mean values between the tolerance limits quoted on the appropriate piece part drawing. All results shall be expressed in units based on millimetres, and shall be accurate to three significant figures.

The minimum physical cross-section area A_{\min} is given as: $A_{\min} = \min(A_i)$

NOTE A_g to be used for the measurement of the saturation flux density B_{\max} on ring cores with rectangular cross-section.

4.3 Calculations are only applicable to the component parts of a closed magnetic circuit.

4.4 All dimensions used for the purpose of calculations shall be the mean value within the tolerance limits quoted on the appropriate piece part drawing.

4.5 All irregularities in the outline of the core, such as small cut-outs, notches, chamfers, etc. shall be ignored unless otherwise described.

4.6 When the calculation involves the sharp corner of a piece part, then the mean length of flux path for that corner shall be taken as the mean circular path joining the centres of area of the two adjacent uniform sections, and the cross-sectional area associated with that length shall be taken as the average area of the two adjacent uniform sections.

Calculation of effective parameters l_e , A_e and V_e .

The effective parameters can be defined as

$$l_e = C_1^2 / C_2 \quad A_e = C_1 / C_2 \quad V_e = l_e A_e = C_1^3 / C_2^2$$

where

l_e is the effective magnetic length of the core (mm);

A_e is the effective cross-sectional area (mm²);

V_e is the effective volume (mm³);

C_1 is the core constant (mm⁻¹);

C_2 is the core constant (mm⁻³).

5 Formulae for the various types of cores

5.1 Ring cores

iTeh STANDARD PREVIEW

5.1.1 Ring cores in general

(standards.iteh.ai)

Drawings of ring cores are shown in Figure 1.

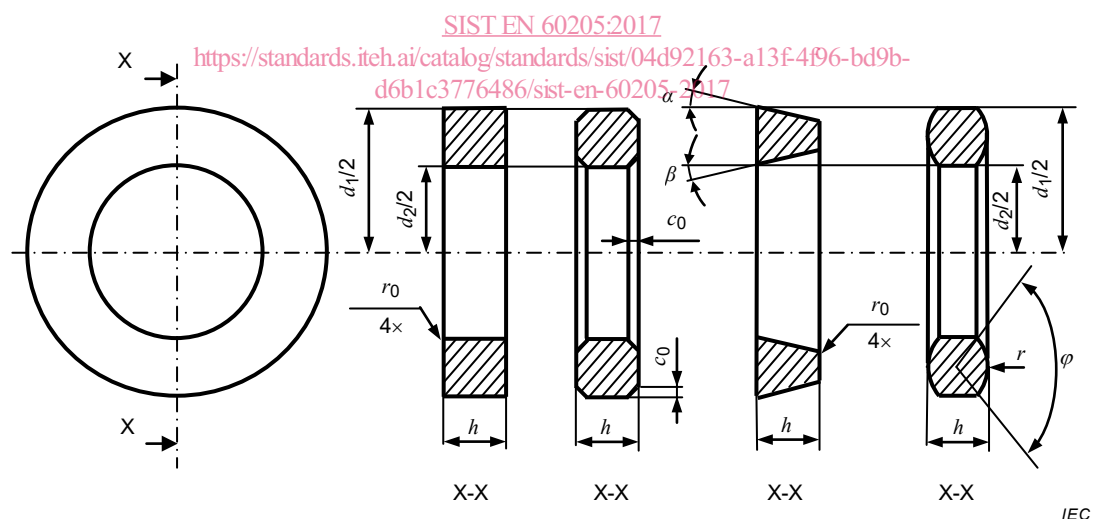


Figure 1 – Ring cores

$$C_1 = \frac{2\pi}{h_e \ln(d_1/d_2)}$$

$$C_2 = \frac{4\pi(1/d_2 - 1/d_1)}{h_e^2 \ln^3(d_1/d_2)}$$

5.1.2 For ring cores of rectangular cross-section with sharp corners

$$h_e = h$$

The geometrical cross-section of a ring core with rectangular shape A_g is given as:

$$A_g = h \frac{d_2 - d_1}{2}$$

5.1.3 For ring cores of rectangular cross-section with an appreciable average rounding radius r_0

$$h_e = h(1 - k_1) \quad k_1 = \frac{1,7168r_0^2}{h(d_1 - d_2)}$$

5.1.4 For ring cores of rectangular cross-section with appreciable chamfer c_0

$$h_e = h(1 - k_3) \quad k_3 = \frac{4c_0^2}{h(d_1 - d_2)}$$

The geometrical cross-section of a ring core with appreciable chamfer shape A_g is given as:

$$A_g = h \frac{d_2 - d_1 - 2c_0^2}{2}$$

iTeh STANDARD PREVIEW
(standards.iteh.ai)

5.1.5 For ring cores of trapezoidal cross-section with sharp corners

SIST EN 60205:2017
<https://standards.iteh.ai/catalog/standards/sig/04d92163-a13f-4f96-bd9b-4c1c572486>

$$h_e = h(1 - k_2) \quad k_2 = \frac{h(\tan \alpha + \tan \beta)}{d_1 - d_2}$$

5.1.6 For ring cores of trapezoidal cross-section with an appreciable average rounding radius r_0

$$h_e = h(1 - k_1 - k_2)$$

5.1.7 For ring cores of cross-section with circular arc frontal sides

$$h_e = h - \frac{d_1 - d_2}{4 \sin^2(\varphi/2)} \left(2 \sin \frac{\varphi}{2} - \frac{\sin \varphi}{2} - \frac{\varphi}{2} \right)$$

$$\varphi = 2 \arcsin \frac{d_1 - d_2}{4r}$$

When the winding is uniformly distributed over a ring core, it may be expected that, at all points inside the ring core, the flux lines will be parallel to its surface.

No leakage flux will therefore leave or enter the ring core. This justifies the use of a theoretically more correct derivation of the effective parameters, which does not make use of the assumption that the flux is uniformly distributed over the cross-section.