



SLOVENSKI STANDARD
oSIST prEN ISO 10683:2016
01-julij-2016

Vezni elementi - Cinkova lamelna prevleka, ki ni izdelana z elektrolizo (ISO/DIS 10683:2016)

Fasteners - Non-electrolytically applied zinc flake coatings (ISO/DIS 10683:2016)

Verbindungselemente - Nichtelektrolytisch aufgebrachte Zinklamellenüberzüge (ISO/DIS 10683:2016)

Fixations - Revêtements non électrolytiques de zinc lamellaire (ISO/DIS 10683:2016)

Ta slovenski standard je istoveten z: prEN ISO 10683 rev

ICS:

21.060.01	Vezni elementi na splošno	Fasteners in general
25.220.40	Kovinske prevleke	Metallic coatings

oSIST prEN ISO 10683:2016

en,fr,de

DRAFT INTERNATIONAL STANDARD

ISO/DIS 10683

ISO/TC 2/SC 14

Secretariat: DIN

Voting begins on:
2016-06-21Voting terminates on:
2016-09-12

Fasteners — Non-electrolytically applied zinc flake coatings

Fixations — Revêtements non électrolytiques de zinc lamellaire

ICS: 21.060.01; 25.220.40

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 10683:2018

<https://standards.iteh.ai/catalog/standards/sist/f7cbcb07-ea54-4a93-a769-d003379f3ae1/sist-en-iso-10683-2018>

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

ISO/CEN PARALLEL PROCESSING



Reference number
ISO/DIS 10683:2016(E)

iTeh STANDARD PREVIEW (standards.iteh.ai)

SIST EN ISO 10683:2018

<https://standards.iteh.ai/catalog/standards/sist/f7c9cb07-ea54-4a93-a769-d003379f3ae1/sist-en-iso-10683-2018>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2016, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

	Page
Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	2
4 General characteristics of the coating	2
4.1 Zinc flake coating systems.....	2
4.2 Composition of the systems.....	2
4.3 Mechanical and physical properties and curing.....	2
4.4 Avoidance of internal hydrogen embrittlement.....	3
4.5 Coating systems and coating processes.....	3
5 Corrosion protection and testing	3
5.1 General.....	3
5.2 Neutral salt spray test.....	3
5.3 Sulfur dioxide test (Kesternich test).....	4
5.4 Bulk handling, automatic processes such as feeding and/or sorting, storage and transport.....	4
6 Dimensional requirements and testing	4
6.1 General.....	4
6.2 Bolts, screws, studs and nuts with ISO metric threads.....	4
6.2.1 Coating thickness.....	4
6.2.2 Gaugeability and assemblability.....	5
6.3 Other fasteners.....	5
7 Mechanical and physical properties and testing	6
7.1 Appearance.....	6
7.2 Corrosion resistance related to temperature.....	6
7.3 Test methods for thickness or coating weight determination.....	6
7.4 Ductility.....	7
7.5 Adhesion/cohesion.....	7
7.6 Sacrificial cathodic protection.....	7
7.7 Torque/tension relationship.....	7
7.8 Determination of hexavalent chromium.....	8
8 Applicability of tests	8
8.1 General.....	8
8.2 Tests mandatory for each lot.....	8
8.3 Tests for in-process control.....	8
8.4 Tests to be conducted when specified by the purchaser.....	8
9 Designation	9
9.1 Designation of zinc flake coating systems for the order.....	9
9.2 Designation of zinc flake coating systems for labelling.....	9
10 Ordering requirements	10
Annex A (informative) Design aspects and assembly of coated fasteners	11
Annex B (informative) Coating thickness and thread clearance for ISO metric screw threads	15
Annex C (informative) Control of the corrosivity of the cabinet for neutral salt spray test for coated fasteners	22
Bibliography	30

ISO/DIS 10683:2016(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 2, *Fasteners*, SC 14, *Surface coatings*.

This third edition cancels and replaces the second edition (ISO 10683:2014). The main technical changes are the following:

- Normative references have been updated;
- the restriction of gauging to external threads in the 2nd paragraph of [6.2.2](#) has been removed;
- last column in [Table B.2](#) with maximum clearance for tolerance position e has been removed..

Introduction

The revision of ISO 10683:2000 was made in order to define the relevant requirements on zinc flake coated fasteners (coating systems with and without hexavalent chromium) for all parties involved in the fastener field, i.e. chemical suppliers, coaters, fastener manufacturers, distributors and end users. It covers all types of fasteners, i.e. fasteners with ISO metric thread, fasteners with non-ISO metric thread (including thread forming, ASME inch 60° screw thread, etc.) and non-threaded fasteners (including washers, pins, clips, etc.). It also provides basic advice for the design and use of coated fasteners in assembly.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 10683:2018

<https://standards.iteh.ai/catalog/standards/sist/f7cbcb07-ea54-4a93-a769-d003379f3ae1/sist-en-iso-10683-2018>

Fasteners — Non-electrolytically applied zinc flake coatings

1 Scope

This International Standard specifies requirements for non-electrolytically applied zinc flake coatings for steel fasteners. It applies to coatings:

- with or without hexavalent chromium;
- with or without top coat;
- with or without lubricant (integral lubricant and/or subsequently added lubricant).

National regulations for the restriction or prohibition of certain chemical elements should be taken into account in the countries or regions concerned.

It applies to bolts, screws, studs and nuts with ISO metric thread, to fasteners with non-ISO metric thread, and to non-threaded fasteners such as washers, pins, clips, etc.

NOTE Coatings in accordance with this International Standard are especially used for high strength fasteners ($\geq 1\ 000$ MPa) to avoid risk of internal hydrogen embrittlement (see 4.4).

Information for design and assembly of coated fasteners is given in [Annex A](#).

This International Standard does not specify requirements for such fastener properties as weldability or paintability. It does not apply to mechanically applied zinc coatings.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1463, *Metallic and oxide coatings — Measurement of coating thickness — Microscopical method*

ISO 1502, *ISO general-purpose metric screw threads — Gauges and gauging*

ISO 1891-2, *Fasteners — Terminology — Part 2: Vocabulary and definitions for coatings*

ISO 3269, *Fasteners — Acceptance inspection*

ISO 3613:2010, *Metallic and other inorganic coatings — Chromate conversion coatings on zinc, cadmium, aluminium-zinc alloys and zinc-aluminium alloys — Test methods*

ISO 6988, *Metallic and other non organic coatings — Sulfur dioxide test with general condensation of moisture*

ISO 8991, *Designation system for fasteners*

ISO 9227:2012, *Corrosion tests in artificial atmospheres — Salt spray tests*

ISO 16047, *Fasteners — Torque/clamp force testing*

ISO/DIS 10683:2016(E)

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 1891-2 apply.

4 General characteristics of the coating

4.1 Zinc flake coating systems

Zinc flake coating systems are produced by applying a zinc flake dispersion to the surface of a steel fastener, usually with the addition of aluminium flakes, in a suitable medium. Under the influence of heat (curing), a bonding amongst flakes and also between flakes and substrate is generated, thus forming an inorganic surface coating sufficiently electrically conducting to ensure cathodic protection. The coating may or may not contain hexavalent chromium, Cr(VI).


Special techniques may be necessary to avoid excessive or insufficient coating thickness.

Special techniques may be necessary to prevent lightweight and/or flat fasteners from sticking together (e.g. washers, clips, fasteners with captive washer, flanged nuts).

An additional top coat can be applied to increase corrosion resistance and/or to achieve specific properties (e.g. torque/tension properties, chemical resistance, aspect, colour, electrical insulation/conductivity – see [A.2](#)).

4.2 Composition of the systems

There are four basic zinc flake coating systems as shown in [Figure 1](#).

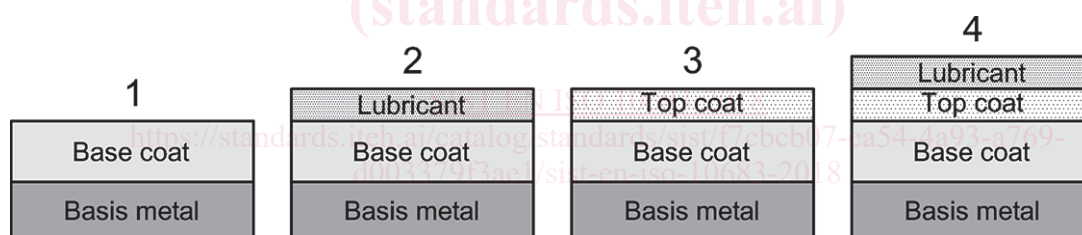

Key

- 1 only base coat
- 2 base coat + lubricant
- 3 base coat + top coat
- 4 base coat + top coat + lubricant

Figure 1 — Basic zinc flake coating systems

Base coat and top coat can be with integral lubricant, see detailed possible combinations in [A.1.2](#).

4.3 Mechanical and physical properties and curing

The coating process shall not adversely influence the mechanical and physical properties of the fasteners.

NOTE Distributors who coat non-coated fasteners are considered as alteration coating distributors in accordance with ISO 16426.[9]

Depending on the zinc flake coating system, the curing temperatures can be up to 320 °C. The curing temperature shall not be above the tempering temperature of quenched and tempered fasteners.

WARNING — The curing process (especially with higher temperature and/or longer duration) may affect the fatigue limit of fasteners with thread rolled after heat treatment. See also [A.1.3](#) for other possible effects of curing.

4.4 Avoidance of internal hydrogen embrittlement

A characteristic of zinc flake coating systems is that hydrogen is not generated during the deposition process.

Pre-treatment processes using alkaline/solvent cleaner followed by mechanical cleaning do not generate hydrogen, thus eliminating all risk of internal hydrogen embrittlement (IHE).

When mechanical cleaning is not suitable for functional reasons (e.g. for fasteners with captive washers, fasteners with internal threads, fasteners to be rack coated), chemical cleaning (pickling) may be applied, provided that acid with suitable inhibitor and minimum cleaning cycle time are used to minimize the risk of internal hydrogen embrittlement. Fasteners with hardness greater than 385 HV or property class 12.9 and above shall not be subjected to acid cleaning. The duration between cleaning and coating shall be as short as possible.

A phosphating process is permitted as an alternative to mechanical cleaning (hydrogen may be generated during this pre-treatment process, however the curing process allows outward diffusion). The duration between phosphating and coating shall be as short as possible.

Cathodic cleaning processes are not permitted.

NOTE Zinc flake coatings have a high permeability for hydrogen which, during the curing process, allows outward diffusion of hydrogen which may have been absorbed during the pre-treatment process as specified in this subclause.

4.5 Coating systems and coating processes

The type and geometry of the fasteners shall be considered when selecting a coating system and the related coating process, see [A.2](#).

5 Corrosion protection and testing

5.1 General

Corrosion resistance in accelerated corrosion tests cannot be directly related to corrosion protection behaviour in particular service environments. However, accelerated tests are used to evaluate the corrosion resistance of the coating.

5.2 Neutral salt spray test

The neutral salt spray test (NSS) in accordance with ISO 9227:2012, 5.2, is used to evaluate the corrosion resistance of the coating systems. For coated fasteners, the salt spray cabinet shall be controlled in accordance with [Annex C](#).

The neutral salt spray test shall be carried out on fasteners alone, not sooner than 24 h after coating in the “as-coated” condition, i.e. before sorting, packaging and/or assembling.

After the neutral salt spray test using test duration of [Table 1](#) there shall be no visible basis metal corrosion (red rust).

ISO/DIS 10683:2016(E)

Table 1 — Standard categories for neutral salt spray test

Neutral salt spray test duration (without red rust)	Reference thickness of the coating system ^a
240 h	4 µm
480 h	5 µm
600 h	6 µm
720 h	8 µm
960 h	10 µm

^a The reference thickness includes base coat(s) and top coat(s) if any, with or without Cr(VI). The corrosion resistance shall be decisive for acceptance, the reference thickness is given for guidance only.
The composition of the system (base coat only, base coat + top coat, etc.) shall be specified at the time of the order.

NOTE Guidance for the selection of coating thickness in relation to corrosion protection is given in [Annex B](#).

5.3 Sulfur dioxide test (Kesternich test)

This test is only intended for outdoor building fasteners.

The sulfur dioxide test with general condensation of moisture in accordance with ISO 6988 is used to evaluate the corrosion resistance of the coating systems; for outdoor building fasteners, the test shall be carried out with two litres of SO₂.

The sulfur dioxide test shall be carried out on fasteners alone, no sooner than 24 h after coating in the “as-coated” condition, i.e. before sorting, packaging and/or assembling.

The minimum number of cycles shall be agreed between the supplier and the purchaser at the time of the order, i.e. 2 cycles, 3, 5, 8, 10, 12, 15 cycles, etc.

5.4 Bulk handling, automatic processes such as feeding and/or sorting, storage and transport

Bulk handling, automatic processes such as feeding and/or sorting, storage and transport can cause a significant reduction of corrosion protection depending on the coating system and type and geometry of the fasteners. This may especially occur for Cr(VI)-free coating systems where less self-healing effect takes place and/or where top coats are sensitive to impact damage and/or abrasion.

When necessary, an agreement should be reached between the supplier and the purchaser, e.g. by reducing the minimum duration to neutral salt spray test and/or by increasing the thickness of the coating system.

6 Dimensional requirements and testing

6.1 General

Before coating, fasteners shall be within the specified dimensions. For ISO metric threads special requirements may apply, see [6.2.2](#), [B.4](#) and [B.5](#).

6.2 Bolts, screws, studs and nuts with ISO metric threads

6.2.1 Coating thickness

When considering the coating thickness related to the desired corrosion resistance, the dispersion of the thickness of the coating system shall be taken into account, see [B.3](#).