

SLOVENSKI STANDARD **oSIST prEN ISO 1182:2019**

01-september-2019

Preskusi odziva proizvodov na ogenj - Preskus negorljivosti (ISO/DIS 1182:2019)

Reaction to fire tests for products - Non-combustibility test (ISO/DIS 1182:2019)

Prüfungen zum Brandverhalten von Produkten - Nichtbrennbarkeitsprüfung (ISO/DIS 1182:2019)

Essais de réaction au feu de produits - Essai d'incombustibilité (ISO/DIS 1182:2019)

Ta slovenski standard je istoveten z: prEN ISO 1182

ICS:

13.220.50	Požarna odpornost gradbenih materialov in elementov	Fire-resistance of building materials and elements
-----------	---	---

oSIST prEN ISO 1182:2019

en

DRAFT INTERNATIONAL STANDARD

ISO/DIS 1182

ISO/TC 92/SC 1

Secretariat: BSI

Voting begins on:
2019-05-29Voting terminates on:
2019-08-21

Reaction to fire tests for products — Non-combustibility test

Essais de réaction au feu de produits — Essai d'incombustibilité

ICS: 13.220.50

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN ISO 1182:2020](https://standards.iteh.ai/catalog/standards/sist/36888eed-5e43-41c3-ad45-9078a16a66ba/sist-en-iso-1182-2020)

<https://standards.iteh.ai/catalog/standards/sist/36888eed-5e43-41c3-ad45-9078a16a66ba/sist-en-iso-1182-2020>

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

This document is circulated as received from the committee secretariat.

ISO/CEN PARALLEL PROCESSING



Reference number
ISO/DIS 1182:2019(E)

© ISO 2019

iTeh STANDARD PREVIEW (standards.iteh.ai)

SIST EN ISO 1182:2020

<https://standards.iteh.ai/catalog/standards/sist/36888eed-5e43-41c3-ad45-9078a16a66ba/sist-en-iso-1182-2020>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2019

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Fax: +41 22 749 09 47
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Apparatus	2
5 Test specimen	9
5.1 General.....	9
5.2 Preparation.....	9
5.3 Number.....	10
6 Conditioning	10
7 Test procedure	11
7.1 Test environment.....	11
7.2 Set-up procedure.....	11
7.2.1 Specimen holder.....	11
7.2.2 Thermocouple.....	11
7.2.3 Electricity supply.....	11
7.2.4 Furnace stabilization.....	12
7.3 Calibration procedure.....	12
7.3.1 Furnace wall temperature.....	12
7.3.2 Furnace temperature.....	14
7.3.3 Procedure frequency.....	16
7.4 Standard test procedure.....	16
7.5 Observations during test.....	17
8 Expression of results	17
8.1 Mass loss.....	17
8.2 Flaming.....	17
8.3 Temperature rise.....	18
9 Test report	18
Annex A (informative) Precision of test method	19
Annex B (informative) Typical designs of test apparatus	21
Annex C (normative) Thermocouples for additional measurements	24
Annex D (informative) Temperature recording	26
Bibliography	31

ISO/DIS 1182:2019(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 1182 was prepared by Technical Committee ISO/TC 92, *Fire safety*, Subcommittee SC 1, *Fire initiation and growth*.

This fifth edition cancels and replaces the fourth edition (ISO 1182:2002), which has been technically revised.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 1182:2020

<https://standards.iteh.ai/catalog/standards/sist/36888eed-5e43-41c3-ad45-9078a16a66ba/sist-en-iso-1182-2020>

Introduction

This fire test has been developed for use by those responsible for the selection of construction products which, whilst not completely inert, produce only a very limited amount of heat and flame when exposed to temperatures of approximately 750 °C.

The limitation of the field of application to testing homogeneous products and substantial components of non-homogeneous products was introduced because of problems in defining specifications for the specimens. The design of the specimen of non-homogeneous products strongly influences the test results, which is the reason non-homogeneous products cannot be tested to this International Standard.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 1182:2020

<https://standards.iteh.ai/catalog/standards/sist/36888eed-5e43-41c3-ad45-9078a16a66ba/sist-en-iso-1182-2020>

Reaction to fire tests for products — Non-combustibility test

SAFETY PRECAUTIONS — The attention of all persons concerned with managing and carrying out this test is drawn to the fact that fire testing can be hazardous and that there is a possibility that toxic, harmful smoke and gases can be evolved during the test. Operational hazards can also arise during the testing of specimens and the disposal of test residues.

An assessment of all potential hazards and risks to health should be made and safety precautions should be identified and provided. Written safety instructions should be issued. Appropriate training should be given to relevant personnel. Laboratory personnel should ensure that they follow written safety instructions at all times.

1 Scope

This International Standard specifies a method of test for determining the non-combustibility performance, under specified conditions, of homogeneous products and substantial components of non-homogeneous products.

Information on the precision of the test method is given in [Annex A](#).

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 13943, *Fire safety — Vocabulary*

IEC 60584-2, *Thermocouples — Part 2: Tolerances*

EN 13238, *Reaction to fire tests for building products — Conditioning procedures and general rules for selection of substrates*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 13943 and the following apply.

3.1

product

material, element or component about which information is required

3.2

material

single basic substance or uniformly dispersed mixture of substances

Note 1 to entry: Examples of materials are metal, stone, timber, concrete, mineral wool with uniformly dispersed binder and polymers.

3.3

loose fill material

material without any physical shape

3.4

homogeneous product

product, consisting of a single material, having uniform density and composition throughout

ISO/DIS 1182:2019(E)

3.5

non-homogeneous product

product, composed of more than one component, substantial or non-substantial, not having uniform density and composition throughout

3.6

substantial component

material that constitutes a significant part of a non-homogeneous product and that has a layer with a mass/unit area more than or equal to 1,0 kg/m² or a thickness more than or equal to 1,0 mm

Note 1 to entry: Two or more non-substantial layers that are adjacent to each other (i.e. with no substantial component(s) in between the layers) are regarded as one substantial component when they collectively comply with the requirements for a layer being a substantial component.

3.7

non-substantial component

material that does not constitute a significant part of a non-homogeneous product and that has a layer with a mass/unit area below 1,0 kg/m² and a thickness below 1,0 mm

3.8

sustained flaming

persistence of flame at any part of the visible part of the specimen lasting 5 s or longer

Note 1 to entry: Steady blue-coloured luminous gas zones should not be regarded as flaming. Such gas zones should only be noted under "observations during test" in the test report.

4 Apparatus

4.1 General

The test apparatus shall be capable of creating the conditions specified in 7.1. A typical design of furnace is given in Annex B; other designs of furnace may be used.

NOTE 1 All dimensions given in the description of the test apparatus are nominal values, unless tolerances are specified.

The apparatus shall consist of a furnace comprising essentially a refractory tube surrounded by a heating coil and enclosed in an insulated surround. A cone-shaped airflow stabilizer shall be attached to the base of the furnace and a draught shield to its top.

The furnace shall be mounted on a stand and shall be equipped with a specimen holder and a device for inserting the specimen-holder into the furnace tube.

Thermocouples, as specified in 4.4, shall be provided for measuring the furnace temperatures and the furnace wall temperature. The thermal sensor, as specified in 4.5, shall be provided for measuring the furnace temperature along its central axis.

NOTE 2 Annex C gives details of additional thermocouples to be used if the specimen surface temperature and the specimen centre temperature are required.

4.2 Furnace, draught shield and stand

4.2.1 Furnace tube, made of an alumina refractory material as specified in [Table 1](#), of density $(2\,800 \pm 300)$ kg/m³. It shall be (150 ± 1) mm high with an internal diameter of (75 ± 1) mm and a wall thickness of (10 ± 1) mm.

Table 1 — Composition of the furnace tube refractory material

Material	Composition % (kg/kg mass)
Alumina (Al ₂ O ₃)	> 89
Silica and alumina (SiO ₂ , Al ₂ O ₃)	> 98
Ferric oxide (Fe ₂ O)	< 0,45
Titanium dioxide (TiO ₂)	< 0,25
Manganese oxide (Mn ₃ O ₄)	< 0,1
Other trace oxides (sodium, potassium, calcium and magnesium oxides)	The balance

The furnace tube shall be fitted in the centre of a surround made of insulating material 150 mm in height and of 10 mm wall thickness, and fitted with top and bottom plates recessed internally to locate the ends of the furnace tube. The annular space between the tubes shall be filled with a suitable insulating material.

NOTE 1 An example of a typical furnace tube design is given in [B.2](#).

An open-ended cone-shaped airflow stabilizer shall be attached to the underside of the furnace. The stabilizer shall be 500 mm in length, and reduce uniformly from 75 ± 1 mm internal diameter at the top to $10 \pm 0,5$ mm at the bottom. The stabilizer shall be manufactured from 1 mm-thick sheet steel, with a smooth finish on the inside. The joint between the stabilizer and the furnace shall be a close, airtight fit, with a smooth finish internally. The upper half of the stabilizer shall be insulated externally with a suitable insulating material.

NOTE 2 An example of suitable insulating material is given in [B.3](#).

4.2.2 Draught shield, made of the same material as the stabilizer cone, and provided at the top of the furnace. It shall be 50 mm high and have an internal diameter of (75 ± 1) mm. The draught shield and its joint with the top of the furnace shall have a smooth finish internally, and the exterior shall be insulated with a suitable insulating material.

NOTE An example of suitable insulating material is given in [B.4](#).


4.2.3 Stand, firm and horizontal, on which the assembly of the furnace, stabilizer cone and draught shield are mounted. There shall be a base and draught screen attached to the stand to reduce draughts around the bottom of the stabilizer cone. The draught screen shall be 550 mm high and the bottom of the stabilizer cone shall be 250 mm above the base plate.

4.3 Specimen holder and insertion device

4.3.1 Specimen holder, as specified in [Figure 1](#) and made of nickel/chromium or heat-resisting steel wire. A fine metal gauze tray of heat-resisting steel shall be placed in the bottom of the holder. The mass of the holder shall be (15 ± 2) g.

NOTE Due to ageing specimen holders can lose weight, mass of the holder shall be controlled regularly.

Dimensions in millimetres

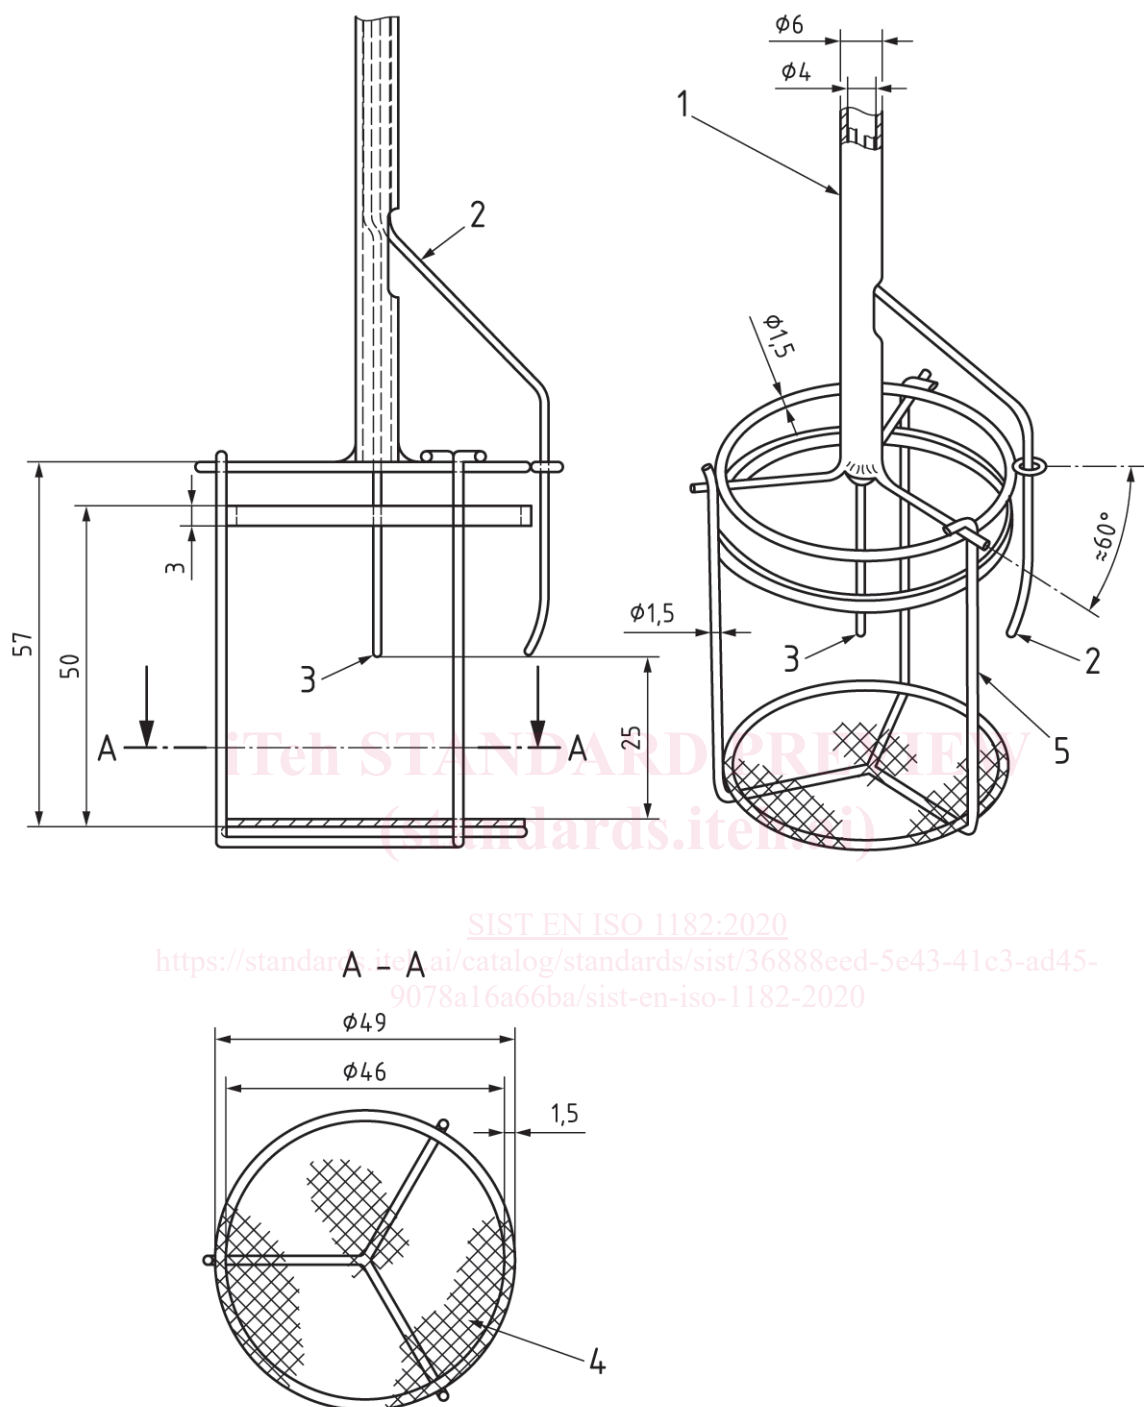

SIST EN ISO 1182:2020

<https://standards.itec.ai/catalog/standards/sist/36888eed-5e43-41c3-ad45-9078a16a66ba/sist-en-iso-1182-2020>

Key

- 1 stainless steel tube
- 2 specimen surface thermocouple
- 3 specimen centre thermocouple
- 4 aperture mesh 0,9 mm diameter of wire 0,4 mm
- 5 vertical specimen holder bar

Figure 1 — Specimen holder