

---

---

**Test method for staple length  
of dehaired cashmere — Hand-  
arranging method**

*Méthode d'essai de la longueur de fibre du cachemire épilé —  
Méthode d'organisation à la main*

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[ISO 18596:2015](https://standards.iteh.ai/catalog/standards/sist/d9db4a7a-2795-486b-8292-068d3f0e70da/iso-18596-2015)

<https://standards.iteh.ai/catalog/standards/sist/d9db4a7a-2795-486b-8292-068d3f0e70da/iso-18596-2015>



**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO 18596:2015

<https://standards.iteh.ai/catalog/standards/sist/d9db4a7a-2795-486b-8292-068d3f0e70da/iso-18596-2015>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2015, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Ch. de Blandonnet 8 • CP 401  
CH-1214 Vernier, Geneva, Switzerland  
Tel. +41 22 749 01 11  
Fax +41 22 749 09 47  
copyright@iso.org  
www.iso.org

# Contents

	Page
Foreword .....	iv
<b>1 Scope .....</b>	<b>1</b>
<b>2 Normative references .....</b>	<b>1</b>
<b>3 Terms and definitions .....</b>	<b>1</b>
<b>4 Principle .....</b>	<b>1</b>
<b>5 Apparatus .....</b>	<b>1</b>
<b>6 Sample preparation .....</b>	<b>2</b>
<b>7 Test procedure .....</b>	<b>2</b>
7.1 Plotting .....	3
<b>8 Calculations and expression of results .....</b>	<b>4</b>
8.1 Hand-arranging staple length .....	4
8.2 Short fibre content .....	4
8.3 Test result .....	4
<b>9 Test report .....</b>	<b>4</b>
<b>Annex A (informative) Example of calculations made to obtain the hand-arranging staple length ..</b>	<b>6</b>

## iTeh STANDARD PREVIEW (standards.iteh.ai)

ISO 18596:2015

<https://standards.iteh.ai/catalog/standards/sist/d9db4a7a-2795-486b-8292-068d3f0e70da/iso-18596-2015>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 38, *Textiles*, Subcommittee SC 23, *Fibres and yarns*.

ISO 18596:2015

<https://standards.iteh.ai/catalog/standards/sist/d9db4a7a-2795-486b-8292-068d3f0e70da/iso-18596-2015>

# Test method for staple length of dehaired cashmere — Hand-arranging method

## 1 Scope

This International Standard specifies a test method for a staple length of dehaired cashmere by a hand-arranging method.

This International Standard is also applicable to dehaired camel, dehaired yak, etc.

## 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 139, *Textiles — Standard atmospheres for conditioning and testing*

## 3 Terms and definitions

For the purpose of this document, the following terms and definitions apply.

### 3.1

#### **dehaired cashmere**

cashmere which has been scoured and dehaired

ISO 18596:2015

https://standards.iso.org/standards/sist/d9db4a7a-2795-486b-8292-068d3f0e70da/iso-18596-2015

### 3.2

#### **hand-arranging staple length**

average fibre length measured on the length distribution graph which is arranged uniformly with fibres

### 3.3

#### **short fibre content**

number of fibres equal to or less than 15 mm in length as a percentage of the total number of fibres

## 4 Principle

Fibres are uniformly arranged onto a length distribution graph on a flannelette board. The length values are measured at 10 mm intervals. The weighted mean of these length values is called the hand-arranging staple length.

## 5 Apparatus

**5.1 Flannelette board**, covered with black knit flannelette (polyester fibres, 150 g/m<sup>2</sup> to 250 g/m<sup>2</sup> fabric weight).

**5.2 Tweezers**.

**5.3 Steel plate rulers**, with the minimum scale of 0,5 mm.

**5.4 Coordinate papers**, with the minimum scale of 1 mm.

## 6 Sample preparation

### 6.1 Lot sample

#### 6.1.1 Proportion and amount

Randomly draw samples from each bale if the total number of bales in the lot is five or fewer.

If the number of bales in the lot exceeds five bales, draw samples from 20 % of the additional number of bales. Quantities less than one bale are counted as one bale. The total mass of the lot sample shall not be less than 300 g.

#### 6.1.2 Sampling

Randomly select and draw samples from the top, middle and bottom positions, deeper than 15 cm from the outermost bale surface.

### 6.2 Laboratory sample

Spread out the lot sample on the test table and blend it by hand into a homogeneous state. Then divide it into two equal parts. One is the laboratory sample, and the other is retained as a spare.

### 6.3 Test specimen

Randomly draw 0,09 g to 0,15 g of fibres from each side of the laboratory sample at different positions (from no fewer than 40 positions). Mix these fibres well, then divide them into three equal parts. Two parts are used in parallel tests, the third is retained as a spare test specimen.

### 6.4 Atmospheres for conditioning and testing

Atmospheres used for conditioning and testing shall be in accordance with ISO 139. All the samples shall be conditioned for a minimum of 24 h immediately before testing and remain conditioned during testing.

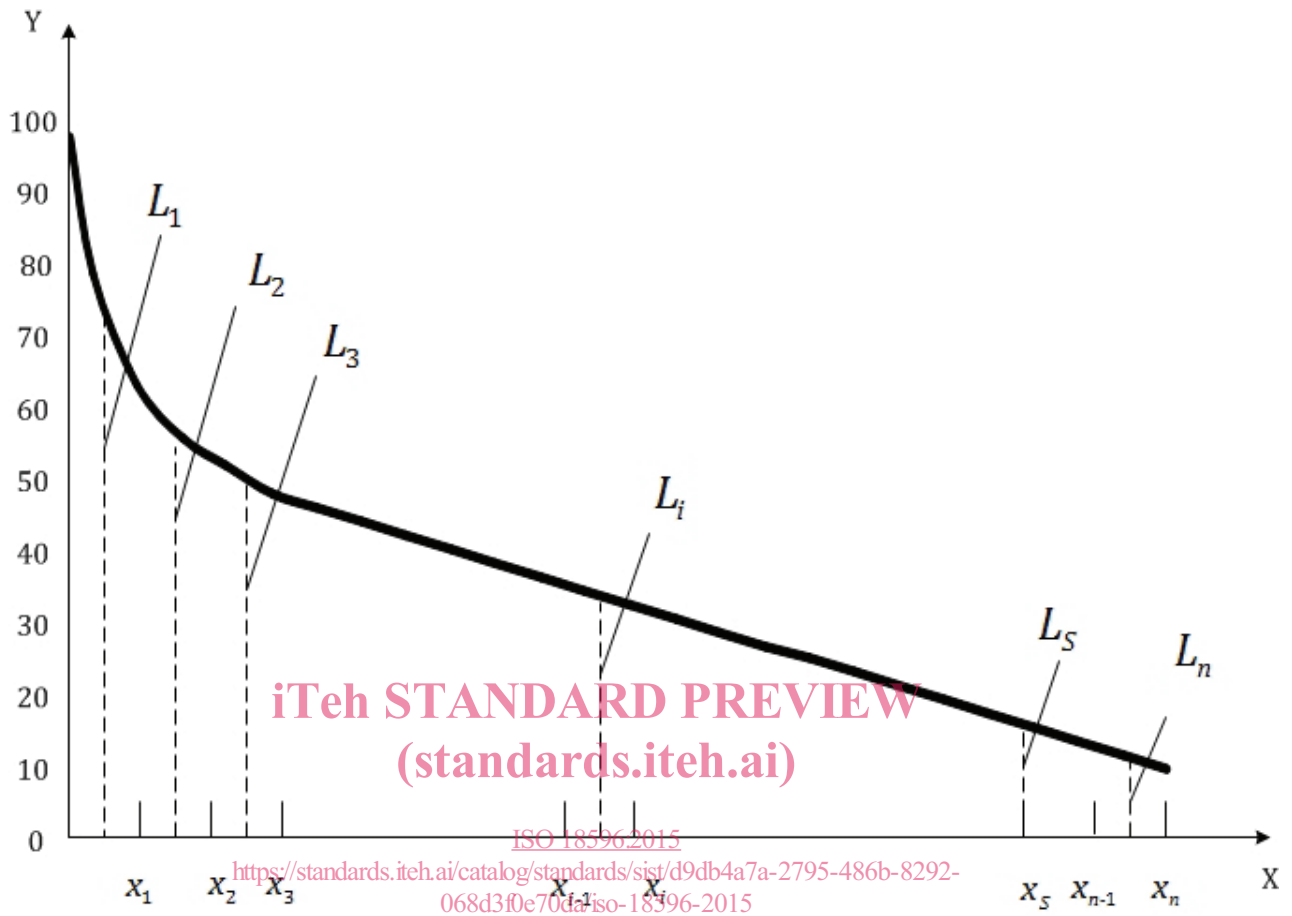
## 7 Test procedure

### 7.1 Layout of the fibre

7.1.1 Repeatedly sort the test specimen by hand into a natural neat bundle aligned at one end.

7.1.2 While holding the aligned end of the specimen with one hand, place the other end on the flannelette board and press by thumb. Slowly draw an equivalent amount of fibres out of the fibre bundle, then successively arrange the fibres from long to short on the flannelette board keeping one end aligned.

7.1.3 After all the fibres have been pulled out completely, take all the fibres with tweezers and re-sort the sample into a fibre bundle again. Repeat the preceding operations (not more than five times) until all the fibres are uniformly arranged into a length distribution graph whose bottom margin is  $250 \text{ mm} \pm 10 \text{ mm}$ , the fibres are naturally parallel to each other and the distribution's thickness is uniform as shown in [Figure 1](#).

**Key**

- X abscissa  
Y fibre length

**Figure 1 — Length distribution graph****7.1 Plotting**

Take the bottom margin as the abscissa, and the fibre length as the ordinate as shown in [Figure 1](#). Mark the abscissa  $x_1, x_2, \dots, x_i, \dots, x_{n-1}$  at 10 mm intervals from the origin. If the interval of the last group is not more than 10 mm, mark the terminal point's abscissa as  $x_n$ .

Measure the corresponding length  $L_1, L_2, \dots, L_i, \dots, L_n$  of each group's midpoint with steel plate rulers. Mark all the points on the coordinate papers. The base line of length distribution graph is  $x_n$  mm.

## 8 Calculations and expression of results

### 8.1 Hand-arranging staple length

Calculate the hand-arranging staple length from Formula (1), expressed in integer:

$$L = \frac{10 \times \sum_{i=1}^{n-1} L_i + (x_n - x_{n-1}) \times L_n}{x_n} \quad (1)$$

where

$L$  is the hand-arranging staple length, expressed in millimetres (mm);

$L_i$  is the staple length corresponding to different distances, expressed in millimetres (mm);

$x_n$  is the terminal point's abscissa value corresponding to the last length group, expressed in millimetres (mm);

$x_{n-1}$  is the starting point's abscissa value corresponding to the last length group, expressed in millimetres (mm);

$L_n$  is the staple length corresponding to the last length group's midpoint, expressed in millimetres (mm).

**iTeh STANDARD PREVIEW**  
(standards.iteh.ai)

### 8.2 Short fibre content

Calculate the short fibre content from Formula (2), rounded to one decimal place:

$$D = \frac{x_n - x_s}{x_n} \times 100 \% \quad (2)$$

ISO 18596:2015  
<https://standards.iteh.ai/catalog/standards/sist/d9db4a7a-2795-486b-8292-068d3f0e70da/iso-18596-2015>

where

$D$  is the short fibre content, expressed as a percentage (%);

$x_n$  is the terminal point's abscissa value corresponding to the last length group, expressed in millimetres (mm);

$x_s$  is the abscissa corresponding to the staple length of 15 mm, expressed in millimetres (mm).

### 8.3 Test result

Take the average of the two test specimens' value as the test result.

When the absolute value of the difference between the two specimens is more than 2 mm, the third specimen shall be tested. The final test result is the mean value of the three specimens.

## 9 Test report

The test report shall contain at least the following information:

- a) a reference to this International Standard, i.e. ISO 18596;
- b) the description of the samples;
- c) the standard atmosphere for conditioning and testing;



- d) testing results, including hand-arranging staple length, short fibre content;
- e) deviation from this International Standard, if any;
- f) anything unusual during the testing;
- g) testing date.

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[ISO 18596:2015](https://standards.iteh.ai/catalog/standards/sist/d9db4a7a-2795-486b-8292-068d3f0e70da/iso-18596-2015)

<https://standards.iteh.ai/catalog/standards/sist/d9db4a7a-2795-486b-8292-068d3f0e70da/iso-18596-2015>