



Designation: F 879M-02 Designation: F 879M – 02a (Reapproved 2008)

Standard Specification for Stainless Steel Socket Button and Flat Countersunk Head Cap Screws [~~Metric~~](Metric)¹

This standard is issued under the fixed designation F 879M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the Department of Defense.

1. Scope

1.1 This specification covers the chemical and mechanical requirements for stainless steel metric hexagon socket button (SBHCS) and flat countersunk (SFHCS) head cap screws with nominal thread M 3 through M 20 intended for use in applications requiring general corrosion resistance.

~~1.2 Two property classes are covered:~~

~~1.2.1 Austenitic Class A1-50 in an annealed condition at 500 MPa minimum, and~~

~~1.2.2 Austenitic Class A1-70 in a cold-worked condition at 700 MPa minimum.~~

~~1.3~~

1.2 The following three property classes are covered:

1.2.1 Austenitic Class A 1-50 in an annealed condition at 585 MPa maximum,

1.2.2 Austenitic Class A1-55 in a cold worked condition at 550 MPa minimum, and

1.2.3 Austenitic Class A 1-70 in a cold-worked condition at 700 MPa minimum.

1.3 Units—The values stated in SI units are to be regarded as standard. No other units of measurement are included in this standard.

1.4 The following hazard caveat pertains only to Section 12, Test Methods: *This standard does not purport to address all of the safety problems, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards:*²

A 262 Practices for Detecting Susceptibility to Intergranular Attack in Austenitic Stainless Steels

A 342/A 342M Test Methods for Permeability of Feebly Magnetic Materials

A 380 Practice for Cleaning, Descaling, and Passivation of Stainless Steel Parts, Equipment, and Systems ^{79m-02a2008}

A 555/A 555M Specification for General Requirements for Stainless Steel Wire and Wire Rods

A 751 Test Methods, Practices, and Terminology for Chemical Analysis of Steel Products

A 967 Specification for Chemical Passivation Treatments for Stainless Steel Parts

D 3951 Practice for Commercial Packaging

E 18 Test Methods for Rockwell Hardness of Metallic Materials

E 92 Test Method for Vickers Hardness of Metallic Materials

E 384 Test Method for Microindentation Hardness of Materials

F 606M Test Methods for Determining the Mechanical Properties of Externally and Internally Threaded Fasteners, Washers, and Rivets [~~Metric~~](Metric)

F 738M Specification for Stainless Steel Metric Bolts, Screws, and Studs

F 788/F 788M Specification for Surface Discontinuities of Bolts, Screws, and Studs, Inch and Metric Series

F 1470 Guide for Fastener Sampling for Specified Mechanical Properties and Performance Inspection

2.2 *ASME Standards:*

¹ This specification is under the jurisdiction of ASTM Committee F16 on Fasteners and is the direct responsibility of Subcommittee F16.04 on Nonferrous Fasteners. Current edition approved June 10, 2002. Published June 2002. Originally published as F879-84. Last previous edition F879-01.

Current edition approved May 1, 2008. Published August 2008. Originally approved in 1984. Last previous edition approved in 2002 as F 879 – 02a.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* Vol 01.03 volume information, refer to the standard's Document Summary page on the ASTM website.

- B 18.3.4M Hexagon Socket Button Head Cap Screws (Metric Series)³
 B 18.3.5M Hexagon Socket Flat Countersunk Head Cap Screws (Metric Series)³

3. Classification

3.1 The designation of the property class and conditions of this specification shall be consistent with the stainless steel designations in Specification F 738M.

~~3.2 The austenitic stainless steel socket screw shall be designated F879M A1-50 or F879M A1-70.~~

3.2 The austenitic stainless steel socket screw shall be designated F879M A1-50, F879M A1-55, or F 879M A1-70.

4. Ordering Information

4.1 Orders for material under this specification shall include the following information:

4.1.1 Quantity (number of pieces of each item).

4.1.2 Name of the screw, SBHCS or SFHCS.

4.1.3 Dimensions, including nominal thread designation, thread pitch, and nominal screw length (millimetres). A standard part number may be used for this definition.

~~4.1.4 Property Class A1-50 or A1-70.~~

4.1.4 Property Class A 1-50, A1-55, or A 1-70.

4.1.5 Certification, if required (see Section 15).

4.1.6 ASTM specification and year of issue.

4.1.7 Any special or supplemental requirements (see Supplementary Requirements S1 through S3).

5. Materials and Manufacture

5.1 Screws shall be formed by upsetting or extruding, or both.

5.2 Screws shall be roll threaded.

5.3 *Heat Treatment*—Austenitic alloys Class A 1-50 screws, following manufacture, shall be annealed by heating to 1040 ± 30°C to obtain maximum corrosion resistance and minimum permeability. The screws shall be held for a sufficient time at temperature, then cooled at a rate sufficient to prevent precipitation of the carbide and provide the properties specified in Table 1.

5.4 When ~~Condition~~Property Class A1-55 or A1-70 is specified, the austenitic alloys shall be annealed as specified in 5.3, generally by the raw material manufacturer, then cold worked to develop specific properties.

6. Chemical Composition

6.1 It is the intent of this specification that screws shall be ordered by property class. The chemical composition of the screws shall conform to the requirements of Table 2.

6.2 Unless otherwise specified in the inquiry and purchase order (see Supplementary Requirement S2) ~~when A1-50 or A1-70 property class is specified, S2),~~ the choice of stainless steel used shall be that of the fastener manufacturer as determined by his fabrication methods and material availability. The specific stainless steel used by the manufacturer shall be clearly identified on all certification required in the purchase order and shall have a chemical composition conforming to the limits specified in Table 2.

³ Annual Book of ASTM Standards, Vol 03.04.

³ Available from Global Engineering Documents, 15 Inverness Way, East Englewood, CO 80112-5704, <http://www.global.ih.com>.

TABLE 1 Mechanical Property Requirements

Property Class	Nominal Thread Diameter ^A	Full Size Product Tests		Machined Specimen Tests			Core Hardness ^B		
		Tensile Strength, MPa	Minimum Extension, min ^C	Tensile Strength, MPa	Yield Strength, MPa	Elongation, %, min	Vickers	Rockwell	
		min	max	min	max	min	min	min	
A1-50		585 max	0.6D	585 max	350 max	40	-	220	-
A1-50	M3-M20	585 max	0.6D	585 max	380 max	40	210 max	220	-
M3-M14A 1-70		525 min	0.4D	600 min	300 min	20	190	330B96	G33
A1-55	M3-M20	550 min	0.4D	550 min	270 min	25	160 min	50B96	G33 HRA min
M16-M20A 1-70		440 min	0.4D	550 min	270 min	25	160	310	B83
A1-70	M3-M20	700 min	0.4D	600 min	450 min	20	220 min	310	B83

^A Actual full-size testing of Class A1-55 and A1-70 may result in decreased tensile strength because of the head configuration (see Table 3). For fasteners with nominal thread diameters larger than M20, the mechanical properties shall be agreed upon between the user and manufacturer.

^B Core hardness is only required when full-size product tensile testing cannot be accomplished.

^C D denotes nominal thread size.

TABLE 2 Chemical Requirements

Property Class	UNS Designation	Alloy	Composition, % maximum except as shown								
			Carbon	Manganese	Phosphorus	Sulfur	Silicon	Chromium	Nickel	Copper	Molybdenum
Austenitic Alloys											
	S30400	304	0.08	2.00	0.045	0.030	1.00	18.0 to 20.0	8.0 to 10.5	1.00	
	S30400	304	0.08	2.00	0.045	0.030	1.00	18.0 to 20.0	8.0 to 10.5	1.00	...
S30403	304L	0.030	2.00	0.045	0.030	1.00	18.0 to 20.0	8.0 to 12.0	1.00	...	
S30403	304L	0.030	2.00	0.045	0.030	1.00	18.0 to 20.0	8.0 to 12.0	1.00	...	
A1-50	S30500	305	0.12	2.00	0.045	0.030	1.00	17.0 to 19.0	10.5 to 13.0	1.00	
A1-50	S30500	305	0.12	2.00	0.045	0.030	1.00	17.0 to 19.0	10.5 to 13.0	1.00	...
A1-70	S38400	384	0.08	2.00	0.045	0.030	1.00	15.0 to 17.0	17.0 to 19.0		...
	S30430	18-9LW	0.10	2.00	0.045	0.030	1.00	17.0 to 19.0	8.0 to 10.0	3.00 to 4.00	...
	S30430	18-9LW	0.10	2.00	0.045	0.030	1.00	17.0 to 19.0	8.0 to 10.0	3.00 to 4.00	...
S30433	302HQ	0.03	2.00	0.045	0.030	1.00	17.0 to 19.0	8.0 to 10.0	3.0 to 4.0		
S30433	302HQ	0.03	2.00	0.045	0.030	1.00	17.0 to 19.0	8.0 to 10.0	3.0 to 4.0	...	
	S31600	316	0.08	2.00	0.045	0.030	1.00	16.0 to 18.0	10.0 to 14.0		2.00 to 3.00
	S31603	316L	0.03	2.00	0.045	0.030	1.00	16.0 to 18.0	10.0 to 14.0		2.00 to 3.00

6.3 When chemical analysis is performed by the purchaser using finished fasteners, the chemical composition obtained shall conform to the limits specified in Table 2 for the specific alloy. Chemical composition shall conform to the tolerances specified in Specification A 555/A 555M.

6.3.1 In the event of a discrepancy, a referee analysis of the samples for each lot as specified in 12.1, shall be made in accordance with 11.3.

7. Mechanical Properties

7.1 The finished screws shall conform to the mechanical requirements specified in Table 1.

7.2 Screws having a nominal length equal to or greater than three diameters shall be tensile tested full size and shall meet the full size breaking strength requirements specified in Table 3. Tensile failures through the head are acceptable providing the load requirements are satisfied.

7.3 Screws that are too short (lengths less than specified in 7.2 or that have insufficient threads for tension testing) shall not be subject to tension tests, but shall conform to the maximum and minimum hardness requirements of Table 1.

8. Corrosion Resistance Requirements

8.1 Carbide Precipitation:

8.1.1 Austenitic alloy rod, bar, and wire used to make fasteners in accordance with this specification shall be capable of passing the test for susceptibility to intergranular corrosion as specified in Practice E of Practice A 262.

8.1.2 As stated in Practices A 262, samples may be subjected to the faster and more severe screening test in accordance with Practice A. Failing Practice A, specimens shall be tested to Practice E and be considered satisfactory if passing Practice E.

8.1.3 If the fasteners pass the requirements of 8.1.1, they shall be considered acceptable. If they fail, they shall be tested in accordance with Practice C of Practices A 262 and shall show a corrosion rate not exceeding 0.05 mm/month.

9. Dimensions

9.1 Unless otherwise specified, the dimensions shall conform to the requirements of ASME B 18.3.4M or ASME B 18.3.5M, as specified.

10. Workmanship, Finish, and Appearance

10.1 *Surface Treatment*—Unless otherwise specified, screws shall be cleaned, descaled and passivated in accordance with Practice A380 or Specification A 967 at the option of the manufacturer.

10.2 Surface Discontinuities:

10.2.1 The surface discontinuities for these products shall conform to Specification F 788/F 788M and the additional limitations specified herein.

10.2.1.1 Forging defects that connect the socket to the periphery of the head are not permissible. Defects originating on the periphery and with a traverse indicating a potential to intersect are not permissible. Other forging defects are permissible provided those located in the bearing area, fillet, and top surfaces shall not have a depth exceeding 0.03 *D* or 0.13 mm, whichever is greater. For peripheral discontinuities, the maximum depth may be 0.06 *D* (see Fig. 1).

10.2.1.2 Forging defects located in the socket wall within 0.1 times the actual key engagement, *T*, from the bottom of the socket are not permissible. Discontinuities located elsewhere in the socket shall not have a length exceeding 0.25 *T*, or a maximum depth of 0.03 *D* not to exceed 0.13 mm (see Fig. 2).

10.2.1.3 Seams in the shank shall not exceed a depth of 0.03 *D* or 0.2 mm, whichever is greater.

TABLE 3 Breaking Strength Values for Full Size Fasteners

NOTE 1—Breaking loads are based on tensile stress area and strengths of 585 MPa max for A1-50 and 525 MPa min through M14 and 440 MPa min for A1-70. The minimum loads for class A1-70 are based on the tensile properties of 655 MPa material strength through M14 and 550 MPa material strength M16 and above, reduced by 20 % to allow for the head critical nature of these configurations. Table 1. Actual strength of the threaded section, if size permits, may be determined by removing the head and testing the threaded section as a stud.

Nominal Size and Thread Pitch	Stress Area, mm ²	Property Class		
		A1-50	Alloy Class A1-50 $\frac{5}{5}$	Alloy Class A1-70
		kN, max	kN, min	kN, min
M3 × 0.5	5.03	2.94		2.64
M3 × 0.5	5.03	2.94	2.21	2.82
M4 × 0.7	8.78	5.13		4.61
M4 × 0.7	8.78	5.14	3.86	4.92
M5 × 0.8	14.2	8.31		7.46
M5 × 0.8	14.2	8.30	6.24	7.94
M6 × 1.0	20.1	11.8		10.6
M6 × 1.0	20.1	11.8	8.9	11.3
M8 × 1.25	36.6	21.4		19.2
M8 × 1.25	36.6	21.4	16.1	20.5
M10 × 1.5	58.0	33.9		30.5
M10 × 1.5	58.0	33.9	25.5	32.5
M12 × 1.75	84.3	49.3		44.3
M12 × 1.75	84.3	49.3	37.1	47.2
M14 × 2.0	115.0	67.3		60.4
M14 × 2.0	115.0	67.5	50.8	64.6
M16 × 2.0	157.0	91.9		69.1
M16 × 2.0	157.0	91.7	68.9	87.7
M20 × 2.5	245.0	143.0		108.0
M20 × 2.5	245.0	143	108	137

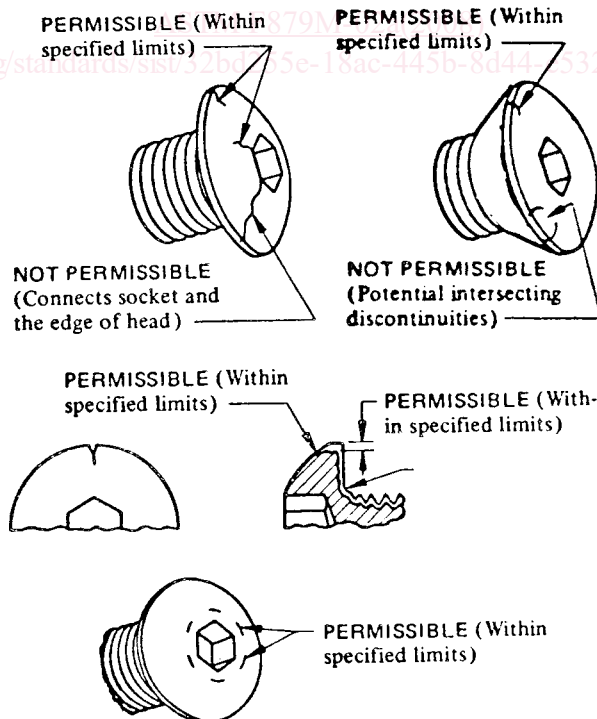


FIG. 1 Head Discontinuities (See 10.2.1)