



Designation: A684/A684M – 08

Standard Specification for Steel, Strip, High-Carbon, Cold-Rolled¹

This standard is issued under the fixed designation A684/A684M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the Department of Defense.

1. Scope*

1.1 This specification covers cold-rolled, high-carbon strip in coils or cut lengths. Strip is classified as product that is 0.3000 in. [7.6 mm] or less in thickness and over $\frac{1}{2}$ to $23^{15}/16$ in. [12.5 to 600 mm] in width, inclusive. Strip tolerance products may be available in widths wider than $23^{15}/16$ in. (600 mm) by agreement between purchaser and supplier; however, such products are technically classified as cold-rolled sheet. The maximum of the specified carbon range is over 0.25 to 1.35 %, inclusive. It is furnished in the following types as specified:

1.1.1 Soft spheroidized annealed high-carbon steel is intended for applications requiring maximum cold forming. It is normally produced to give the lowest maximum Rockwell hardness for each grade.

1.1.2 Soft annealed high-carbon steel is intended for applications requiring moderate cold forming. It is produced to a maximum Rockwell hardness.

1.1.3 Intermediate hardness high-carbon steel is intended for applications where cold forming is slight or a stiff, springy product is needed, or both. It is produced to specified Rockwell hardness ranges, the maximum being higher than obtained for the annealed type.

1.1.4 Full hard high-carbon steel is intended for flat applications. It is produced to minimum Rockwell hardness requirements, which vary with grade, microstructure and gauge. Full hard can be produced with either a pearlitic or spheroidized microstructure or a mixture of both. The minimum hardness should be established between the consumer and the producer.

1.2 This specification is applicable for orders in either inch-pound units or SI units.

1.3 The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system may not be exact equivalents; therefore, each system shall be used independently of the other. Combining values from the two systems may result in non-conformance with the standard.

1.4 The tolerances in this specification are different than those in Specification [A568/A568M](#) and Specification [A109/A109M](#).

1.5 For the purpose of determining conformance with this specification, values shall be rounded to the nearest unit in the right hand place of figures used in expressing the limiting values in accordance with the rounding method of Practice [E29](#).

1.6 This specification is expressed in both inch-pound units and SI units. However, unless the order specifies the applicable “M” specification designation (SI units), the material shall be furnished to inch-pound units. The metric portions of the tables herein list permissible variations in dimensions and mass (see [Note 1](#)) in SI (metric) units. The values listed are not exact conversions of the values listed in the inch-pound tables but instead are rounded or rationalized values. Conformance to SI tolerances is mandatory when the “M” specification is used.

NOTE 1—The term *weight* is used when inch-pound units are the standard. However, under SI the preferred term is *mass*.

2. Referenced Documents

2.1 ASTM Standards:²

[A109/A109M](#) Specification for Steel, Strip, Carbon (0.25 Maximum Percent), Cold-Rolled

[A370](#) Test Methods and Definitions for Mechanical Testing of Steel Products

[A568/A568M](#) Specification for Steel, Sheet, Carbon, Structural, and High-Strength, Low-Alloy, Hot-Rolled and Cold-Rolled, General Requirements for

[A700](#) Practices for Packaging, Marking, and Loading Methods for Steel Products for Shipment

[A751](#) Test Methods, Practices, and Terminology for Chemical Analysis of Steel Products

[A941](#) Terminology Relating to Steel, Stainless Steel, Related Alloys, and Ferroalloys

[E3](#) Guide for Preparation of Metallographic Specimens

[E29](#) Practice for Using Significant Digits in Test Data to Determine Conformance with Specifications

¹ This specification is under the jurisdiction of ASTM Committee [A01](#) on Steel, Stainless Steel and Related Alloys and is the direct responsibility of Subcommittee [A01.19](#) on Steel Sheet and Strip.

Current edition approved Oct. 1, 2008. Published October 2008. Originally approved in 1973. Last previous edition approved in 2006 as [A684/A684M – 06](#). DOI: 10.1520/A0684_A0684M-08.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

*A Summary of Changes section appears at the end of this standard.

E112 Test Methods for Determining Average Grain Size
 E527 Practice for Numbering Metals and Alloys in the Unified Numbering System (UNS)

2.2 Federal Standards:

Fed. Std. No. 123 Marking for Shipments (Civil Agencies)³
 Fed. Std. No. 183 Continuous Identification Marking of Iron and Steel Products³

2.3 Military Standard:

MIL-STD-129 Marking for Shipping and Storage³

2.4 SAE Standard:

J 1086 Recommended Practice for Numbering Metals and Alloys (UNS)⁴

3. Terminology

3.1 Definitions of Terms Specific to This Standard:

3.1.1 *burr*—metal displaced beyond the plane of the surface by slitting or shearing.

3.1.2 *lot*—quantity of material of the same type, size, and finish produced at one time from the same cast or heat, and heat treated in the same heat-treatment cycle.

3.1.3 *spheroidizing*—the heating and cooling of the strip in controlled conditions (annealing) to produce a spheroidal or globular form of carbide microconstituent.

3.1.4 *stretcher strains*—elongated markings that appear on the surface of the strip when dead soft (fully annealed) material is deformed beyond its yield point (see 5.2).

3.2 Refer to Terminology A941 for additional terms used in this standard.

4. Ordering Information

4.1 Orders for material under this specification shall include the following information:

- 4.1.1 ASTM designation and date of issue,
- 4.1.2 Name, type, and steel grade number,
- 4.1.3 Hardness (if intermediate or restricted hardness is specified),
- 4.1.4 Decarburization (if required),
- 4.1.5 Application,
- 4.1.6 Dimensions,
- 4.1.7 Coil size requirements,
- 4.1.8 Edge (indicate No. 1 round, square, etc.),
- 4.1.9 Finish (indicate and specify),
- 4.1.10 Conditions (specify whether material is oiled or dry),
- 4.1.11 Package (bare coils, skid, etc.),
- 4.1.12 Cast or heat (formerly ladle) analysis report (if required), and
- 4.1.13 Special requirements (if required).

4.2 Products covered by this specification are produced to decimal thickness only, and decimal thickness tolerances apply.

NOTE 2—A typical ordering description is as follows: ASTM A684 dated _____ Cold Rolled, High-Carbon Soft, Strip, Spheroidized 1064, 0.042 in. by 6 in. by coil (16 in. ID by 40 in. OD max), No. 5 Edge, No. 2 Finish, Oiled, Bare Skid or “ASTM A684 dated _____ Cold Rolled,

TABLE 1 Rockwell Hardness Testing Ranges for Cold-Rolled High-Carbon Steel Strip

Rockwell “B” and “T” Scales		Rockwell “C” and “N” Scales	
Thickness	Scale	Thickness	Scale
Over 0.030 in. [over 0.8 mm]	B	Over 0.040 in. [over 1.0 mm]	C
0.020 to 0.030 in. [0.5 to 0.8 mm]	30T	0.025 to 0.040 in. [0.6 to 1.0 mm]	30N
Under 0.020 in. [under 0.5 mm]	15T	Under 0.025 in. [under 0.6 mm]	15N

High-Carbon, Soft, Strip, Spheroidized 1064, 0.6 mm by 200 mm by coil (400 mm ID by 7500 mm OD max), No. 3 Edge, No. 2 Finish, Oiled, Bare Skid.”

5. Manufacture

5.1 Condition:

5.1.1 The strip shall be furnished cold rolled spheroidized annealed, soft annealed, intermediate hardness, or full hard, as specified.

5.1.2 Intermediate hardness may be obtained by either rolling the strip after final annealing or by varying the annealing treatment, or both.

5.2 *Pinch Pass*—Spheroidized annealed and annealed material may be pinch rolled after the final anneal to improve flatness, uniformly oil, modify surface, obtain proper mechanical properties and minimize stretcher strains if required by the purchaser.

6. Chemical Requirements

6.1 Limits:

6.1.1 When carbon steel strip is specified to chemical composition, the compositions are commonly prepared using the ranges and limits shown in Table 1. The elements comprising the desired chemical composition are specified in one of three ways:

6.1.1.1 By a maximum limit,

6.1.1.2 By a minimum limit, or

6.1.1.3 By minimum and maximum limits, termed the “range.” By common usage, the range is the arithmetical difference between the two limits (for example, 0.60 to 0.71 is 0.11 range).

6.1.2 Steel grade numbers indicating chemical composition commonly produced to this specification are shown in Table 2 and may be used. Table 3 shows requirements for additional elements.

6.1.3 Additional elements may be present. Limits on such elements are by agreement between purchaser and supplier.

6.1.3.1 Any additional elements specified shall be included in the report of heat analysis.

6.2 Heat (Formerly Ladle) Analysis:

6.2.1 An analysis of each heat of steel shall be made by the manufacturer to determine the percentage of elements specified or restricted by the applicable specification.

6.2.2 When requested, heat analysis for elements listed or required shall be reported to the purchaser or to his representative. Each of the elements listed in Tables 2 and 3 and additional elements agreed upon by the purchaser and the supplier shall be included in the report of heat analysis. When

³ Available from Standardization Documents Order Desk, DODSSP, Bldg. 4, Section D, 700 Robbins Ave., Philadelphia, PA 19111-5098, <http://www.dodssp.daps.mil>.

⁴ Available from Society of Automotive Engineers (SAE), 400 Commonwealth Dr., Warrendale, PA 15096-0001, <http://www.sae.org>.

**TABLE 2 Cold Bending Requirements^{A,B} for Spheroidized, Annealed, and Soft-Annealed Cold-Rolled Carbon Steel Strip**

Type	Degree of Bend	Inside Radius to Thickness	Relation of Bend Test Specimen to Rolling Direction
Annealed	180°	3t	transverse ^C
Spheroidized	180°	2t	transverse ^C

^A Up to 0.100 in. [2.5 mm], incl, thickness maximum. When bend radius for thickness is over 0.100 in. [2.5 mm] the producer should be consulted. These ratios apply to bending performance of the test specimen.

^B These bend tests apply to the bending performance of test specimens only. Where material is to be bent in fabricating operations a more liberal bend radius may be required and should be based on prior experience or consultation with the steel producer, or both.

^C If finished strip width prohibits taking a transverse bend test specimen, a longitudinal specimen may be substituted, except the bend radius shall be reduced by 1 t.

TABLE 3 Heat (Formerly Ladle) Analysis Limits and Ranges

Element	Standard Chemical Limits and Ranges, Limit or Max of Specified Range	Range, %
Carbon ^A	over 0.25 to 0.30, incl	0.06
	over 0.30 to 0.40, incl	0.07
	over 0.40 to 0.60, incl	0.08
	over 0.60 to 0.80, incl	0.11
	over 0.80 to 1.35, incl	0.14
Manganese	to 0.50, incl	0.20
	over 0.50 to 1.15, incl	0.30
	over 1.15 to 1.65, incl	0.35
Phosphorous	to 0.08, incl	0.03
	over 0.08 to 0.15, incl	0.05
Sulfur	to 0.08, incl	0.03
	over 0.08 to 0.15, incl	0.05
	over 0.15 to 0.23, incl	0.07
	over 0.23 to 0.33, incl	0.10
Silicon	to 0.20, incl	0.10
	over 0.20 to 0.30, incl	0.15
	over 0.30 to 0.60, incl	0.30

^A The carbon ranges shown in the column headed "Range" apply when the specified maximum limit for manganese does not exceed 1.00 %. When the maximum manganese limit exceeds 1.00 %, add 0.01 to the carbon ranges shown above.

the amount of copper, nickel, chromium, or molybdenum is less than 0.02 %, the analysis may be reported as <0.02 %. When the amount of vanadium, columbium, or titanium is less than 0.008 %, the analysis may be reported as <0.008 %. The reported heat analysis shall conform to the chemical composition requirements of the appropriate grade in Table 2, if used, the additional elements in Table 3, and the limits of any other elements agreed upon by the purchaser and supplier.

6.3 *Product Analysis*—Product analysis is the chemical analysis of the semi-finished product form. The strip may be subjected to product analysis by the purchaser either for the purpose of verifying that the ordered chemical composition is within specified limits for each element as listed in Table 4 including applicable tolerance for product analysis, or to determine variations in compositions within a cast or heat. Table 5 lists additional chemical composition requirements. The results of analyses taken from different pieces within a heat may differ from each other and from the cast analysis. The chemical composition thus determined shall not vary from the limits specified by more than the amounts shown in Table 6.

6.4 *Methods of Analysis*—Test Methods, Practices, and Terminology A751 shall be used for referee purposes.

7. Metallurgical Structure

7.1 Grain Size:

7.1.1 Unless otherwise specified, the steel strip shall be manufactured to a fine grain (austenitic and ferritic) practice.

7.1.2 Pearlite is the normal structure of cold rolled high-carbon strip unless it has had an intermediate anneal.

7.2 Decarburization:

7.2.1 When specified, the steel strip shall have a maximum permissible depth of complete plus partial decarburization of 0.001 in. [0.025 mm] or 1.5 % of the thickness of the strip, whichever is greater, except that strip less than 0.011 in. [0.279 mm] thick shall show no complete decarburization.

7.3 Annealed is mostly a spheroidized structure, but may contain some vestiges of pearlite.

7.4 Spheroidized annealed is essentially free of pearlite.

7.5 At least one specimen shall be taken from each lot for microexamination.

7.5.1 The specimens shall be prepared for microscopic examination in accordance with Guide E3.

8. Mechanical Requirements

8.1 Unless otherwise specified in the applicable product specification, test specimens must be prepared in accordance with Test Methods and Definitions A370.

8.2 Mechanical tests shall be conducted in accordance with Test Methods and Definitions A370.

8.3 Hardness:

8.3.1 *Spheroidized Annealed and Annealed Types*—When furnished spheroidized annealed or annealed, the hardness of the strip shall not exceed the maximum values specified in Figs. 1 and 2 for the applicable carbon range and type.

8.3.2 *Intermediate Hardness Type*—When furnished as intermediate hardness, the hardness of the strip shall conform to the range specified on the purchase order. The maximum hardness limit and the corresponding minimum shall be specified by the purchaser. If the maximum temper is under Rockwell B 100 (15T93 or 30T82), that scale should be used exclusively. If the minimum temper is over Rockwell C 20 (15N69.5 or 30N41.5), that scale should be used exclusively. For accuracy in testing, the hardness scales should not overlap. On either hardness scale, a range of ten points arithmetic difference is required. Refer to Table 1 for appropriate scale testing requirements.

8.3.3 Full hard is specified to a minimum hardness value. Refer to Table 1 for appropriate scale testing requirements.

8.3.4 At least one specimen shall be taken from each lot.

8.3.5 The sample shall be tested in accordance with Test Methods and Definitions A370.

8.4 Bend Test:

8.4.1 The steel strip produced as spheroidized, or the annealed type shall meet the cold bend requirement in Table 2. Any visible cracking on the tension side of the bend portion shall be cause for rejection.

8.4.2 At least one specimen shall be taken from each lot.

8.4.3 The specimen shall be the full thickness and shall be taken transverse to the rolling direction as described in Test

TABLE 4 Heat (Formerly Ladle) Analysis Chemical Composition, %

UNS Designation ^A	Steel Grade	Carbon	Manganese	Phosphorus, max	Sulfur, max	Silicon ^B
G10300	1030	0.28 to 0.34	0.60 to 0.90	0.030	0.035	0.15 to 0.30
G10350	1035	0.32 to 0.38	0.60 to 0.90	0.030	0.035	0.15 to 0.30
G10400	1040	0.37 to 0.44	0.60 to 0.90	0.030	0.035	0.15 to 0.30
G10450	1045	0.43 to 0.50	0.60 to 0.90	0.030	0.035	0.15 to 0.30
G10500	1050	0.48 to 0.55	0.60 to 0.90	0.030	0.035	0.15 to 0.30
G10550	1055	0.50 to 0.60	0.60 to 0.90	0.030	0.035	0.15 to 0.30
G10600	1060	0.55 to 0.65	0.60 to 0.90	0.030	0.035	0.15 to 0.30
G10640	1064	0.60 to 0.70	0.50 to 0.80	0.030	0.035	0.15 to 0.30
G10650	1065	0.60 to 0.70	0.60 to 0.90	0.030	0.035	0.15 to 0.30
G10700	1070	0.65 to 0.75	0.60 to 0.90	0.030	0.035	0.15 to 0.30
G10740	1074	0.70 to 0.80	0.50 to 0.80	0.030	0.035	0.15 to 0.30
G10800	1080	0.75 to 0.88	0.60 to 0.90	0.030	0.035	0.15 to 0.30
G10850	1085	0.80 to 0.93	0.70 to 1.00	0.030	0.035	0.15 to 0.30
G10860	1086	0.80 to 0.93	0.30 to 0.50	0.030	0.035	0.15 to 0.30
G10950	1095	0.90 to 1.03	0.30 to 0.50	0.030	0.035	0.15 to 0.30

^A New designation established in accordance with Practice E527 and SAE J 1086.

^B When agreed by purchaser and supplier, other silicon ranges are permissible.

TABLE 5 Additional Chemical Composition Requirements—Heat Analysis

Element	Composition—Weight %
Aluminum ^A	...
Copper, max ^B	0.30
Nickel, max ^B	0.30
Chromium, max ^{B,C}	0.25
Molybdenum, max ^B	0.10
Vanadium ^A	...
Columbium ^A	...
Titanium ^A	...

^A Where an ellipsis (...) appears in this table, there is no specified limit, but the analysis shall be reported.

^B The sum of copper, nickel, chromium, and molybdenum shall not exceed 0.80 % on heat analysis. When one or more of these elements is specified, the sum does not apply, in which case only the individual limits on the remaining elements will apply.

^C When the chromium is specified or added for antigrafitization, the maximum shall be 1.40 wt %.

TABLE 6 Tolerances for Product Analysis

Element	Limit or Max of Specification, %	Variations Over Max Limit or Under Min Limit	
		Under Min Limit	Over Max Limit
Carbon	over 0.25 to 0.40, incl	0.03	0.04
	over 0.40 to 0.80, incl	0.03	0.05
	over 0.80	0.03	0.06
Manganese	to 0.60, incl	0.03	0.03
	over 0.60 to 1.15, incl	0.04	0.04
	over 1.15 to 1.65, incl	0.05	0.05
Phosphorus	0.01
Sulfur	0.01
Silicon	to 0.30, incl	0.02	0.03
	over 0.30 to 0.60	0.05	0.05

Methods and Definitions A370. The edges of the bend test specimens shall be rounded and free of burrs; filing or machining is permissible.

9. Dimensions, Mass, and Permissible Variations

9.1 The thickness, width, camber, and length tolerances shall conform to the requirements specified in Tables 5-10.

9.2 *Flatness*—It is not practical to formulate flatness tolerances for cold-rolled carbon spring steel strip to represent the range of widths and thicknesses in coils and cut lengths.

10. Finish and Edges

10.1 *Surface*—The strip shall be furnished with a No. 2 Regular Bright or No. 1 Matte (Dull) finish, as specified.

10.2 *Oiling*—The strip shall be furnished oiled or dry, as specified.

10.3 *Edges*—Cold-rolled carbon steel strip shall be supplied with one of the following edges as specified:

10.3.1 *No. 1*—A prepared edge of a specified contour (round or square) that is produced when a very accurate width is required or when an edge condition suitable for electroplating is required, or both.

10.3.2 *No. 2*—A natural mill edge carried through the cold rolling from the hot-rolled strip without additional processing of the edge.

10.3.3 *No. 3*—An approximately square edge produced by slitting on which the burr is not eliminated. This is produced when the edge condition is not a critical requirement for the finished part. Normal coiling or piling does not provide a definite positioning of the slitting burr.

10.3.4 *No. 4*—An approximately rounded edge. This edge is produced when the width tolerance and edge condition are not as exacting as for No. 1 edges.

10.3.5 *No. 5*—An approximately square edge produced from slit edge material on which the burr is eliminated.

10.3.6 *No. 6*—An approximately square edge. This edge is produced when the width tolerance and edge condition are not as exacting as for No. 1 edges.

10.3.7 *Skived Edges*—Custom-shaped edges produced by mechanical edge shaving with special tooling.

10.4 *Finish*—Cold-rolled carbon steel strip shall be supplied with the following finishes.

10.4.1 *Number 1 or Matte (Dull) Finish*—Finish without luster, produced by rolling on rolls roughened by mechanical or chemical means. This finish is especially suitable for lacquer or paint adhesion, and is beneficial in aiding drawing operations by reducing the contact friction between the die and the strip.

10.4.2 *Number 2 (Regular Bright) Finish*—Finish produced by rolling on rolls having a moderately smooth finish. It is less

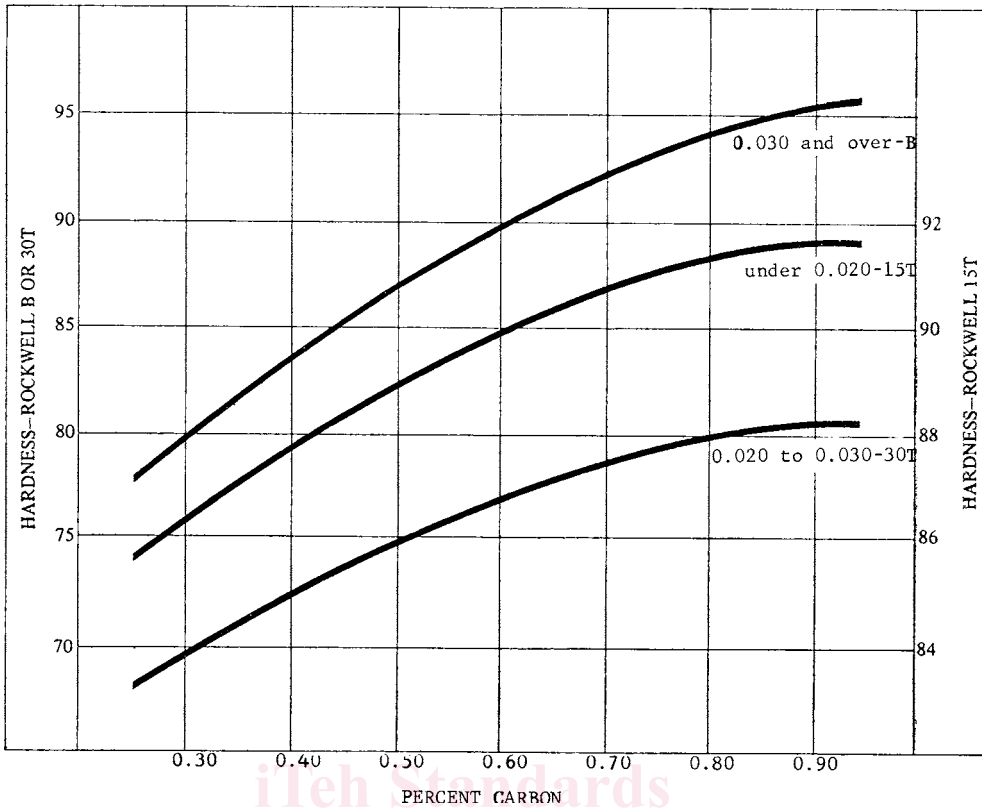


FIG. 1 Approximate Relationship Between Carbon Designations and the Maximum Hardness Limit of Soft Type Annealed Cold Rolled High Carbon Steel Strip

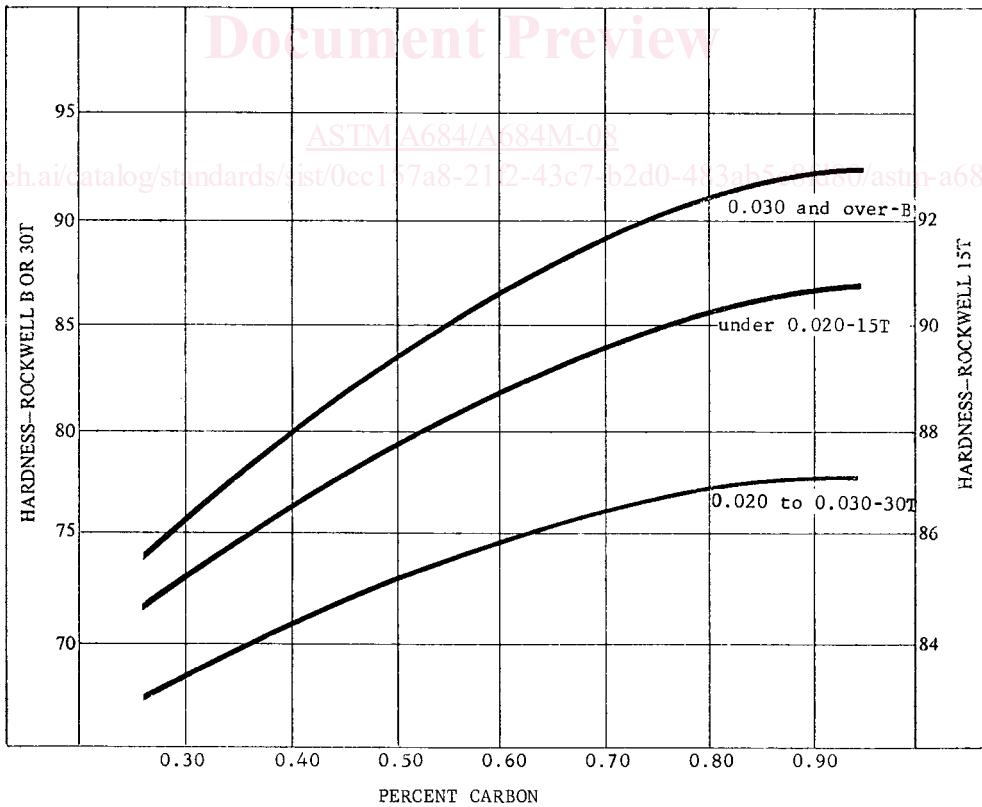


FIG. 2 Approximate Relationship Between Carbon Designations and the Maximum Hardness Limit of Spheroidized Annealed Cold Rolled High Carbon Steel Strip



TABLE 7 Thickness Tolerances of Cold-Rolled Carbon Steel Strip^{A,B,C}

Inch-Pound Units (in.)			
Thickness Tolerances (Plus or Minus, in.)			
Nominal Gauge (in.)	Over ½ to less than 12 wide	12 to less than 18	18 to 23 ¹⁵ / ₁₆
0.251-0.300	0.0030	0.0035	0.0040
0.160-0.250	0.0025	0.0032	0.0036
0.125-0.1599	0.0022	0.0028	0.0032
0.070-0.1249	0.0018	0.0022	0.0028
0.040-0.0699	0.0014	0.0018	0.0024
0.030-0.0399	0.0012	0.0015	0.0020
0.020-0.0299	0.0010	0.0013	0.0015
0.015-0.0199	0.0008	0.0010	0.0012
0.010-0.0149	0.0005	0.0008	0.0010
<0.010	0.0003	0.0006	0.0008
SI Units (mm)			
Thickness Tolerances (Plus or Minus, mm)			
Nominal Gauge (mm)	Over 12.7 to less than 300	300 to less than 450	450 to 600
6.40-7.50	0.080	0.090	0.100
4.00-6.39	0.065	0.080	0.090
3.20-3.99	0.055	0.070	0.080
1.80-3.19	0.045	0.055	0.070
1.00-1.79	0.035	0.045	0.060
0.75-0.99	0.030	0.030	0.050
0.50-0.74	0.025	0.035	0.040
0.38-0.49	0.020	0.025	0.030
0.25-0.37	0.013	0.020	0.025
<0.25	0.007	0.015	0.020

^A Measured ¾ in. or more in from edge; and on narrower than 1 in., at any place between edges.

^B Measured 10 mm or more in from edge; and on narrower than 25 mm, at any place between edges.

^C Number 3 edge strip with thickness tolerance guaranteed at less than ¾ in. (10 mm) from the slit edge, is available by agreement between consumer and strip manufacturer.

suitable that No. 1 (matte) finish for cold forming and may be applicable for certain types of plating.

11. Workmanship

11.1 The steel shall have a workmanlike appearance and shall not have defects of a nature or degree for the grade and quality ordered that will be detrimental to the fabrication of the finished part.

11.2 Coils may contain some abnormalities that render a portion of the coil unusable since the inspection of coils does not afford the same opportunity to remove portions containing imperfections as is the case with cut lengths.

12. Number of Tests and Retests

12.1 The difficulties in obtaining truly representative samples of strip without destroying the usefulness of the coil account for the generally accepted practice of allowing retests for mechanical properties and surface examination. Two additional samples are secured from each end of the coil from which the original sample was taken. A portion of the coil may be discarded prior to cutting the samples for retest. If any of the retests fail to comply with the requirements, the coil shall be rejected.

TABLE 8 Width Tolerances for Edge Numbers 1, 4, 5, and 6 of Cold-Rolled Carbon-Steel Strip

Inch-Pound Units					
Edge Number	Specified Width, in. ^A		Specified Thickness, in. ^B		Width Tolerance, Plus and Minus, in. ^C
	Over	Through	min	max	
1	½	¾	...	0.0938	0.005
1	¾	5	...	0.125	0.005
4	½	1	0.025	0.1875	0.015
4	1	2	0.025	0.2499	0.025
4	2	4	0.035	0.2499	0.047
4	4	6	0.047	0.2499	0.047
5	½	¾	...	0.0938	0.005
5	¾	5	...	0.125	0.005
5	5	9	0.008	0.125	0.010
5	9	20	0.015	0.105	0.010
5	20	23 ¹⁵ / ₁₆	0.023	0.080	0.015
6	½	1	0.025	0.1875	0.015
6	1	2	0.025	0.2499	0.025
6	2	4	0.035	0.2499	0.047
6	4	6	0.047	0.2499	0.047
SI Units					
Edge Number	Specified Width, mm ^A		Specified Thickness, mm ^B		Width Tolerance, Plus and Minus, mm ^C
	Over	Through	min	max	
1	12.5	200	...	3.0	0.13
4	...	25	0.6	5.0	0.38
4	25	50	0.6	6.0	0.65
4	50	150	1.0	6.0	1.20
5	...	100	...	3.0	0.13
5	100	500	0.4	3.0	0.25
5	500	600	0.6	2.0	0.38
6	...	25	0.6	5.0	0.38
6	25	50	0.6	6.0	0.65
6	50	150	1.0	6.0	1.20

^A Specified width must be within ranges stated for specified edge number.

^B Specified thickness must be within ranges stated for specified width.

^C When edge, width and thickness are not defined by this table, tolerances are by agreement between producer and supplier.

13. Rework and Retreatment

13.1 Lots rejected for failure to meet the specified requirements may be resubmitted for test provided the manufacturer has reworked the lots as necessary to correct the deficiency or has removed the nonconforming material.

14. Inspection

14.1 The manufacturer shall afford the purchaser’s inspector all reasonable facilities necessary to satisfy him that the material is being produced and furnished in accordance with this specification. Mill inspection by the purchaser shall not interfere unnecessarily with the manufacturer’s operations. Unless otherwise agreed to, all tests and inspections, except product analysis, shall be made at the place of production.

15. Rejection and Rehearing

15.1 Unless otherwise specified, any rejection based on tests made in accordance with this specification shall be reported to the purchaser within a reasonable time.

15.2 Material that shows injurious defects subsequent to its acceptance at the purchaser’s works shall be rejected and the