
**Thermal spraying — Classification
method of adhesive strength by
indentation**

*Projection thermique — Méthode de classification de la résistance
adhésive par indentation*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 19207:2016

<https://standards.iteh.ai/catalog/standards/sist/dadab135-88b0-4569-a147-1bb43ae892a4/iso-19207-2016>



iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 19207:2016

<https://standards.iteh.ai/catalog/standards/sist/dadab135-88b0-4569-a147-1bb43ae892a4/iso-19207-2016>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2016, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

	Page
Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Symbols and units	1
5 Principle	3
6 Test pieces and sample preparation	3
6.1 Thicknesses of coating and substrate	4
6.2 Sample size	4
6.3 Sample cutting	4
6.4 Mounting	4
6.5 Surface preparation	4
7 Apparatus	5
7.1 Indentation testing machines	5
7.2 Indenter	5
7.3 Impression and crack measurements	6
8 Procedure and conditions of testing	6
8.1 Indentation	6
8.2 Impression and crack length measurement	7
8.2.1 General	7
8.2.2 Method A	7
8.2.3 Method B	7
9 Evaluation of adhesion index	9
9.1 Criteria of interfacial crack initiation and critical indentation force	9
9.2 Classification of adhesive strength and notation of adhesion index	9
9.3 Test validity	11
10 Test report	12
10.1 Items to be reported	12
10.2 Items to be selected to report	12
Bibliography	13

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html.

The committee responsible for this document is ISO/TC 107, *Metallic and other inorganic coatings*.

ISO 19207:2016

<https://standards.iteh.ai/catalog/standards/sist/dadab135-88b0-4569-a147-1bb43ae892a4/iso-19207-2016>

Introduction

Adhesion of coatings specified here is required for three reasons:

- for selection of coating material and spray method;
- for quality assurance of thermal spraying;
- for product design and performance assessment of coatings.

This International Standard provides the classification method of adhesive strength for thermal spray coatings by using Vickers hardness testing machine generally and widely used. In the present test method, a pyramidal Vickers diamond indenter is indented with test force at the interface of coatings. When the test force exceeds the threshold value corresponding to the adhesive strength, an interfacial crack is generated. Accordingly, it is possible to evaluate the adhesive strength of coatings by the test force applied as discrete values when using conventional Vickers testing machine. This International Standard classifies the adhesive strength, called adhesion index, evaluated from the maximum indentation force without visible cracking and can be also applied to evaluate coatings with a high adhesive, such as cermet coatings. The present test method can be applied to sprayed coatings if the crack initiated by the indentation can be observed by using optical microscope.

The maximum indentation force does not therefore require much more effort in the experimental procedure and can describe the property of system combination (substrate chemistry, pre-preparation/roughness of substrate surface, coating chemistry and spraying related coating properties), provided the measurements are obtained carefully in line with the methods proposed in this International Standard. This International Standard recommends good practice to minimize levels of uncertainty in the measurement process. The procedure has been validated through underpinning technical work within the round robin test programme conducted by the Subcommittee on Standard Development, Japan Thermal Spray Society.

[ISO 19207:2016](https://standards.iteh.ai/catalog/standards/sist/dadab135-88b0-4569-a147-1bb43ae892a4/iso-19207-2016)

<https://standards.iteh.ai/catalog/standards/sist/dadab135-88b0-4569-a147-1bb43ae892a4/iso-19207-2016>

iTeh STANDARD PREVIEW **(standards.iteh.ai)**

ISO 19207:2016

<https://standards.iteh.ai/catalog/standards/sist/dadab135-88b0-4569-a147-1bb43ae892a4/iso-19207-2016>

Thermal spraying — Classification method of adhesive strength by indentation

1 Scope

This International Standard specifies the classification method of adhesive strength for thermal spray coatings at room temperature by using Vickers hardness testing machine. This International Standard classifies the adhesive strength, called adhesion index, evaluated from the maximum indentation force without visible cracking, and it is applicable for relative dense metal coatings, ceramic coatings and cermet coatings. This International Standard can be used within comparison within each coating system.

The indentation method is not recommended for very thin and very porous coatings and also for the coating system with lower cohesion strength than adhesion strength. It is recommended that this test method can be applied for a coating of which porosity is less than approximately 15 %.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 6507-1, *Metallic materials — Vickers hardness test — Part 1: Test method*

ISO 6507-2, *Metallic materials — Vickers hardness test — Part 2: Verification and calibration of testing machines*

ISO 14917, *Thermal spraying — Terminology, classification*

ISO 14923, *Thermal spraying — Characterization and testing of thermally sprayed coatings*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 14917, ISO 14923 and the following apply.

3.1

critical indentation force

maximum indentation force without visible cracking between substrate and coating

3.2

adhesion index

AI

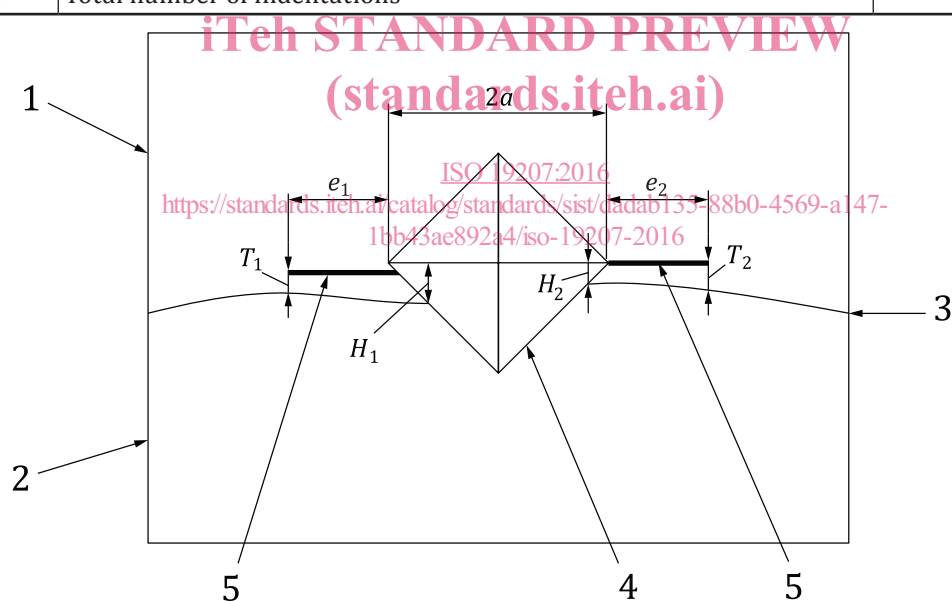
index of adhesive strength of coatings defined by the critical indentation force

4 Symbols and units

For the purposes of this document, the following symbols and units apply (see [Figures 1](#) and [2](#)).

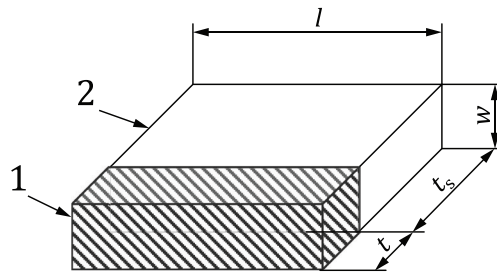
Table 1 — Symbols and designations

Symbol	Designation	Unit
a	Impression-diagonal half-length parallel to interface	mm
e	Visible crack length mean value	mm
e_1, e_2	Individual crack lengths at corner of an impression (lengths from crack tip to edge of impression diagonal, parallel with the macroscopic interface)	mm
F	Test force (indentation force)	N
F_{eq}	Equivalent indentation force when using the special conical indenter	N
H	Mean value in impression position	mm
H_1, H_2	Individual impression position	mm
l	Sample length	mm
T	Mean value in crack tip position	mm
T_1, T_2	Individual crack tip position	mm
t	Coating thickness	mm
t_s	Substrate thickness	mm
w	Sample width	mm
CF	Visible cracking frequency	%
N_c	Number of indentations with visible cracking	—
N_t	Total number of indentations	—

**Key**

- 1 coating
- 2 substrate (or bond coat)
- 3 interface
- 4 impression
- 5 visible crack

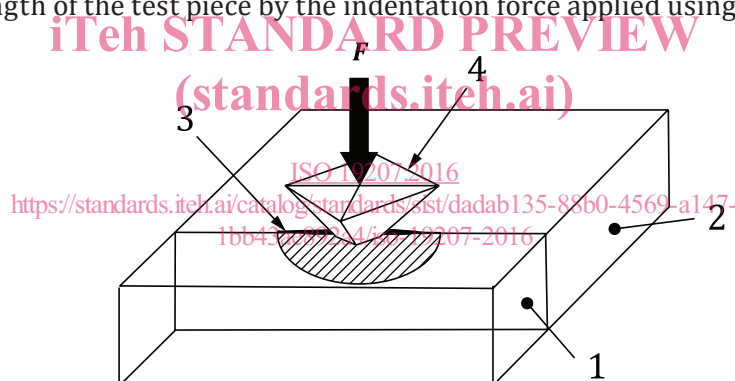
Figure 1 — Schematic diagram of indentation characteristics

**Key**

- 1 coating
- 2 substrate (with bond coat)

Figure 2 — Sample geometry**5 Principle**

When a pyramidal Vickers diamond indenter is indented with the indentation force at the interface (see [Figure 3](#)), an interfacial crack opening force that acts perpendicularly to the interface is generated. This crack opening force is proportional to the test force. When the crack opening force exceeds the adhesive strength of the test piece, an interfacial crack is generated. Accordingly, it is possible to classify the adhesive strength of the test piece by the indentation force applied using the Vickers indenter.

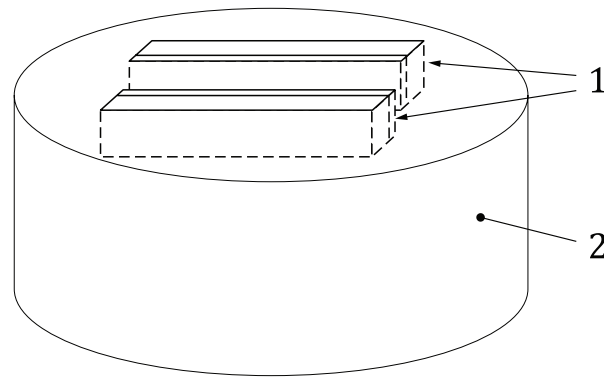
**Key**

- 1 coating
- 2 substrate (with bond coat)
- 3 visible crack
- 4 Vickers diamond indenter

Figure 3 — Interfacial indentation test**6 Test pieces and sample preparation**

The surface of the substrate to be coated by spraying shall be flat. After thermal spraying, samples are cut from the coated plate. Samples shall be coated of resin so as to obtain the specimen to be polished before proceeding to the test (see [Figure 4](#)).

In the samples, the thermal spray coating shall be adhered to the base material (or bond coating) and any cracking is not acceptable in the evaluation section before the test.

**Key**

- 1 coating samples
- 2 resin

Figure 4 — Test piece for indentation test**6.1 Thicknesses of coating and substrate**

The substrate shall have sufficient thickness in order to eliminate the effect of that in the experimental results. It is recommended that the thickness of substrate, t_s , (see Figure 2) is at least 5 mm.

The minimum thickness of the thermal spray coating, t , (see Figure 2) shall be at least twice the half-length of the impression in the case of high stiffness coatings, such as WC-12Co cermet coating. It is recommended that the thickness of coating is at least five times the half-length of the impression in the case of low stiffness coatings, such as thermal barrier coating which has very low elastic modulus.

6.2 Sample size

The width of the cut samples, w , (see Figure 2) shall be sufficiently greater than the depth of the indentation. It is recommended that the width of the cut sample is at least 5 mm.

The length of the cut samples, l , (see Figure 2) shall be of a sufficient length to enable the indenter to be applied at adequate intervals. It is recommended that the length of the cut samples, l , is longer than 20 mm.

6.3 Sample cutting

The appropriate cutting method and condition shall be selected in order to prevent the cutting to damage the sample. Wheel cutting or electro spark discharge machines are convenient to use for the cutting.

6.4 Mounting

The samples shall be embedded in resin without the gap between the resin and the samples. It is recommended that the sample is embedded in resin after it has been bonded to a rigid supporting jig when higher testing force is applied.

6.5 Surface preparation

The test surfaces shall be polished. The polished sample surface finish should be adequate enough to enable determination of the lengths of the impression diagonal and the crack. It is recommended that the test surface is buffed with the alumina or diamond powder to mirror surface as the final polishing.

The test shall be carried out on a surface which is free from the damaged layer induced by cutting and other specimen preparations.

7 Apparatus

7.1 Indentation testing machines

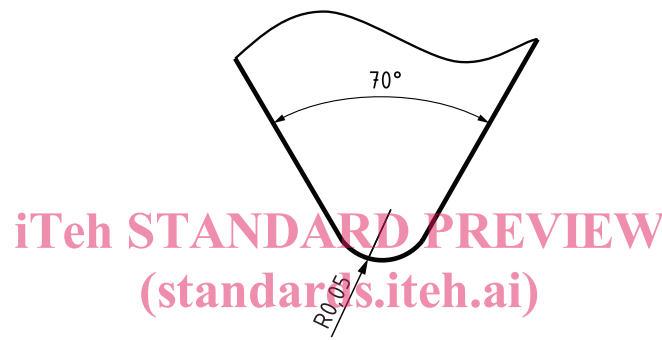
The indentation testing machine shall have the capability of applying predetermined indentation forces within the required scope and shall fulfil the requirements of ISO 6507-2.

7.2 Indenter

The indenter for use with testing machines shall be a standard Vickers indenter in the shape of a right pyramid with a square base specified in ISO 6507-2.

When no interfacial visible crack is generated using a standard Vickers indenter due to the high adhesive strength of coatings, a special conical diamond indenter with a point angle of 70° and a point radius of 0,05 mm can be used (see [Figure 5](#)).

When the special conical indenter is used, the dimensions are defined as shown in [Figure 6](#).



ISO 19207:2016
<https://standards.iteh.ai/catalog/standards/sist/1bb43ae892a4/iso-19207-2016>
Figure 5 — Shape of special conical indenter