

---

---

## Plastics — Instrumented micro-indentation test for hardness measurement

*Plastiques — Essai instrumenté de micro-indentation pour le mesurage de la dureté*

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

[ISO/TS 19278:2019](https://standards.iteh.ai/catalog/standards/sist/9b80d8c3-2802-4aaf-b419-7463b42a65a1/iso-ts-19278-2019)

<https://standards.iteh.ai/catalog/standards/sist/9b80d8c3-2802-4aaf-b419-7463b42a65a1/iso-ts-19278-2019>



**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO/TS 19278:2019

<https://standards.iteh.ai/catalog/standards/sist/9b80d8c3-2802-4aaf-b419-7463b42a65a1/iso-ts-19278-2019>



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2019

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Fax: +41 22 749 09 47  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

	Page
Foreword.....	iv
Introduction.....	v
<b>1 Scope.....</b>	<b>1</b>
<b>2 Normative references.....</b>	<b>1</b>
<b>3 Terms and definitions.....</b>	<b>1</b>
<b>4 Principle.....</b>	<b>2</b>
<b>5 Apparatus.....</b>	<b>2</b>
5.1 General.....	2
5.2 Indenter.....	2
5.3 Displacement measurement device.....	3
5.4 Loading unit and force measuring device.....	3
5.5 Periodic checks of test apparatus.....	3
<b>6 Test specimen.....</b>	<b>3</b>
<b>7 Conditioning.....</b>	<b>3</b>
<b>8 Procedure.....</b>	<b>4</b>
<b>9 Number of test specimens.....</b>	<b>5</b>
<b>10 Expression of results.....</b>	<b>5</b>
<b>11 Test report.....</b>	<b>6</b>
<b>Annex A (informative) Precision statement.....</b>	<b>8</b>
<b>Bibliography.....</b>	<b>9</b>

ITeh STANDARD PREVIEW  
 (standards.iteh.ai)  
<https://standards.iteh.ai/catalog/standards/sist/9b80d8c3-2802-4aaf-b419-7463b42a65a1/iso-ts-19278-2019>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 2, *Mechanical behaviour*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

## Introduction

This document was developed in response to a demand to define an instrumented indentation hardness test method in the micro scale for quality control of plastics materials and material selection. The test conditions are defined to ensure reproducibility and comparability of test results.

The Rockwell hardness method (ISO 2039-2) and the ball indentation method (ISO 2039-1) have been formulated for determining the indentation hardness of plastics. These test methods use different scales depending on the hardness of the material and it is difficult to compare hardness values of materials when they are measured on different scales.

The Vickers hardness test method (ISO 6507-1), used for metallic materials, is a method that does not use different scales. The Vickers hardness is calculated as the ratio of indentation load and the residual area of contact of the indenter. However, when this method is applied to plastics materials, it is difficult to measure the residual area of contact of the indenter because the edge of the indentation cannot be specified.

The instrumented indentation hardness test method (ISO 14577-1) is intended for hardness measurement in the range from nano-indentation to macro-indentation. In this method, since the contact area of the indenter is directly determined from the indentation depth, the above-mentioned problem is solved. It is therefore possible to determine the indentation hardness of the plastic materials.

In this document, in order to avoid errors due to detection of initial contact, a test force that can result in sufficient indentation depth within the range of micro-indentation is specified. For example, the range of indentation depth under this condition, which is from 10  $\mu\text{m}$  to 50  $\mu\text{m}$  in the case of the four types of materials described in this document, also corresponds to the dimension (scale) of the diagonal length range of 0,020 mm to 1,400 mm specified by the Vickers hardness test method (ISO 6507-1). In this document, the measurement time of a single condition is specified similarly to the Rockwell hardness method (ISO 2039-2).

[ISO/TS 19278:2019](https://standards.iteh.ai/catalog/standards/sist/9b80d8c3-2802-4aaf-b419-7463b42a65a1/iso-ts-19278-2019)

<https://standards.iteh.ai/catalog/standards/sist/9b80d8c3-2802-4aaf-b419-7463b42a65a1/iso-ts-19278-2019>

**iTeh STANDARD PREVIEW**  
**(standards.iteh.ai)**

ISO/TS 19278:2019

<https://standards.iteh.ai/catalog/standards/sist/9b80d8c3-2802-4aaf-b419-7463b42a65a1/iso-ts-19278-2019>

# Plastics — Instrumented micro-indentation test for hardness measurement

## 1 Scope

This document specifies a hardness test method for plastics using instrumented indentation in the micro scale with one clearly defined test condition to ensure reproducibility and comparability of test results.

The test method is selectively suitable for use with the following materials:

- moulding, extrusion and cast thermoplastic materials; rigid and semi-rigid thermoplastics sheets;
- rigid and semi-rigid thermosetting moulding materials; thermosetting sheets.

This test method could also be utilized for nanometric filled system, considering the fillers are distributed uniformly in the polymer matrix.

This test method allows dumbbell type specimen, strip type specimen, platens and specimen cut from any finished parts or products.

This test method is useful for quality control, material selection, and screening of new formulations.

NOTE This document does not aim to describe all scientific or technical aspects of microhardness testing on plastics in general.

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 291, *Plastics — Standard atmospheres for conditioning and testing*

ISO 2602, *Statistical interpretation of test results — Estimation of the mean — Confidence interval*

ISO 4287, *Geometrical Product Specifications (GPS) — Surface texture: Profile method — Terms, definitions and surface texture parameters*

ISO 14577-1, *Metallic materials — Instrumented indentation test for hardness and materials parameters — Part 1: Test method*

## 3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>


## 4 Principle

The original Berkovich indenter is forced under a specified load into the surface of the test specimen. The depth of indentation is measured under load. Indentation hardness  $H_{IT}$  is calculated from  $F_{max}$  and  $A_p$  (see 10.1).

## 5 Apparatus

### 5.1 General

The testing apparatus comprises of a rigid frame, a stage, a test specimen holder, an indenter, a loading unit, and a displacement measuring device. The apparatus is required to measure and record the applied force, the indentation depth, and the time throughout the testing cycle. The apparatus shall have the capability of compensating for the machine compliance and of utilizing the appropriate indenter area function in accordance with ISO 14577-1. The general design is as shown in Figure 1.

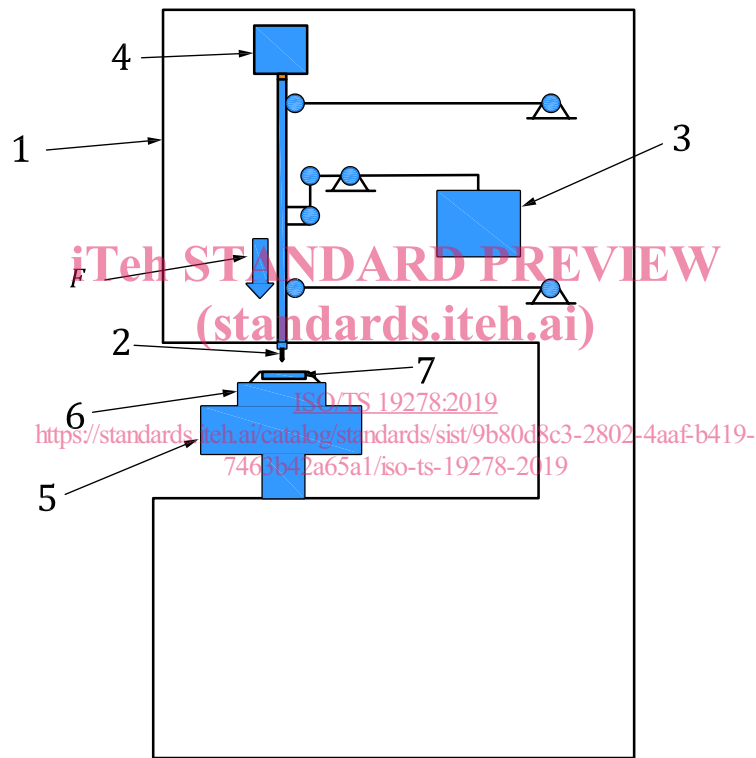

#### Key

- |   |                               |   |                      |
|---|-------------------------------|---|----------------------|
| 1 | machine frame                 | 5 | stage                |
| 2 | indenter                      | 6 | test specimen holder |
| 3 | loading unit                  | 7 | test specimen        |
| 4 | displacement measuring device |   |                      |
| F | test force                    |   |                      |

Figure 1 — Example of testing apparatus

### 5.2 Indenter

The testing apparatus shall be equipped with an original Berkovich indenter in accordance with ISO 14577-1. The indenter should be calibrated according to ISO 14577-2.



### 5.3 Displacement measurement device

The displacement measuring device measures the indentation displacement directly or measures the displacement reference with touch point of the presser foot to surface of the test specimen. The maximum permissible error of the displacement is  $\pm 1\%$  of indentation depth, when the displacement is more than  $6\ \mu\text{m}$ .

### 5.4 Loading unit and force measuring device

The loading unit applies predetermined test forces. The loading unit and the force measuring device shall satisfy the following conditions.

- a) The loading unit is able to apply 500 mN.
- b) The repeatability of the test force is  $\pm 1,5\%$ .
- c) The tolerance of the force application time is  $\pm 10\%$ .

### 5.5 Periodic checks of test apparatus

Periodic checks of the test apparatus using a control chart shall be conducted.

NOTE Some reference materials which hardness value is close to that of plastics, for example certified reference material for instrumented indentation test made from plastics or a hardness reference plate for macro Vickers hardness (preferably 30 HV, see ISO 6507-1 and ISO 6507-3 for details), can be used for this purpose.

iTeh STANDARD PREVIEW

## 6 Test specimen (standards.iteh.ai)

6.1 Test specimens should be prepared by the appropriate methods described in ISO 294-1, ISO 294-2, ISO 294-3 and ISO 20753.

<https://standards.iteh.ai/catalog/standards/sist/9b80d8c3-2802-4aaf-b419-7463b42a65a1/iso-ts-19278-2019>

6.2 The test specimen thickness shall be at least 40 times the  $h_{\text{max}}$  value.

NOTE The minimum requirement of the test specimen thickness differs owing to the test specimen hardness. For example, if the hardness of the test specimen is about  $H_{\text{IT}} 0,5/30/40/30 = 95\ \text{N/mm}^2$ , the indentation depth of  $F_{\text{max}}$  is about  $16\ \mu\text{m}$ , the minimum thickness of the test specimen is about  $640\ \mu\text{m}$ . If the hardness of the test specimen is about  $H_{\text{IT}} 0,5/30/40/30 = 225\ \text{N/mm}^2$ , the indentation depth of  $F_{\text{max}}$  is about  $11\ \mu\text{m}$ , the minimum thickness of the test specimen is about  $440\ \mu\text{m}$ .

6.3 The test specimen shall not be twisted and shall have parallel surfaces for testing.

6.4 The surface roughness  $R_a$  (as defined in ISO 4287) shall be satisfied by  $R_a \leq h_{\text{max}}/20$ .

NOTE Any curvature in the surface can influence test result.

6.5 It is important to specify the position and orientation of the test specimen, when the test specimen is prepared by machining.

6.6 The test specimen which is cut from any finished parts or products shall be prepared with the cutting size to minimize cutting effect on the test results (see 8.7).

## 7 Conditioning

Unless other environmental conditions have been agreed between the interested parties or required by the specification standard of the material, the preferred conditions are  $(23 \pm 2)\ ^\circ\text{C}$  and  $(50 \pm 10)\ \%$  relative humidity, as defined in ISO 291.