

SLOVENSKI STANDARD oSIST prEN ISO 21968:2018

01-december-2018

Nemagnetne kovinske prevleke na kovinskih in nekovinskih osnovnih materialih - Merjenje debeline nanosa prevleke - Metoda vrtinčnih tokov (ISO 21968:2005)

Non-magnetic metallic coatings on metallic and non-metallic basis materials - Measurement of coating thickness - Phase-sensitive eddy-current method (ISO/DIS 21968:2018)

Nichtmagnetische metallische Überzüge auf metallischen und nichtmetallischen Grundwerkstoffen - Messung der Schichtdicke - Phasensensitives Wirbelstromverfahren (ISO/DIS 21968:2018)

Revêtements métalliques non magnétiques sur des matériaux de base métalliques et non métalliques - Mesurage de l'épaisseur de revêtement - Méthode par courants de Foucault sensible aux variations de phase (ISO/DIS 21968:2018)

Ta slovenski standard je istoveten z: prEN ISO 21968

ICS:

25.220.40 Kovinske prevleke Metallic coatings

oSIST prEN ISO 21968:2018 en

oSIST prEN ISO 21968:2018

DRAFT INTERNATIONAL STANDARD ISO/DIS 21968

ISO/TC **107** Secretariat: **KATS**

Voting begins on: Voting terminates on:

2018-10-08 2018-12-31

Non-magnetic metallic coatings on metallic and nonmetallic basis materials — Measurement of coating thickness — Phase-sensitive eddy-current method

Revêtements métalliques non magnétiques sur des matériaux de base métalliques et non métalliques — Mesurage de l'épaisseur de revêtement — Méthode par courants de Foucault sensible aux variations de phase

ICS: 25.220.40

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

This document is circulated as received from the committee secretariat.

ISO/CEN PARALLEL PROCESSING



Reference number ISO/DIS 21968:2018(E)





COPYRIGHT PROTECTED DOCUMENT

© ISO 2018

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office CP 401 • Ch. de Blandonnet 8 CH-1214 Vernier, Geneva Phone: +41 22 749 01 11 Fax: +41 22 749 09 47 Email: copyright@iso.org Website: www.iso.org

Published in Switzerland



COPYRIGHT PROTECTED DOCUMENT

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office Ch. de Blandonnet 8 • CP 401 CH-1214 Vernier, Geneva, Switzerland Tel. + 41 22 749 01 11 Fax + 41 22 749 09 47 copyright@iso.org www.iso.org

Teh Standards in hold sandards in hold s

Con	Contents	
Forewordv		
1	Scope	1
2	Normative references	1
3	Terms and definitions	2
4	Principle of measurement	2
5	Factors affecting measurement uncertainty	5
5.1	Basic influence of the coating thickness	5
5.2	Electrical properties of the coating	
5.3	Geometry: base material thickness	
5.4	Geometry: edge effects	
5.5	Geometry: surface curvature	6
5.6	Surface roughness	6
5.7	Lift-off effect	6
5.8	Probe pressure	8
5.9	Probe tilt	
5.10	Temperature effects	8
5.11	Intermediate coatings	8
5.12	Intermediate coatings External electromagnetic fields	8
6	Calibration and adjustment of the instrument	0
o 6.1	GeneralGeneral	
6.2	Thickness reference standards	
6.3	Methods of adjustment	
	and the second s	
7	Measurement procedure and evaluation	
7.1	General	
7.2	Number of measurements and evaluation	11
8	Uncertainty of the results	11
8.1	General remarks	11
8.2	Uncertainty of the calibration of the instrument	12
8.3	Stochastic errors	
8.4	Uncertainties caused by factors summarized in Clause 5	13
8.5	Combined uncertainty, expanded uncertainty and final resultresult	14
9	Precision	1.1
9.1	General	
9.1 9.2	Repeatability (r)	
9.2	Reproducibility limit (R)	
9.3 10	Test report	
	•	
	ex A (informative) Eddy current generation in a metallic conductor	
A.1	General	
A.2	Example 1: conductive coating on a non-conductive base material	
A.3	Example 2: conductive coating on a conductive and/or magnetic base metal	
A.4	Example 3: non-conductive coating on a conductive and/or magnetic base metal	23

Annex	B (informative) Basics of the determination of the uncertainty of a measurement of	
	the used measurement method corresponding to ISO/IEC Guide 98-3	. 25
B.1	General	. 25
B.2	Type A	. 25
B.3	Type B	. 26
Annex	C (informative) Basic performance requirements for coating thickness gauges which	
	are based on the phase-sensitive eddy current method described in this document	. 27
C.1	Technical specification	
C.2	Check/verification of instruments and probes	
C.2.1	Prior to the supply, after repair and at regular intervals after use	
C.2.2	Performed on site	
Annov	D (informative) Examples for the experimental estimation of factors affecting the	
Aimex	measurement accuracy	20
D.1	General	
D.1 D.2	Edge effect	
D.2 D.3	Base metal thickness	
D.3 D.4	Surface curvature	
D.4 D.5	Conductivity and permeability of the base metal	
D.6	Lift-off-height	
	Litt-oil-neight	၁၁
Annex	E (informative) Table of the student factor	. 35
Annex	r F (informative) Example of uncertainty estimation (see Clause 8)8	. 36
F.1	Sample details	. 36
F.2	Steps	. 36
F.2.1	the example sample is measured by the following steps	. 36
F.2.2	All other possible factors affecting the measurement accuracy are considered to be	
	negligible in this example (edge effect, base metal thickness, curvature, temperature	
	drift, etc.)	. 38
F.2.3	Further conclusions: it is obvious that the resulting uncertainty is limited by the	
	largest uncertainty component, in this case the uncompensated lift-off effect (see	
	5.7). Therefore, an increase of the number of repeated measurements would reduce	
	$u_{\rm sto}$, however, the combined uncertainty would not be strongly affected in this way.	
	However the compensation of the lift-off effect would reduce the combined	
	uncertainty to	. 38
Annex	G (informative) Details on precision	. 39
G.1	General notes on the round-robin test	
G.2	Samples	
G.3	Film thickness gauges	
G.4	Calibration	
G.5	Number of measurements	
G.6	Evaluation	
Riblio	graphy	. 41

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html.

The committee responsible for this document is ISO/107, *Metallic and other inorganic coatings*.

This second edition cancels and replaces the firstedition (ISO 21968:2005), which has been technically revised with changes as follows.

- adaption of this document to the current requirements of ISO/IEC Guide 98 3 (GUM:1995);
- inclusion of hints, practical examples and simple estimations of the measurement uncertainty for most important factors;
- inclusion of a repeatability and reproducibility values for typical applications of this method;
- expansion of the Annex with further applications, experimental estimations of factors affecting the accuracy;
- editioriel amendments according to the current ISO directives part 2.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

oSIST prEN ISO 21968:2018

Tell's And Ards tell all and the files of the standard of the

Non-magnetic metallic coatings on metallic and non-metallic basis materials — Measurement of coating thickness — Phase-sensitive eddy-current method

1 Scope

This document specifies a method for using phase sensitive eddy current instruments for non-destructive measurements of the thickness of non-magnetic metallic coatings on metallic and non-metallic basis materials such as:

- 1. zinc, cadmium, copper, tin or chromium on steel;
- 2. Copper or silver on composite materials.

The phase sensitive method can be applied without thickness errors to smaller surface areas and to stronger surface curvatures than the amplitude sensitive eddy current method specified in ISO 2360, and is less affected by the magnetic properties of the basis material. However, the phase sensitive method is more affected by the electrical properties of the coating materials.

In this document the term "coating" is used for materials such as, for example, paints and varnishes, electroplated coatings, enamel coatings, plastic coatings, claddings and powder coatings.

This method is particularly applicable to measurements of the thickness of metallic coatings. These coatings can be non-magnetic metallic coatings on non-conductive, conductive or magnetic base materials, but also magnetic coatings on non-conductive or conductive base materials.

When measuring metallic coatings on metallic basis material, the product of conductivity and permeability (σ, μ) of one of the materials should be at least a factor of 2 times the product of conductivity and permeability for the other material. Non-ferromagnetic materials have a relative permeability of 1.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 2064, Metallic and other inorganic coatings — Definitions and conventions concerning the measurement of thickness

ISO 4618, Paints and varnishes — Terms and definitions

ISO 5725-1:1994, Accuracy (trueness and precision) of measurement methods and results — Part 1: General principles and definitions

ISO/IEC Guide 98-3, Uncertainty of measurement — Part 3: Guide to the expression of uncertainty in measurement (GUM:1995)

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 2064 and ISO 4618 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at http://www.electropedia.org/
- ISO Online browsing platform: available at http://www.iso.org/obp

3.1

adjustment of a measuring system

set of operations carried out on a measuring system so that it provides prescribed indications corresponding to given values of a quantity to be measured

Note 1 to entry: Adjustment of a measuring system can include zero adjustment, offset adjustment, and span adjustment (sometimes called gain adjustment).

Note 2 to entry: Adjustment of a measuring system should not be confused with calibration, which is a prerequisite for adjustment.

Note 3 to entry: After an adjustment of a measuring system, the measuring system must usually be recalibrated.

Note 4 to entry: Colloquially the term "calibration" is frequently, but falsely, used instead of the term "adjustment". In the same way, the terms "verification" and "checking" are often used instead of the correct term "calibration".

[SOURCE: ISO/IEC Guide 99:2007, 3.11 (also known as "VIM"), modified – Note 4 to entry has been added.]

3.2

calibration

operation that, under specified conditions, in a first step, establishes a relation between the quantity values with measurement uncertainties provided by measurement standards and corresponding indications with associated measurement uncertainties and, in a second step, uses this information to establish a relation for obtaining a measurement result from an indication

Note 1 to entry: A calibration may be expressed by a statement, calibration function, calibration diagram, calibration curve, or calibration table. In some cases, it may consist of an additive or multiplicative correction of the indication with associated measurement uncertainty.

Note 2 to entry: Calibration should not be confused with adjustment of a measuring system, often mistakenly called "self-calibration", nor with verification of calibration.

Note 3 to entry: Often, the first step alone in the above definition is perceived as being calibration.

[SOURCE: ISO/IEC Guide 99:2007, 2.39 (also known as "VIM")]

4 Principle of measurement


Phase-sensitive eddy current instruments work on the principle that a high frequency electromagnetic field generated by the probe system of the instrument will produce eddy currents in the coating on which the probe is placed and in the base material beneath the coating in case this base material is conductive (see Figure 1). These induced currents cause a change of the electromagnetic field


surrounding the probe coil system and therefore result in a change of the amplitude and the phase angle of the probe coil impedance. The induced eddy current density is a function of the coating thickness, the conductivity of the coating material, the used frequency of the probe system and the base metal conductivity. If the thickness of a coating of constant conductivity is increased for a given frequency the impedance vector describes a so-called local function of the thickness in the impedance plane (see Figure 2). Each point of this local curve connects a phase angle of the impedance vector with the respective coating thickness. Consequently, this impedance angle (phase shift) can be used as a measure of the thickness of the coating on the conductor by means of a calibration with reference standards (see also Annex A).

In order to measure a change of the coil impedance phase angle the test coil is usually part of a coil system and coupled with the exciting coil on one ferrite core like in a transformer (see Figure 1). The changes of phase angle and amplitude due to the impact of the induced eddy currents can be measured e.g. using a lock in amplifier. These values are usually pre-processed by digital means and the resulting thickness is then calculated and displayed.

The probe and measuring system/display may be integrated into a single instrument.

NOTE 1 Annex C describes the basic performance requirements of the equipment.




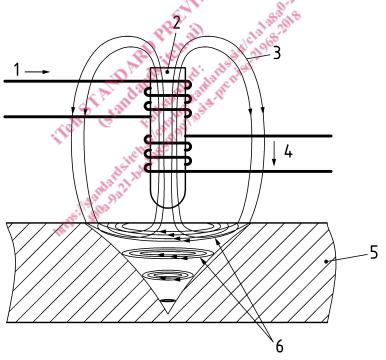

Key

- 1 exiciting current
- 2 ferrit core of probe
- 3 high frequency alternating magnetic field
- 4 measured signal U=f(t(φ))
- 5 induced eddy currents
- 6 base material (conductive)

Figure 1 — Phase-sensitive eddy current method

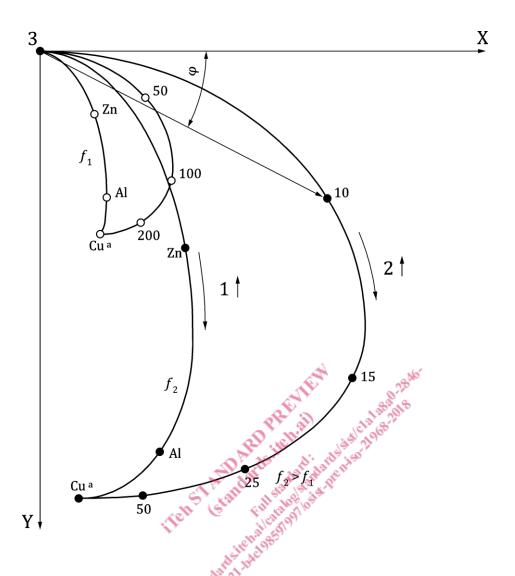

Key

- $-\infty$ thickness local curve of Cu for the frequence f_1
- $-\bullet$ thickness local curve of Cu for the frequence f_2
- 1 conductivity 2 thickness 3 coil air (unaffected)
- X real part
- Y imaginary part

Figure 2 — thickness local curve of Cu in the normalized impedance plane for two frequencies $\mathbf{f_1}$ and $\mathbf{f_2}$

For each instrument there is a maximum measurable thickness of the coating.

Since this thickness range depends on both the applied frequency of the probe system and the electrical conductivity of the coating, the maximum thickness should be determined experimentally, unless otherwise specified by the manufacturer.

An explanation of eddy current generation and the calculation of the maximum measurable coating thickness, t_{max} , is given in Annex A.