



SLOVENSKI STANDARD
oSIST prEN ISO 505:2017
01-julij-2017

Naprave za kontinuirni transport - Trakovi tračnih transporterjev - Postopek določanja odpornosti proti vzdolžnemu trganju tekstilnih trakov tračnih transporterjev (ISO/FDIS 505:2017)

Conveyor belts - Method for the determination of the tear propagation resistance of textile conveyor belts (ISO/FDIS 505:2017)

Fördergurte - Verfahren zur Bestimmung der Weiterreißfestigkeit von Textil-Fördergurten (ISO/FDIS 505:2017)

Courroies transporteuses - Méthode de détermination de la résistance à la propagation d'une déchirure dans les courroies transporteuses à carcasse textile (ISO/FDIS 505:2017)

Ta slovenski standard je istoveten z: prEN ISO 505

ICS:

53.040.20 Deli za transporterje Components for conveyors

oSIST prEN ISO 505:2017

en,fr,de

FINAL
DRAFTINTERNATIONAL
STANDARDISO/FDIS
505

ISO/TC 41/SC 3

Secretariat: JISC

Voting begins on:
2017-05-18Voting terminates on:
2017-08-10

Conveyor belts — Method for the determination of the tear propagation resistance of textile conveyor belts

Courroies transporteuses — Méthode de détermination de la résistance à la propagation d'une déchirure dans les courroies transporteuses à carcasse textile

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 505:2018

<https://standards.iteh.ai/catalog/standards/sist/d39c4944-c26e-4445-9233-b8c9810d873a/sist-en-iso-505-2018>

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

ISO/CEN PARALLEL PROCESSING



Reference number
ISO/FDIS 505:2017(E)

© ISO 2017

iTeh STANDARD PREVIEW (standards.iteh.ai)

SIST EN ISO 505:2018

<https://standards.iteh.ai/catalog/standards/sist/d39c4944-c26e-4445-9233-b8c9810d873a/sist-en-iso-505-2018>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2017, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Apparatus	1
6 Test pieces	2
6.1 Method of sampling.....	2
6.2 Shape and dimensions.....	2
6.3 Number.....	2
6.4 Preparation.....	2
7 Method of test	4
7.1 Conditioning of test pieces.....	4
7.2 Test conditions.....	4
7.3 Procedure.....	4
7.4 Expression of results.....	5
7.5 Test report.....	5

iTeh STANDARD PREVIEW
(standards.iteh.ai)

SIST EN ISO 505:2018

<https://standards.iteh.ai/catalog/standards/sist/d39c4944-c26e-4445-9233-b8c9810d873a/sist-en-iso-505-2018>

ISO/FDIS 505:2017(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html.

This document was prepared by ISO/TC 41, *Pulleys and belts (including veebelts)*, Subcommittee SC 3, *Conveyor belts*.

This fourth edition cancels and replaces the third edition (ISO 505:1999), which has been technically revised.

The main changes compared to the previous edition are as follows:

- the Normative references have been updated.

Conveyor belts — Method for the determination of the tear propagation resistance of textile conveyor belts

1 Scope

This document specifies a method of test for the measurement of the propagation resistance of an initial tear in textile conveyor belts, either in full thickness or of the carcass only.

This test is intended for application to textile belts in installations where there is a risk of longitudinal tearing.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 6133, *Rubber and plastics — Analysis of multi-peak traces obtained in determinations of tear strength and adhesion strength*

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <http://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

4 Principle

The test consists in measuring, by means of tensile testing at a given speed, the force necessary to propagate an initial tear made in a test piece.

5 Apparatus

The apparatus consists of a dynamometric tensile testing machine with the following essential characteristics:

- a) the machine shall be chosen so that the forces to be measured come within the upper 90 % range of its full rated capacity;
- b) the speed of separation of the jaws shall be capable of being adjusted to (50 ± 10) mm/min;
- c) the free distance between the jaws shall be capable of being adjusted to at least 300 mm.

The machine shall be provided with a device for the graphical recording of the force necessary to continue tearing the test piece.

ISO/FDIS 505:2017(E)

6 Test pieces

6.1 Method of sampling

Test pieces shall be taken from the sample in the longitudinal direction of the belt and at a minimum distance of 50 mm from the edges of the belt.

6.2 Shape and dimensions

Shape: rectangular.

Length: 300 mm.

Width: (100 ± 1) mm.

Thickness: Full belt thickness or without covers.

If it is found that weft threads are pulled out of the test piece instead of breaking, the width of the test piece should be increased to 300 mm.

6.3 Number


Two test pieces shall be used: one in sense A and one in sense B (see [Figure 4](#)).

6.4 Preparation

Where the test is to be conducted without covers, the covers of the test pieces shall be removed by stripping or by buffing.

If there is a breaker ply, strip the corresponding covers without cutting the breaker ply over a width of 20 mm only, i.e. 10 mm on each side of the longitudinal axis of the test piece with the exception of the zone held in the jaws of the machine (see [Figure 1](#)).

Dimensions in millimetres

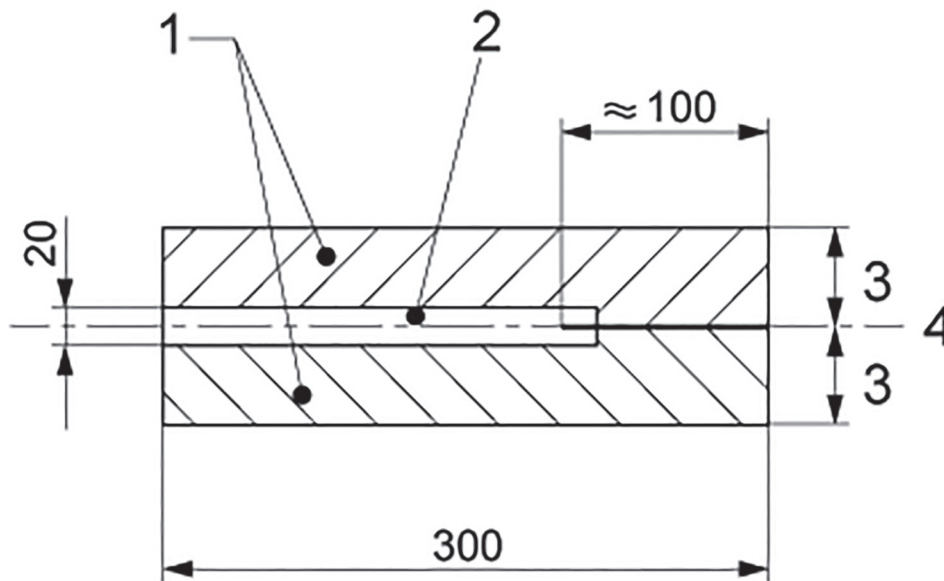


Key

- 1 with covers
- 2 covers removed
- 3 50 or 150 (see 6.2)
- 4 cut line

Figure 1 — Test pieces with breaker

Cut the test pieces from the middle of one of their ends over a length of about 100 mm parallel to the length (see Figure 2).

Dimensions in millimetres

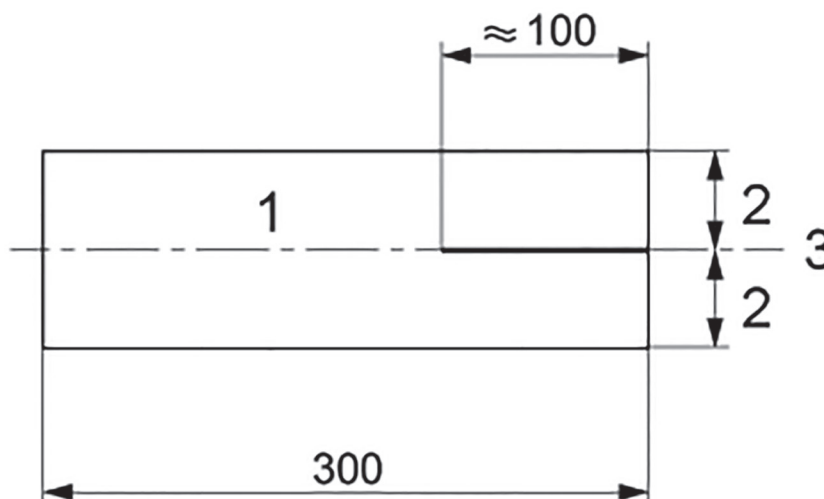

Key


- 1 without covers
- 2 50 or 150 (see 6.2)
- 3 cut line

Figure 2 — Test pieces without breaker

ISO/FDIS 505:2017(E)

If necessary, the width of the test piece (cut-edge) may be adjusted to the gripping width of the jaws by tapering the edges symmetrically on a length at most the same as that of the cut (see [Figure 3](#)), with the width at the end of the cut part as great as the width of the jaws permits.

Dimensions in millimetres

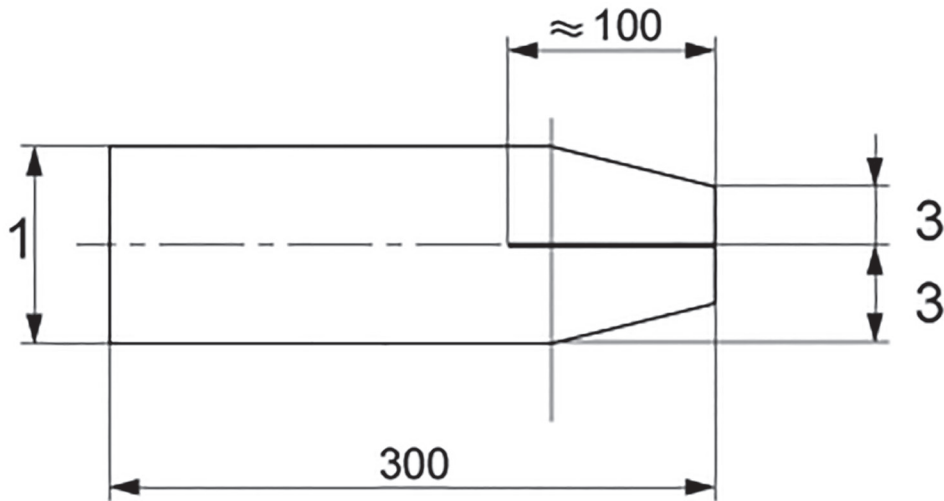

Key

- 1 300 or 100 (see [6.2](#))
- 2 cut line
- 3 see [6.4](#)

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Figure 3 — Tapered test piece

SIST EN ISO 505:2018

<https://standards.iteh.ai/catalog/standards/sist/d39c4944-c26e-4445-9233-b8c9810d873a/sist-en-iso-505-2018>

7 Method of test

7.1 Conditioning of test pieces

The tests shall start not less than 24 h after manufacturing. This time includes 8 h for conditioning. The conditioning atmosphere shall be one of the following:

- temperature (20 ± 2) °C with (65 ± 5) % relative humidity, or,
- temperature (23 ± 2) °C and (50 ± 5) % relative humidity, or,
- temperature (27 ± 2) °C and (65 ± 5) % relative humidity.

The tests shall be conducted in the same atmosphere as used for conditioning.

The atmosphere at which the test pieces were conditioned and tested shall be reported in the test report.

In the event of dispute, the period of conditioning shall be 72 h.

7.2 Test conditions

The test conditions with regard to temperature and humidity shall be those adopted in [7.1](#).

7.3 Procedure

Mount the two cut ends of the test piece in the jaws of the tensile testing machine either in sense A or in sense B (see [Figure 4](#)), so that the inner edges of the cut are situated at the centre of each jaw.