
**Paints and varnishes — Wettability —
Part 2:
Determination of the surface free
energy of solid surfaces by measuring
the contact angle**

iTeh STANDARD PREVIEW
*Peintures et vernis — Mouillabilité —
Partie 2: Détermination de l'énergie libre de surface des surfaces
solides par la mesure de l'angle de contact*
(standards.iteh.ai)

ISO 19403-2:2017

<https://standards.iteh.ai/catalog/standards/sist/e893ab01-8e02-4544-9444-50602335b69f/iso-19403-2-2017>



iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 19403-2:2017

<https://standards.iteh.ai/catalog/standards/sist/e893ab01-8e02-4544-9444-50602335b69f/iso-19403-2-2017>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2017, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

	Page
Foreword.....	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Apparatus and materials	2
6 Sampling	3
7 Procedure	4
7.1 General for measuring on the horizontal drop.....	4
7.1.1 Setting up the contact angle measuring system.....	4
7.1.2 Test conditions.....	4
7.1.3 Conditioning of the test panels.....	4
7.2 Measurement.....	4
7.2.1 General.....	4
7.2.2 Static method.....	4
7.2.3 Dynamic method (progressive contact angle).....	5
7.2.4 Determination of the contact angle.....	6
8 Evaluation	6
8.1 General.....	6
8.2 Owens-Wendt-Rabel-Kaelble method (OWRK method).....	6
8.3 Wu method.....	7
9 Precision	8
9.1 General.....	8
9.2 Repeatability limit, r	8
9.3 Reproducibility limit, R	8
9.4 Calculation in accordance with Owens-Wendt-Rabel-Kaelble method (OWRK method).....	8
10 Test report	9
Annex A (informative) Notes on measuring practice	10
Bibliography	14

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html. (standards.iteh.ai)

This document was prepared by Technical Committee ISO/TC 35, *Paints and varnishes*, Subcommittee SC 9, *General test methods for paints and varnishes*. ISO 19403-2:2017

<https://standards.iteh.ai/catalog/standards/sist/e893ab01-8e02-4544-9444-506b23751697/iso-19403-2-2017>

A list of all parts in the ISO 19403 series can be found on the ISO website.

Paints and varnishes — Wettability —

Part 2:

Determination of the surface free energy of solid surfaces by measuring the contact angle

1 Scope

This document specifies a test method to measure the contact angle for the determination of the surface free energy of a solid surface. The method can be applied for the characterization of substrates and coatings.

NOTE 1 For the determination of the surface free energy of polymers and coatings, either the method in accordance with Owens, Wendt, Rabel and Kaelble or the method in accordance with Wu is used preferably.

NOTE 2 The morphological and chemical homogeneity have an influence on the measuring results.

NOTE 3 The procedures indicated in this document are based on the state-of-the-art employing the drop projection method in penumbral shadow. Other methods are not excluded.

NOTE 4 Measuring the contact angle on powders is not part of this document. For further information, see the bibliography.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

2 Normative references

ISO 19403-2:2017

<https://standards.iteh.ai/catalog/standards/sist/e893ab01-8e02-4544-9444-351013510135>

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 4618, *Paints and varnishes — Terms and definitions*

ISO 19403-1, *Paints and varnishes — Wettability — Part 1: Terminology and general principles*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 4618 and ISO 19403-1 apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

4 Principle


A minimum of three drops of at least two test liquids are dosed onto the flat surface of a test specimen. For every drop, the contact angle is measured. From the averaged contact angles of every liquid, their surface tensions, as well as their polar and dispersive fractions, the surface free energy of the solid is calculated by means of an appropriate model, divided into the polar and dispersive fractions.

5 Apparatus and materials

Ordinary laboratory apparatus, together with the following.

5.1 Contact angle measuring system.

Any state-of-the-art contact angle measuring device, preferably systems with digital image capture and analysis for measuring the contact angle. [Figure 1](#) shows a schematic example of a contact angle measuring system.

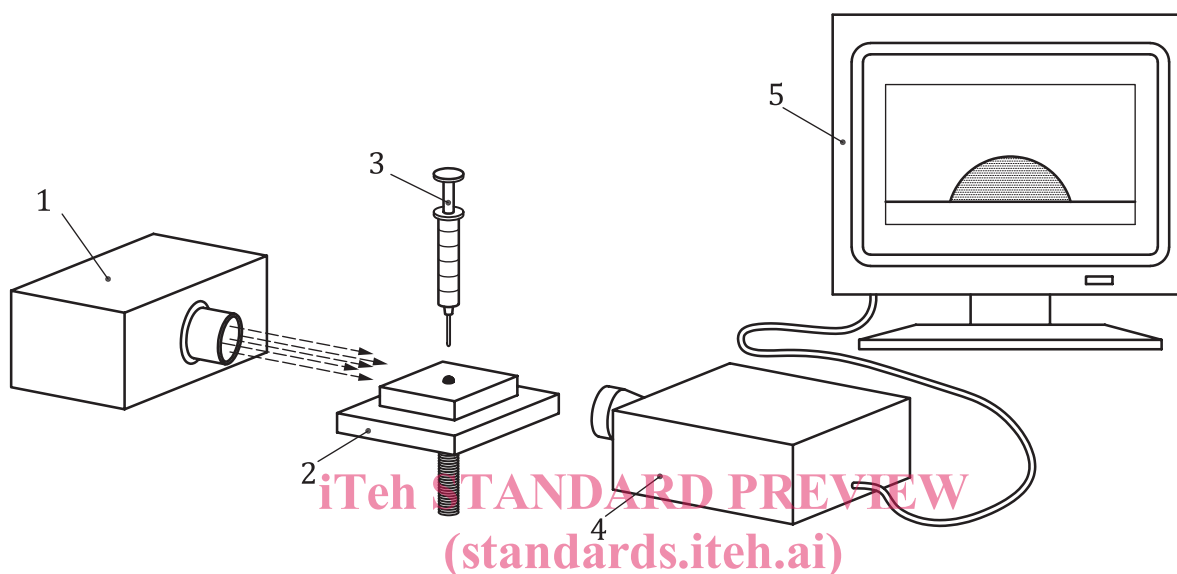

Key

- 1 light source
- 2 specimen holder
- 3 graduated micro syringe
- 4 optical system
- 5 screen

ISO 19403-2:2017
<https://standards.iteh.ai/catalog/standards/sist/e893ab01-8e02-4544-9444-50602335b69f/iso-19403-2-2017>

NOTE 1 The image capturing system is oriented in a way that the optimal image resolution ratio (ratio of width and height) can be used.

NOTE 2 The device used can differ from the schematic diagram in regard to light path and the arrangement of the components.

Figure 1 — Schematic diagram of a contact angle measuring system

5.2 Dosing unit.

The dosing unit makes it possible to precisely apply drops in the range of microlitres to the surface.

5.3 Test liquids.

At least two of the test liquids suggested in [Table 1](#). The test liquids shall have at least “purity grade” for analysis. Water shall have a surface tension of at least 71,5 mN/m.

It is recommended to test the suitability of the liquids used in accordance with ISO 19403-3 or EN 14370 prior to measuring their surface tensions. For guidance, the values from the literature for the surface tension, σ_l , are indicated in [Table 1](#). It is also possible to use an individually measured value of the surface tension as reference value. According to experience, the measured value should not deviate more than $\pm 2\%$ from the value from the literature or the individually determined value.

The test liquids shall not physically or chemically affect the surface. The test liquids have a maximum of different polar and dispersive fractions of surface tension.

For at least one of the test liquids used, the polar fractions shall be larger than 0 mN/m (see [Table 1](#)).

In case only two test liquids are used, water and di-iodomethane are recommended. In case three liquids are used, ethylene glycol should be used additionally.

In case of high viscous test liquids like glycerol and ethylene glycol, a needle with higher inner diameter could be necessary to achieve the recommended dosing rate.

NOTE The values in [Table 1](#) refer to 25 °C measuring temperature. For measuring under standard atmosphere (see [7.1.2](#)), no significant deviations can be assumed.

Table 1 — Suggested test liquids

Test liquid	Surface tension	Dispersive fraction	Polar fraction	Source
	σ_l mN/m	σ_l^d mN/m	σ_l^p mN/m	
Water	72,8	21,8	51,0	Reference [4]
Di-iodomethane ^a	50,8	50,8	0,0	Reference [4]
1,2-ethanediol (ethylene glycol)	47,7	30,9	16,8	Reference [4]
1,2,3-propanetriol (glycerol)	63,4	37,0	26,4	Reference [4]
Hexadecane	27,6	27,6	0,0	Reference [4]
1-bromo-naphthalene ^b	44,6	44,6	0,0	Reference [4]
Benzyl alcohol	38,9	29,0	9,9	Reference [5]
Decalin (isomer mixture)	30,6	30,6	0,0	Reference [4]
cis-Decalin	32,2	32,2	0,0	Reference [2]
trans-Decalin	29,9	29,9	0,0	Reference [2]

^a Di-iodomethane is relative instable, yellowing after short time by splitting-off iodine.

Di-iodomethane swells and dissolves a lot of plastics and of organic coatings.

Di-iodomethane reacts with common metals (e.g. magnesium).

^b 1-bromo-naphthalene reacts with common metals (e.g. magnesium).

1-bromo-naphthalene tends to swelling and dissolving of high-molecular compounds.

6 Sampling

Take a representative specimen of the substrate to be tested. The specimens shall not be contaminated before measuring.

Preferably, the specimen should have the minimum size of 10 cm × 10 cm.

See also [Annex A](#).

7 Procedure

7.1 General for measuring on the horizontal drop

7.1.1 Setting up the contact angle measuring system

Choose the location of the contact angle measuring system so that it is not exposed to

- vibrations,
- intense air flows (e.g. caused by air conditioning), and
- intense exposure to light from outside (e.g. windows, bright lighting).

Align the contact angle measuring system horizontally.

7.1.2 Test conditions

Carry out the test at (23 ± 2) °C and a relative humidity of (50 ± 5) % (see ISO 3270) and make sure that all test media have this temperature.

7.1.3 Conditioning of the test panels

Condition the test panels at a temperature of (23 ± 2) °C and a relative humidity of (50 ± 5) % for a minimum of 16 h prior to testing. Carry out the test immediately after conditioning.

7.2 Measurement

7.2.1 General

Place a preferably flat test specimen of the surface to be measured on the sample holder. Adjust the sample holder so that the surface of the test specimen is located in the lower half of the image and that it is horizontally aligned.

Fill the dosing system with the chosen liquid. Pay attention to fill without contamination or bubbles.

Set up an image representation that is sufficient in regard to brightness and contrast (mind the specifications given by the manufacturer).

NOTE 1 If possible, set the light source of the contact angle measuring device so that the grey values within the drop close to the phase interface do not exceed the value 40 (referring to 256 grey value grades) and amount to a minimum of 170 on the outside of the drop.

NOTE 2 It can be reasonable to test the modes of operation of the optical components by means of two-dimensional images of drops. Such reference images are commercially available.


Move the needle to the upper margin of the image and bring into focus. Set up the zoom of the contact angle measuring device so that the width of the contour of the drop takes up two thirds of the width of the image.

7.2.2 Static method

Position the dosing needle approximately 3 mm to 6 mm above the surface of the test specimen. Dose the drop so that the volume of the drop is between 2 µl and 6 µl, depending on the chosen liquid (for diiodomethane between 1 µl and 3 µl).

Apply one drop of the test liquid to the surface (see [Figure 2](#)).

NOTE 1 The contact between the drop and the solid surface can be achieved by putting down by means of the needle or by picking up by means of the specimen table.

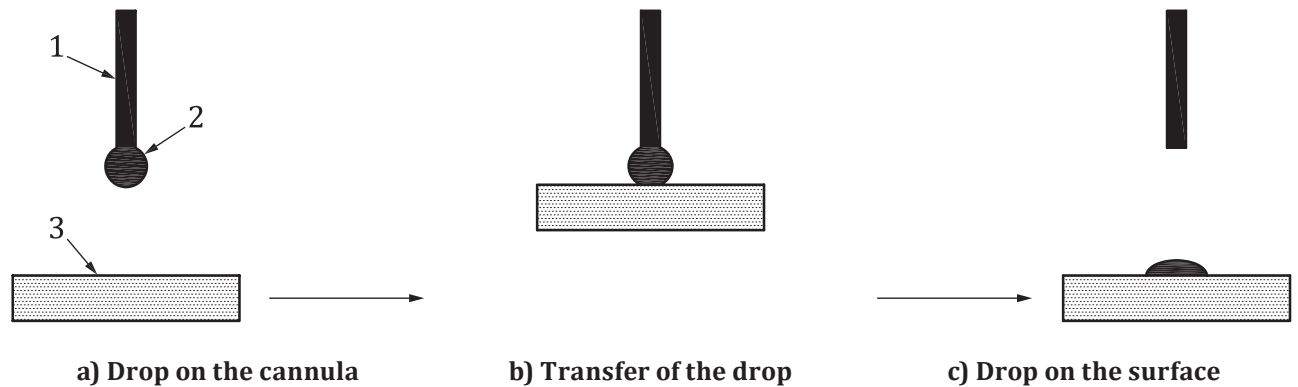**Key**

- 1 cannula
- 2 test liquid
- 3 surface of test specimen

Figure 2 — Putting down or picking up the drop

Align the baseline so that it runs through the three-phase points of the drop.

NOTE 2 A top-view angle can be set to help find the three-phase points.

Start measuring the contact angle immediately after finishing dosing. Prior to and during measuring, no mutual transformation of materials between the test liquid and the surface should occur.

7.2.3 Dynamic method (progressive contact angle)

Choose the distance between the dosing needle and the surface so that the influence on the expected contour of the drop is as slight as possible.

NOTE 1 As a first guidance for the distance between the needle and the surface of the test specimen, the one-and-a-half-times diameter of the needle can be used.

Especially for low contact angles, minimize the pull-up of liquid on the needle, if necessary, by using a poorly wettable material of the needle.

Choose the dosing speed as slow as possible so that the contact angle of the drop is as close to the thermodynamic equilibrium contact angle as possible.

NOTE 2 Typical dosing rates are in the range of 10 µl/min.

NOTE 3 It is common to start measuring only after a dosing of 3 µl minimal volume.

NOTE 4 Due to the limited image section, it is not ideal to measure contact angles below 10° by means of the dynamic method.

Align the baseline so that it runs through the three-phase points of the drop.

NOTE 5 A slight top-view angle of the camera to the horizontal can be set to help find the three-phase points. The top-view angle causes an image error of the drop projection. This may have an influence on the measuring result of the contact angle and can be corrected.

Start measuring the contact angle immediately after dosing the minimal volume. Record the measuring values as function of time. Prior to and during measuring, no mutual transformation of materials between the test liquid and the surface shall occur.

NOTE 6 In comparison to the measuring method of the static contact angle, interfering transformations of material often occur less in regard to the dynamic contact angle.

7.2.4 Determination of the contact angle

Determine the contact angle by means of the numerical method, which describes the contour of the drop best.

Depending on how the individual drops of liquid perform on different solid surfaces, different methods for the determination of the contact angle shall be used [e.g. circle equation for contact angles below 20°, conic section equation for contact angles between 20° and 110°, polynom equation or Young-Laplace equation for contact angles above 110° (see notes in [Annex A](#))]. For the dynamic method, the recommendations given by the manufacturer should be noted; normally, the polynom method is of advantage.

Measure on a minimum of three different measuring points on the test specimen in order to obtain sufficient information in regard to the homogeneity of a test specimen. Previously wetted positions shall not be used. Arguable readings which may be caused by dust, contaminations, etc. shall not be included in the calculation of the mean value.

Repeat the measuring with at least one more liquid, which was selected in accordance with the criteria indicated in [5.3](#).

8 Evaluation

8.1 General

The value of the contact angle for every liquid is calculated as arithmetic mean value of the measuring values.

iTech STANDARD PREVIEW
(standards.itech.ai)

For the determination of the surface free energy, the standard deviation for the static method should not be more than 3° and for the dynamic method not more than 5°.

In case the standard deviation is more than 5° for the dynamic method, the individual measuring values shall be checked. In order to improve the reliability, the mean value can be calculated for smaller periods.

For the calculation of the surface free energy, the Owens-Wendt-Rabel-Kaelble method is used preferably. For low-energy surfaces, the calculation in accordance with Wu can be necessary in regard to the range of a surface free energy of (20 ± 2) mJ/m² or lower.

It is recommended for both methods to obtain the standard deviation of the surface free energy and their components in accordance with the Gauß error propagation (see References [7] and [8]). It is recommended to obtain the error in measurement of σ_1^d in accordance with the Gauß error propagation (see References [7] and [8]).

8.2 Owens-Wendt-Rabel-Kaelble method (OWRK method)

For evaluation, the polar and dispersive fractions of the test liquids are used (see [Table 1](#)). For the calculation of the surface free energy, [Formula \(1\)](#):

$$\frac{(1 + \cos \theta) \cdot \sigma_1}{2\sqrt{\sigma_1^d}} \tag{1}$$

is plotted for every individual test liquid against [Formula \(2\)](#):

$$\sqrt{\frac{\sigma_1^p}{\sigma_1^d}} \tag{2}$$

where

θ is the mean value of the measured contact angle for the respective liquid;

σ_1 is the surface tension of the respective liquid;

σ_1^p and σ_1^d are the polar and dispersive fractions of the surface tension.

The values for $\sqrt{\frac{\sigma_1^p}{\sigma_1^d}}$ ($= x$) and $\frac{\sigma_1}{2\sqrt{\sigma_1^d}}$ [$= y/(1+\cos\theta)$] can be taken from [Table 2](#).

Table 2 — Calculated values for insertion into the linear equation

Liquid	$\sqrt{\frac{\sigma_1^p}{\sigma_1^d}} = x$	$\frac{\sigma_1}{2\sqrt{\sigma_1^d}} = y/(1 + \cos \theta)$ mN/m
Water	1,529 5	7,796 0
Di-iodomethane	0,000 0	3,563 7
1,2-ethanediol (ethylene glycol)	0,737 4	4,290 5
1,2,3-propanetriol (glycerol)	0,844 7	5,211 4
Hexadecane	0,000 0	2,626 8
1-bromo-naphthalene	0,000 0	3,339 2
Benzyl alcohol	0,584 3	3,611 8
Decalin (isomer mixture)	0,000 0	2,765 9
cis-Decalin	0,000 0	2,837 3
trans-Decalin	0,000 0	2,734 0

The value from the middle column is inserted for x . The value from the right column is multiplied with the value of $(1 + \cos\theta)$ for the respective liquid and the result is inserted for y . Subsequently, a linear regression is done in order to obtain the gradient m and the ordinate section b of the straight line. From the square of the gradient, the polar fraction of the free surface energy of the solid σ_s^p is calculated and from the square of the ordinate section b , the disperse fraction σ_s^d . From the sum of both fractions, the surface energy of the solid, σ_s , is calculated.

NOTE Alternatively, the statistics methods offered by the manufacturers of the devices can be used.

8.3 Wu method

The polar and dispersive fractions of the surface free energy are numerically obtained by means of the nonlinear regression of [Formula \(3\)](#):

$$\sigma_1 (1 + \cos \theta) = 4 \left(\frac{\sigma_s^d \cdot \sigma_1^d}{\sigma_s^d + \sigma_1^d} + \frac{\sigma_s^p \cdot \sigma_1^p}{\sigma_s^p + \sigma_1^p} \right) \quad (3)$$

NOTE 1 Preferably, an error square minimization in accordance with Gauß is used for the numerical calculation (see Reference [\[6\]](#)).