



Designation: D1720-96 (Reapproved 2000) Designation: D 1720 - 03 (Reapproved 2008)

Standard Test Method for Dilution Ratio of Active Solvents in Cellulose Nitrate Solutions¹

This standard is issued under the fixed designation D 1720; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the Department of Defense.

1. Scope

1.1 This test method covers the determination of the volume ratio of hydrocarbon diluent to active solvent required to cause persistent heterogeneity (precipitation) in a solution of cellulose nitrate.

1.2

1.2 The values stated in SI units are to be regarded as standard. No other units of measurement are included in this standard.

1.3 The following applies to all specified limits in this standard; for purposes of determining conformance with this standard, an observed value or a calculated value shall be rounded off "to the nearest unit" in the last right-hand digit used in expressing the specification limit, in accordance with the rounding-off method of Practice E 29.

1.4 This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use. For specific hazard statements, see Section 6.

1.5 For hazard information and guidance, see the supplier's Material Safety Data Sheet.

2. Referenced Documents

2.1 ASTM Standards:²

D 301 Test Methods for Soluble Cellulose Nitrate

D 841 Specification for Nitration Grade Toluene

D 4615 Specification for *n*-Butyl Acetate (All Grades)³ Specification for *n*-Butyl Acetate (All Grades)

E 29 Practice for Using Significant Digits in Test Data to Determine Conformance with Specifications

3. Terminology

3.1 Definitions of Terms Specific to This Standard:

3.1.1 *dilution ratio, n*—the maximum number of unit volumes of a diluent that can be added to a unit volume of solvent to cause the first persistent heterogeneity (precipitation) in the solution at a concentration of 8 g cellulose nitrate per 100 mL of combined solvent plus diluent and at a temperature of $25 \pm 3^\circ\text{C}$.

NOTE 1—The dilution ratio decreases as the cellulose nitrate concentration at the end point increases. It is, therefore, necessary to set an arbitrary concentration of cellulose nitrate as part of the dilution ratio term. For this purpose 8.0 g of cellulose nitrate per 100 mL of solvent plus diluent has been adopted.

4. Significance and Use

4.1 By use of standard or reference grade materials for any two of the three components, namely, oxygenated solvent, diluent, or cellulose nitrate, the effect of different batches or different types of the third component can be determined.

4.2 This test method is applicable for the determination of the following:

4.2.1 The dilution ratio of toluene as the standard diluent to an oxygenated solvent under test, using as the solute standard cellulose nitrate as defined in 5.2.

4.2.2 The dilution ratio of a hydrocarbon diluent under test to *n*-butyl acetate as the standard solvent, using as a solute standard cellulose nitrate as defined in 5.2.

¹ This test method is under the jurisdiction of ASTM Committee D01 on Paint and Related Coatings, Materials, and Applications and is the direct responsibility of Subcommittee D01.35 on Solvents, Plasticizers, and Chemical Intermediates.

Current edition approved Nov. 10, 1996. Published January 1997. Originally published as D1720-60F. Last previous edition D1720-93.

Current edition approved Nov. 1, 2008. Published November 2008. Originally approved in 1960. Last previous edition approved in 2003 as D 1720 - 03.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* Vol 06.03, volume information, refer to the standard's Document Summary page on the ASTM website.

4.2.3 The dilution ratio of toluene, as the standard diluent, to *n*-butyl acetate as the standard solvent, using as the solute cellulose nitrate of varying solubility characteristics.

4.3 The information developed through this test may be useful in the formulation of cellulose-based lacquers and adhesives.

5. Materials

5.1 *n*-Butyl Acetate (90 to 92 %), conforming to Specification D 4615.

NOTE 2—This grade of *n*-butyl acetate contains 8 to 10 % *n*-butyl alcohol.

5.2 Cellulose Nitrate, conforming to the Sampling section (Appearance, Ash, and Stability requirements) of Test Methods D 301 and of such quality that, when used in determining the toluene dilution ratios of *n*-butyl acetate and methyl *n*-propyl ketone, it will give results between the following limits:

	Toluene Dilution Ratio
<i>n</i> -butyl acetate	2.73 to 2.83
methyl <i>n</i> -propyl ketone	3.80 to 3.90

5.3 Toluene (*Toluol*), conforming to Specification D 841.

6. Hazards

6.1 Soluble cellulose nitrate is a flammable material, the degree of flammability varying with the extent and nature of the wetting medium. Cellulose nitrate is always wet with water or alcohol in commercial handling, shipping, and storage, in which condition it presents no unusual hazard. Dry cellulose nitrate, if ignited by fire, spark, or static electricity, burns very rapidly. Do not store samples of dry cellulose nitrate at any time. Dry only that portion required for immediate test. Wear a face shield when the oven is opened after samples have been heated. Wet excess material and the samples left after testing with water and dispose of properly.

7. Drying Cellulose Nitrate

7.1 Dry not more than 20 g of cellulose nitrate at a time by spreading in a thin layer on a tray at room temperature for 12 to 16 h, or on top of a 100°C oven where the temperature is 35 to 40°C for about 8 h (**Warning**, see 6.1). Alternatively, use a steam or hot water-heated oven maintained at 45 to 50°C to dry specimens in about 8 h. For safety reasons, the oven should have the latch removed.

7.2 Another simple way to dry small quantities of cellulose nitrate is to use a drier assembled from common laboratory apparatus. The assembled drier is shown in Fig. 1. Hot air from a laboratory electric oven is drawn through wet cellulose nitrate contained in a brass tube hooked up through a thistle tube, or small funnel, and suction flask to a water aspirator or other vacuum source. The brass pipe should be about 40 mm in diameter and 200 mm long, these relative dimensions having been found to give efficient results. Such a tube will hold about 25 g, dry weight, of wet cellulose nitrate. The pipe is insulated to conserve heat. The suction flask end of the brass tube is fitted with a thistle tube, or a small funnel, over the mouth of which is tied a silk cloth screen. An indentation made in the funnel edge allows insertion of the thermometer. The funnel and thermometer are held in place by means of a rubber stopper. When using an oven temperature of 85°C and vacuum supplied by a water aspirator or other vacuum source, the alcohol-wet cellulose nitrate will be dried in about 4 h.

7.3 If larger quantities of cellulose nitrate are required, the drying equipment described in the Procedure section of Drying Samples of Test Methods D 301 may be used.

8. Preparation of Solution

8.1 When testing either a solvent or diluent, first estimate the probable dilution ratio for the unknown component in relation to the other to determine the amount of solvent required to dissolve the cellulose nitrate (Table 1). This volume of solvent should be such that there will be approximately 10 g of cellulose nitrate present per 100 mL of solvent plus diluent at the end point.

NOTE 3—Reference to published data on similar types of solvents or diluents will provide a good approximation of the amount of solvent required. If data are not available, several solutions with varying amounts of solvents may be required to arrive at a suitable volume to use.

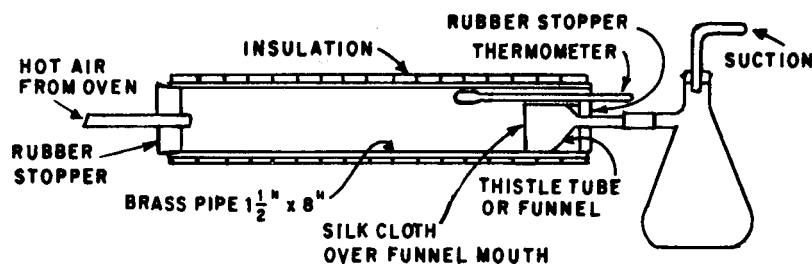


FIG. 1 Assembled Drier