

ISO/TC 89

Secretariat: DIN

Voting begins on:  
**2015-09-24**

Voting terminates on:  
**2015-11-24**

## Wood-based panels — Determination of formaldehyde release —

### Part 4: Desiccator method

*Panneaux à base de bois — Détermination du dégagement de  
formaldéhyde*

*Partie 4: Méthode au dessiccateur*

ISO STANDARD PREVIEW  
(standard.iteh.ai)  
Full standard available at  
<https://standards.iteh.ai/catalog/standards/sis/299dfba5-d0cd-461c-8dee-8978f0d68f79/iso-12460-4-2015>

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

Please see the administrative notes on page iii



Reference number  
ISO/FDIS 12460-4:2015(E)

## ISO/CEN PARALLEL PROCESSING

This final draft has been developed within the International Organization for Standardization (ISO), and processed under the **ISO-lead** mode of collaboration as defined in the Vienna Agreement. The final draft was established on the basis of comments received during a parallel enquiry on the draft.

This final draft is hereby submitted to the ISO member bodies and to the CEN member bodies for a parallel two-month approval vote in ISO and formal vote in CEN.

**Positive votes shall not be accompanied by comments.**

**Negative votes shall be accompanied by the relevant technical reasons.**

iTeh STANDARD PREVIEW  
(standards.iteh.ai)  
Full standard:  
<https://standards.iteh.ai/catalog/standards/sist/99dfba5-d0cd-461c-8dee-8978f0d68f79/iso-12460-4-2016>



### COPYRIGHT PROTECTED DOCUMENT

© ISO 2015, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Ch. de Blandonnet 8 • CP 401  
CH-1214 Vernier, Geneva, Switzerland  
Tel. +41 22 749 01 11  
Fax +41 22 749 09 47  
[copyright@iso.org](mailto:copyright@iso.org)  
[www.iso.org](http://www.iso.org)

# Contents

Page

<b>Foreword</b>	<b>iv</b>
<b>1 Scope</b>	<b>1</b>
<b>2 Normative references</b>	<b>1</b>
<b>3 Principle</b>	<b>1</b>
<b>4 Reagents</b>	<b>1</b>
<b>5 Apparatus</b>	<b>2</b>
<b>6 Test pieces</b>	<b>2</b>
6.1 Sampling	2
6.2 Dimensions	4
6.3 Number of test pieces	4
6.4 Number of emission tests	4
6.5 Conditioning	4
<b>7 Procedure</b>	<b>4</b>
7.1 Desiccator preparation	4
7.1.1 New desiccators	4
7.1.2 Before each determination	4
7.2 Test conditions	5
7.3 Positioning of the test pieces	5
7.4 Monitoring of test conditions	5
7.4.1 Temperature	5
7.4.2 Background formaldehyde	5
7.5 Test duration	5
7.6 Sample collection	5
<b>8 Determination of formaldehyde</b>	<b>5</b>
8.1 General	5
8.2 Principle	5
8.3 Procedure	6
8.4 Calibration curve	6
8.4.1 General	6
8.4.2 Formaldehyde standard solution	6
8.4.3 Formaldehyde calibration solution	6
8.4.4 Determination of the calibration curve	7
8.5 Calculation of the concentration of formaldehyde in the glass crystallizing dish in the desiccator	7
<b>9 Expression of results</b>	<b>7</b>
<b>10 Test report</b>	<b>7</b>
<b>Bibliography</b>	<b>9</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 89, *Wood-based panels*.

This second edition cancels and replaces the first edition (ISO 12460-4:2008), which has been technically revised with the following changes:

- a) introduction was deleted;
- b) reference to JANS 16 was deleted in the scope;
- c) provisions for low emitting boards were added in [5.6](#).

It also incorporates the Amendment ISO 12460-4:2008/AMD 1:2011.

ISO 12460 consists of the following parts, under the general title *Wood-based panels — Determination of formaldehyde release*:

- *Part 1: Formaldehyde emission by the 1-cubic-metre chamber method*
- *Part 3: Gas analysis method*
- *Part 4: Desiccator method*
- *Part 5: Extraction method (called perforator method)*

# Wood-based panels — Determination of formaldehyde release —

## Part 4: Desiccator method

### 1 Scope

This part of ISO 12460 specifies a desiccator method for the determination of the quantity of formaldehyde emitted from particleboard, fibreboard, plywood, oriented strand board (OSB), and wooden laminated flooring.

### 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 16999, *Wood-based panels — Sampling and cutting of test pieces*

### 3 Principle

Emission of formaldehyde is determined by placing test pieces of known surface area in a desiccator at a controlled temperature and measuring the quantity of emitted formaldehyde absorbed in a specified volume of water during 24 h.

### 4 Reagents

Use only reagents of recognized analytical grade, unless otherwise specified, and distilled or demineralized water or water of equivalent purity.

#### 4.1 Acetylacetone-ammonium acetate solution.

Dissolve 150 g ammonium acetate ( $\text{C}_2\text{H}_3\text{O}_2\text{NH}_4$ ) in 800 ml water in a 1 000 ml one-mark volumetric flask (5.9). Add 3 ml glacial acetic acid ( $\text{C}_2\text{H}_4\text{O}_2$ ) and 2 ml acetylacetone (pentane-2,4-dione,  $\text{C}_5\text{H}_8\text{O}_2$ ) and mix thoroughly into the solution. Make up to the mark with water. During storage, protect the solution from light. Discard the solution 3 days after preparation.

#### 4.2 Iodine standard solution, $c(\text{I}_2) = 0,05 \text{ mol/l}$ .

Standardize the solution before use.

#### 4.3 Sodium thiosulfate standard solution, $c(\text{Na}_2\text{S}_2\text{O}_3) = 0,1 \text{ mol/l}$ .

Standardize the solution before use.

#### 4.4 Sodium hydroxide standard solution, $c(\text{NaOH}) = 1 \text{ mol/l}$ .

Standardize the solution before use.

**4.5 Sulfuric acid standard solution**,  $c(\text{H}_2\text{SO}_4) = 1 \text{ mol/l}$ .

Standardize the solution before use.

**4.6 Starch solution**, 1 % mass fraction.

## 5 Apparatus

The usual laboratory apparatus and, in particular, the following:

**5.1 Glass desiccators**, with an enclosed volume of  $(11 \pm 2) \text{ l}$  capable of enclosing a support (5.2).

**5.2 Wire grid or support**, of diameter  $(240 \pm 15) \text{ mm}$  of stainless steel wire such that the distance between parallel pieces of wire is not less than 15 mm (see Figure 1).

**5.3 Glass crystallizing dish**, circular of inside diameter  $(115 \pm 1) \text{ mm}$  and depth  $(60 \pm 2) \text{ mm}$ .

**5.4 Sample holder**, of stainless steel wire, to hold the test pieces upright in the desiccator (see Figure 2).

**5.5 Temperature-measuring device**, e.g. a thermocouple, capable of measuring temperature with an error limit of  $\pm 0,1 \text{ }^\circ\text{C}$ , placed inside a desiccator (5.1) located adjacent to the desiccator(s) containing the test pieces.

**5.6 Spectrophotometer**, capable of measuring absorbance at 412 nm. The use of cells of pathlength at least 50 mm is recommended and is required for low emitting boards. Fluorimetric determination can also be used to gain more sensitivity.

**5.7 Water bath**, capable of maintaining a temperature of  $(65 \pm 2) \text{ }^\circ\text{C}$ .

**5.8 Volumetric flasks**, six, of capacity 100 ml.

**5.9 Volumetric flasks**, two, of capacity 1 000 ml.

**5.10 Bulb pipettes**, of capacities 5 ml, 10 ml, 15 ml, 20 ml, 25 ml, 50 ml, and 100 ml or suitable auto pipette.

**5.11 Microburette or auto dispenser**.


**5.12 Flasks with stoppers**, of capacity 100 ml.

**5.13 Balance**, capable of measuring to 0,001 g.


## 6 Test pieces

### 6.1 Sampling

Sampling and cutting of the test pieces shall be carried out in accordance with ISO 16999.

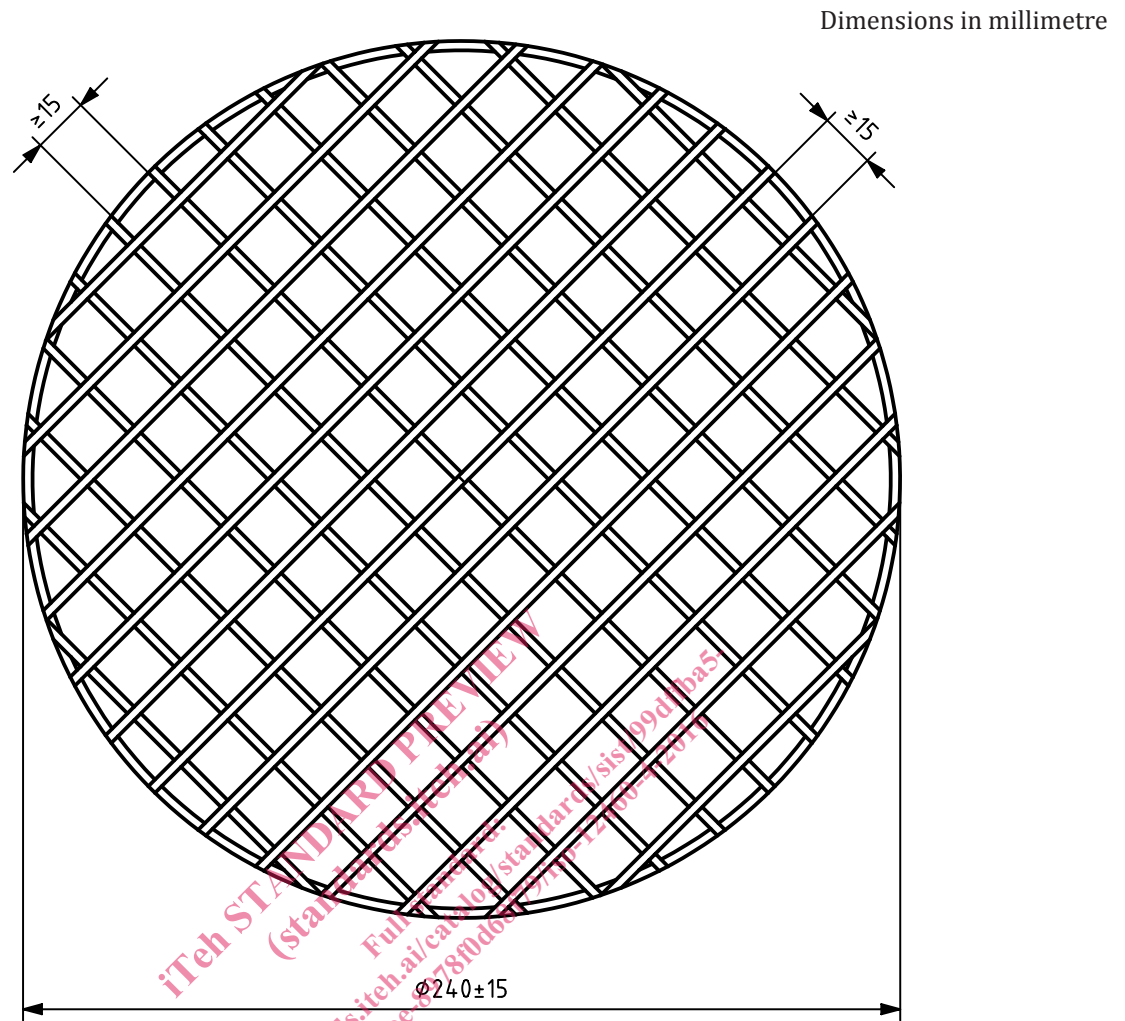

**Figure 1 — Stainless steel wire grid for supporting the test pieces in the desiccator**

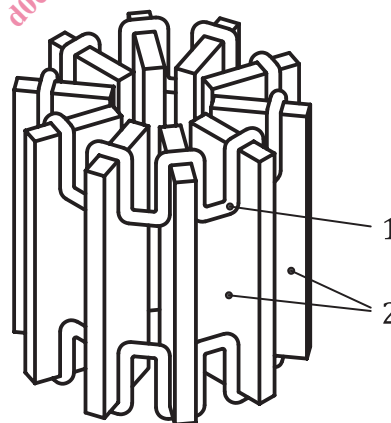

**Key**

- 1 supporting metal
- 2 test pieces

**Figure 2 — Example of wire sample holder to hold the test pieces in the desiccator**

## 6.2 Dimensions

The test pieces, of thickness,  $\delta$ , in millimetres, shall be of length  $(150 \pm 1,0)$  mm and of width  $(50 \pm 1,0)$  mm.

## 6.3 Number of test pieces

The number of test pieces shall be determined by their total surface area. The sum of the areas of the ends, sides and faces shall be as close as possible to 1 800 cm<sup>2</sup>.

## 6.4 Number of emission tests

The emission tests shall be carried out in duplicate.

NOTE For internal routine control, a single emission test might be sufficient.

The differences between emissions of the two tests shall be within 20 % of their arithmetic average, otherwise a third emission test shall be carried out.

## 6.5 Conditioning

Condition the test pieces for 7 days or to constant mass in an atmosphere with a mean relative humidity of  $(65 \pm 5)$  % and a temperature of  $(20 \pm 2)$  °C.

Constant mass is considered to have been reached when the results of two successive weighing operations, carried out at an interval of 24 h, do not differ by more than 0,1 % of the mass of the test piece.

The test pieces to be conditioned shall be separated by at least 25 mm and positioned so that air can circulate freely over all surfaces.

Test pieces containing low levels of formaldehyde will absorb formaldehyde from the atmosphere when background levels of formaldehyde are high. Care should be taken to avoid such conditions during storage and conditioning by use of a formaldehyde removal system or by maintaining low volumes of test pieces in the room. The background level is measured by exposing a glass crystallizing dish (5.3) containing 300 ml water to the conditioning atmosphere for 24 h, and analysing the resulting solution. The maximum background level shall be less than the nominal emission level of the test pieces (e.g. for test pieces from a sample with expected emissions of 0,3 mg/l, the background levels should be less than 0,3 mg/l).

## 7 Procedure

### 7.1 Desiccator preparation

#### 7.1.1 New desiccators

Thoroughly clean new desiccators and those previously used for purposes other than the determination of formaldehyde.

#### 7.1.2 Before each determination

Rinse the desiccator (5.1) and the glass dish (5.3) with water and dry them before each determination. Place  $(300 \pm 1)$  ml of water at  $(20 \pm 1)$  °C in the glass dish (5.3), and locate it centrally at the bottom of the desiccator. Position the wire mesh support (5.2) above the glass dish within the desiccator.



## 7.2 Test conditions

Place the desiccator on a vibration-free surface in an environment capable of maintaining the air temperature inside the desiccator at  $(20 \pm 0,5) ^\circ\text{C}$ .

## 7.3 Positioning of the test pieces

Insert the test pieces, free of any loose particles, into the wire sample holder (5.4) before placing it inside the desiccator. Position the sample holder containing the test pieces inside the desiccator at the centre of the wire mesh support so that it is located directly above the glass dish.

## 7.4 Monitoring of test conditions

### 7.4.1 Temperature

Prepare a control desiccator (5.1) as specified in 7.1.2 but containing no test pieces, and fit it with a temperature-measuring device (5.5). Monitor the temperature inside the desiccator continuously, or at intervals not exceeding 15 min, and record the mean temperature during the test period.

Alternatively, the temperature may be monitored by locating the temperature-measuring device (5.5) in the test environment adjacent to the desiccator.

### 7.4.2 Background formaldehyde

Measure the background formaldehyde in the testing environment using the control desiccator (7.4.1). The maximum accepted background level is 0.05 mg/l.

## 7.5 Test duration

The duration of the test shall be  $24 \text{ h} \pm 10 \text{ min}$ .

## 7.6 Sample collection

Thoroughly mix the formaldehyde solution contained in the glass dish. Rinse a 100 ml one-mark volumetric flask (5.8) with the formaldehyde solution and then fill it to the mark with the solution. Use a glass stopper to seal the flask. If the sample is not to be analysed immediately, store it between  $0 ^\circ\text{C}$  and  $5 ^\circ\text{C}$  for a maximum of 30 h.

Follow the same procedure for the measurement of background formaldehyde.

# 8 Determination of formaldehyde

## 8.1 General

Determine the formaldehyhde content of the aqueous solutions photometrically by the acetylacetone method.

## 8.2 Principle

The determination is based on the Hantzsch reaction in which the formaldehyde reacts with ammonium ions and acetylacetone to yield diacetyldihydrotoluidine (DDL). DDL has an absorption maximum at 412 nm. The reaction is specific to formaldehyde (see Reference [1]).