
**Metallic and other inorganic
coatings — Measurement of Young's
modulus of thermal barrier coatings
by beam bending**

*Revêtements métalliques et autres revêtements inorganiques —
Mesurage du module de Young des revêtements barrières thermiques
par flexion de poutre*

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 19477:2016

<https://standards.iteh.ai/catalog/standards/sist/5677aa8c-26bf-4fed-9fa0-edf0d4eacfl4/iso-19477-2016>



iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 19477:2016

<https://standards.iteh.ai/catalog/standards/sist/5677aa8c-26bf-4fed-9fa0-edf0d4eacfl4/iso-19477-2016>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2016, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

| | Page |
|---|-----------|
| Foreword..... | iv |
| Introduction..... | v |
| 1 Scope..... | 1 |
| 2 Normative references..... | 1 |
| 3 Terms and definitions..... | 1 |
| 4 Principle..... | 2 |
| 5 Apparatus for measuring Young's modulus..... | 2 |
| 5.1 Testing machine..... | 3 |
| 5.2 Four-point bending jig..... | 3 |
| 5.3 Strain measuring equipment..... | 4 |
| 6 Specimen..... | 4 |
| 7 Measuring procedure..... | 5 |
| 7.1 Specimen dimension..... | 5 |
| 7.2 Force–strain diagram..... | 5 |
| 8 Calculation of Young's modulus..... | 8 |
| 9 Test report..... | 9 |
| Annex A (informative) Measurement method of Young's modulus of TBC specimen with significant porosity..... | 11 |
| Bibliography..... | 14 |

ITIH STANDARD PREVIEW
 (standards.iteh.ai)
 ISO 19477:2016
<https://standards.iteh.ai/catalog/standards/sist/5677aa8c-26bf-4fed-9fa0-edf0d4eacfl4/iso-19477-2016>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html.

The committee responsible for this document is ISO/TC 107, *Metallic and other inorganic coatings*.

ISO 19477:2016

<https://standards.iteh.ai/catalog/standards/sist/5677aa8c-26bf-4fed-9fa0-edf0d4eacfl4/iso-19477-2016>

Introduction

Thermal barrier coatings are highly advanced material systems, generally applied to surfaces of hot-section components made of nickel or cobalt-based superalloys, such as combustors, blades, and vanes of power-generation gas turbines in thermal power plants and aero-engines operated at elevated temperatures.

The function of these coatings is to protect metallic components for extended periods at elevated temperatures by employing thermally insulating materials which can sustain an appreciable temperature difference between load bearing alloys and coating surfaces. These coatings permit the high-temperature operation by shielding these components, thereby extending their lives.

Although Young's modulus is an important property of thermal barrier coatings, the existing ISO standard only describes a method for measuring the Young's modulus of monolithic ceramics.

This International Standard specifies a method for measuring the Young's modulus of thermal barrier coatings that consist of multilayers formed on substrate by thermal spraying.

The measuring procedure of this International Standard is applicable for the measurement of the Young's modulus of various thermally sprayed coatings.

iTeh STANDARD PREVIEW (standards.iteh.ai)

[ISO 19477:2016](https://standards.iteh.ai/catalog/standards/sist/5677aa8c-26bf-4fed-9fa0-edf0d4eacfl4/iso-19477-2016)

<https://standards.iteh.ai/catalog/standards/sist/5677aa8c-26bf-4fed-9fa0-edf0d4eacfl4/iso-19477-2016>

iTeh STANDARD PREVIEW
(standards.iteh.ai)

ISO 19477:2016

<https://standards.iteh.ai/catalog/standards/sist/5677aa8c-26bf-4fed-9fa0-edf0d4eacfl4/iso-19477-2016>

Metallic and other inorganic coatings — Measurement of Young's modulus of thermal barrier coatings by beam bending

1 Scope

This International Standard specifies a method for measuring the in-plane Young's modulus, at room temperature, of thermal barrier coatings formed on substrates by thermal spraying.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1463, *Metallic and oxide coatings — Measurement of coating thickness — Microscopical method*

ISO 3611, *Geometrical product specifications (GPS) — Dimensional measuring equipment: Micrometers for external measurements — Design and metrological characteristics*

ISO 4287, *Geometrical Product Specifications (GPS) — Surface texture: Profile method — Terms, definitions, and surface texture parameters* (standards.iteh.ai)

ISO 13385 (all parts), *Geometrical product specifications (GPS) — Dimensional measuring equipment*

ISO 7500-1, *Metallic materials — Calibration and verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Calibration and verification of the force-measuring system*

ISO 14188, *Metallic and other inorganic coatings — Test methods for measuring thermal cycle resistance and thermal shock resistance for thermal barrier coatings*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 14188 and the following apply.


3.1

thermal barrier coating

TBC

two-layer coating consisting of a metallic bond coat (BC) and a ceramic top coat (TC), in order to reduce heat transfer from outside of the top coat through the coating to the substrate

Note 1 to entry: See [Figure 1](#).

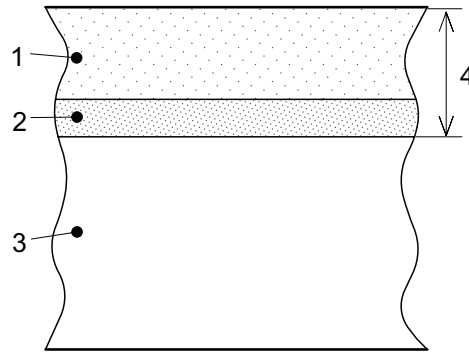

Key

- 1 TC
- 2 BC
- 3 substrate
- 4 TBC

Figure 1 — Diagrammatic view of a section of TBC

[SOURCE: ISO 14188:2012, 3.1, modified — a different note to entry and figure has been used.]

3.2 composite beam
beam consisting of multiple layers

iTeh STANDARD PREVIEW
(standards.iteh.ai)

4 Principle


ISO 19477:2016

The fundamental procedures for measuring the Young's moduli of the substrate, BC, and TC consist of the measurement of the force-strain diagram of three types of specimens (substrate, substrate with BC, and substrate with TBC) by a four-point bending method and of calculations according to the theory of composite beam.^{[1][2][3][4][5]}

5 Apparatus for measuring Young's modulus

An example of the apparatus for measuring the Young's modulus is schematically shown in [Figure 2](#).

The apparatus consists of four-point bending jig, testing machine, and strain measuring equipment.

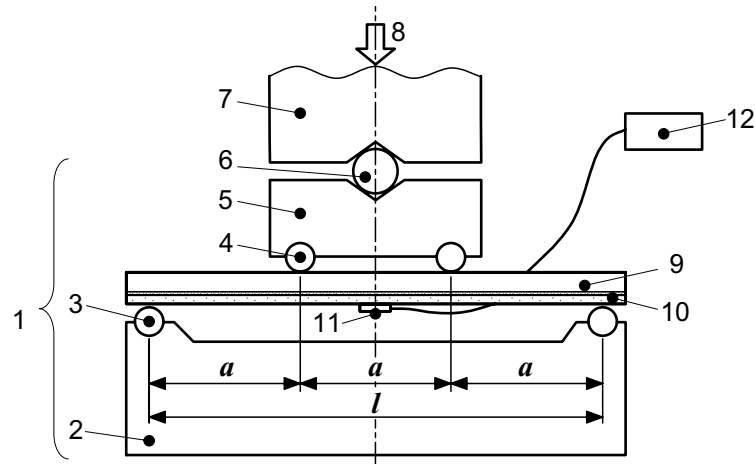

Key

| | | | |
|---|------------------------|-----|----------------------------------|
| 1 | four-point bending jig | 9 | specimen |
| 2 | support bed | 10 | TBC |
| 3 | support roller | 11 | strain gauge |
| 4 | load roller | 12 | strain measuring equipment |
| 5 | load bed | a | distance between load rollers |
| 6 | ball | l | distance between support rollers |
| 7 | testing machine | | |
| 8 | force | | |

iTeh STANDARD PREVIEW
(standards.iteh.ai)

Figure 2 — Typical apparatus for measuring the Young's modulus (in the case that the tensile force is applied to the TBC)

5.1 Testing machine

The testing machine is specified according to ISO 7500-1.

5.2 Four-point bending jig

The four-point bending jig consists of the load bed, load roller, support bed, support roller, and ball, as follows.

- a) The load bed, load roller, support bed, support roller, and ball shall have sufficient rigidity to prevent their plastic deformation during testing.
- b) The width of load bed, load roller, support bed, and support roller shall be larger than that of specimen.
- c) The distance between load rollers shall be between 15 mm and 30 mm.
- d) The distance between support rollers shall be three times the distance between load rollers.
- e) The radii of support rollers and load rollers shall be the same and shall be between 2,0 mm and 3,0 mm.
- f) The surface roughness of rollers shall be $\leq 0,4 \mu\text{m Ra}$ according to ISO 4287.
- g) The ball is used to ensure that the force is distributed evenly between the left and right load rollers.

5.3 Strain measuring equipment


The strain measuring equipment shall be specified as follows.

- a) The strain measuring equipment shall be capable of identifying, to the accuracy of $\pm 1\%$, the strain to be measured with the strain gauge.
- b) The strain gauge length should normally be ≤ 5 mm.

6 Specimen

The specimens shall be specified as follows.

- a) The three types of specimens, the substrate, BC, and TBC specimens shall be used.
- b) The specimen shape is a beam type (see [Figure 3](#)) and the dimensions of the specimen shall be as given in [Table 1](#).

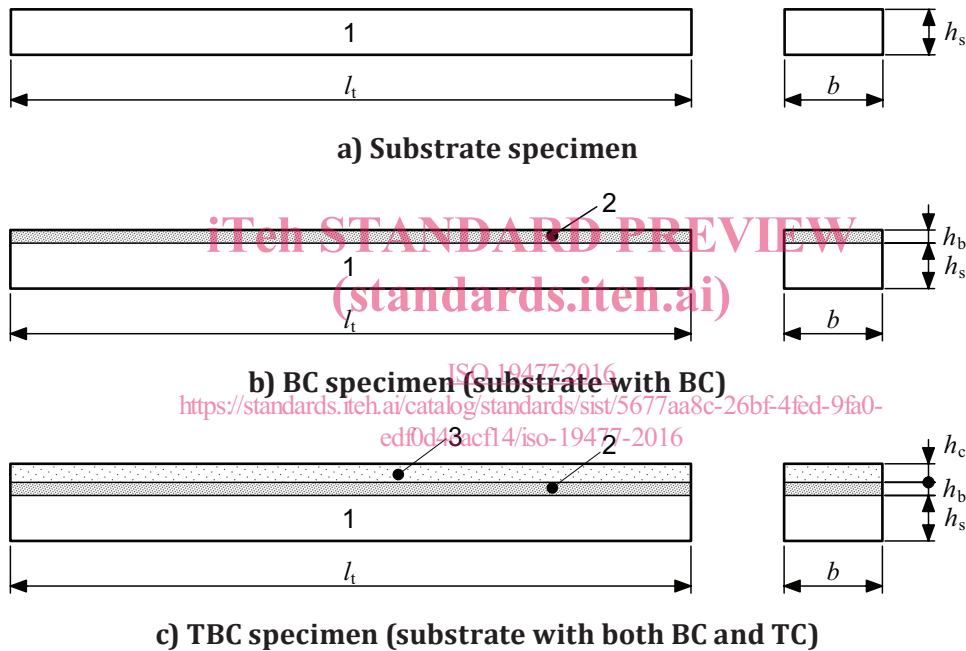

Key

- 1 substrate
- 2 BC
- 3 TC
- l_t total length
- b width
- h_s substrate thickness
- h_b BC thickness
- h_c TC thickness

Figure 3 — Shape of specimens

Table 1 — Dimensions of specimen

| Symbol | Designation | Dimension |
|------------|----------------------------------|--|
| l (mm) | distance between support rollers | $3 a$ |
| l_t (mm) | total length | $l + 6 \leq l_t$ |
| b (mm) | width | $4 \leq b \leq (1/6) l$ |
| h_s (mm) | substrate thickness | $1,5 \leq h_s \leq 3,0$ |
| h_b (mm) | BC thickness | $0,10 \leq h_b$ and $h_s / 20 \leq h_b$ for BC specimen |
| h_c (mm) | TC thickness | $0,20 \leq h_c$ and $(h_s + h_b) / 10 \leq h_c$ for TBC specimen |

- c) The thickness tolerance of the substrate shall be $\pm 0,01$ mm.
- d) The side surface of the BC and TBC specimens shall be polished to remove the coating deposited on the side surface. The polishing shall be done cautiously so that it does not damage the coating.

7 Measuring procedure

7.1 Specimen dimension

The dimensions of the specimen shall be measured as follows.

- a) The total length of the specimen shall be measured according to ISO 13385.
- b) The width of the specimen shall be measured according to ISO 3611.
- c) The thickness of the substrate shall be measured according to ISO 3611.
- d) The thickness of BC and TC shall be measured on an image of the coating cross section according to ISO 1463.

<https://standards.iteh.ai/catalog/standards/sist/5677aa8c-26bf-4fed-9fa0-edf0d4eacfl4/iso-19477-2016>

7.2 Force-strain diagram

- a) The strain gauge shall be attached to the coating surface for the BC and TBC specimens.
- b) The strain gauge shall be attached at the middle portion of the specimen, parallel to the longitudinal direction, as shown in [Figure 4](#).

For the TBC specimen with significant porosity, where adhesive for fixing the strain gauge might significantly penetrate into the coating, measurement should be done according to [Annex A](#).