

DRAFT INTERNATIONAL STANDARD

ISO/DIS 14705

ISO/TC 206

Secretariat: JISC

Voting begins on:
2016-01-12

Voting terminates on:
2016-04-12

Fine ceramics (advanced ceramics, advanced technical ceramics) — Test method for hardness of monolithic ceramics at room temperature

Céramiques techniques — Méthode d'essai de dureté des céramiques monolithiques à température ambiante

ICS: 81.060.30

iTeh STANDARD PREVIEW
(standards.iteh.ai)
Full standard:
<https://standards.iteh.ai/catalog/standards/sist/561eda62-96ae-44f3-a698-ea6b8bd88632/iso-14705-2016>

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENT AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.



Reference number
ISO/DIS 14705:2015(E)

© ISO 2015

iTeh STANDARD PREVIEW
(standards.iteh.ai)
Full standard:
<https://standards.iteh.ai/catalog/standards/sist/561eda62-96ae-44f3-a698-ea6b8bd88632/iso-14705-2016>



COPYRIGHT PROTECTED DOCUMENT

© ISO 2015, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Vickers hardness	2
4.1 Principle.....	2
4.2 Symbols, abbreviations and designations	2
4.3 Significance and use.....	4
4.4 Apparatus	5
4.5 Test pieces	5
4.6 Procedure	5
4.7 Test report.....	7
5 Knoop hardness	10
5.1 Principle.....	10
5.2 Symbols and designations	10
5.3 Significance and use.....	12
5.4 Apparatus	12
5.5 Test pieces	13
5.6 Procedure	13
5.7 Test report.....	14

iTeh STANDARD PREVIEW
 (standards.iteh.ai)
 Full standard available at
<https://standards.iteh.ai/catalog/standards/sist/5610da62-96ae-44f3-a698-ea6b8bd8632/iso-14705-2016>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 14705 was prepared by Technical Committee ISO/TC 206, *Fine ceramics*.

This second/third/... edition cancels and replaces the first/second/... edition (), [clause(s) / subclause(s) / table(s) / figure(s) / annex(es)] of which [has / have] been technically revised.

iTeh STANDARD PREVIEW
(standards.iteh.ai)
Full standard available at
<https://standards.iteh.ai/catalog/standards/sist/261edab2-96ae-44f3-a698-ea6b8bd88632/iso-14705-2016>

Fine ceramics (advanced ceramics, advanced technical ceramics) — Test method for hardness of monolithic ceramics at room temperature

1 Scope

This International Standard specifies a test method for determining the Vickers and Knoop hardness of monolithic fine ceramics at room temperature.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 4545-1:2005, *Metallic materials — Knoop hardness test — Part 1: Test method*

ISO 4545-2:2005, *Metallic materials — Knoop hardness test — Part 2: Verification and calibration of testing machines*

ISO 4545-3:2005, *Metallic materials — Knoop hardness test — Part 3: Calibration of reference blocks*

ISO 4545-4:2005, *Metallic materials — Knoop hardness test — Part 4: Table of hardness values*

ISO 6507-1:2005, *Metallic materials — Vickers hardness test — Part 1: Test method*

ISO 6507-2:2005, *Metallic materials — Vickers hardness test — Part 2: Verification and calibration of testing machines*

ISO 6507-3:2005, *Metallic materials — Vickers hardness test — Part 3: Calibration of reference blocks*

ISO 6507-4:2005, *Metallic materials — Vickers hardness test — Part 4: Tables of hardness values*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

Vickers hardness

value obtained by dividing the applied force by the surface area of the indentation computed from the mean of the measured diagonals of the indentations, assuming that the indentation is an imprint of the undeformed indenter

3.2

Vickers indenter

indenter in the shape of a right-angle pyramid with a square base and an angle between opposite faces of 136°

See Table 1 and Figure 1.

Table 1 — Symbols, abbreviations and designations for Vickers hardness testing

Symbol or abbreviation	Designation
α	Angle between the opposite faces at the vertex of the pyramidal indenter ($136^\circ \pm 0,5^\circ$)
F	Test force, in newtons
d	Arithmetic mean, in millimetres, of the two diagonals d_1 and d_2
HV	Vickers hardness $= \text{Constant} \times \frac{\text{Test force}}{\text{Surface area of indentation}}$ $= 0,102 \frac{2F \sin \frac{136^\circ}{2}}{d^2} = 0,1891 \frac{F}{d^2}$
c	Arithmetic mean of the half of the two median crack lengths $2c_1$ and $2c_2$
S.D.	Standard deviation $= \sqrt{\frac{\sum (\overline{HV} - HV_n)^2}{n - 1}}$ <p>where</p> $\overline{HV} \text{ is the arithmetic mean of the Vickers hardness } = \frac{\sum HV_n}{n}$ $HV_n \text{ is the HV obtained from } n\text{th indentation}$ $n \text{ is the number of indentations}$
NOTE	Constant = $\frac{1}{g} = \frac{1}{9,807} = 0,102$ where g is the acceleration due to gravity.

Table 2 — Hardness symbols and the nominal values of test forces, F , for Vickers hardness testing

Hardness symbol	Test force, F (nominal value)
HV 0,5	4,903 N
HV 1	9,807 N
HV 2	19,61 N
HV 3	29,42 N
HV 5	49,03 N
HV 10	98,07 N
HV 20	196,1 N

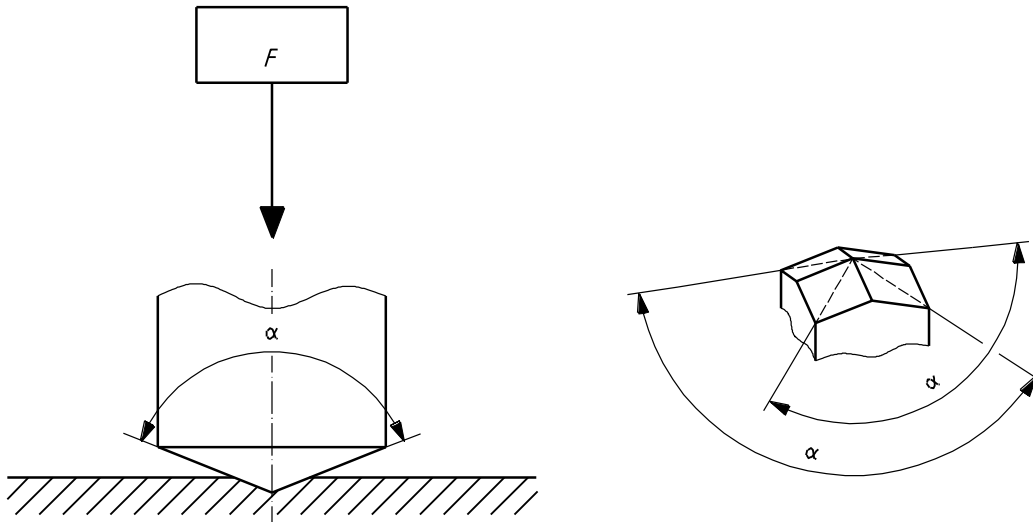


Figure 1 — Vickers indenter (diamond pyramid)

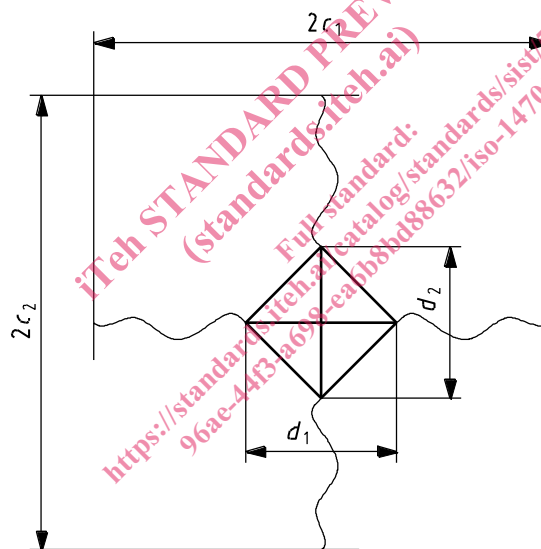


Figure 2 — Vickers indentation

4.3 Significance and use

Vickers indentation diagonal lengths are approximately 2,8 times shorter than the long diagonal of Knoop indentations, and the indentation depth is approximately 1,5 times deeper than Knoop indentations made at the same force. Vickers indentations are influenced less by the specimen surface flatness, parallelism of the diamond axis to the test piece surface normal, and surface finish than Knoop indentations, but these parameters should be considered nonetheless. Vickers indentations are much more likely to cause cracks in fine ceramics than are Knoop indentations. Conversion between hardness scales shall not be made.

Vickers indentations on metallic materials are mainly formed by the plastic deformation. However, Vickers indentations on fine ceramics are formed by micro-cracking and micro-fracture, besides plastic deformation. This difference shall be noted for comparing the hardnesses of metals and ceramics.

4.4 Apparatus

4.4.1 Testing machine, capable of applying a predetermined test force in the range of 4,903 N (0,5 kgf) to 98,07 N (10 kgf), preferably 9,807 N (1 kgf), in accordance with ISO 6507-2. Verification of the test force shall be carried out in accordance with ISO 6507-2.

4.4.2 Diamond indenter, in the shape of a right-angle pyramid with a square base, as specified in ISO 6507-1 and ISO 6507-2. Verification of the indenter shall be carried out in accordance with ISO 6507-2.

4.4.3 Measuring device, capable of measuring the indentation diagonals with a readout resolution of $\pm 0,2 \mu\text{m}$ or finer. A numerical aperture (NA) of between 0,60 and 0,95 for the objective lens for the microscope is recommended. Verification of the measuring device shall be carried out in accordance with ISO 6507-2.

NOTE Indirect verification can be carried out by means of standardized blocks calibrated in accordance with ISO 6507-3, following ISO 6507-2, or other approved and traceable ceramic standard reference blocks.

4.5 Test pieces

4.5.1 The test shall be carried out on a surface which is smooth, flat and free from foreign matter. The test piece shall be polished to permit accurate measurement of the diagonal lengths of the indentation. Preparation shall be carried out in such a way that any alteration of the surface hardness is minimized.

4.5.2 The thickness of the test piece shall be at least 0,5 mm. It shall be at least 1,5 times the diagonal of the indentation, d , and at least 2 times the crack length, c , whichever is greater. No indentation damage shall be visible at the back of the test piece on completion of the test.

4.6 Procedure

4.6.1 In general, the test shall be carried out at room temperature within the limits of 10 °C to 35 °C. Tests carried out under controlled conditions shall be made at a temperature of 23 °C \pm 5 °C.

4.6.2 The recommended test force is 9,807 N (1 kgf). In cases where significant chipping or lateral crack-spalling occurs or where the impression is too faint, the test forces within the range 4,903 N (0,5 kgf) to 196,1 N (20 kgf), listed in Table 2, may be used. Other instances where a heavier load may be required are where the grain structure is very coarse and the indentation area at lower loads may contact only a few grains of the material (e.g. a multiphase material).

4.6.3 The following items shall be confirmed before the test.

- a) Check the zero of the measuring system.
- b) Check the measuring system using a calibrated scale or certified indentation in a test block.
- c) Check the operation of the loading system by performing a test on a certified test block.
- d) Check the condition of the indenter by examination of the indentation made in the test block. Replace the indenter, if necessary, by taking into account the conditions given in 4.6.10.

4.6.4 The indenter shall be cleaned prior to and during the test series, as ceramic powders or fragments from the ceramic test piece can adhere to the diamond indenter.


4.6.5 The test piece shall be placed on a rigid support. The support surface shall be clean and free from foreign matter. It is important that the test piece lies firmly on the support, so that displacement cannot occur during the test.

4.6.6 Carefully adjust the illumination and focusing conditions, in order to obtain the optimum view and clarity of the indentation. Both indentation tips shall be in focus at the same time. Do not change the focus when measuring the distance from tip to tip.

4.6.7 Bring the indenter into contact with the test surface and apply the test force in a direction perpendicular to the surface, without shock or vibration, until the applied force attains the specified value. The time from the initial application of the force until the full test force is reached shall not be less than 1 s nor greater than 5 s. The duration of application of the constant maximum test force shall be 15 s.

4.6.8 Throughout the test, the apparatus shall be protected from shock or vibration.

4.6.9 The distance between the centre of any indentations and the edge of the test piece shall be at least 2,5 times the mean diagonal of the indentation, and at least 5 times the mean length of the crack, as shown in Figure 3. The distance between the centres of two adjacent indentations shall be at least 4 times the mean diagonal of the indentation, and at least 5 times the mean length of the crack, as shown in Figure 3. If two adjacent indentations differ in size and crack length, the spacing shall be based on the mean diagonal of the larger indentation and the longer crack length.

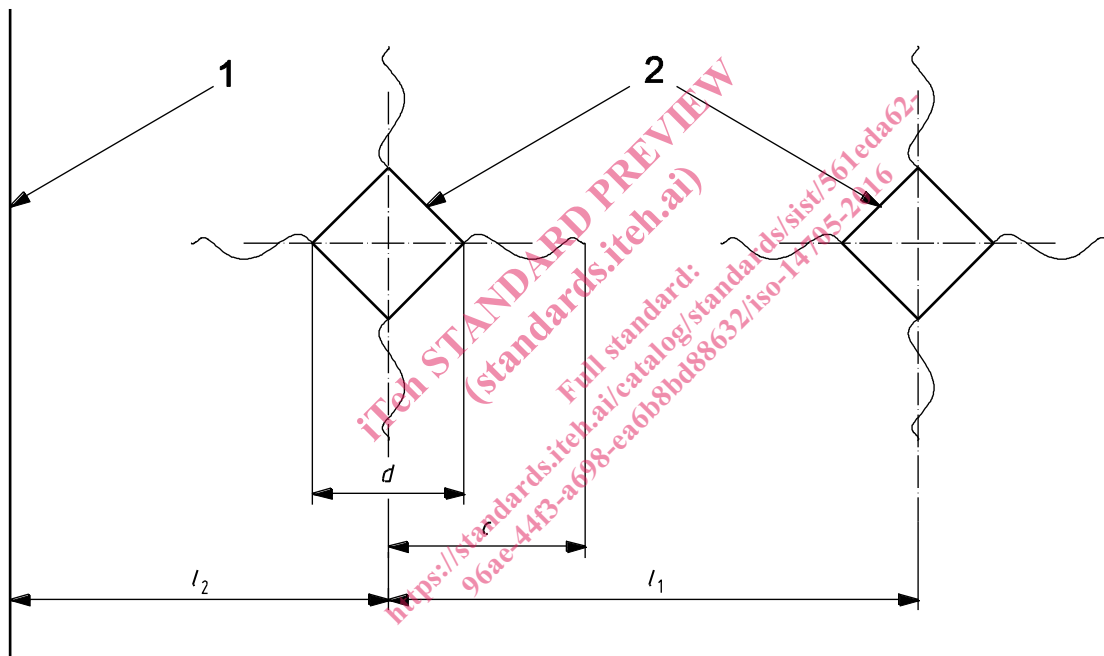

Key

- 1 edge of test piece
- 2 indentations
- c* length from the centre of indentation to the end of crack
- d* length of indent diagonal
- l_1 distance between centres of indentations
 $l_1 \geq 4d$ and $5c$
- l_2 distance from centre of indentation to the edge of sample
 $l_2 \geq 2,5d$ and $5c$

Figure 3 — Closest permitted spacing between indentations and from indentation to the test piece edge for Vickers indentations