



SLOVENSKI STANDARD SIST EN 13603:2021

01-september-2021

Nadomešča:
SIST EN 13603:2013

Baker in bakrove zlitine - Preskusne metode za ocenjevanje kakovosti zaščitnih kositrovih prevlek na okroglih bakrovih vlečenih žicah za elektrotehniko

Copper and copper alloys - Test methods for assessing protective tin coatings on drawn round copper wire for electrical purposes

Kupfer und Kupferlegierungen - Prüfverfahren zur Beurteilung von Schutzüberzügen aus Zinn auf gezogenen Runddrähten aus Kupfer für die Anwendung in der Elektrotechnik

Cuivre et alliages de cuivre - Méthodes d'évaluation des revêtements en étain sur les fils ronds étirés en cuivre pour usages électriques

<https://standards.iteh.ai/catalog/standards/sist/9cea57c4-0d86-4f60-92cb-ccda9073b333/sist-en-13603-2021>

Ta slovenski standard je istoveten z: EN 13603:2021

ICS:

25.220.40	Kovinske prevleke	Metallic coatings
77.150.30	Bakreni izdelki	Copper products

SIST EN 13603:2021

en,fr,de

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 13603:2021](#)

<https://standards.iteh.ai/catalog/standards/sist/9cea57c4-0d86-4f60-92cb-eda9073b333/sist-en-13603-2021>

EUROPEAN STANDARD

EN 13603

NORME EUROPÉENNE

EUROPÄISCHE NORM

May 2021

ICS 25.220.40; 77.150.30

Supersedes EN 13603:2013

English Version

Copper and copper alloys - Test methods for assessing protective tin coatings on drawn round copper wire for electrical purposes

Cuivre et alliages de cuivre - Méthodes d'évaluation des revêtements en étain sur les fils ronds étirés en cuivre pour usages électriques

Kupfer und Kupferlegierungen - Prüfverfahren zur Beurteilung von Schutzüberzügen aus Zinn auf gezogenen Runddrähten aus Kupfer für die Anwendung in der Elektrotechnik

This European Standard was approved by CEN on 12 April 2021.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

Contents	Page
European foreword	3
1 Scope	4
2 Normative references	4
3 Terms and definitions	4
4 Thickness of the unalloyed tin coating	5
4.1 General.....	5
4.2 Principle of the method based on the electrolytic dissolution of the tin coating.....	5
4.2.1 General.....	5
4.2.2 Reagents and materials	5
4.2.3 Apparatus	5
4.2.4 Preparation of the test piece	7
4.2.5 Procedure for determining the thickness of unalloyed tin coatings.....	7
4.2.6 Expression of results	10
4.3 Principle of the method based on XRF	11
4.3.1 General.....	11
4.3.2 Devices with measuring spots larger than the wire diameter — Overlap technique.....	11
4.3.3 Devices with measuring spots smaller than the wire diameter – Full-spot technique	12
4.3.4 Preparation of the test piece	12
4.3.5 Factors affecting the measuring accuracy	13
5 Continuity of the tin coating	17
5.1 Principle.....	17
5.2 Test solution	17
5.3 Reference solution.....	18
5.4 Preparation of the test piece	18
5.5 Cleaning of the test piece	18
5.6 Immersion for testing.....	18
5.7 Determination.....	19
5.7.1 General.....	19
5.7.2 Comparison by Nessler cylinders.....	19
5.7.3 Colorimetric method	19
6 Adherence of the tin coating	19
6.1 Principle.....	19
6.2 Stock solution	19
6.3 Test solution	19
6.4 Preparation of the test piece	19
6.5 Cleaning of the test piece	20
6.6 Immersion for testing.....	20
6.7 Examination.....	20
7 Test report	21
Bibliography	22

European foreword

This document (EN 13603:2021) has been prepared by Technical Committee CEN/TC 133 “Copper and copper alloys”, the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by November 2021, and conflicting national standards shall be withdrawn at the latest by November 2021.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 13603:2013.

In comparison with the previous edition, the following technical modifications have been made:

- included the X-ray fluorescence analysis (XRF) to measure the thickness of the tin layer.

According to the CEN-CENELEC Internal Regulations, the national standards organisations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

[SIST EN 13603:2021](https://standards.iteh.ai/catalog/standards/sist/9cea57c4-0d86-4f60-92cb-ceeda9073b333/sist-en-13603-2021)

<https://standards.iteh.ai/catalog/standards/sist/9cea57c4-0d86-4f60-92cb-ceeda9073b333/sist-en-13603-2021>

EN 13603:2021 (E)

1 Scope

This document specifies methods for assessing the tin coating on drawn round copper wire for the manufacture of electrical conductors, e.g. according to EN 13602.

This document includes test methods for the determination of the following characteristics:

- a) thickness of the unalloyed tin coating;
- b) continuity of the tin coating;
- c) adherence of the tin coating.

WARNING — This document can involve the use of hazardous materials, operations, and equipment. This document does not purport to address all of the safety problems associated with their use. It is the responsibility of the user of this document to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use. Moreover this document does not cover the aspects related to the people protection against the X-ray. To obtain information applicable to this aspect, it is convenient to refer to national and international standards, and also to the local regulations if they exist.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 610, *Tin and tin alloys - Ingot tin*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1

unalloyed tin coating

layer of pure tin on the surface of tinned wire

3.2

alloyed tin coating

diffusion layer of copper and tin formed at the copper wire and tin coating interface during tinning and subsequent drawing and annealing processes

3.3

total tin coating

sum of the thicknesses of the unalloyed tin coating and the alloyed tin coating

3.4

measuring area

area of the surface over which a single measurement is made

3.5

X-ray fluorescence

XRF

secondary radiation occurring when a high intensity incident X-ray beam impinges upon a material placed in the path of the incident beam

Note 1 to entry: The secondary emission has wavelengths and energies characteristic of that material.

[SOURCE: EN ISO 3497:2000-12, 2.1]

4 Thickness of the unalloyed tin coating

4.1 General

This document refers to two different methods to measure the thickness of the tin coating layers on copper wires, the first one is based on the electrolytic dissolution of the tin layer. The second one is based on the direct measure of the tin layer on the wires by means of the reflection of an X-ray beam on its surface.

4.2 Principle of the method based on the electrolytic dissolution of the tin coating

4.2.1 General

Anodic dissolution of a well-defined area of the unalloyed coating using a suitable electrolyte, followed by detection of the virtually complete dissolution of the unalloyed coating by a rapid change in cell voltage. Calculation of the unalloyed coating thickness from the quantity of electricity (in coulombs) used, which can in turn be calculated from:

- a) the time interval between the start of the test and the first rapid change of cell voltage, if it is conducted at constant current density; or
- b) the integrated quantity of electricity used in dissolving the unalloyed coating.

4.2.2 Reagents and materials

4.2.2.1 Electrolyte, either a hydrochloric acid electrolyte or an electrolyte recommended by the instrument manufacturer.

For the hydrochloric acid electrolyte, dilute 170 ml of hydrochloric acid (HCl), $\rho = 1,18$ g/ml, to 1 000 ml with deionised water.

NOTE The unalloyed tin coating dissolves anodically at an efficiency of nearly 100 %; for determination of the electrolyte efficiency, see 4.2.5.6.

WARNING — Hydrochloric acid causes burns and is irritating to the respiratory system. Avoid breathing the vapour and prevent contact with eyes and skin.

This electrolyte dissolves tin coatings at very low cell voltages at which there is no anodic attack on the substrates when they are exposed at the end of the test.

4.2.2.2 Tin, tin grade in accordance with EN 610.

4.2.3 Apparatus

Suitable instruments may be constructed from readily available components. Alternatively, a proprietary instrument may be used.

EN 13603:2021 (E)**4.2.3.1 Direct reading instruments**

Proprietary direct reading instruments are available for use with electrolytes recommended by the manufacturer.

The calculation of thickness of tin coating from current density is made electronically. The instrument shall have some means of indicating when the unalloyed tin coating has been fully removed.

4.2.3.2 Other instruments

Instruments other than proprietary direct reading instruments record the quantity of electricity, in coulombs, used in dissolving the unalloyed coating from the measuring area, usually in arbitrary units, from which the thickness can be calculated using factors or tables.

4.2.3.3 Electrolytic cell

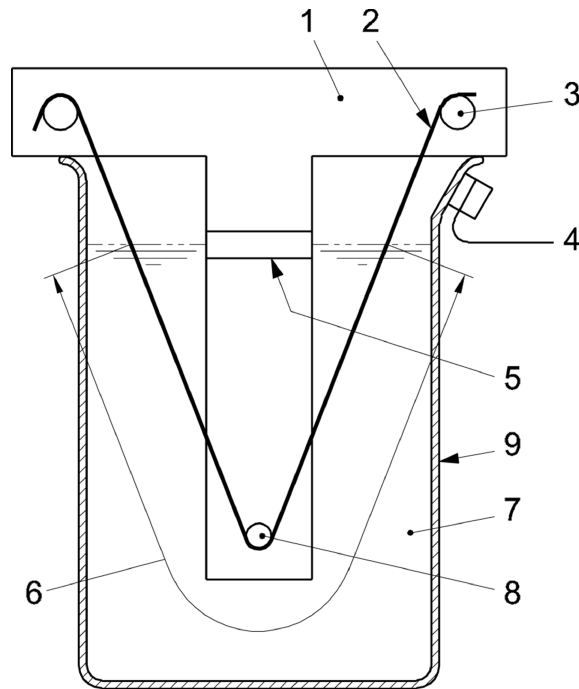
The electrolytic cell consists of a container for the electrolyte, a cathode and an anode, which is the test piece. If the container is made of metal, such as stainless steel, the container can serve as the cathode. If the container is made of insulating material, a separate cathode is required.

Also required are a device for supporting the appropriate length of the test piece and an agitation mechanism. Depending on the wire diameter, the test piece may be a straight length of wire or, if necessary to obtain sufficient surface area for smaller diameter wires, a holding device such as that shown schematically in Figure 1 is required. A magnetic stirrer or similar system shall be used to provide agitation.

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 13603:2021](https://standards.iteh.ai/catalog/standards/sist/9cea57c4-0d86-4f60-92cb-eda9073b333/sist-en-13603-2021)

<https://standards.iteh.ai/catalog/standards/sist/9cea57c4-0d86-4f60-92cb-eda9073b333/sist-en-13603-2021>

**Key**

- 1 tee-frame to support test piece of non-conducting material, manufactured from nylon or other plastics
- 2 test piece
- 3 test piece connection (anode)
- 4 cathode connection
- 5 electrolyte level
- 6 test piece length L
- 7 electrolyte
- 8 non-metallic pin
- 9 cathode (stainless steel or lead), container (beaker)

iTeh STANDARD PREVIEW
(standards.iteh.ai)

[SIST EN 13603:2021](https://standards.iteh.ai/catalog/standards/sist/9cea57c4-0d86-4f60-92cb-ceeda9073b333/sist-en-13603-2021)

<https://standards.iteh.ai/catalog/standards/sist/9cea57c4-0d86-4f60-92cb-ceeda9073b333/sist-en-13603-2021>

Figure 1 — Alternative method for supporting fine wire or wire which cannot be straightened

4.2.4 Preparation of the test piece

Select a suitable length of test piece in order to provide the appropriate test piece area for exposure to the electrolyte. If necessary, clean the test surface with a suitable organic solvent (see 5.5).

Care should be taken to avoid removal of metal during the cleaning operation.

4.2.5 Procedure for determining the thickness of unalloyed tin coatings

4.2.5.1 General

If commercial equipment is used, follow the manufacturer's instructions with respect to the operating procedure for measurement, the electrolyte and, if necessary, calibration. Appropriate attention shall be given to the factors listed in 4.2.5.4. The performance of the instrument shall be checked using a reference specimen of pure tin wire. A tin grade in accordance with EN 610 shall be used. The test shall be carried out in accordance with 4.2.5.6.

If the instrument readings or the calculation of K give an electrolytic efficiency of equal to or greater than 98 %, the instrument may be used without further adjustment. Otherwise, the cause of discrepancy shall be remedied. Proprietary instruments shall be calibrated in accordance with the manufacturer's instructions.

EN 13603:2021 (E)**4.2.5.2 Determination of measuring area**

The measuring area A in square centimetres is given by the Formula (1):

$$A = \frac{d \times L \times \pi}{100} \quad (1)$$

where

- A is the measuring area in square centimetres;
- d is the diameter of the test piece in millimetres;
- L is the length of the test piece in millimetres.

For the determination of the measuring area, the length L of the test piece in millimetres shall be determined with an accuracy of 1 % and the diameter d of the test piece for wires with a nominal diameter of < 0,6 mm shall be determined with an accuracy of 1 % and for wires with a nominal diameter of $\geq 0,6$ mm with an accuracy of 0,5 %.

An exact area of stripping is necessary for accuracy and the main source of error is due to the meniscus and current field at the electrolyte surface.

4.2.5.3 Electrolysis (Dissolution of the unalloyed tin coating)

The electrolyte (4.2.2.1) and test piece shall be introduced into the cell so that a known area is exposed to the electrolyte. Efforts shall be made to ensure that no gas bubbles occur on the measuring area by use of the agitation mechanism. The electrical connections shall be made and the agitator operated. Electrolysis shall be continued until dissolution of the unalloyed tin coating is complete, as indicated by a sharp change in the anode potential or cell voltage, or by the operation of the automatic cut-out.

After completion of the test, the test piece shall be removed from the cell, rinsed with water and examined to ensure that complete removal of the unalloyed tin coating has occurred over the measuring area (see 4.2.5.4.9).

4.2.5.4 Factors affecting the measuring accuracy**4.2.5.4.1 Coating thickness**

The optimum accuracy is achieved with coating thicknesses in the range 0,2 μm up to 50 μm .

4.2.5.4.2 Current variation

For instruments using the constant current and time measuring technique, current variation will cause errors. For instruments using a current-time integrator, too large a change in current can change the anode current efficiency or interfere with the end-point, causing an error.

4.2.5.4.3 Area variation

The accuracy of the thickness measurement will be no better than the accuracy to which the measuring area is known. Area variations due to electrolyte level (excessive agitation), can lead to measurement errors. In some cases it can be advantageous to measure the length after electrolysis is complete and re-calculate the area.

4.2.5.4.4 Agitation

Agitation (i.e. the rate of stirring) shall be sufficient to remove any gas bubbles formed during the test, which can adhere to the test piece or cathode. Excessive agitation shall be avoided to prevent interference with the length of test piece submerged.

4.2.5.4.5 Condition of the test piece surface

Oil, grease, paint, corrosion products, staining or other surface chemical treatments can interfere with the test.

4.2.5.4.6 Cleanliness of the cell

Deposition of tin can take place on the cathode in some electrolytes. This deposit can alter the cell voltages. It is, therefore, essential to keep the cathode clean.

4.2.5.4.7 Cleanliness of the electrical connections

In the case of instruments other than the constant current type, if the electrical connections are not clean, the current/potential relationship will be disturbed and false end-points obtained.

4.2.5.4.8 Calibration standards

Measurements made using calibration standards are subject to the additional error of the calibration standards.

4.2.5.4.9 Non-uniform dissolution

If the rate of dissolution is not uniform over the measuring area, a premature end-point can be obtained and yield low results. Examination of the surface shall be made after the test (see 4.2.5.3) to verify that most of the coating has dissolved.

The presence of other matter in the coating, the roughness of the coating surface and the presence of porosity in the coating can cause fluctuation of the cell voltage. Such fluctuation can affect the end-point.

4.2.5.4.10 Electrolyte efficiency

The determination of tin thickness by this method depends upon the efficiency of the electrolyte K being at least 98 %. The value of K should be determined periodically (see 4.2.5.6).

4.2.5.5 Measurement uncertainty

The test equipment and the procedure shall be such that the coating thickness can be measured to within a 5,0 % uncertainty under the following conditions:

- the electrical current shall be controlled within 10 mA;
- the time shall be controlled within 1 s;
- the area shall be controlled within the accuracy given in 4.2.5.2;
- the efficiency of the electrolyte K shall be greater than 98 % (see 4.2.5.6).

4.2.5.6 Determination of electrolyte efficiency

Where a manufacturer of apparatus recommends the use of a particular electrolyte for determining tin thickness on copper wire, the control of electrolyte efficiency shall be in accordance with the manufacturer's instructions. In other cases, the value of K shall be determined periodically using the following procedure:

- a) a suitable test anode shall be manufactured comprising wire in the range of diameter 0,5 mm up to and including 2,00 mm, of suitable length, coated with pure, unalloyed tin (4.2.2.2) to a thickness of at least 4 μm ;
- b) the test anode shall be accurately weighed and its mass recorded;