

ISO/DTR 18228-5

ISO/TC 221

Secretariat: BSI

Date: 2024-07-01

Design using geosynthetics —

**Part 5:
Stabilization**

Conception utilisant des géosynthétiques —

Partie 5: Stabilisation

iTeh Standards
(<https://standards.itih.ai>)
Document Preview

[ISO/DTR 18228-5](https://standards.itih.ai/catalog/standards/iso/09b5ec71-3aeb-4987-bcf2-d0b9189f5778/iso-dtr-18228-5)

<https://standards.itih.ai/catalog/standards/iso/09b5ec71-3aeb-4987-bcf2-d0b9189f5778/iso-dtr-18228-5>

ISO/DTR 18228-5:(en)

© ISO ~~2022~~2024

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: + 41 22 749 01 11

Fax: +41 22 749 09 47

Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[ISO/DTR 18228-5](#)

<https://standards.iteh.ai/catalog/standards/iso/09b5ec71-3aeb-4987-bcf2-d0b9189f5778/iso-dtr-18228-5>

Contents

Foreword..... v

Introduction..... vi

1 Scope..... 1

2 Normative references 1

3 Terms and definitions..... 1

4 Concepts and fundamental principles 1

4.1 General..... 1

4.2 Benefits..... 3

4.3 Confinement and particle restraint..... 4

4.3.1 General..... 4

4.3.2 Internal confinement — Description of mechanism 4

4.3.3 External confinement — Description of mechanism 6

4.4 Vehicular action..... 9

4.5 Loading conditions (cyclic and static) 9

4.6 Multi component systems 10

4.7 Static loads — Settlement control and limitation 10

4.8 Reduction in deformation from trafficking..... 10

4.9 Reduction in unbound aggregate degradation 10

4.10 Extension of design life..... 11

4.11 Ground and groundwater conditions..... 11

4.12 Climatic conditions 11

4.13 Sustainability 12

4.14 Impact of filtration, separation and drainage requirements 12

5 Typical applications 13

5.1 Stabilized granular (aggregate) layers in trafficked areas 13

5.2 Stabilized granular (aggregate) layers in railways 14

5.3 Stabilized granular (aggregate) layers in working platforms 15

6 Design methods..... 16

6.1 General..... 16

6.2 Unpaved roads..... 16

6.2.1 Giroud-Han (2004) method..... 16

6.2.2 Leng-Gabr (2006) method 17

6.2.3 Pokharel (2010) method for geocells 18

6.2.4 Emersleben (2009) method for geocells..... 20

6.3 Paved roads 23

6.3.1 Modified American Association of State Highway and Transportation Officials (AASHTO) (1993) method 23

6.3.2 MEPDG methods..... 25

6.4 Working platforms and load transfer platforms..... 25

6.4.1 General..... 25

6.4.2 Static method for clay subgrade 26

6.4.3 BCR method for soft sand subgrade 28

6.5 Railways 29

6.5.1 Network Rail (UK) design specifications 29

6.5.2 Ev2 method..... 30

6.5.3 Railway ballast stabilization..... 32

6.5.4 Design method for railway stabilization with geocells 33

6.6 Design of the geosynthetics layout 35

ISO/DTR 18228-5:(en)

7	Materials.....	38
7.1	Properties of aggregate	38
7.2	Key properties for geosynthetics – Internal confinement.....	38
7.3	Key properties for geosynthetics – External confinement.....	38
8	Testing	39
8.1	General.....	39
8.2	Accelerated pavement tests (APT).....	40
8.3	Tests for geotextiles and geogrids	40
8.4	Tests for geocells	41
Annex A (informative)	Tensioned membrane design	42
A.1	Description of tensioned membrane mechanism	42
A.2	Design methodology	42
	Bibliography	46

iTeh Standards
(<https://standards.iteh.ai>)
Document Preview

[ISO/DTR 18228-5](https://standards.iteh.ai/catalog/standards/iso/09b5ec71-3aeb-4987-bcf2-d0b9189f5778/iso-dtr-18228-5)

<https://standards.iteh.ai/catalog/standards/iso/09b5ec71-3aeb-4987-bcf2-d0b9189f5778/iso-dtr-18228-5>

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

~~Attention is drawn to the possibility that some of the elements of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at www.iso.org/patents. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see).~~

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 221, *Geosynthetics*.

A list of all parts in the ISO/TR 18228 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

ISO/DTR 18228-5:(en)

Introduction

The ISO 18228 series provides guidance for designs using geosynthetics for soils and below ground structures in contact with natural soils, fills and asphalt. The series contains 10 parts which cover designs using geosynthetics, including guidance for characterization of the materials to be used and other factors affecting the design and performance of the systems which are particular to each part, with ISO/TR 18228-1 providing general guidance relevant to the subsequent parts of the series.

The series is generally written in a limit state format and guidelines are provided in terms of partial material factors and load factors for various applications and design lives, where appropriate.

Ultimate limit state (ULS) design is necessary for some applications, e.g. slab foundation design, working platform design etc., but usually must be proven separately. This document is a state of practice report and information is provided in terms of the application of the mechanisms and design methods. A discussion on separation, filtration and other relevant engineering issues addressed with geosynthetics are addressed in the separate parts of ISO 18228.

This document includes information relating to the stabilization function. Details ~~of~~ regarding design ~~methodology~~ methodologies adopted in a number of regions are provided.

iTeh Standards
(<https://standards.itih.ai>)
Document Preview

[ISO/DTR 18228-5](https://standards.itih.ai/catalog/standards/iso/09b5ec71-3aeb-4987-bcf2-d0b9189f5778/iso-dtr-18228-5)

<https://standards.itih.ai/catalog/standards/iso/09b5ec71-3aeb-4987-bcf2-d0b9189f5778/iso-dtr-18228-5>

Design using geosynthetics —

Part 5: Stabilization

1 Scope

This document provides a summary of general guidance for the design of geosynthetics to fulfil the function of stabilization of granular layers in contact with natural soils, fills, asphalt or other materials.

The concepts of the summarised guidance are ~~always~~ based on installed materials, the installation process and on either the strength or deformation behaviour, or both, of geosynthetics.

This document provides general considerations to support the design of unbound layers of paved and unpaved roads, working platforms and foundations utilizing the stabilization function of geosynthetics. This is typically for the serviceability limit state (SLS).

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 10318-1, *Geosynthetics — Part 1: Terms and definitions*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 10318-1 apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

4 Concepts and fundamental principles


4.1 General

There are two primary mechanisms by which geosynthetics can improve the performance of a granular layer, the confinement mechanism and the tensioned membrane mechanism. ~~It is important that the~~The distinction between these two mechanisms and their relevant applications ~~are~~must be understood.


The first mechanism provides stabilization by way of particle confinement, or lateral restraint. By minimizing the movement of aggregate particles, confinement increases the shear resistance and widens the load distribution angle, improving the mechanical properties of the granular (*i.e.* aggregate) layer, thereby controlling deformation under load (*i.e.* SLS).

The second mechanism provides reinforcement by way of friction, or interlock, or deforming, or a combination of these three, out of the plane under load. In this case, the geosynthetic material is anchored on each side of the loaded area to create a tensioned membrane. In doing so, it provides support to the granular (*i.e.* aggregate) layer, thus decreasing deformations (*i.e.* SLS) and increasing bearing capacity (*i.e.* ULS).

Figure 1 illustrates the difference between the two mechanisms.

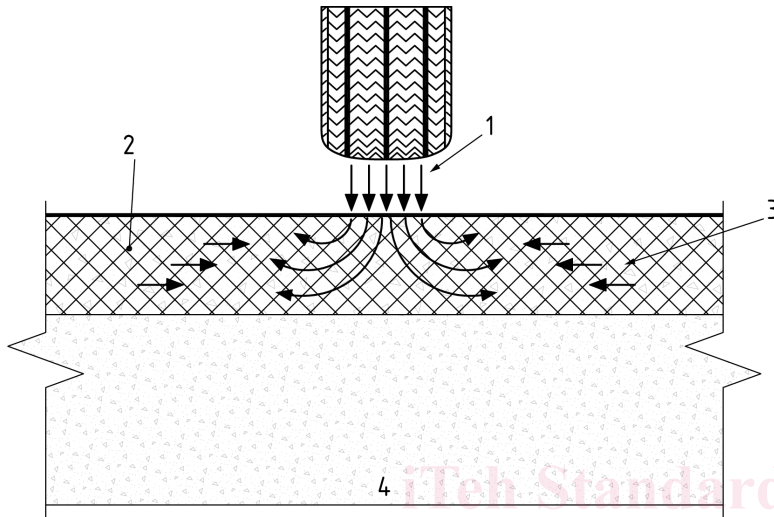

a) Lateral restraint

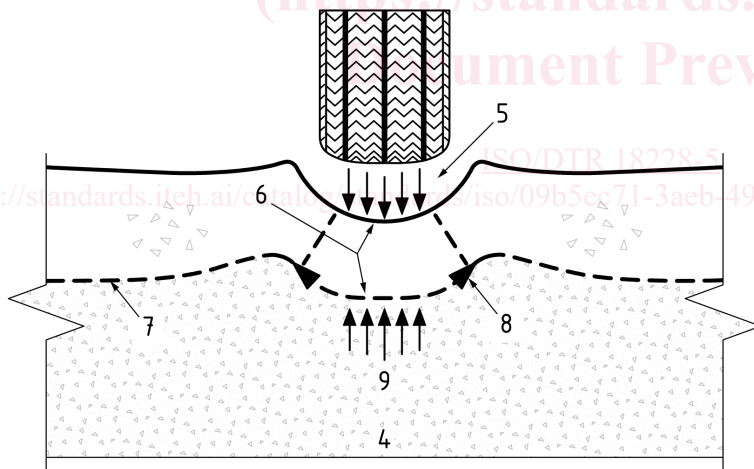

b) Tensioned membrane

Key

- 1 wheel load creates stresses which, unchecked, would cause strains as shown
- 2 stabilised composite layer of aggregate and geosynthetic
- 3 geosynthetic acts with aggregate to provide lateral restraint, inhibit strains, and thereby support the vertical load
- 4 aggregate
- 5 wheel path rut
- 6 geosynthetic
- 7 membrane tension in geosynthetic
- 8
- 9

- 4 subgrade
5 wheel load
- 9 vertical support component of membrane

NOTE ~~Figure 1~~ **Figure 1** shows the primary mechanisms by which geosynthetics can improve the performance of a granular layer.

Figure 1 — Mechanisms to improve the performance of a granular layer

In stabilization (i.e. confinement), the geosynthetic operates most effectively at relatively low levels of strain. Stabilization ~~will be~~ is less influential in designs where high levels of strain are anticipated. Where high levels of strain are anticipated, the tension membrane effect (reinforcement) ~~will be~~ is dominant.

There is considerable discussion in the literature about the relative magnitude of the strain within the geosynthetic in the stabilization and reinforcement mechanisms. The boundary between the operational strain envelopes of these two mechanisms and ~~indeed~~ the nature of any transition between them has not been ~~defined~~ adequately ~~defined~~ by any research to date. This is partly because it is extremely difficult to measure the level of strain of a buried geosynthetic. This means that, a universally recognised design methodology based on this parameter is not yet available.

~~Following from the above, the~~ **The** design life of the project is also suggested as a key consideration and, as a result, the rate of deformation. Designing for geosynthetic stabilization results in the successful control of the rate and level of system deformation to that which is tolerable within the design life of the project.

The tensioned membrane mechanism can require large deformations to mobilize the tensile strength of the geosynthetic for it to be effective. Due to the importance of the tensile strength, the geosynthetic in a tensioned membrane mechanism is considered to be performing a reinforcement function. This is not the only mechanism through which geosynthetics perform the reinforcement function and the reader is referred to ISO/TR 18228-7 where other situations are described. However, because the tensioned membrane mechanism can be used in the application of unpaved roads, for ease of reference, a discussion of the tensioned membrane reinforcement mechanism is provided in ~~Annex A~~ **Annex A** of this document.

4.2 Benefits

Geosynthetics are utilized to facilitate construction and improve the performance of unbound aggregate layers over subgrades of varying strength. The benefits of geosynthetics have been well documented in numerous case histories. These cover the range of full-scale laboratory experiments to instrumented field studies. Many of these are highlighted in the ~~reference section of this report~~ **Bibliography**. In these cases, the geosynthetic and aggregate together form a stabilized layer.

Further, ~~this~~ stabilization of ~~the~~ unbound aggregate leads to an enhancement in both the surface resilient modulus of unbound layers or subgrade and bearing capacity of the stabilized layer. The composite structure of aggregate fill, geosynthetic and subgrade must:

- a) ~~a)~~ effectively withstand service-loading pressures;
- b) ~~b)~~ control subgrade and unbound aggregate layer deformation within a range suited to the in-service requirements;
- c) ~~c)~~ not progressively deteriorate over time through either aggregate deformation, breakdown or contamination.

The corresponding functions of separation and filtration can also contribute to an improvement in performance where site conditions require them to be provided.

4.3 Confinement and particle restraint

4.3.1 General

Stabilization by geosynthetics ~~requires~~necessitates the minimization of particle movement through confinement. Minimization of particle movement is achieved by particle restraint. For geosynthetics to provide particle restraint, they ~~would normally~~must have adequate tensile stiffness and sufficient interaction with the soil.

Confinement is the dominant stabilization mechanism at low levels of strain (typically less than 1 %, but possibly up to 2 %) of the geosynthetic within the aggregate, depending also on the importance of the stabilized system (e.g. highway versus haul road) and the position of the geosynthetic within the stabilized system (usually at lower levels higher strains are acceptable). If strain values are expected to be above this, ~~then~~ the designer can consider whether other mechanisms need to be included. For the purposes of this document, two types of confinement have been considered and named internal and external.

4.3.2 Internal confinement — Description of mechanism

Internal confinement is the intimate interaction of a two-dimensional geosynthetic with aggregate in a compacted granular layer thereby creating a pseudo-composite material of improved shear strength and stiffness. The interaction can occur via interlock, surface friction or both. For interlock to be effective, the geosynthetic must have apertures (e.g. a geogrid) into which granular particles can penetrate.

While vertically loaded, additional shear stress is transmitted from the aggregate to the geosynthetic which in turn results in deformation (strain) in the geosynthetic. The shear resistance caused by friction and mechanical interlock generates a physical restraint of the aggregate particles. The stiffness provided by the geosynthetic reduces development of lateral tensile strain and stress in the base aggregate over a defined height above the geosynthetic (the stabilized or ~~“confined zone”~~) by preventing the development of explicit displacements of the aggregate.


The confined zone has a limited thickness. Above it, a transition zone is developed which extends until there is no influence on the granular (i.e. aggregate) layer from the geosynthetic (i.e. unconfined zone). ~~Figure 2~~Figure 2 illustrates the various zones.

The efficiency of confinement and thickness of the confined and transition zones varies with different geosynthetic and soil types. The details therefore are usually defined for each type of geosynthetic and soil individually. From ~~Figure 2~~Figure 2 it is evident that, when a relatively high aggregate thickness is required, designing with multiple layers of geosynthetics ~~would allow~~allows a reduction in or elimination of the unconfined zone, thus affording a more effective stabilization.


The magnitude by which the horizontal and vertical strain in the aggregate layer can be reduced depends on the stiffness of the composite layer. This is, in turn, a function of the geosynthetic tensile stiffness required for the stress equilibrium (especially at low strain levels) as well as on the efficiency of the aggregate and geosynthetic interaction.

During the application of load to the granular (i.e. aggregate) layer (e.g. trafficking or compaction), the interaction discussed above distributes stress throughout the stabilized granular (aggregate) layer and geosynthetic, thus reducing any stresses transmitted to the underlying subgrade. The limitation of movement under load provided in this way via a geosynthetic is referred to as the provision of lateral restraint.


The creation of the confined zone with limited particle movement naturally limits the deformation of the granular (i.e. aggregate) layer as a whole. The resultant reduced stress transmission to the subgrade limits its deformation. It is typically the underlying subgrade that is the weakest material in the construction section and one of the principle aims in developing a confined and stabilized granular (i.e. aggregate) layer is to limit any stress and strain transmission to this weaker layer.

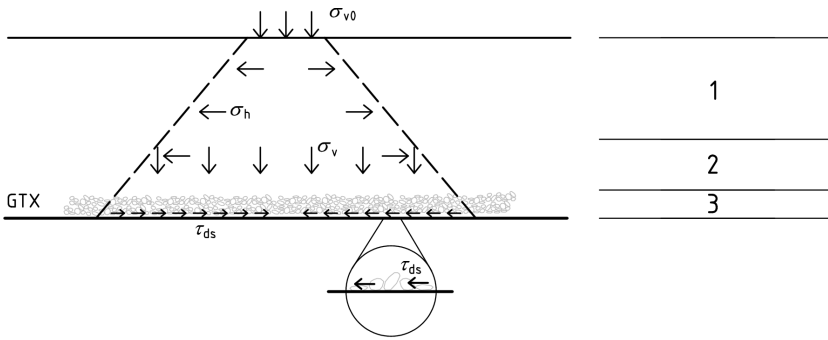

a) Interaction by direct shear only

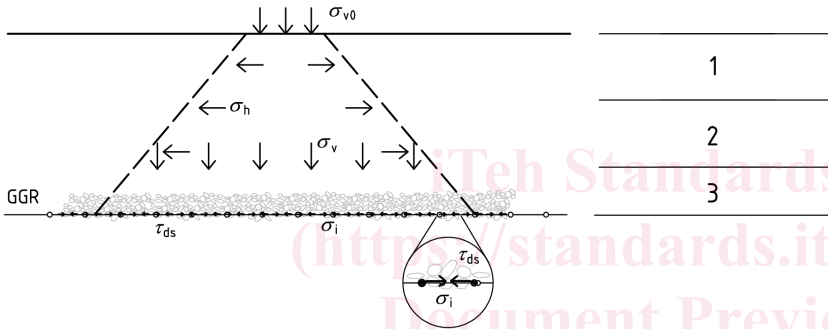

b) Interaction by direct shear, interlocking or both

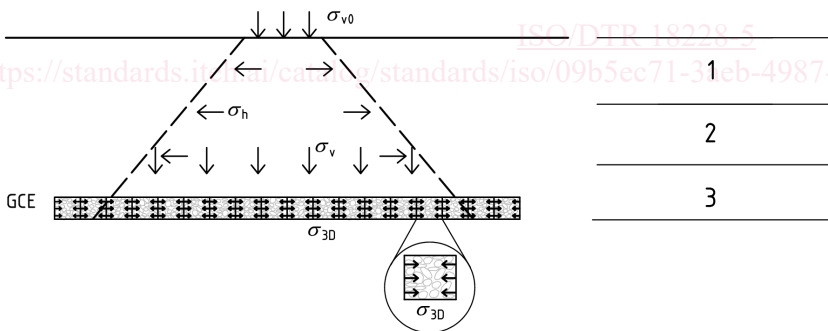

c) Interaction with geocell

Key

- σ_{v0} vertical stress applied at the top surface
- σ_h horizontal stress
- σ_v vertical stress at the subgrade interface
- τ_{ds} direct shear stress
- σ_i interlocking confining stress
- GTX geotextile
- GGR geogrid

GCE	geocells
1	unconfined zone
2	transition zone
3	confined zone

Figure 2 — Interaction of granular (aggregate) material with geosynthetics

Reducing the horizontal strain leads to a decrease in the Poisson ratio of the soil and geosynthetic composite material compared to the Poisson ratio of the unstabilized soil. Reducing the Poisson ratio increases the horizontal stiffness which means that the geosynthetic stabilized soil layer is able to distribute the vertical stresses σ_{v0} applied at the top surface on a wider area, as shown in [Figure 3](#).

In terms of the well-known concept of load distribution angle, for the unstabilized soil layer the vertical stress on the subgrade σ_{vu} will have a load distribution angle α_u [\[Figure 3a\]](#), while for the two dimensional and three-dimensional geosynthetic stabilized soil layer, the vertical stress on the subgrade σ_{vs} will ~~get have~~ have a much wider and ~~more~~ more uniform distribution according to the increased load distribution angle α_s [\[Figures 3b\]](#) and [3c](#).

On the other hand, it is evident that at equal maximum value of σ_{vu} and σ_{vs} , the load that the stabilized soil layer can support will be much higher than the load supported by the unstabilized soil layer. In other words, the improved vertical load distribution on the subgrade affords a higher bearing capacity of the stabilized system compared to that of the unstabilized system.

These concepts have been demonstrated by research and monitored stabilized versus unstabilized soil layers under different types of loads and are widely used in the presently available design methods.

4.3.3 External confinement — Description of mechanism

External confinement occurs when a volume of material is confined by a three-dimensional geosynthetic system, which can be made of a geocell or a factory or in-situ three-dimensional assembling of geosynthetic components. For ease of use, reference will be made to geocells only in this document, although the details apply equally to the factory and in-situ 3D assembling of geosynthetic components.

The geocell stabilization mechanism limits horizontal infill soil deformation via the geocell walls, thereby confining the infill soil. The limitation of horizontal deformation is based on four factors.

- Hoop tension forces in the cell walls.
- Resistance from the surrounding cells.
- Friction between cell walls and infill material.
- Connection strength of joined walls.


Under vertical load, horizontal earth pressure is restrained by the cell walls. The resulting strains in the cell walls mobilize hoop stresses within the loaded cell [\(Figure 4\)](#). The magnitude of the activated hoop stress depends on the geocell material, stress-strain behaviour, magnitude of load, number of load cycles, location of the applied load, type of infill material, and the foundation characteristics.

The hoop stresses and resistance provided by surrounding cells restrict lateral deformation of the fill by producing confining stresses σ_{3D} [\[Figure 3c\]](#). The intensity of the confining stresses depends on the height to diameter ratio of the geocell, the height of surcharge and the tensile properties of the geocell.


The confined zone shown in [Figure 3c](#) includes two parts:-

- 1) ~~cell~~ Cell height,
- 2) ~~limited~~ Limited thickness above and, possibly, beneath the geocell.


Above the confined zones, a transition zone is developed which extends until there is no influence on the granular (i.e. aggregate) layer from the geocell (i.e. unconfined zone). Figure 3c (Figure 3e)) illustrates the increased load spread angle under load.

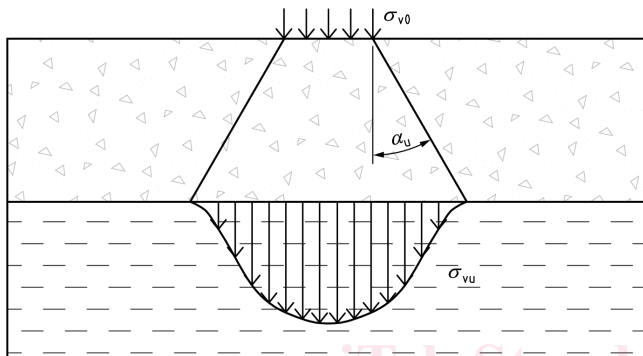

a) Unstabilized granular (aggregate) layer

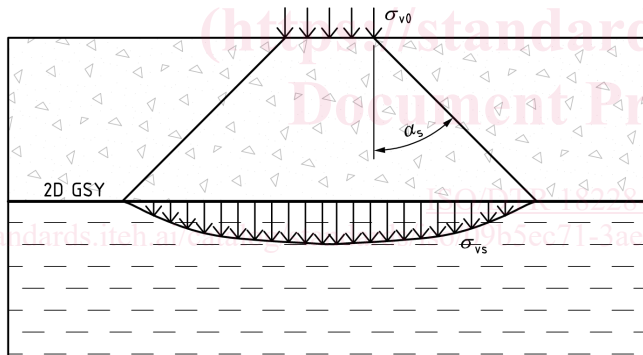

b) Two-dimensional confinement of granular (aggregate) layer

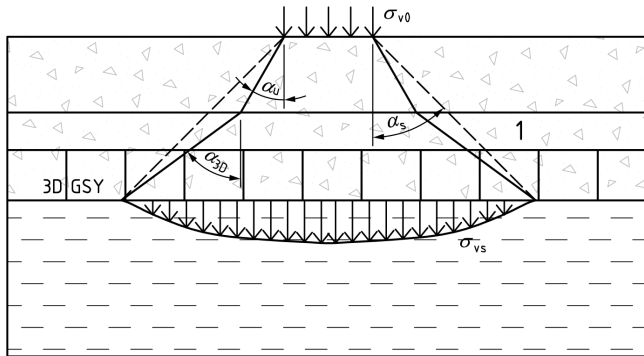

c) ~~three~~Three-dimensional confinement of granular (aggregate) layer

Key

- σ_{v0} vertical stress applied at the top surface
- σ_{vu} vertical stress on the subgrade with unstabilized granular (aggregate) layer
- σ_{vs} vertical stress on the subgrade with stabilized granular (aggregate) layer
- α_u load spreading angle with unstabilized granular (aggregate) layer
- α_s load spreading angle with stabilized granular (aggregate) layer
- α_{3D} load spreading angle within three-dimensional structure
- 1 confined zone

Figure 3 — Increase of the load distribution angle for bearing capacity increase

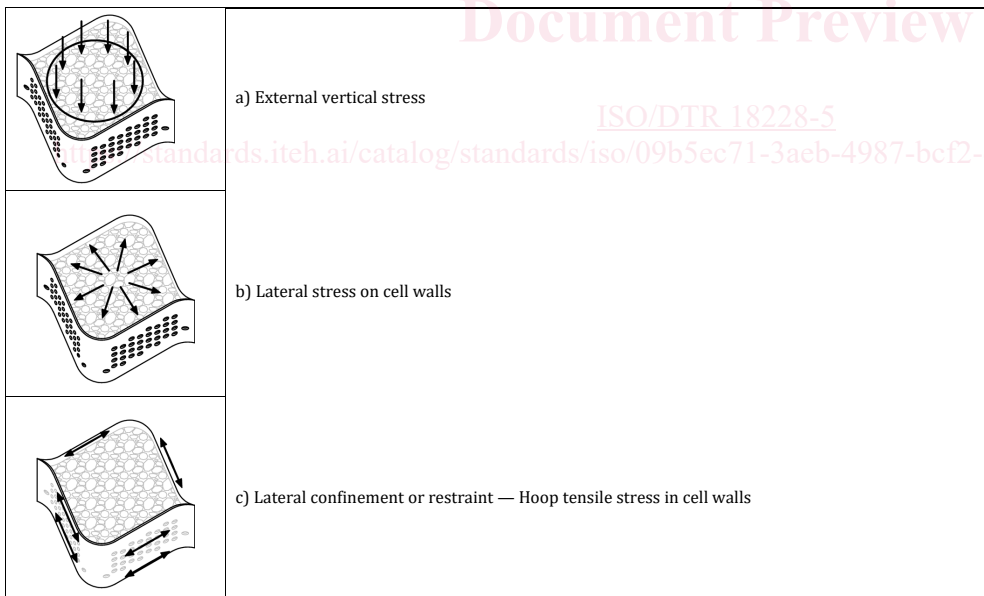


Figure 4 — Confinement mechanisms in geocells: Development of cell hoop stress by external vertical stress